

5101-230  
Flat-Plate  
Solar Array Project

DOE/JPL-1012-86  
Distribution Category UC-63b

# Handbook of Photothermal Test Data on Encapsulant Materials

R.H. Liang  
K.L. Oda  
S.Y. Chung  
M.V. Smith  
A. Gupta

May 1, 1983

Prepared for  
**U.S. Department of Energy**  
Through an Agreement with  
**National Aeronautics and Space Administration**  
by  
**Jet Propulsion Laboratory**  
California Institute of Technology  
Pasadena, California

JPL Publication 83-32

Prepared by the Jet Propulsion Laboratory, California Institute of Technology, for the U.S. Department of Energy through an agreement with the National Aeronautics and Space Administration.

The JPL Flat-Plate Solar Array Project is sponsored by the U.S. Department of Energy and is part of the Photovoltaic Energy Systems Program to initiate a major effort toward the development of cost-competitive solar arrays.

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights.

Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

This publication reports on work done under NASA Task RE-152, Amendment 66, DOE/NASA IAA No. DE-AI01-76ET20356.

## ABSTRACT

This report describes laboratory tests performed to characterize candidate encapsulation materials with respect to changes in their physical and chemical properties caused by photothermal aging. Several key material properties relating directly to material degradation and deterioration of performance have been identified and have been monitored as functions of aging conditions and time. This handbook provides a status report on accelerated testing activities and presents experimental data collected before and during December 1982. It will be updated periodically as more data become available.

The use of these data in development and dissemination of predictive models describing the rate of aging as a function of stress parameters is a separate and ongoing task. A preliminary version of this model will be published soon in a separate Flat Plate Solar Array Project report.

## CONTENTS

|      |   |    |
|------|---|----|
| I.   | INTRODUCTION . . . . .                        | 1  |
|      | A. BACKGROUND . . . . .                       | 1  |
|      | B. MATERIAL PROPERTIES MONITORED . . . . .    | 1  |
|      | C. TEST DESIGN . . . . .                      | 2  |
|      | D. TEST SAMPLES . . . . .                     | 4  |
| II.  | EVA (SPRINGBORN A-9918) . . . . .             | 9  |
|      | A. OPTICAL TRANSMITTANCE . . . . .            | 10 |
|      | B. MECHANICAL PROPERTIES . . . . .            | 21 |
|      | C. WEIGHT LOSS . . . . .                      | 36 |
|      | D. OTHER PROPERTIES . . . . .                 | 39 |
| III. | PVB (MONSANTO SAFLEX) . . . . .               | 43 |
|      | A. OPTICAL TRANSMITTANCE . . . . .            | 44 |
|      | B. MECHANICAL PROPERTIES . . . . .            | 49 |
|      | C. WEIGHT LOSS . . . . .                      | 58 |
| IV.  | RTV SILICONE ELASTOMER (GE RTV-615) . . . . . | 61 |
|      | A. OPTICAL TRANSMITTANCE . . . . .            | 62 |
|      | B. MECHANICAL PROPERTIES . . . . .            | 71 |
|      | C. WEIGHT LOSS . . . . .                      | 83 |
|      | D. OTHER PROPERTIES . . . . .                 | 86 |
| V.   | EMA (SPRINGBORN A-13404) . . . . .            | 89 |
|      | A. MECHANICAL PROPERTIES. . . . .             | 90 |
|      | B. WEIGHT LOSS . . . . .                      | 94 |
|      | C. OTHER PROPERTIES . . . . .                 | 97 |

|       |  |     |
|-------|--|-----|
| VI.   | PnBA (SPRINGBORN A-13870)                                  | 101 |
|       | A. MECHANICAL PROPERTIES                                   | 102 |
|       | B. WEIGHT LOSS   | 108 |
|       | C. OTHER PROPERTIES  | 110 |
| VII.  | POLYURETHANE (H.J. QUINN -- DEVELOPMENT ASSOCIATES Z-2591) | 113 |
|       | A. OPTICAL TRANSMITTANCE                                   | 114 |
|       | B. MECHANICAL PROPERTIES                                   | 117 |
|       | C. WEIGHT LOSS   | 124 |
|       | D. OTHER PROPERTIES  | 127 |
| VIII. | KORAD (XCEL CORP.)   | 131 |
| IX.   | TEDLAR (DU PONT UTB-100)                                   | 133 |
| X.    | ACRYLAR (3M CO. X-22416)                                   | 137 |
| XI.   | KYNAR (PENNWALT CORP.)                                     | 145 |
| XII.  | REFERENCES   | 149 |

## FIGURES

|  |    |
|--|----|
| 1. Photothermal Radiation Apparatus . . . . .  | 3  |
| 2. Controlled Environmental Reactor (CER) . . . . .  | 5  |
| 3. Change in Optical Transmittance as a Function of Open<br>Photothermal Aging of EVA at 70°C . . . . .      | 10 |
| 4. Change in Optical Transmittance as a Function of Covered<br>Photothermal Aging of EVA at 70°C . . . . .   | 11 |
| 5. Change in Optical Transmittance as a Function of Thermal<br>Aging of EVA at 70°C . . . . .                | 12 |
| 6. Change in Optical Transmittance as a Function of Open<br>Photothermal Aging of EVA at 85°C . . . . .      | 13 |
| 7. Change in Optical Transmittance as a Function of Covered<br>Photothermal Aging of EVA at 85°C . . . . .   | 14 |
| 8. Change in Optical Transmittance as a Function of Thermal<br>Aging of EVA at 85°C . . . . .                | 15 |
| 9. Change in Optical Transmittance as a Function of Open<br>Photothermal Aging of EVA at 105°C . . . . .     | 16 |
| 10. Change in Optical Transmittance as a Function of Covered<br>Photothermal Aging of EVA at 105°C . . . . . | 17 |
| 11. Change in Optical Transmittance as a Function of Thermal<br>Aging of EVA at 105°C . . . . .              | 18 |
| 12. Change in Optical Transmittance as a Function of Covered<br>Photothermal Aging of EVA at 135°C . . . . . | 19 |
| 13. Change in Optical Transmittance as a Function of Thermal<br>Aging of EVA at 135°C . . . . .              | 20 |
| 14. Change in Stress/Strain Response as a Function of Open<br>Photothermal Aging of EVA at 70°C . . . . .    | 21 |
| 15. Change in Stress/Strain Response as a Function of Covered<br>Photothermal Aging of EVA at 70°C . . . . . | 22 |
| 16. Change in Stress/Strain Response as a Function of Thermal<br>Aging of EVA at 70°C . . . . .              | 23 |
| 17. Change in Stress/Strain Response as a Function of Open<br>Photothermal Aging of EVA at 85°C . . . . .    | 24 |

|     |  |    |
|-----|--|----|
| 18. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EVA at 85°C . . . . .    | 25 |
| 19. | Change in Stress/Strain Response as a Function of Thermal Aging of EVA at 85°C . . . . .                 | 26 |
| 20. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of EVA at 105°C . . . . .      | 27 |
| 21. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EVA at 105°C . . . . .   | 28 |
| 22. | Change in Stress/Strain Response as a Function of Thermal Aging of EVA at 105°C . . . . .                | 29 |
| 23. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of EVA at 135°C . . . . .      | 30 |
| 24. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EVA at 135°C . . . . .   | 31 |
| 25. | Change in Stress/Strain Response as a Function of Thermal Aging of EVA at 135°C . . . . .                | 32 |
| 26. | Weight Loss as a Function of Open Photothermal Aging of EVA at 70°C, 85°C, 105°C, and 135°C . . . . .    | 36 |
| 27. | Weight Loss as a Function of Covered Photothermal Aging of EVA at 70°C, 85°C, 105°C, and 135°C . . . . . | 37 |
| 28. | Weight Loss as a Function of Thermal Aging of EVA at 70°C, 85°C, 105°C, and 135°C . . . . .              | 38 |
| 29. | Change in Optical Transmittance as a Function of Open Photothermal Aging of PVB at 70°C . . . . .        | 44 |
| 30. | Change in Optical Transmittance as a Function of Covered Photothermal Aging of PVB at 70°C . . . . .     | 45 |
| 31. | Change in Optical Transmittance as a Function of Thermal Aging of PVB at 70°C . . . . .                  | 46 |
| 32. | Change in Optical Transmittance as a Function of Covered Photothermal Aging of PVB at 135°C . . . . .    | 47 |
| 33. | Change in Optical Transmittance as a Function of Thermal Aging of PVB at 135°C . . . . .                 | 48 |
| 34. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of PVB at 70°C . . . . .       | 49 |
| 35. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of PVB at 70°C . . . . .    | 50 |

|     |  |    |
|-----|--|----|
| 36. | Change in Stress/Strain Response as a Function of Thermal Aging of PVB at 70°C . . . . .               | 51 |
| 37. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of PVB at 135°C . . . . .    | 52 |
| 38. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of PVB at 135°C . . . . . | 53 |
| 39. | Change in Stress/Strain Response as a Function of Thermal Aging of PVB at 135°C . . . . .              | 54 |
| 40. | Weight Loss as a Function of Open Photothermal Aging of PVB at 55°C, 70°C, and 135°C . . . . .         | 58 |
| 41. | Weight Loss as a Function of Covered Photothermal Aging of PVB at 55°C, 70°C, and 135°C . . . . .      | 59 |
| 42. | Weight Loss as a Function of Thermal Aging of PVB at 55°C, 70°C, and 135°C . . . . .                   | 60 |
| 43. | Change in Optical Transmittance as a Function of Open Photothermal Aging of RTV at 70°C . . . . .      | 62 |
| 44. | Change in Optical Transmittance as a Function of Covered Photothermal Aging of RTV at 70°C . . . . .   | 63 |
| 45. | Change in Optical Transmittance as a Function of Thermal Aging of RTV at 70°C . . . . .                | 64 |
| 46. | Change in Optical Transmittance as a Function of Open Photothermal Aging of RTV at 85°C . . . . .      | 65 |
| 47. | Change in Optical Transmittance as a Function of Covered Photothermal Aging of RTV at 85°C . . . . .   | 66 |
| 48. | Change in Optical Transmittance as a Function of Thermal Aging of RTV at 85°C . . . . .                | 67 |
| 49. | Change in Optical Transmittance as a Function of Open Photothermal Aging of RTV at 105°C . . . . .     | 68 |
| 50. | Change in Optical Transmittance as a Function of Covered Photothermal Aging of RTV at 105°C . . . . .  | 69 |
| 51. | Change in Optical Transmittance as a Function of Thermal Aging of RTV at 105°C . . . . .               | 70 |
| 52. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of RTV at 70°C . . . . .     | 71 |
| 53. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of RTV at 70°C . . . . .  | 72 |

|     |  |     |
|-----|--|-----|
| 54. | Change in Stress/Strain Response as a Function of Thermal Aging of RTV at 70°C . . . . .                   | 73  |
| 55. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of RTV at 85°C . . . . .         | 74  |
| 56. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of RTV at 85°C . . . . .      | 75  |
| 57. | Change in Stress/Strain Response as a Function of Thermal Aging of RTV at 85°C . . . . .                   | 76  |
| 58. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of RTV at 105°C . . . . .        | 77  |
| 59. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of RTV at 105°C . . . . .     | 78  |
| 60. | Change in Stress/Strain Response as a Function of Thermal Aging of RTV at 105°C . . . . .                  | 79  |
| 61. | Weight Loss as a Function of Open Photothermal Aging of RTV at 70°C and 85°C . . . . .                     | 83  |
| 62. | Weight Loss as a Function of Covered Photothermal Aging of RTV at 70°C, 85°C, and 105°C . . . . .          | 84  |
| 63. | Weight Loss as a Function of Thermal Aging of RTV at 70°C, 85°C, and 105°C . . . . .                       | 85  |
| 64. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EMA at 135°C . . . . .     | 90  |
| 65. | Change in Stress/Strain Response as a Function of Thermal Aging of EMA at 135°C . . . . .                  | 91  |
| 66. | Weight Loss as a Function of Open Photothermal Aging of EMA at 135°C . . . . .                             | 94  |
| 67. | Weight Loss as a Function of Covered Photothermal Aging of EMA at 135°C . . . . .                          | 95  |
| 68. | Weight Loss as a Function of Thermal Aging of EMA at 135°C in a Covered (Sandwich) Configuration . . . . . | 96  |
| 69. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of PnBA at 135°C . . . . .       | 102 |
| 70. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of PnBA at 135°C . . . . .    | 103 |
| 71. | Change in Stress/Strain Response as a Function of Thermal Aging of PnBA at 135°C . . . . .                 | 104 |

|     |   |     |
|-----|---|-----|
| 72. | Weight Loss as a Function of Covered Photothermal Aging of PnBA at 135°C . . . . .  | 108 |
| 73. | Weight Loss as a Function of Thermal Aging of PnBA at 135°C in a Covered (Sandwich) Configuration . . . . .                             | 109 |
| 74. | Change in Optical Transmittance as a Function of Open Photothermal Aging of Polyurethane at 70°C . . . . .                              | 114 |
| 75. | Change in Optical Transmittance as a Function of Covered Photothermal Aging of Polyurethane at 70°C . . . . .                           | 115 |
| 76. | Change in Optical Transmittance as a Function of Thermal Aging of Polyurethane at 70°C . . . . .  | 116 |
| 77. | Change in Stress/Strain Response as a Function of Open Photothermal Aging of Polyurethane at 70°C . . . . .                             | 117 |
| 78. | Change in Stress/Strain Response as a Function of Covered Photothermal Aging of Polyurethane at 70°C . . . . .                          | 118 |
| 79. | Change in Stress/Strain Response as a Function of Thermal Aging of Polyurethane at 70°C . . . . .                                       | 119 |
| 80. | Change in Stress/Strain Response as a Function of Thermal Aging of Polyurethane at 135°C in a Closed (Sandwich) Configuration . . . . . | 120 |
| 81. | Weight Loss as a Function of Open Photothermal Aging of Polyurethane (Quinn) at 55°C and 70°C . . . . .                                 | 124 |
| 82. | Weight Loss as a Function of Covered Photothermal Aging of Polyurethane (Quinn) at 55°C and 70°C . . . . .                              | 125 |
| 83. | Weight Loss as a Function of Thermal Aging of Polyurethane (Quinn) at 55°C and 70°C . . . . .   | 126 |
| 84. | UV/VIS Transmittance Spectra as a Function of Open Photothermal Aging of Korad at 85°C . . . . .  | 132 |
| 85. | UV/VIS Absorbance Spectra as a Function of Open Photothermal Aging of Tedlar UTB-100 at 85°C . . . . .                                  | 134 |
| 86. | UV/VIS Absorbance Spectra Before and After 30 days of Aging of Tedlar UTB-100 in CER at 55°C . . . . .                                  | 135 |
| 87. | FT-IR Absorbance Spectra Before and After 30 days of Aging of Tedlar UTB-100 in CER at 55°C . . . . .                                   | 136 |
| 88. | UV/VIS Absorbance Spectra Before and After 34 days of Aging of Acrylar Films (X-22416) in CER . . . . .                                 | 138 |
| 89. | UV/VIS Transmittance Spectra Before and After 800 h of Open Photothermal Aging of Acrylar Film at 85°C . . . . .                        | 139 |

|     |  |     |
|-----|--|-----|
| 90. | Change in Transmittance of Acrylar Films at 460 nm at 60°C, 70°C and 80°C . . . . .  | 140 |
| 91. | UV-Screening Capability of Acrylar as a Function of Accelerated Aging Inside the CER at 55°C . . . . .                     | 141 |
| 92. | FT-IR Absorbance Spectra Before and After 34 days of Aging of Acrylar Films (X-22416) in CER at 55°C . . . . .             | 142 |
| 93. | FT-IR Absorbance Spectra Before and After 282 days of Aging of Acrylar Films (X-22416) in CER at 55°C . . . . .            | 143 |
| 94. | Change in Transmittance at 350 nm as a Function of Thermal Aging of Kynar in a Dark Oven at 60°C, 70°C, and 85°C . . . . . | 146 |
| 95. | Reflectance IR Spectra Before and After 29 Hours of Thermal Aging of Kynar Film in a Dark Oven at 150°C . . . . .          | 147 |

## TABLES

|     |   |    |
|-----|---|----|
| 1.  | Matrix of Pottant and Outer Cover Materials Tested . . . . .  | 6  |
| 2.  | Matrix of Pottant Samples versus Aging Conditions and Time . . . . .  | 7  |
| 3.  | Matrix of Outer Cover Samples versus Temperature and Time . . . . .   | 8  |
| 4.  | Modulus at 5% Strain as a Function of Open Photothermal<br>Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C . . . . .                   | 33 |
| 5.  | Modulus at 5% Strain as a Function of Covered Photothermal<br>Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C . . . . .                | 34 |
| 6.  | Modulus at 5% Strain as a Function of Thermal Aging of EVA at<br>30°C, 70°C, 85°C, 105°C, and 135°C . . . . .                             | 35 |
| 7.  | Sol/Gel and Molecular Weight Data as a Function of Open Photo-<br>thermal Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C . . . . .    | 39 |
| 8.  | Sol/Gel and Molecular Weight Data as a Function of Covered Photo-<br>thermal Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C . . . . . | 40 |
| 9.  | Sol/Gel and Molecular Weight Data as a Function of Thermal<br>Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C . . . . .                | 41 |
| 10. | Modulus at 5% Strain as a Function of Open Photothermal Aging<br>of PVB at 30°C, 70°C, and 135°C . . . . .                                | 55 |
| 11. | Modulus at 5% Strain as a Function of Covered Photothermal<br>Aging of PVB at 30°C, 70°C, and 135°C . . . . .                             | 56 |
| 12. | Modulus at 5% Strain as a Function of Thermal Aging of PVB<br>at 30°C, 70°C, and 135°C . . . . .  | 57 |
| 13. | Modulus at 5% Strain as a Function of Open Photothermal Aging<br>of RTV at 30°C, 70°C, 85°C, and 105°C . . . . .                          | 80 |
| 14. | Modulus at 5% Strain as a Function of Covered Photothermal<br>Aging of RTV at 30°C, 70°C, 85°C, and 105°C . . . . .                       | 81 |
| 15. | Modulus at 5% Strain as a Function of Thermal Aging of RTV at<br>30°C, 70°C, 85°C, and 105°C . . . . .                                    | 82 |
| 16. | Sol/Gel and Molecular Weight Data as a Function of Open<br>Photothermal Aging of RTV at 30°C, 70°C, 85°C, and 105°C . . . . .             | 86 |
| 17. | Sol/Gel and Molecular Weight Data as a Function of Covered<br>Photothermal Aging of RTV at 30°C, 70°C, 85°C, and 105°C . . . . .          | 87 |
| 18. | Sol/Gel and Molecular Weight Data as a Function of Thermal<br>Aging of RTV at 30°C, 70°C, 85°C, and 105°C . . . . .                       | 88 |

|     |   |     |
|-----|---|-----|
| 19. | Modulus at 5% Strain as a Function of Covered Photothermal Aging of EMA at 30°C and 135°C . . . . .                             | 92  |
| 20. | Modulus at 5% Strain as a Function of Thermal Aging of EMA at 30°C and 135°C . . . . .  | 93  |
| 21. | Sol/Gel and Molecular Weight Data as a Function of Open Photothermal Aging of EMA at 30°C and 135°C . . . . .                   | 97  |
| 22. | Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of EMA at 30°C and 135°C . . . . .                | 98  |
| 23. | Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of EMA at 30°C and 135°C . . . . .                | 99  |
| 24. | Modulus at 5% Strain as a Function of Open Photothermal Aging of PnBA at 30°C and 135°C . . . . .                               | 105 |
| 25. | Modulus at 5% Strain as a Function of Covered Photothermal Aging of PnBA at 30°C and 135°C . . . . .                            | 106 |
| 26. | Modulus at 5% Strain as a Function of Thermal Aging of PnBA at 30°C and 135°C . . . . .   | 107 |
| 27. | Sol/Gel and Molecular Weight Data as a Function of Open Photothermal Aging of PnBA at 30°C and 135°C . . . . .                  | 110 |
| 28. | Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of PnBA at 30°C and 135°C . . . . .               | 111 |
| 29. | Sol/Gel and Molecular Weight Data as a Function of Thermal Aging of PnBA at 30°C and 135°C . . . . .                            | 112 |
| 30. | Modulus at 5% Strain as a Function of Open Photothermal Aging of Polyurethane at 30°C and 70°C . . . . .                        | 121 |
| 31. | Modulus at 5% Strain as a Function of Covered Photothermal Aging of Polyurethane at 30°C and 70°C . . . . .                     | 122 |
| 32. | Modulus at 5% Strain as a Function of Thermal Aging of Polyurethane at 30°C and 70°C . . . . .                                  | 123 |
| 33. | Sol/Gel and Molecular Weight Data as a Function of Open Photothermal Aging of Polyurethane at 30°C and 70°C . . . . .           | 127 |
| 34. | Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of Polyurethane at 30°C, 70°C and 135°C . . . . . | 128 |
| 35. | Sol/Gel and Molecular Weight Data as a Function of Thermal Aging of Polyurethane at 30°C, 70°C and 135°C . . . . .              | 129 |
| 36. | Shrinkage as a Function of Thermal Aging of Kynar in Dark Oven at 150°C . . . . .   | 148 |

## SECTION I

### INTRODUCTION

#### A. BACKGROUND

The Environmental Isolation Task within the Flat-Plate Solar Array Project (FSA) has the responsibility of (1) developing new materials and processes required to achieve low-cost, durable encapsulation of photovoltaic (PV) modules at a total installed cost of \$14/m<sup>2</sup> for the encapsulation package and (2) performing assessment and prediction of deployed PV module lifetime, through development of a fundamental understanding of degradation processes and mechanisms of the encapsulation materials, and development of outdoor lifetime prediction models for encapsulated modules.

Toward this overall objective of life assessment and prediction, an effort was initiated directed to the characterization of chemical and physical responses of encapsulant materials to accelerated photothermal aging. This effort involves exposure of materials to ultraviolet and visible radiation, elevated temperatures, liquid water spray and various oxygen concentrations. The primary use of these data is in validating and refining analytical models describing chemical changes in materials occurring on long-term exposure. These data may also be used in ranking candidate materials that perform the same functions within the encapsulation package and that belong to the same generic chemical class of compounds with respect to their photothermal aging responses.

These tests are complemented by mechanistic studies performed on selected materials such as ethylene vinyl acetate (EVA), polymethyl methacrylate (PMMA), and poly-n-butyl acrylate (PnBA). The studies involve characterization and monitoring of chemical degradation caused by photothermal aging, i.e., photooxidation, crosslinking and chain scission in polymers. Transient species involved in the overall degradation process, e.g., chain radicals and electronically excited states, are monitored in real time using flash kinetic spectroscopy and transient electron-spin resonance (ESR) spectroscopy. A status report of this work can be found in References 1 through 8.

#### B. MATERIAL PROPERTIES MONITORED

The following properties have been monitored as a function of aging time:


- (1) **Optical Transmittance:** Optical transmittance was measured on a Cary 219 spectrophotometer equipped with a 4-in. integrating sphere and ultraviolet (UV) optics. The collimated and total transmittance were obtained as a function of wavelength in the wavelength range 300-1200 nm. Besides providing a direct measure of chemical changes involving formation of oxidized species such as carbonyl groups in the polymer optical transmittance, measurements may also be used to monitor diminution of cell performance due to loss of transmittance of the encapsulant

material. Optical transmittance measurements also provide a monitor of the UV screening capability of outer-cover films.

- (2) **Weight Loss:** Weight-loss measurements allow monitoring of loss of polymer mass due to evaporation of plasticizers, leaching of additives and formation of volatile degradation products. Weight-loss measurements correlate with the rate of formation of voids in the encapsulation package, which may cause delamination and corrosion.
- (3) **Tensile Modulus:** Uniaxial stress-strain response was monitored as a function of photothermal aging time. Measurements were made as a function of strain rate, up to yield. This stress-strain response can be used to calculate engineering or secant modulus of the material. Work by Spectrolab, Inc., indicates that the strain isolation function of the encapsulation package requires a tradeoff between the thickness of the pottant material and its maximum allowable Young's modulus (Reference 9). The measured stress-strain response also yields information on the stress-relaxation or creep behavior of these materials. Detailed creep measurements on EVA will be reported in a Jet Propulsion Laboratory (JPL) publication.
- (4) **Swelling and Sol/Gel Ratio:** Crosslinked polymers are insoluble in any solvent, but they are subject to swelling. The extent of swelling is determined by the crosslink density of the materials and the match between its solubility parameters and those of the solvent. Partially crosslinked materials can be extracted to yield a sol fraction which has finite molecular weight and a remaining gel which has a crosslinked network. Determination of swelling behavior and sol/gel fraction yield fundamental information on the network crosslink density and network topology, which are critical chemical structural parameters in a polymer that control its physical-mechanical response. The mechanical response of a polymer changes on outdoor aging because aging causes changes in crosslink density and network topology. Hence, the ratio of changes in swelling behavior or sol/gel fraction after aging is a key measure of the outdoor stability of these polymers.

### C. TEST DESIGN

Polymer samples were aged at 55°C, 70°C, 85°C, 105°C, and 135°C. Aging conditions for the four lower-temperature tests have been reported previously (Reference 10) and are described only briefly here. The source of UV radiation used in the four lower-temperature tests (55°C, 70°C, 85°C, and 105°C) was a filtered medium-pressure Hg arc lamp, approximately 200 W/in. of arc length in power. The lamp was placed inside a water-cooled Pyrex jacket. A transparent annular Pyrex oil bath was then fitted around the jacket. The samples were mounted in the space between the Pyrex jacket and the oil bath, and were in contact with the hot oil-bath jacket. The radiation apparatus is shown in Figure 1. Samples (3 x 1/2 in.) were mounted directly on the inner surface of the oil-bath jacket to allow free access of oxygen (open thermal aging).

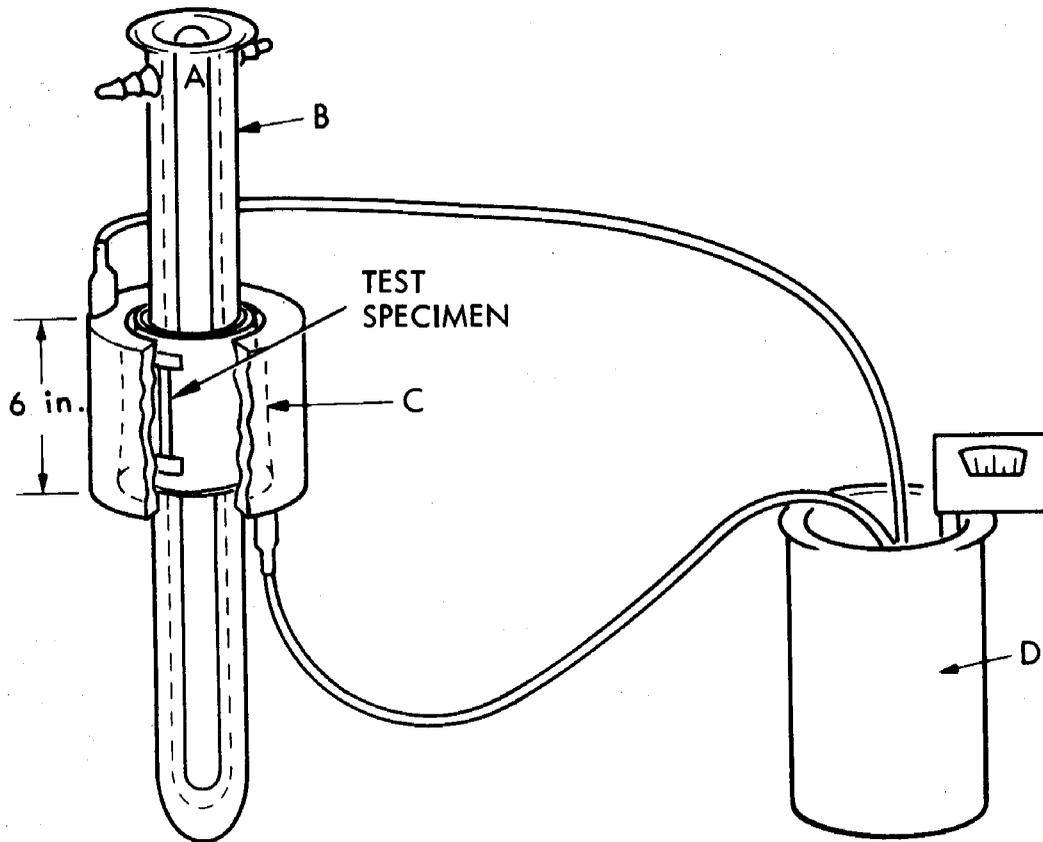

- A = 450-WATT MEDIUM PRESSURE Hg LAMP
- B = PYREX H<sub>2</sub>O COOLING JACKET
- C = OIL JACKET
- D = THERMOSTATICALLY CONTROLLED HOT OIL BATH  
(SAMPLE SPECIMEN PLACED BETWEEN B AND C)

Figure 1. Photothermal Radiation Apparatus

Samples for limited-oxygen-access testing were placed between two sheets of Pyrex glass and the sandwich then was mounted on the bath. This arrangement (covered photothermal aging) allowed limited access of oxygen with its edge effects, as illustrated in Figure 1. Control experiments (with no UV) were also performed by aging samples in a dark stagnant oven.

Although satisfactory data were obtained by use of this radiation equipment, it lacked precise temperature control, especially at elevated temperatures; e.g., a 10°C rise in sample temperature was once observed during one of the 105°C tests. This was caused by enhanced absorbance of radiation by sample films turning yellow as a result of photothermal aging. While the oil bath maintained at 105°C was supplying most of the heating during the initial aging stage, the additional absorbance of photons resulted in the rise in sample temperature. Subsequently, an accelerated aging chamber, the Controlled Environmental Test Chamber (CER), was designed and constructed at JPL to achieve better temperature control.

A detailed description of the CER is to be found in Reference 11. Briefly, the irradiation source in the CER is a medium-pressure Hg lamp filtered to yield a photon flux of up to 6 suns of AM1 ultraviolet radiation in the 295-375 nm wavelength region. In addition, it can provide precise temperature control and simulated rain and fog. Detailed calibration of the photon flux was achieved by radiometry and actinometry. Parallel aging tests were performed inside the CER and at the JPL outdoor site in order to validate its use as an accelerated testing device and to estimate the accelerating factors achieved under specific conditions. The CER has also been demonstrated to be a valid accelerated outdoor simulator with respect to photooxidation (Reference 12). Figure 2 is a photograph of the CER.

The initial CER design allowed aging temperatures ranging from 25°C to 60°C. Subsequently, resistor-type heaters were added to the outside wall of the CER to enhance its high-temperature capability. Additionally, a thermostatted sample holder equipped with its own heat source was designed to reach a sample aging temperature of up to 135°C. All heaters were thermostatically controlled by the voltage output of a thermocouple that is attached directly to the sample films. Continuous temperature control within +3°C were obtained routinely by the CER, even at 135°C.

#### D. TEST SAMPLES

Samples tested were ethylene vinyl acetate copolymer (EVA, Springborn Laboratories, Inc., A-9918); polyvinyl butyral (PVB, Monsanto Co. Saflex); silicone rubber (room-temperature vulcanizing silicon elastomer, General Electric Co. RTV-615) ethylene methyl acrylate copolymer (EMA, Springborn A-13404); and poly-n-butyl acrylate (PnBA, Springborn A-13870). Two kinds of aliphatic polyurethanes manufactured by H.J. Quinn Co. and Development Associates (PU Z-2591) also were tested. Four commercially available outer-cover film materials are being evaluated. These are Korad (Xcel Corp.), Tedlar (Du Pont Co.), Acrylar (3M Co. X-22416), and Kynar (Pennwalt Corp.). The Tedlar sample tested was designated as UTB-100 and a new sample of Tedlar (100BG3OUT) is now being evaluated. Table 1 is a matrix of samples tested and Table 2 is a matrix of the pollutant samples versus aging conditions and aging time. Table 3 is a similar matrix for outer-cover materials.

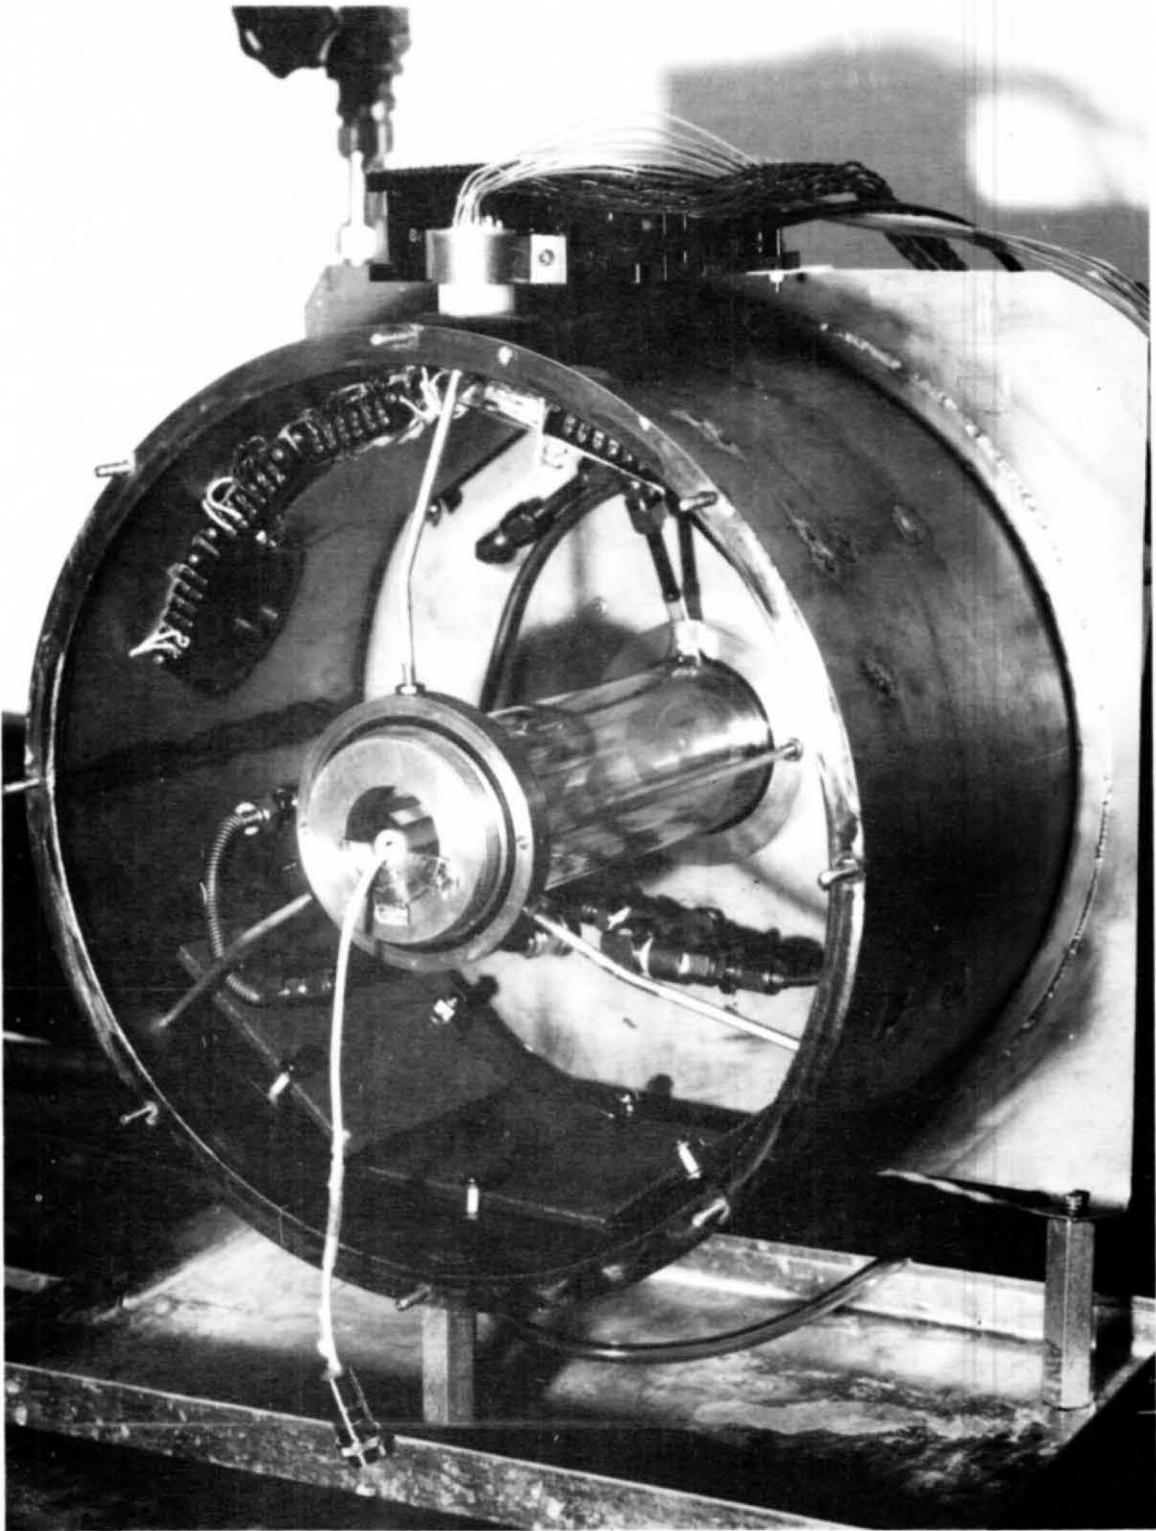


Figure 2. Controlled Environmental Reactor (CER)

Table 1. Matrix of Pottant and Outer Cover Materials Tested

| APPLICATION | MATERIAL  |  |  |   |
|-------------|---|--|--|---|
|             | ACRYLICS  | POLYOLEFINS  | FLUORO-CARBON  | OTHER (SILICONES, POLYURETHANES)  |
| POTTANT     | EMA<br>(SPRINGBORN A-13404)<br><br>PnBA<br>(SPRINGBORN A-13870) | EVA<br>(SPRINGBORN A-9918)<br><br>PVB<br>(MONSANTO SAFLEX) |  | RTV<br>(GE RTV-615)<br><br>PU (QUINN)<br><br>PU (DEVELOPMENT ASSOCIATES Z-2591) |
| OUTER COVER | ACRYLAR<br>(3M X-22416)<br><br>KORAD<br>(XCEL)                  |  | TEDLAR<br>(DU PONT UTB-100)<br><br>KYNAR<br>(PENNWALT) |   |

| TEMP<br>(°C) | CONDITION                  | AGING TIME, h              |      |     |      |      |       |                |      |   |      |
|--------------|----------------------------|----------------------------|------|-----|------|------|-------|----------------|------|---|------|
|              |                            | EVA<br>(SPRINGBORN A-9918) | PVB  | RTV | EMA  | PnBA | QUINN | DEV.<br>ASSOC. |      |   |      |
| 55           | THERMAL AGING              | -                          | 400  | -   | -    | -    | 400   | -              | -    | - | -    |
|              | OPEN PHOTOTHERMAL AGING    | -                          | 400  | -   | -    | -    | 400   | -              | -    | - | -    |
|              | COVERED PHOTOTHERMAL AGING | -                          | 400  | -   | -    | -    | 400   | -              | -    | - | -    |
| 70           | THERMAL AGING              | 500                        | 400  | 500 | -    | -    | 400   | -              | -    | - | -    |
|              | OPEN PHOTOTHERMAL AGING    | 500                        | 400  | 500 | -    | -    | 400   | -              | -    | - | -    |
|              | COVERED PHOTOTHERMAL AGING | 500                        | 400  | 500 | -    | -    | 400   | -              | -    | - | -    |
| 85           | THERMAL AGING              | 800                        | -    | 800 | -    | 800  | -     | -              | -    | - | -    |
|              | OPEN PHOTOTHERMAL AGING    | 800                        | -    | 800 | -    | 800  | -     | -              | -    | - | -    |
|              | COVERED PHOTOTHERMAL AGING | 800                        | -    | 800 | -    | 800  | -     | -              | -    | - | -    |
| 105          | THERMAL AGING              | 800                        | -    | 800 | -    | 800  | -     | -              | -    | - | -    |
|              | OPEN PHOTOTHERMAL AGING    | 800                        | -    | 800 | -    | 800  | -     | -              | -    | - | -    |
|              | COVERED PHOTOTHERMAL AGING | 800                        | -    | 800 | -    | 800  | -     | -              | -    | - | -    |
| 135          | THERMAL AGING              | 1008                       | 1008 | -   | 1008 | 1008 | -     | 1008           | 1008 | - | 1008 |
|              | OPEN PHOTOTHERMAL AGING    | 1008                       | 672  | -   | 672  | 1008 | -     | 672            | 1008 | - | 672  |
|              | COVERED PHOTOTHERMAL AGING | 1008                       | 1008 | -   | 1008 | 1008 | -     | 1008           | 1008 | - | 1008 |

Table 2. Matrix of Pottant Samples versus Aging Conditions and Time

Table 3. Matrix of Outer Cover Samples versus Temperature and Time

| TEMPERATURE,<br>°C | AGING TIME, days   |                   |       |       |
|--------------------|--------------------|-------------------|-------|-------|
|                    | ACRYLAR<br>X-22416 | TEDLAR<br>UTB-100 | KORAD | KYNAR |
| 55                 | 600                | 365               | 0     | 200*  |
| 85                 | 200                | 30                | 15    | 200   |
| 150                |                    |                   |       | 2     |

\* AT 60°C

## SECTION II

### EVA (SPRINGBORN A-9918)

The following figures and tables offer data on optical transmittance (Figures 3 through 13); mechanical properties (Figures 14 through 25, Tables 4 through 6); weight loss (Figures 26 through 28); other properties (Tables 7 through 9) of EVA (Springborn A-9918).

A. OPTICAL TRANSMITTANCE

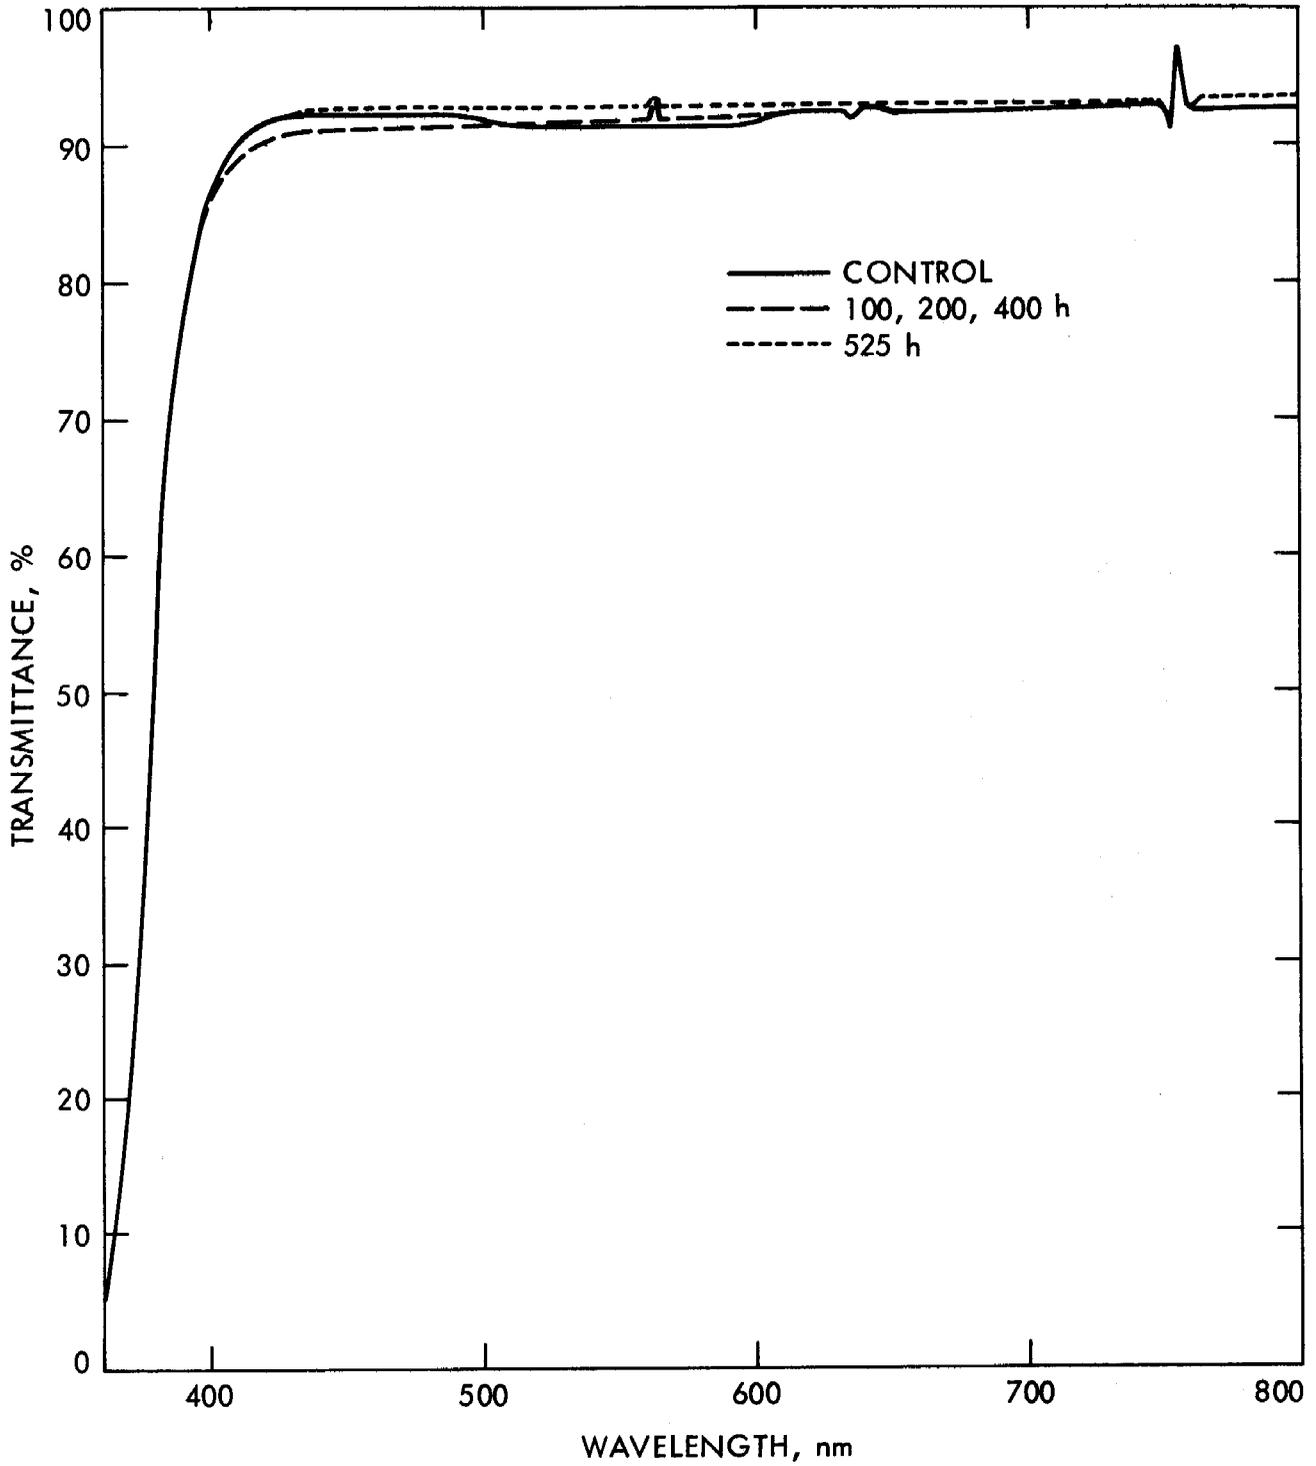


Figure 3. Change in Optical Transmittance as a Function of Open Photothermal Aging of EVA at 70°C

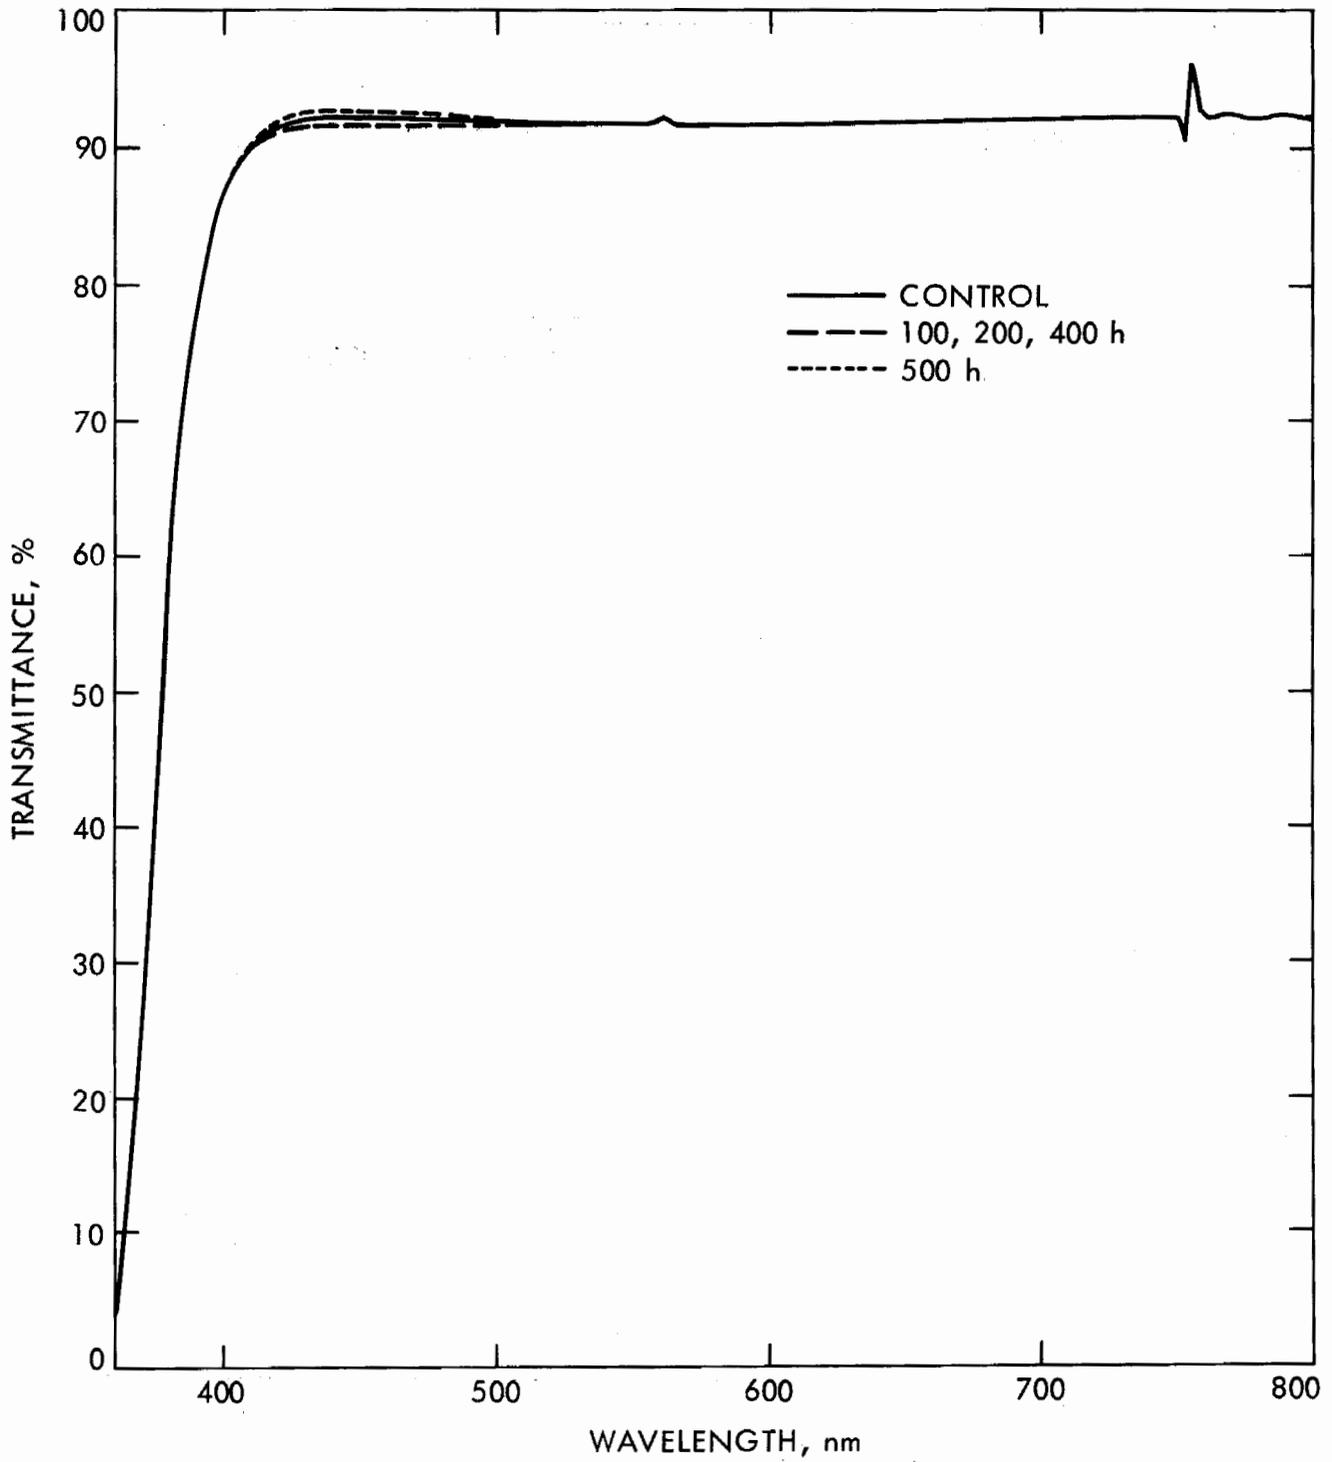


Figure 4. Change in Optical Transmittance as a Function of Covered Photothermal Aging of EVA at 70°C

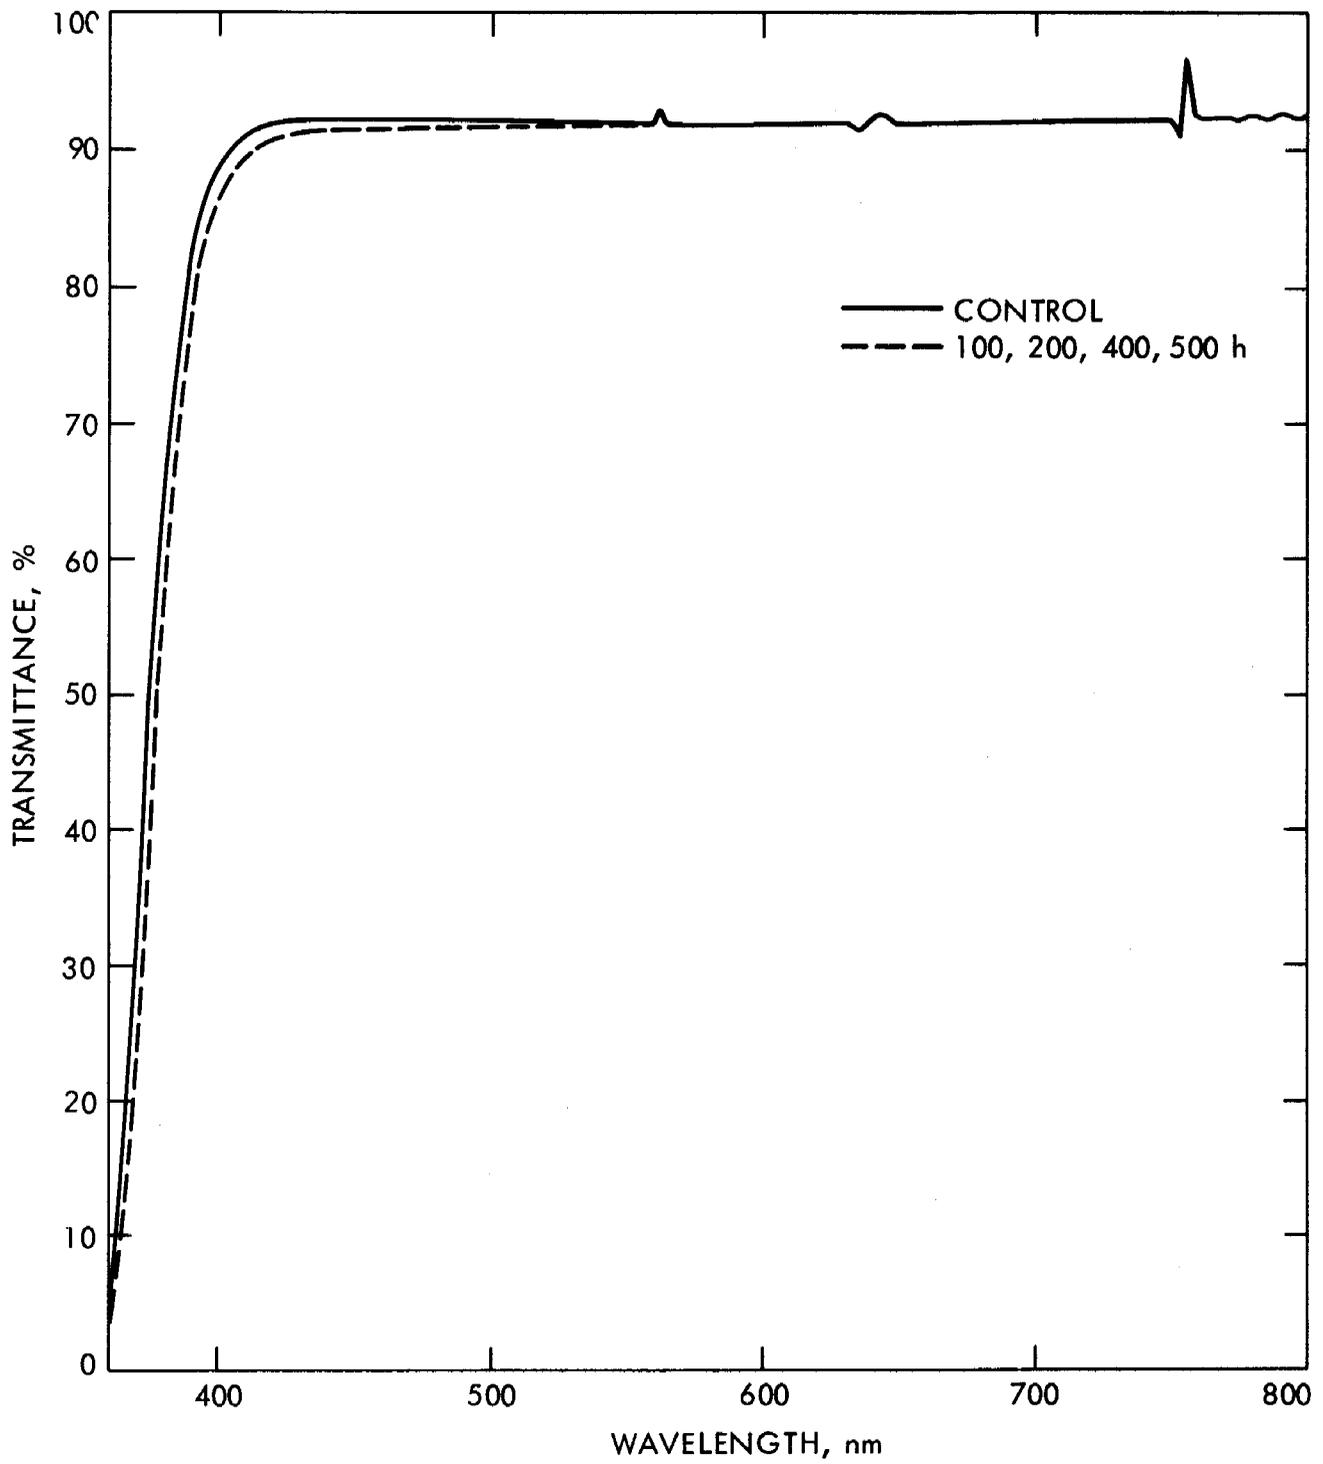


Figure 5. Change in Optical Transmittance as a Function of Thermal Aging of EVA at 70°C

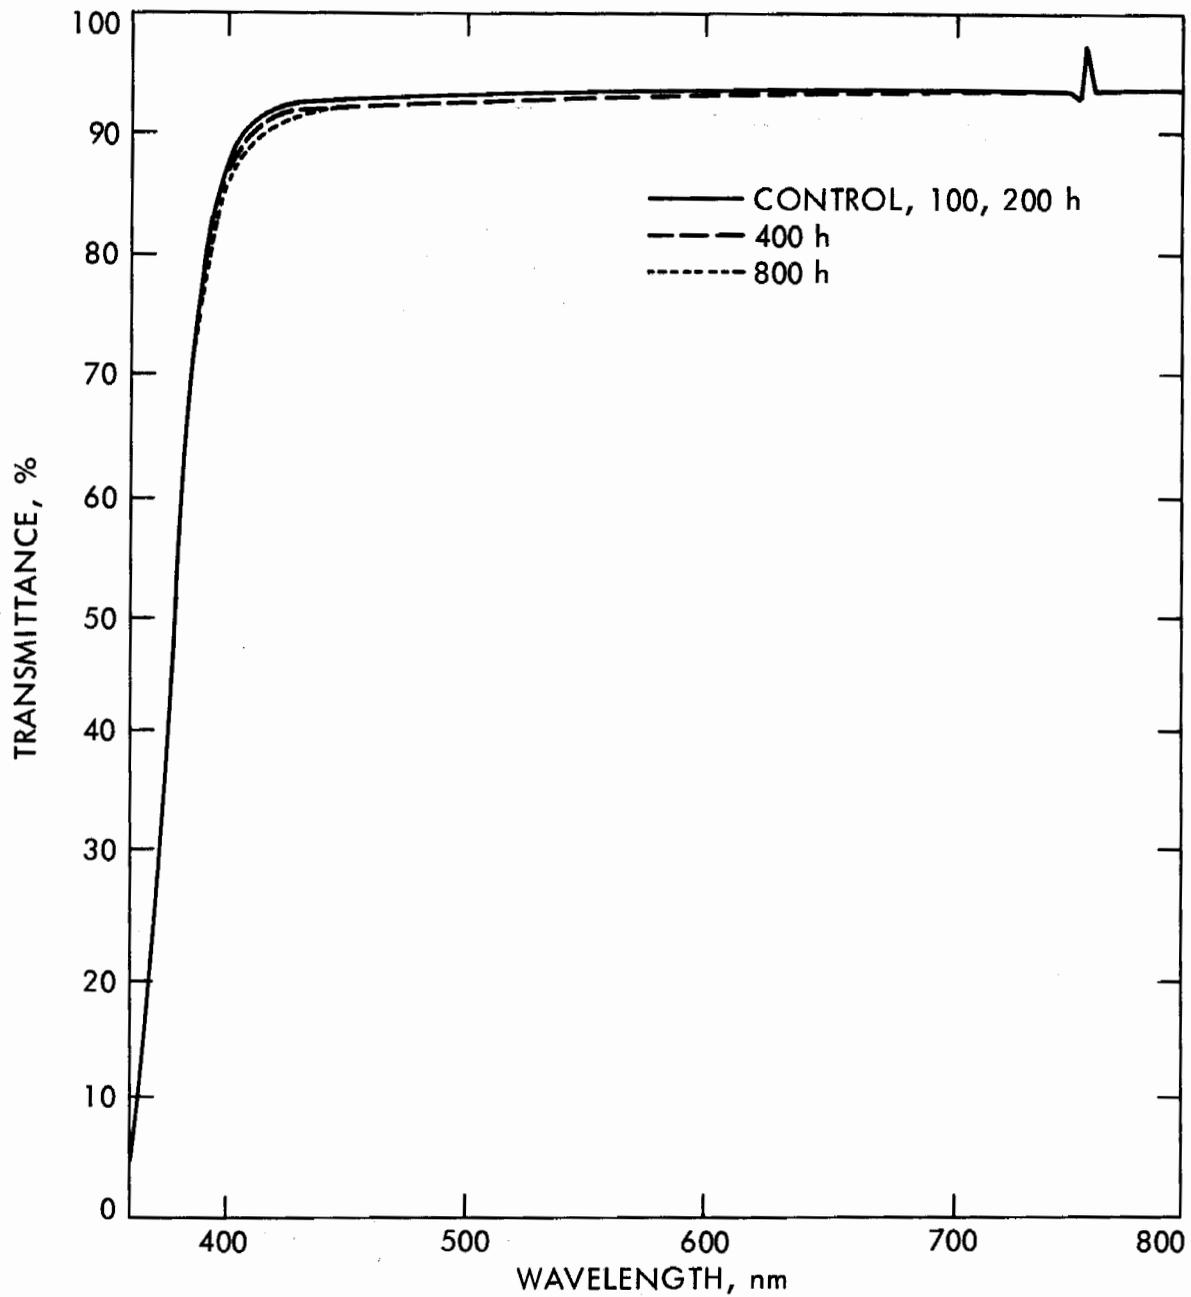


Figure 6. Change in Optical Transmittance as a Function of Open Photothermal Aging of EVA at 85°C

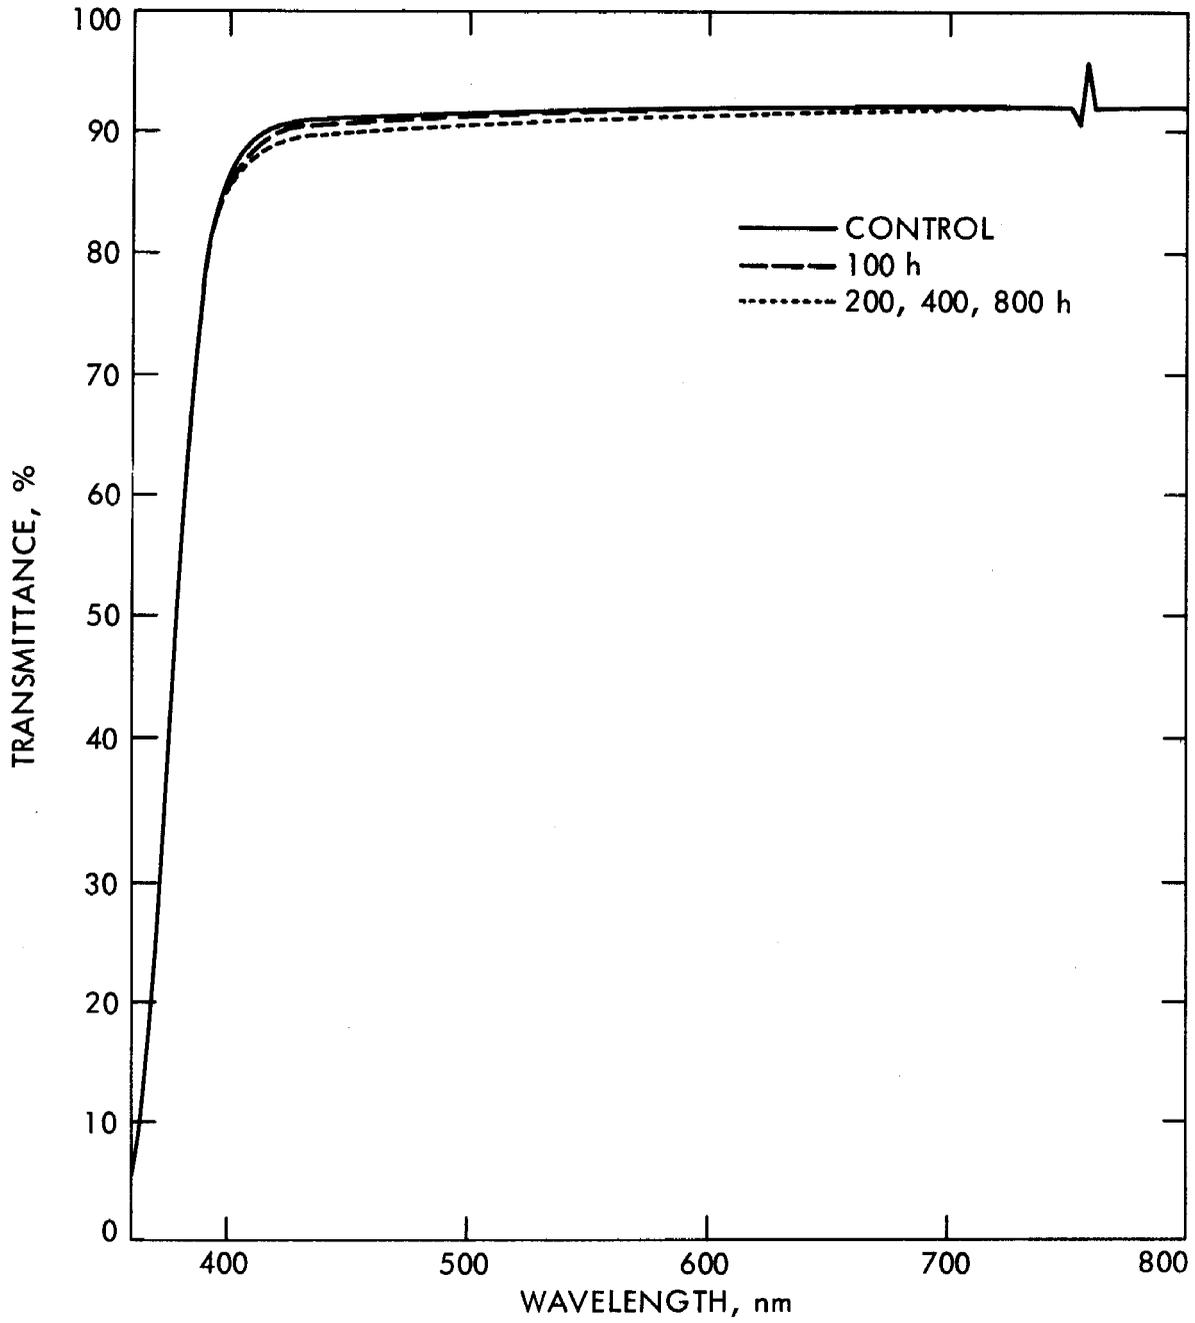


Figure 7. Change in Optical Transmittance as a Function of Covered Photothermal Aging of EVA at 85°C

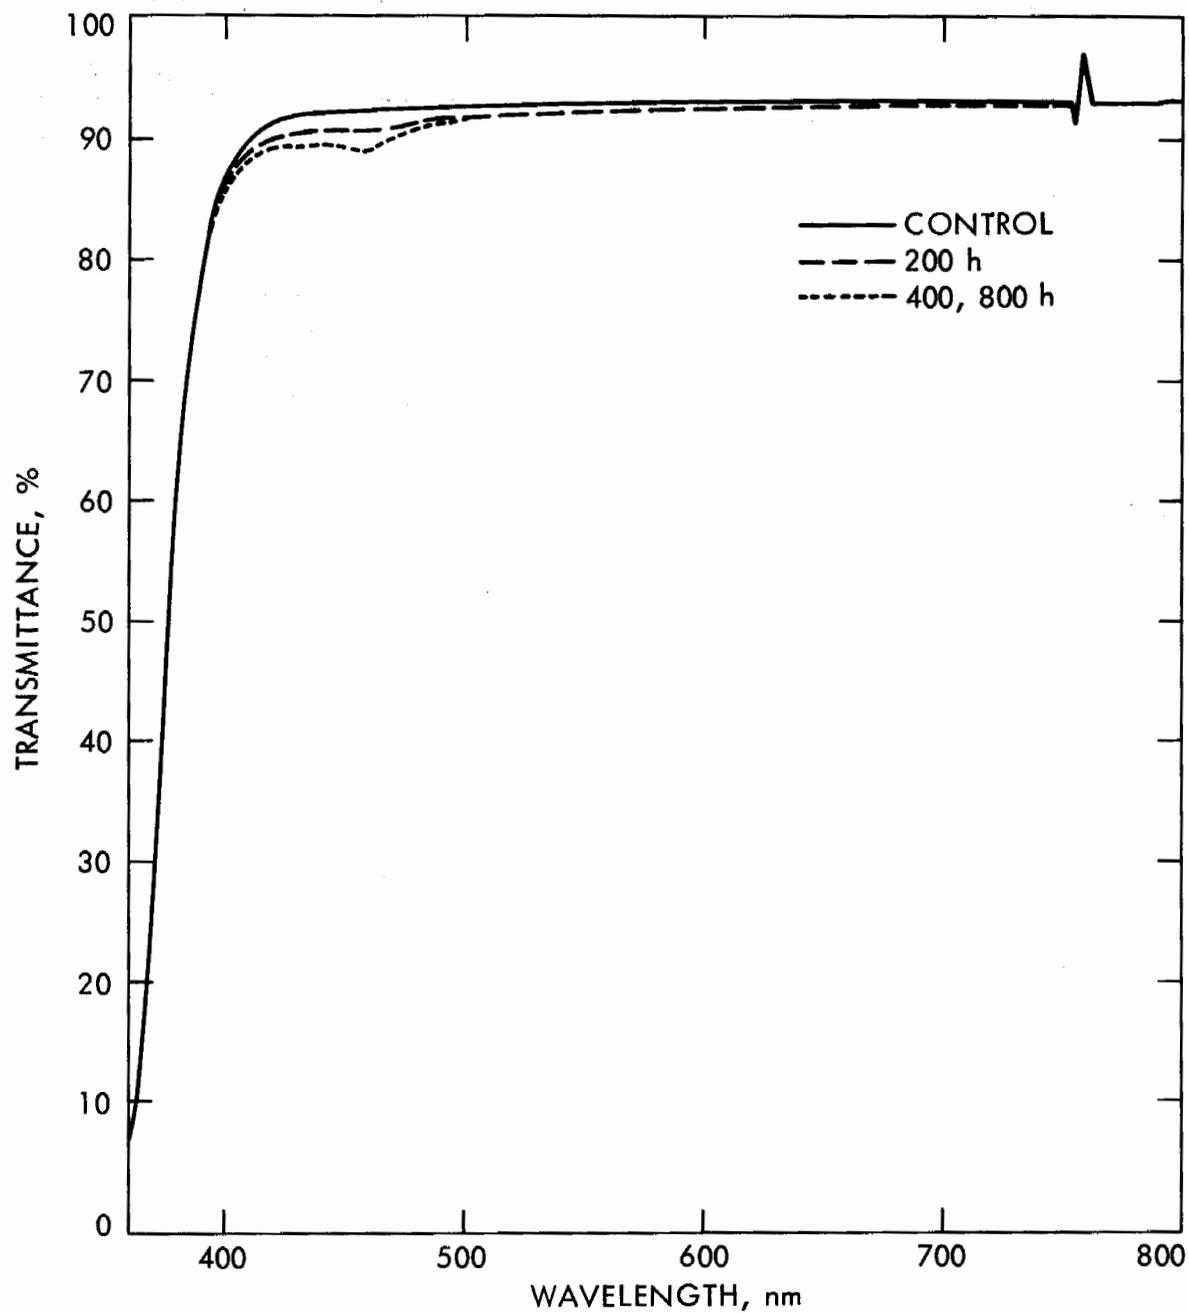


Figure 8. Change in Optical Transmittance as a Function of Thermal Aging of EVA at 85°C

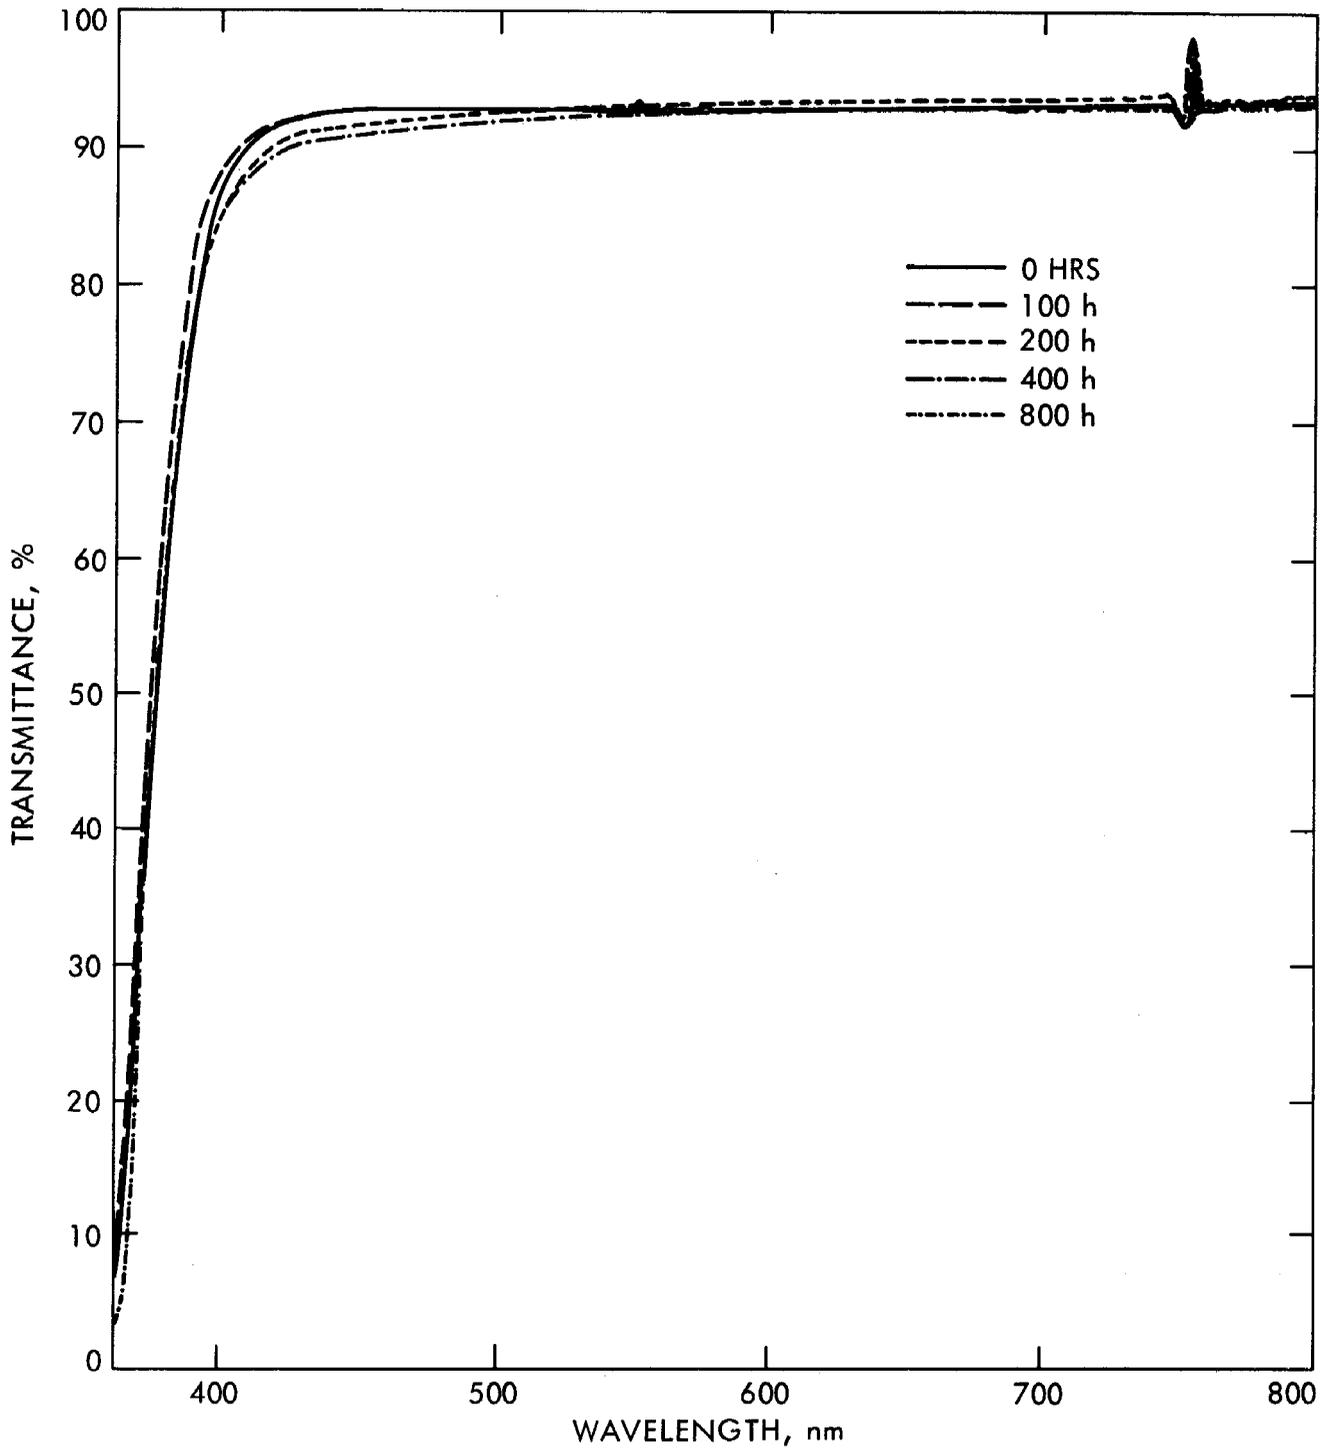


Figure 9. Change in Optical Transmittance as a Function of Open Photothermal Aging of EVA at 105°C

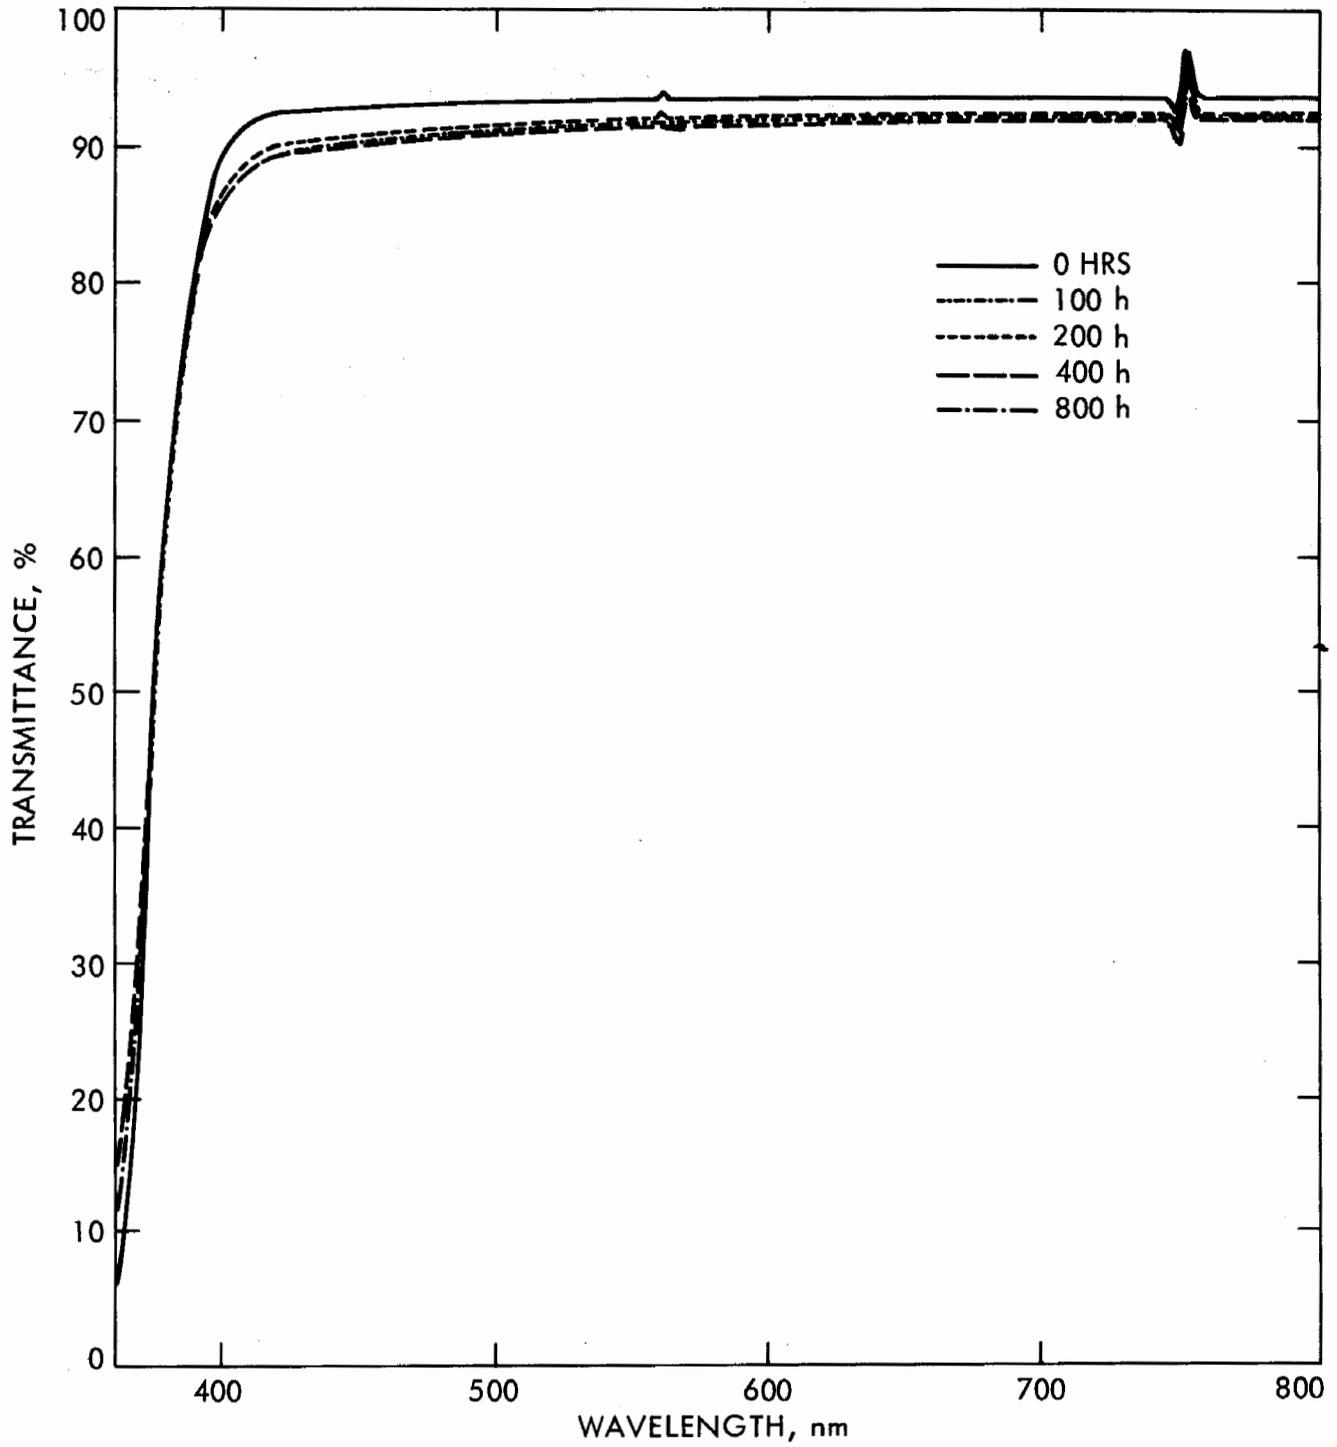


Figure 10. Change in Optical Transmittance as a Function of Covered Photothermal Aging of EVA at 105°C

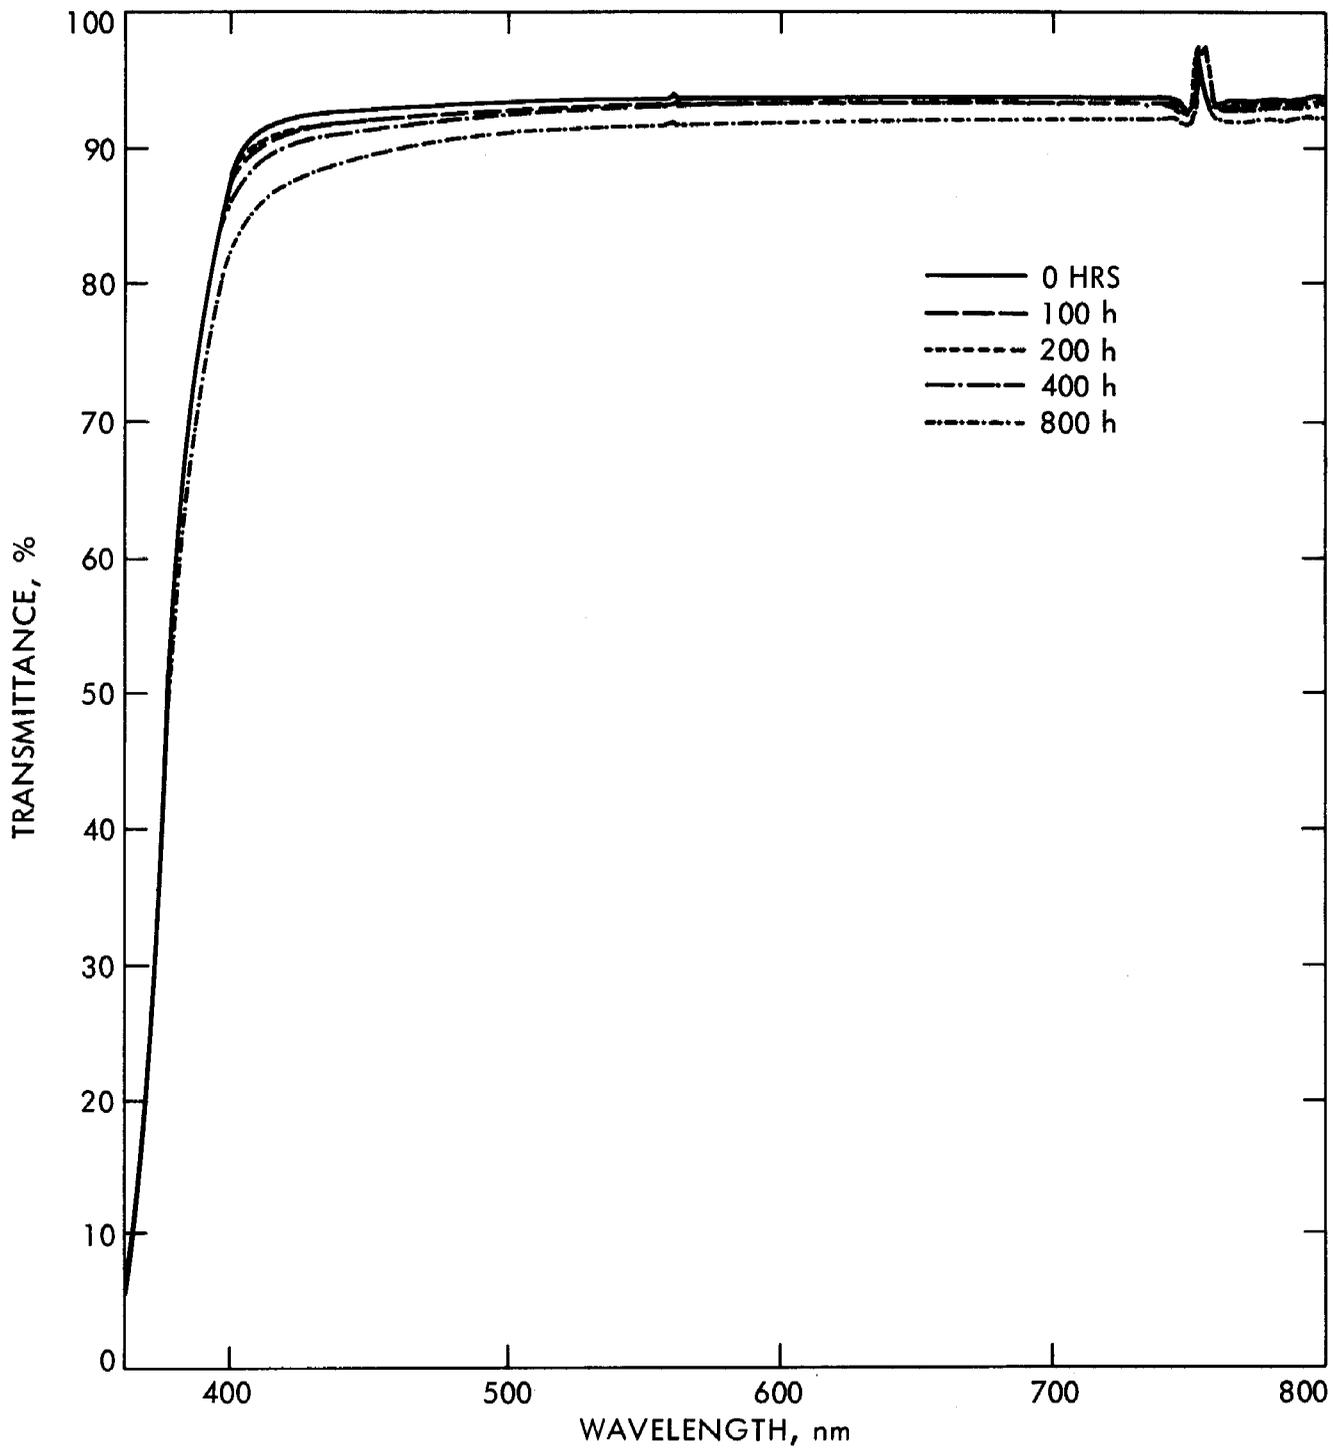


Figure 11. Change in Optical Transmittance as a Function of Thermal Aging of EVA at 105°C

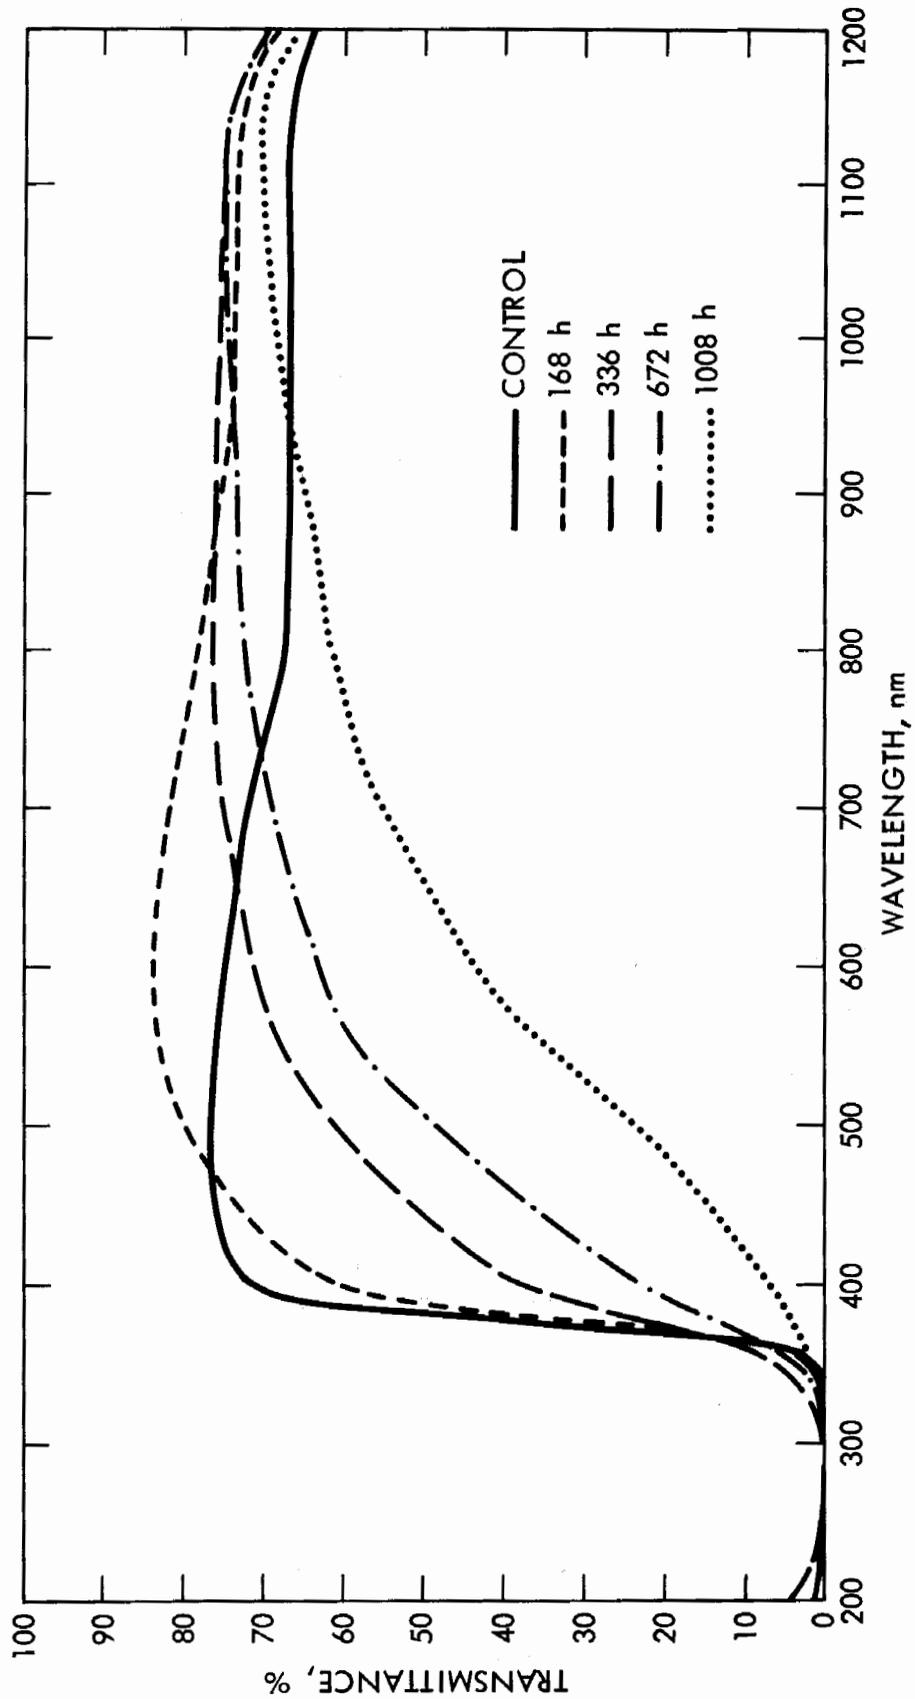


Figure 12. Change in Optical Transmittance as a Function of Covered Photothermal Aging of EVA at 135°C

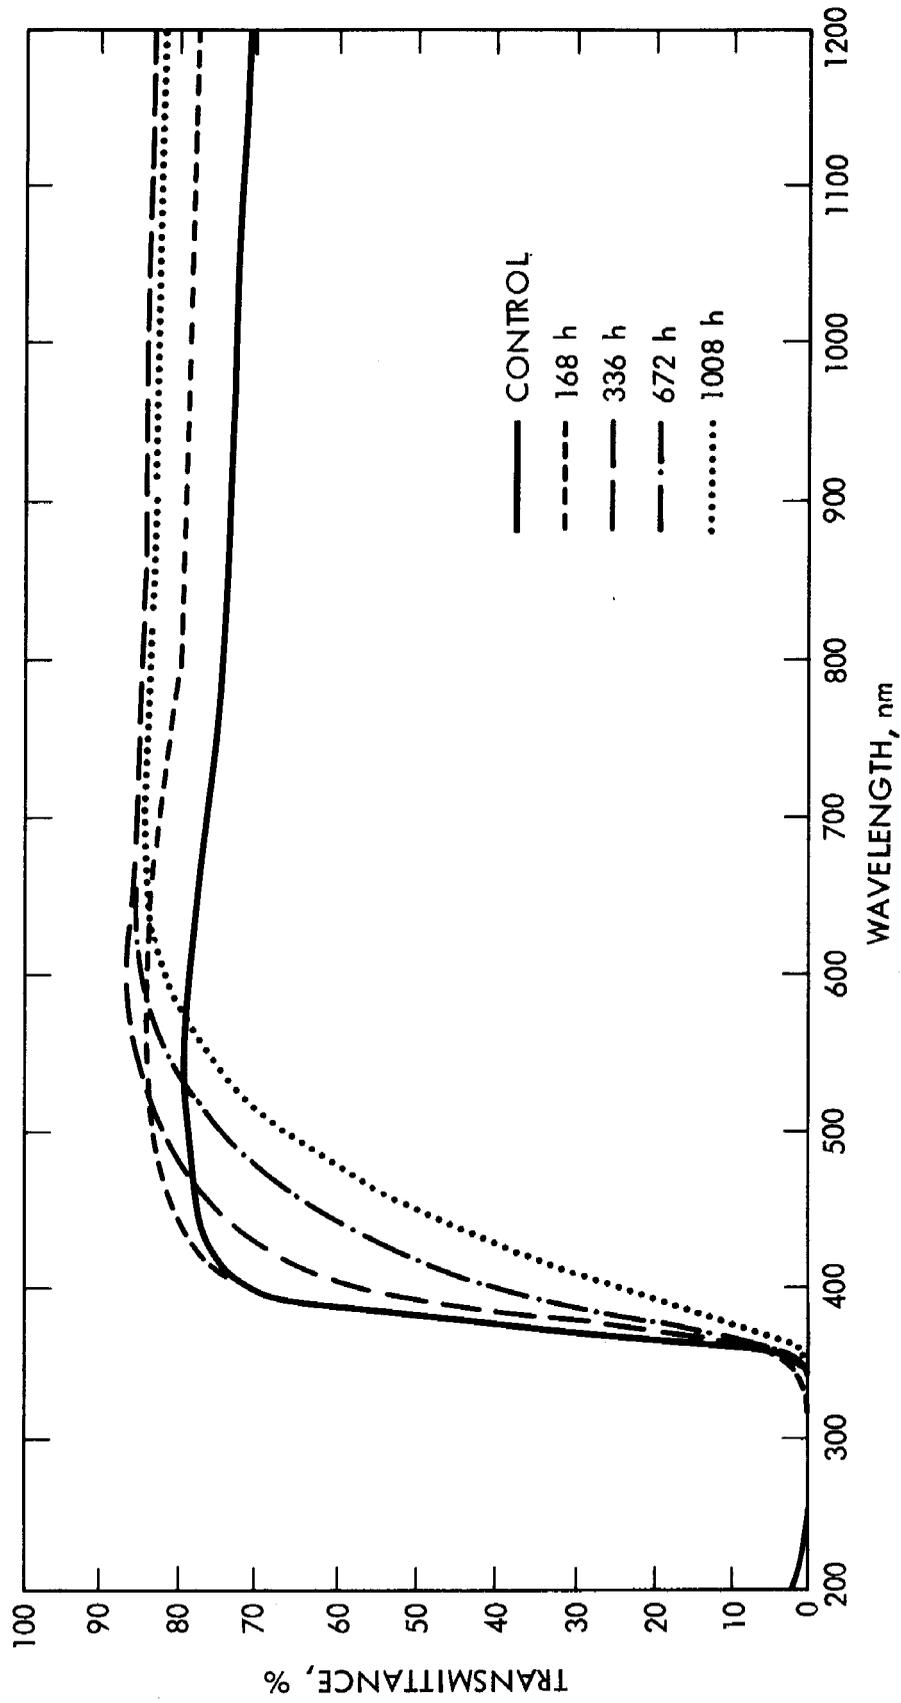


Figure 13. Change in Optical Transmittance as a Function of Thermal Aging of EVA at 135°C

B. MECHANICAL PROPERTIES

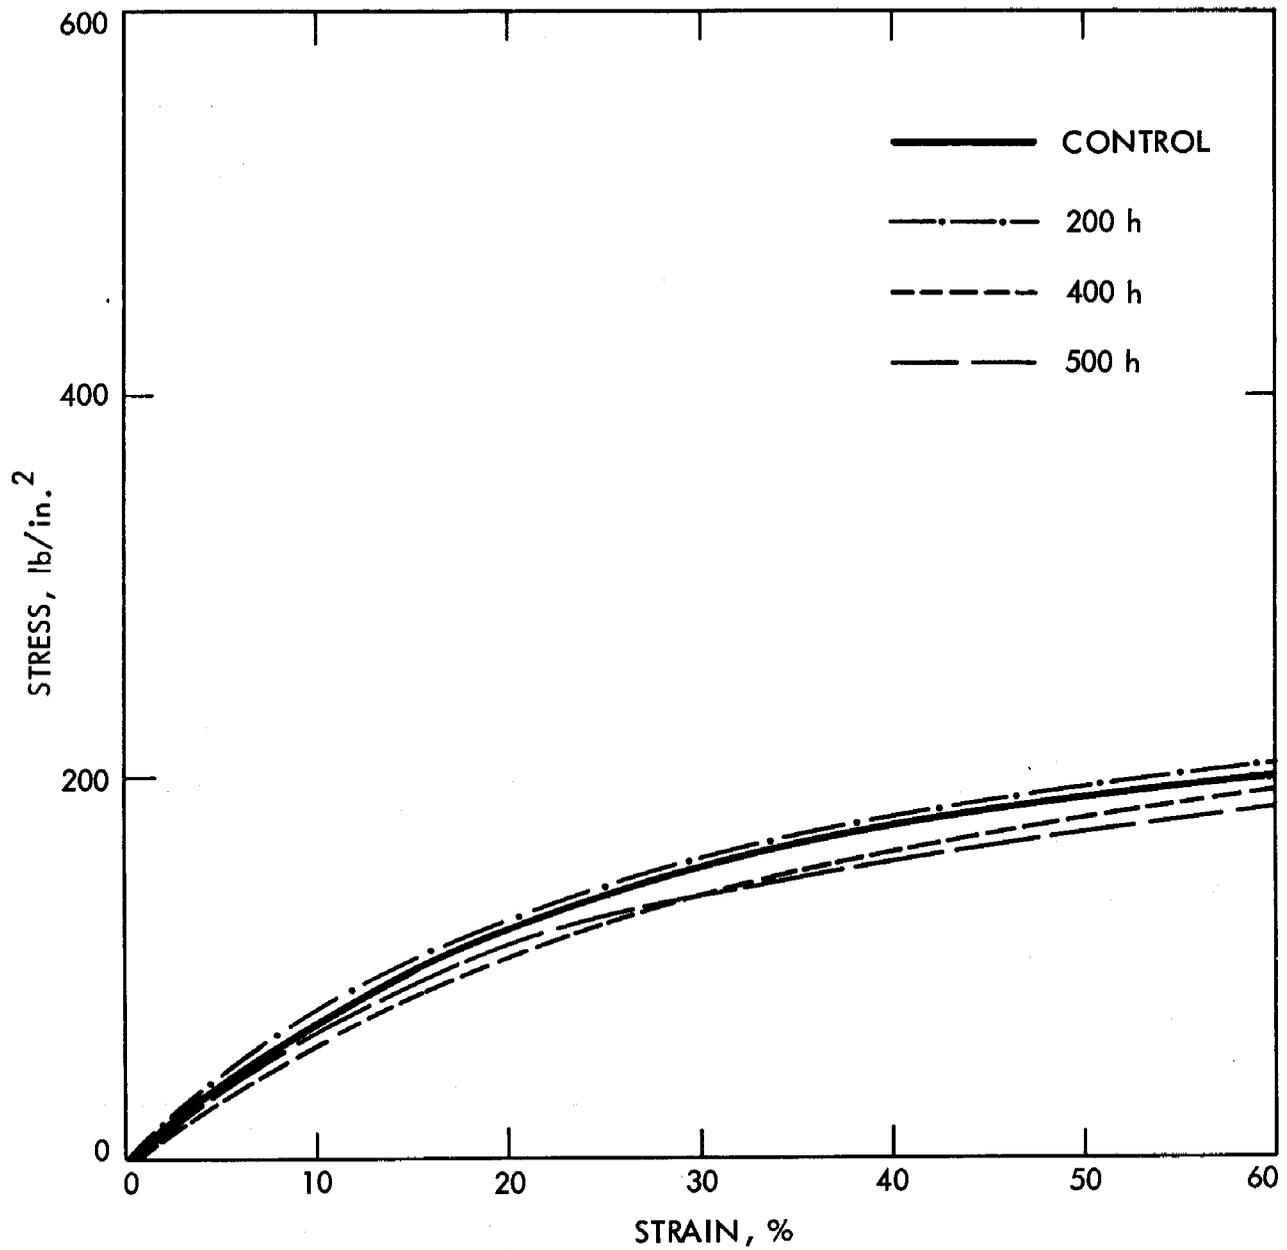


Figure 14. Change in Stress/Strain Response as a Function of Open Photothermal Aging of EVA at 70°C

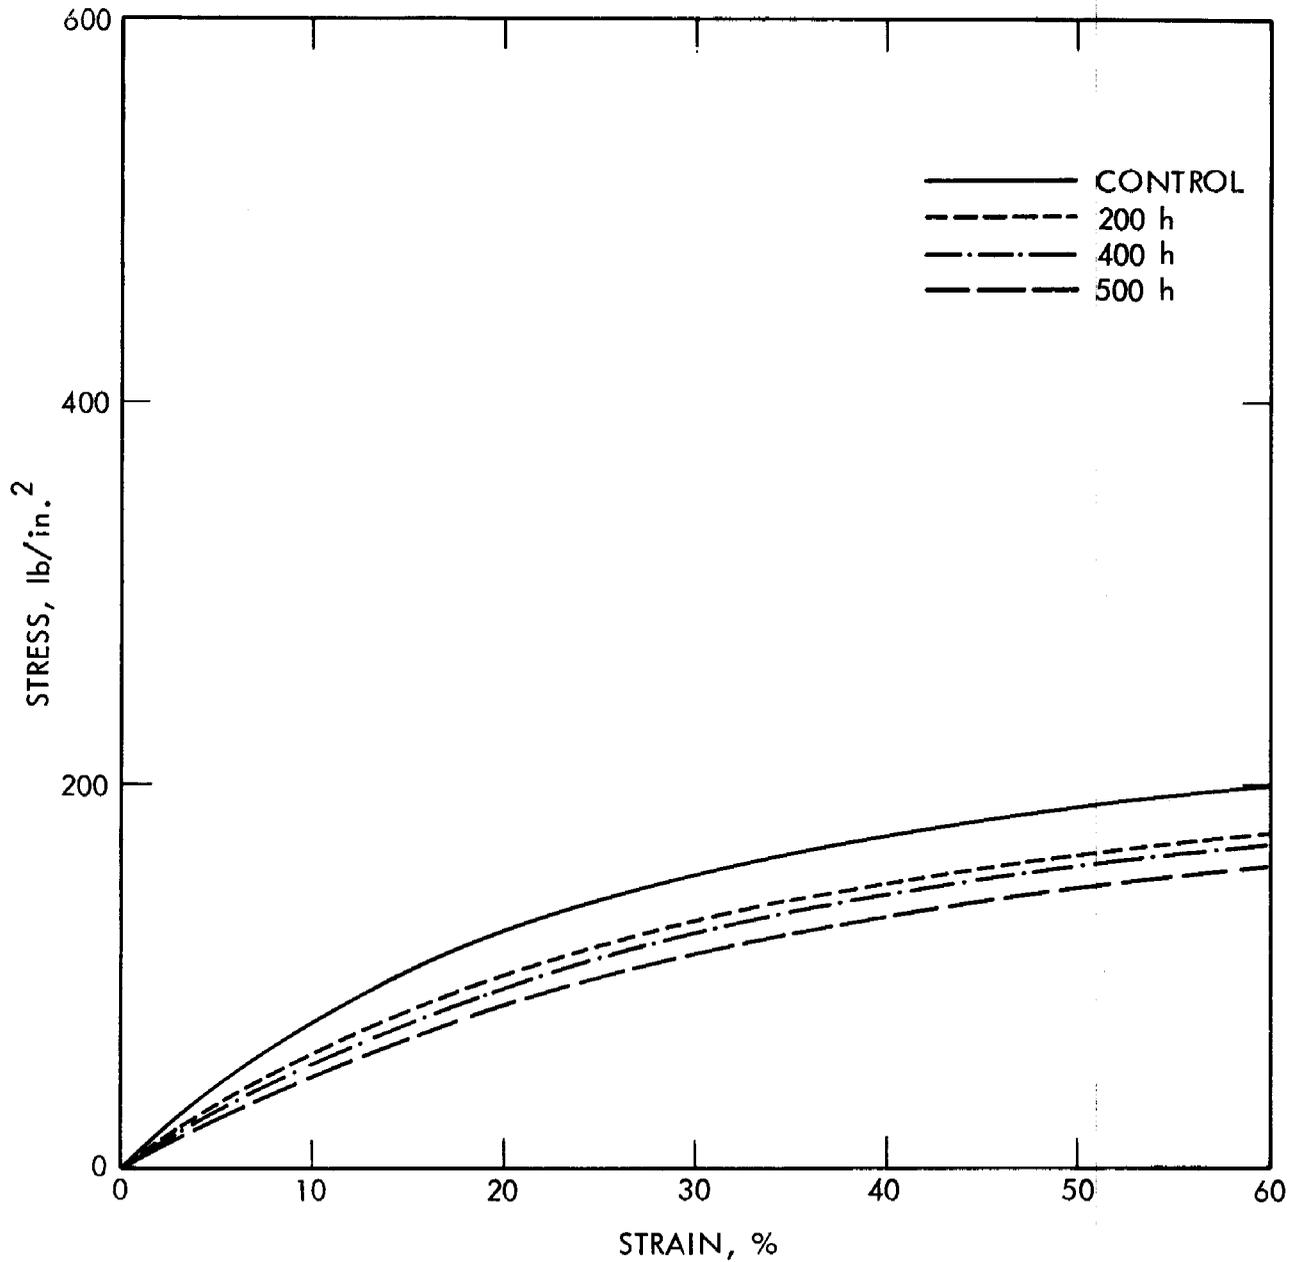


Figure 15. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EVA at 70°C

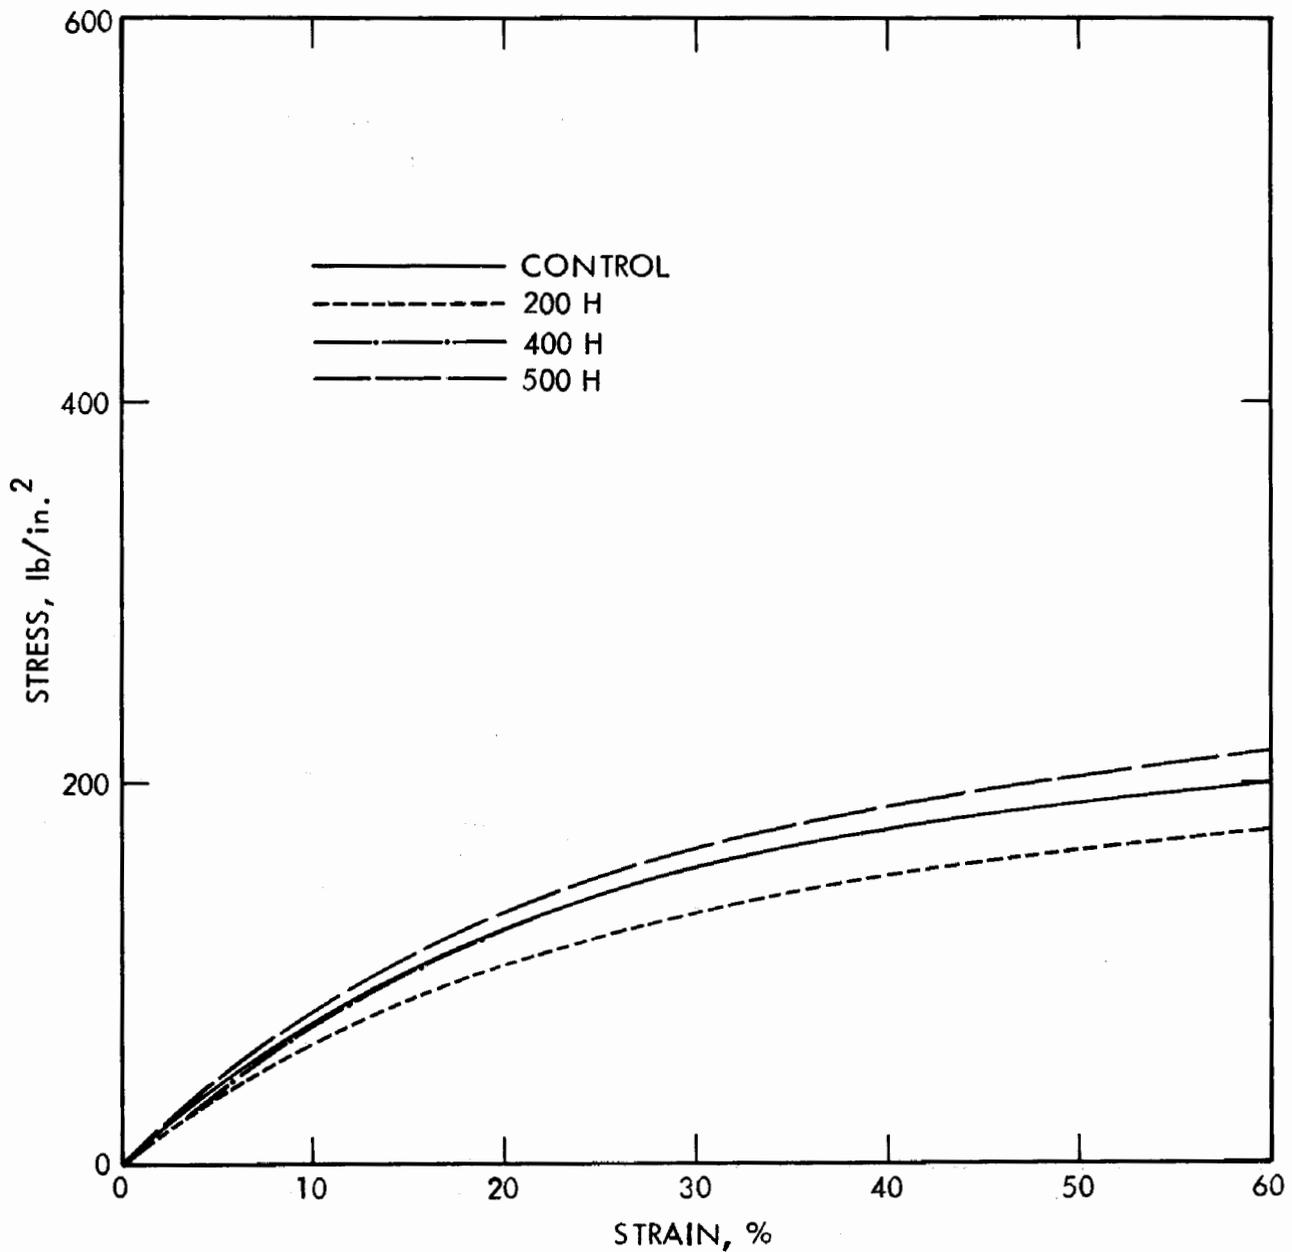


Figure 16. Change in Stress/Strain Response as a Function of Thermal Aging of EVA at 70°C

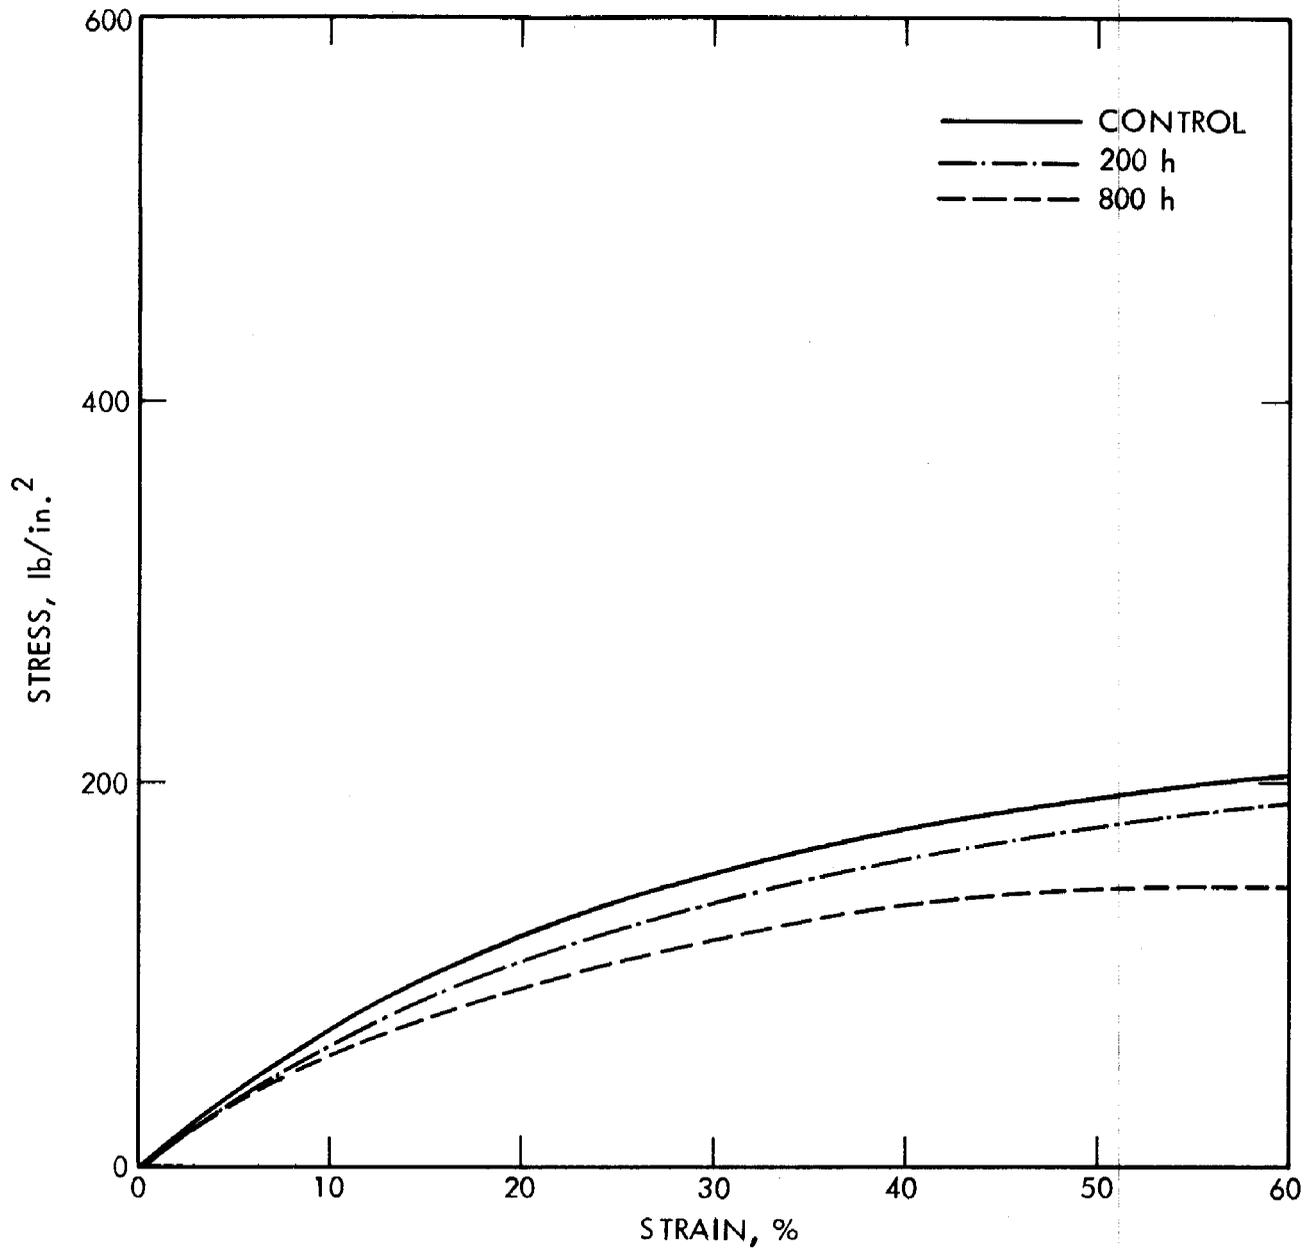


Figure 17. Change in Stress/Strain Response as a Function of Open Photothermal Aging of EVA at 85°C

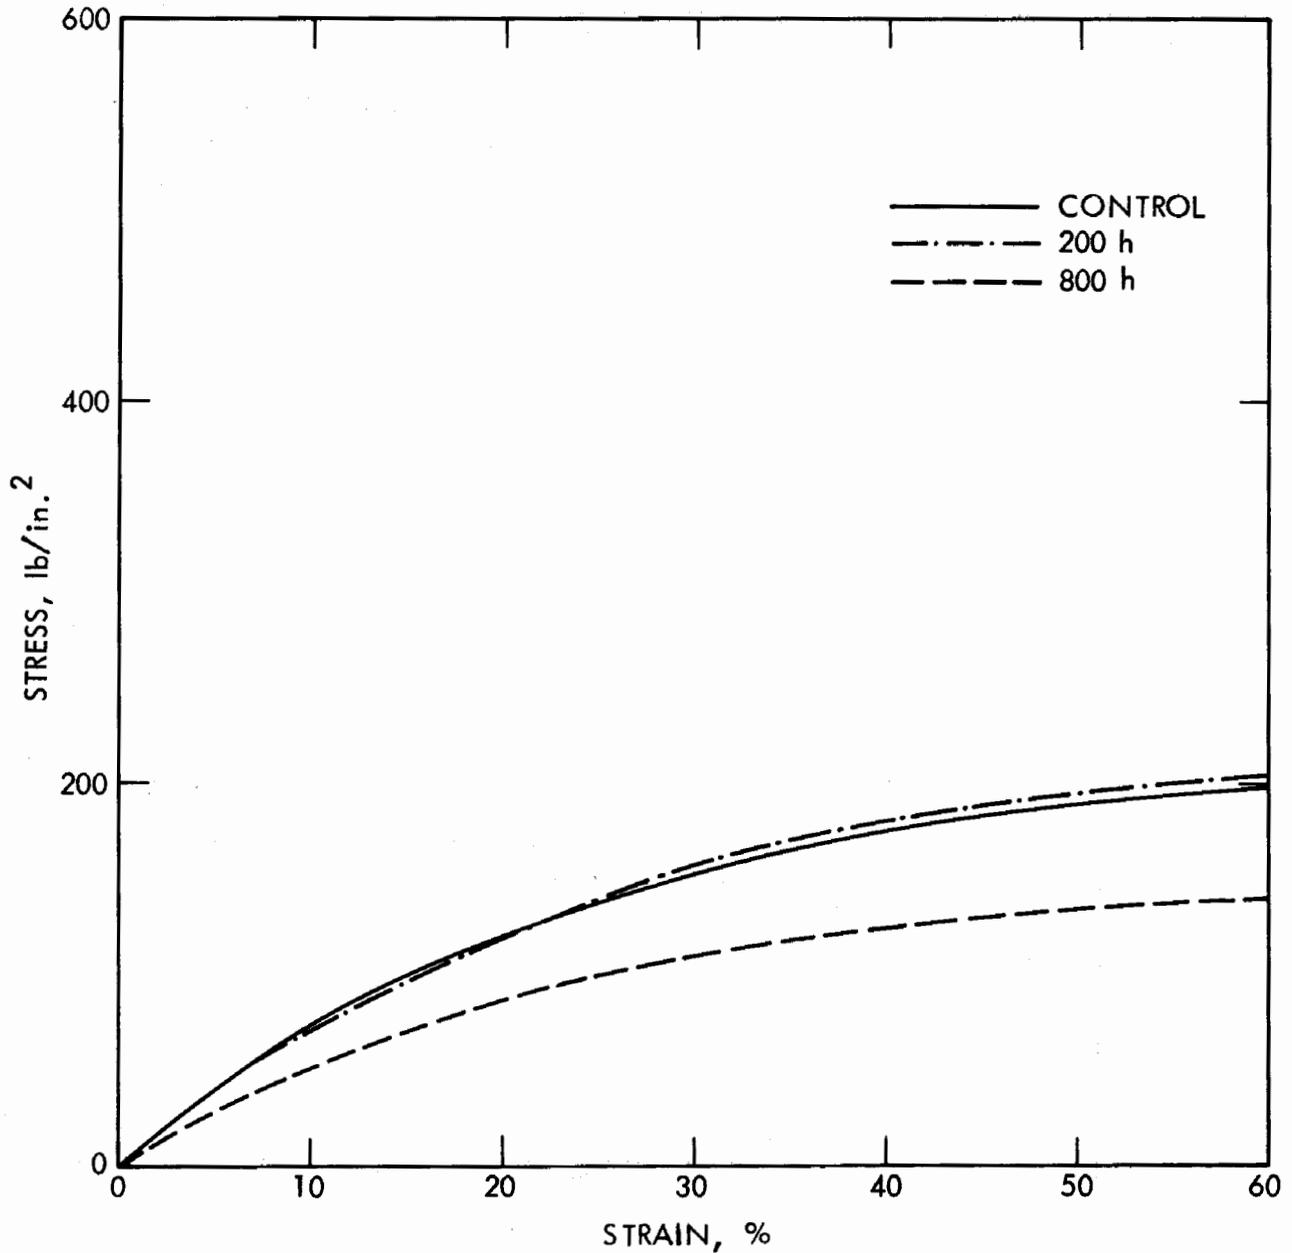


Figure 18. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EVA at 85°C

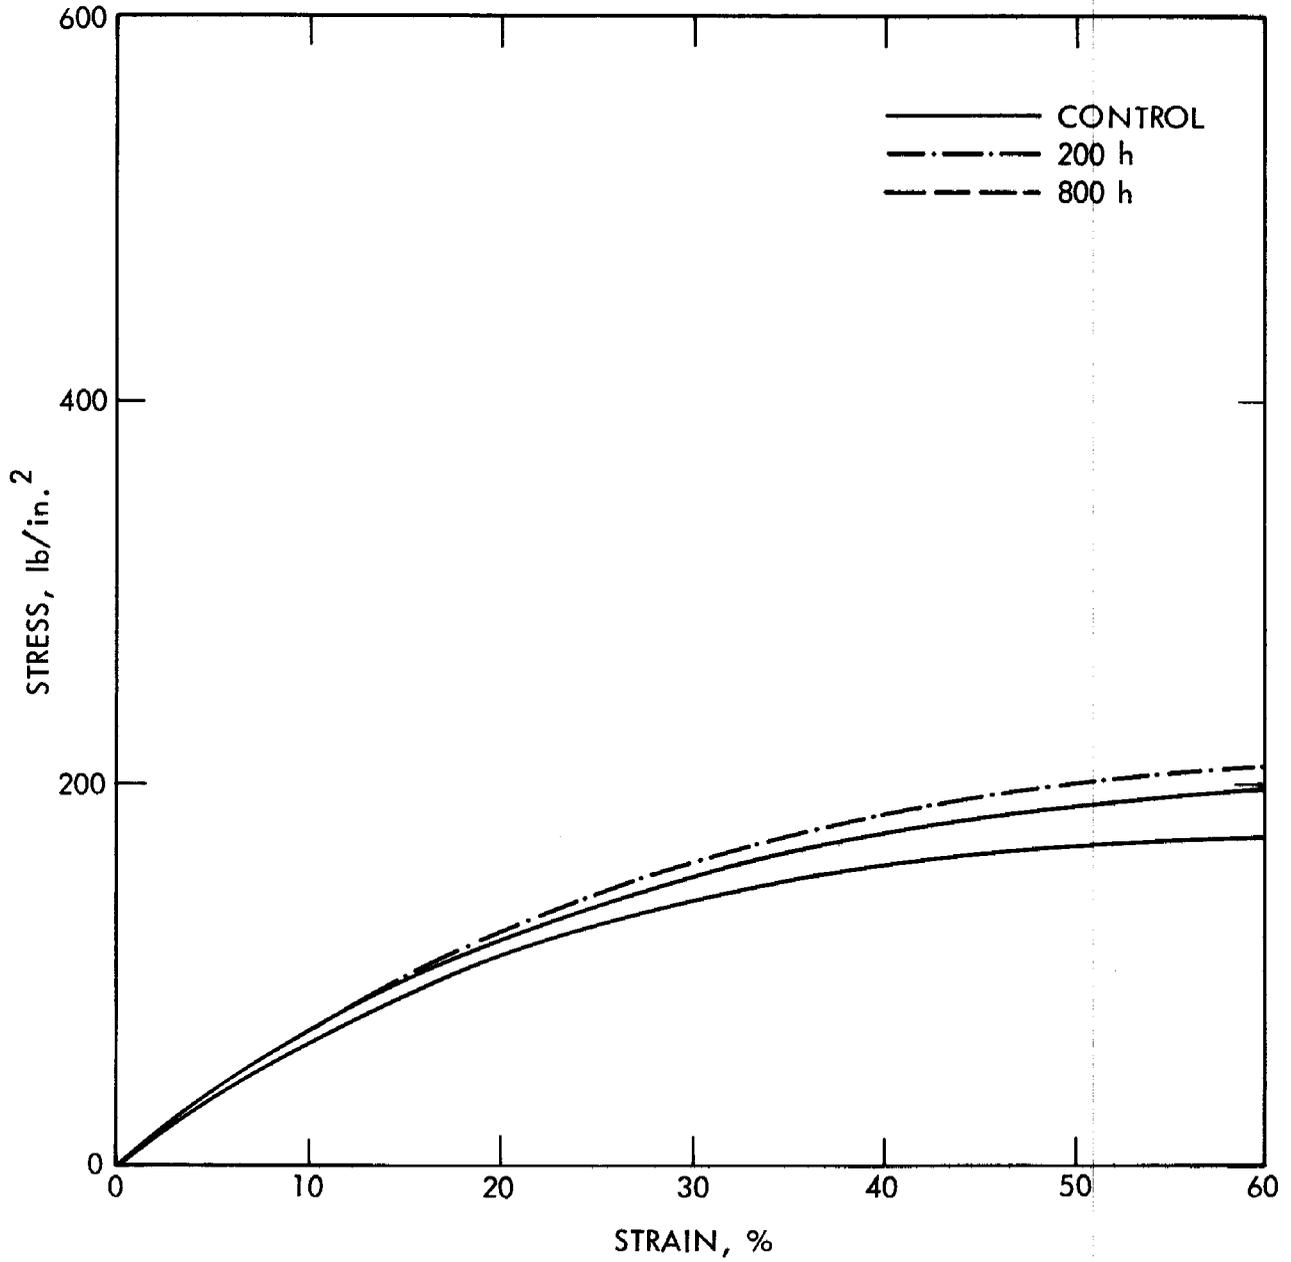


Figure 19. Change in Stress/Strain Response as a Function of Thermal Aging of EVA at 85°C

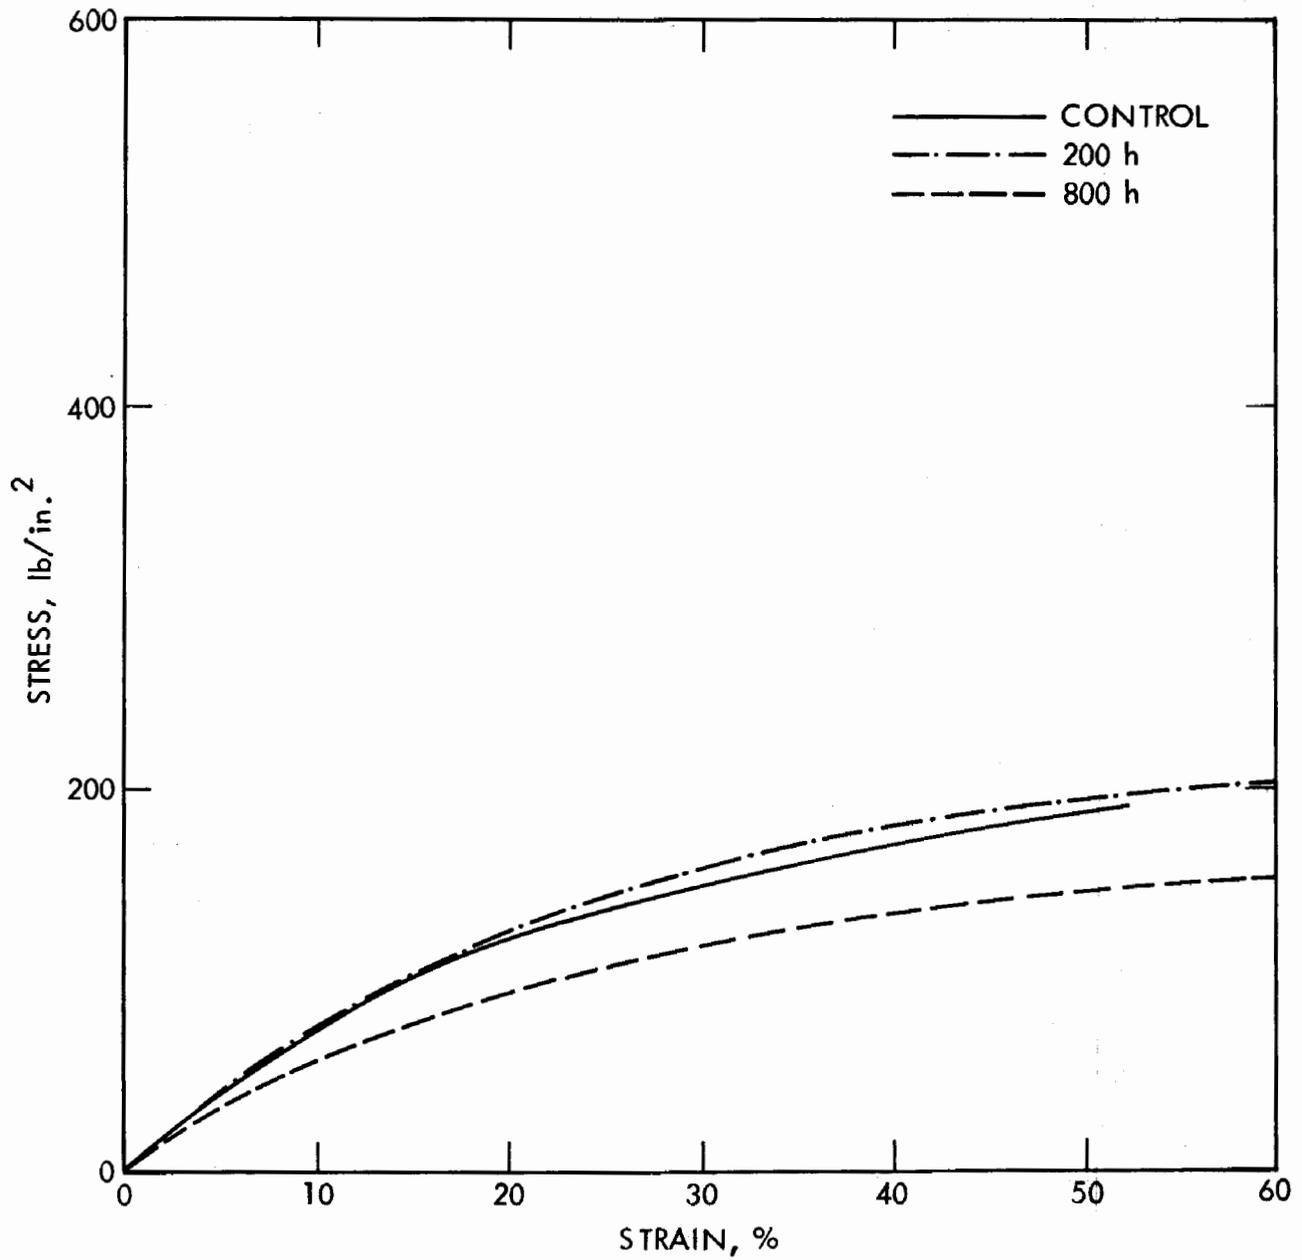


Figure 20. Change in Stress/Strain Response as a Function of Open Photothermal Aging of EVA at 105°C

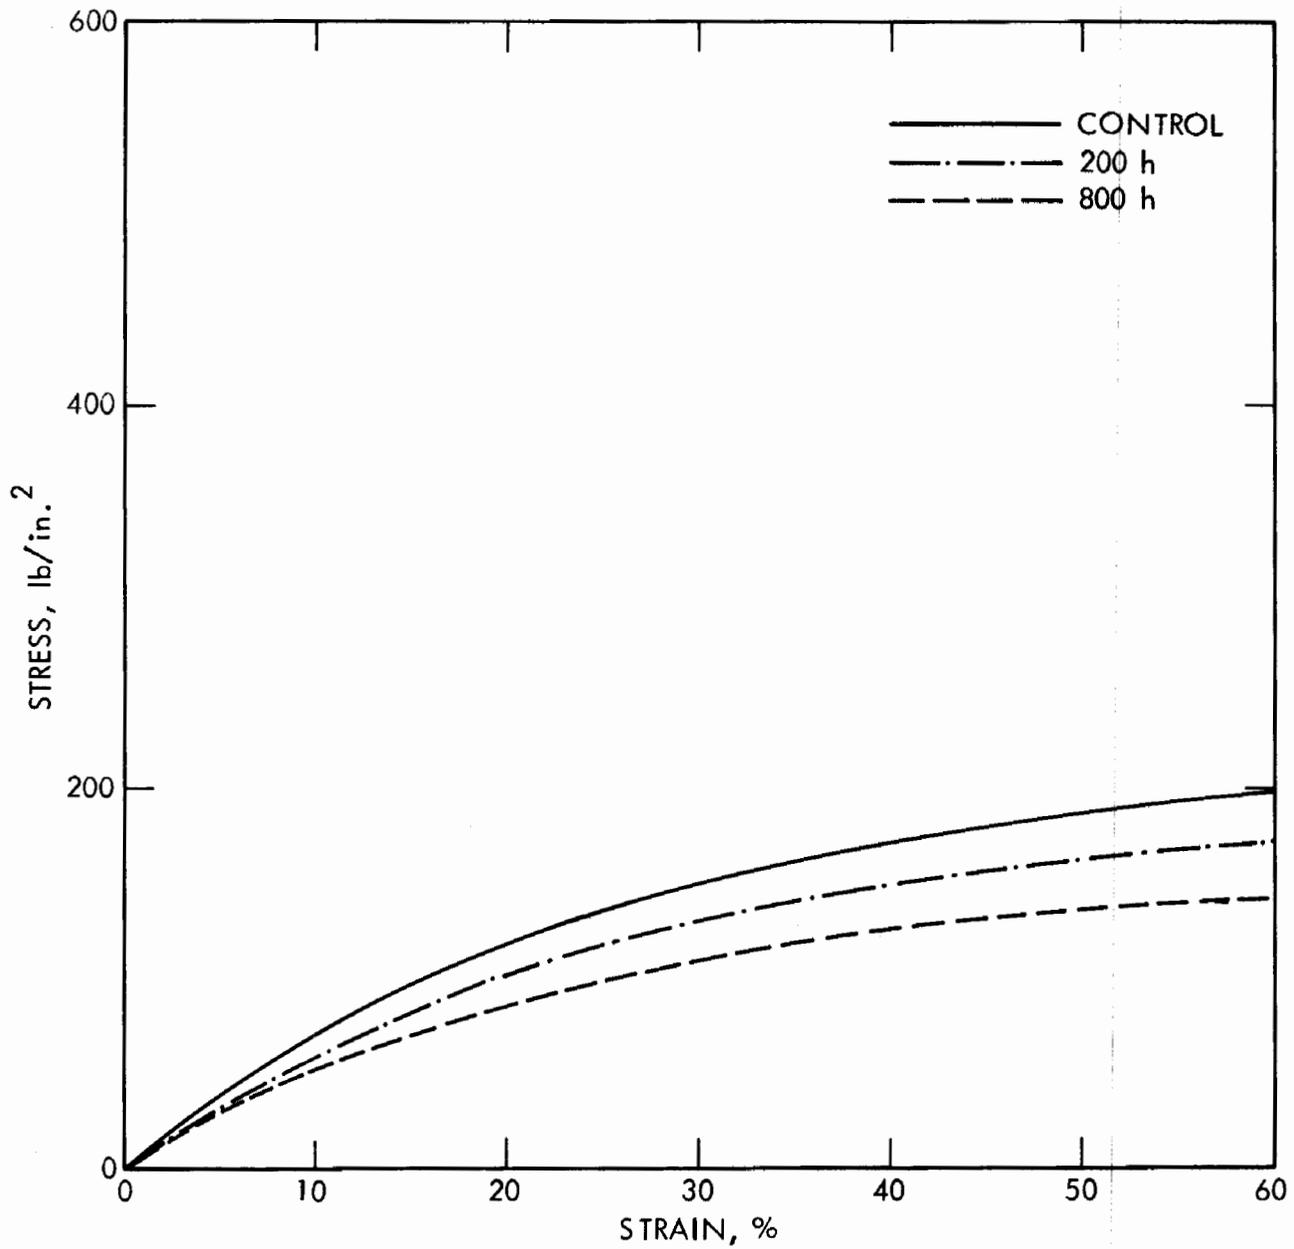


Figure 21. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EVA at 105°C

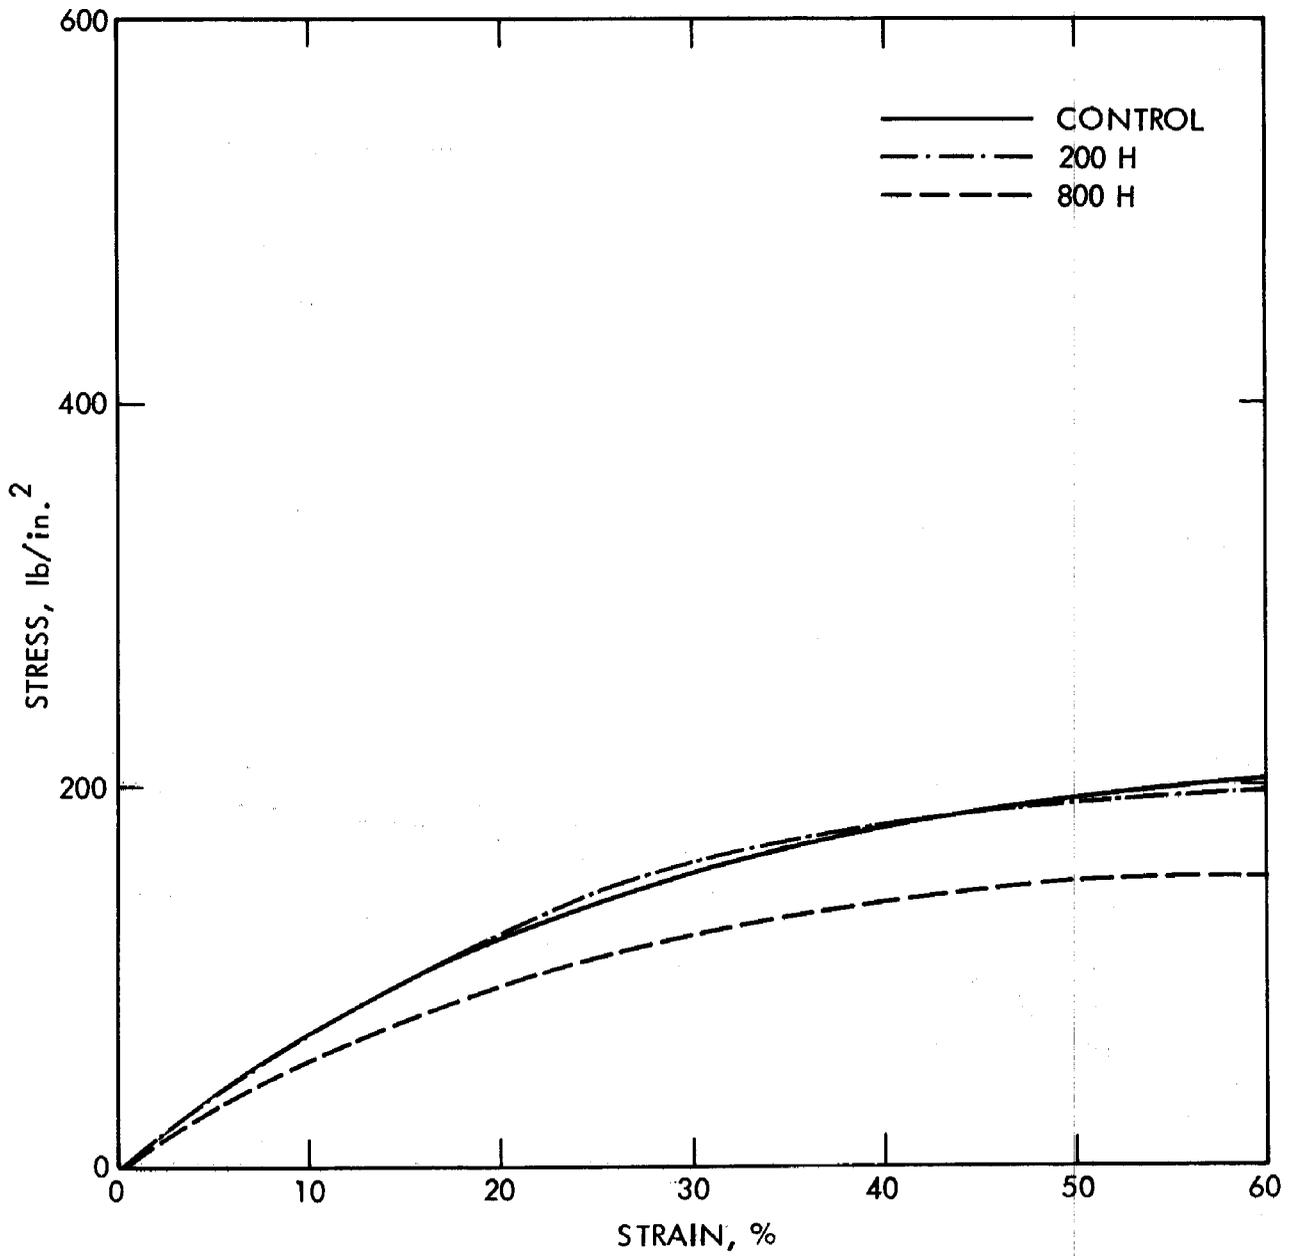


Figure 22. Change in Stress/Strain Response as a Function of Thermal Aging of EVA at 105°C

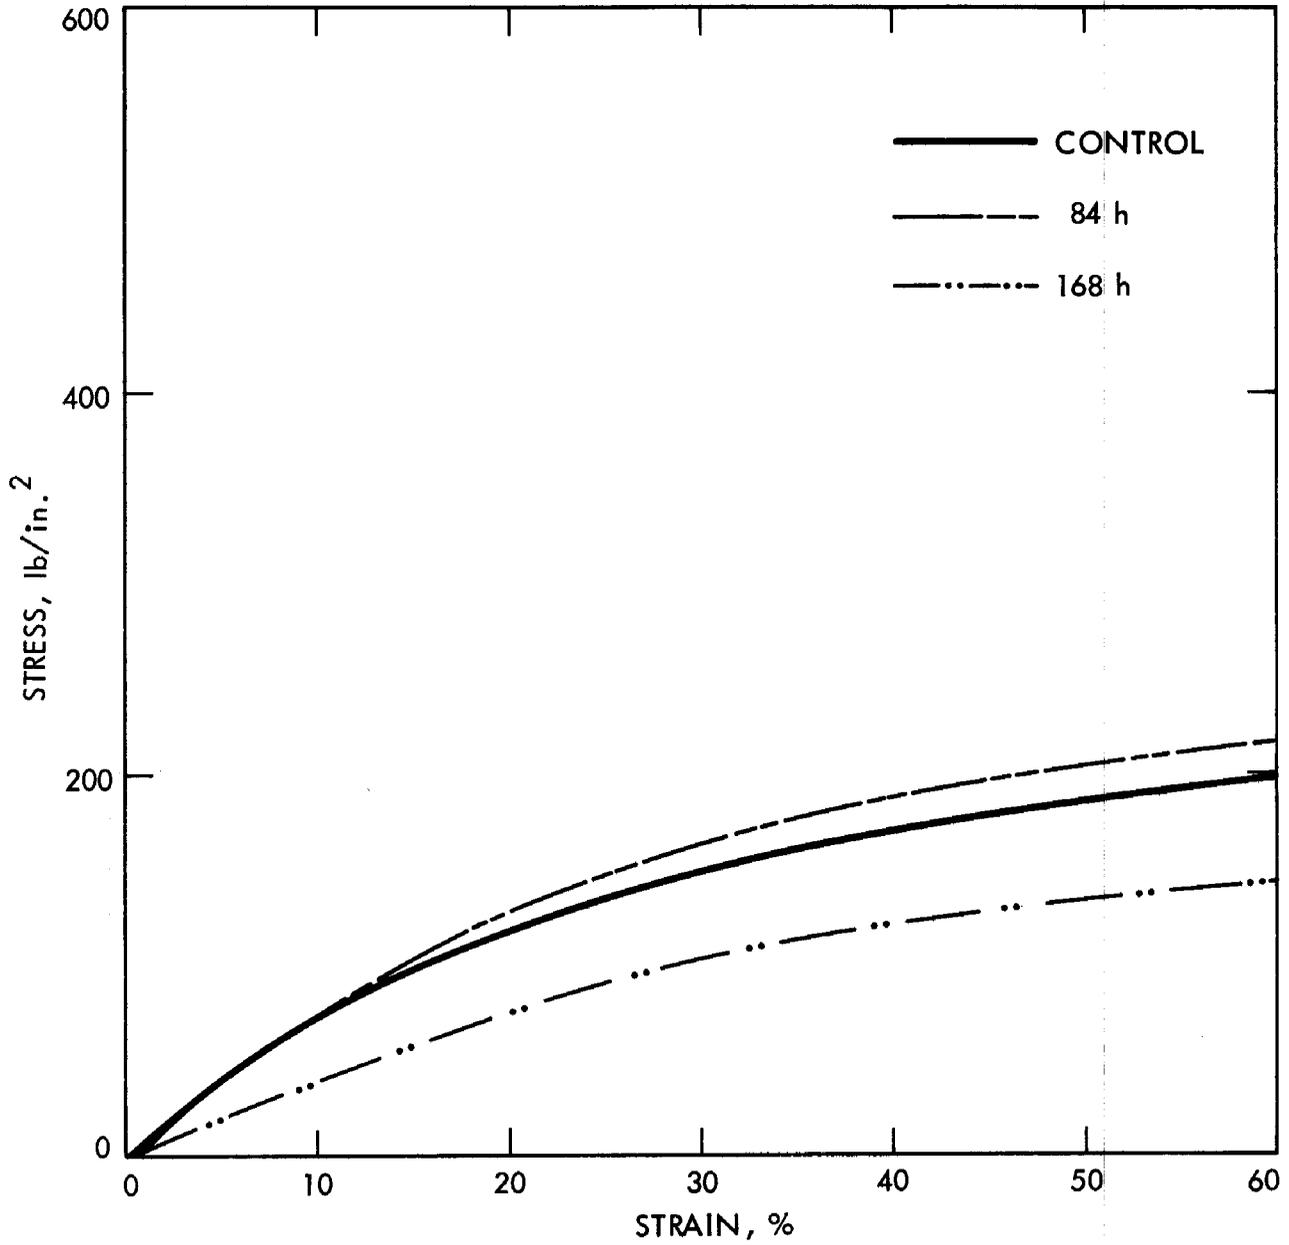


Figure 23. Change in Stress/Strain Response as a Function of Open Photothermal Aging of EVA at 135°C

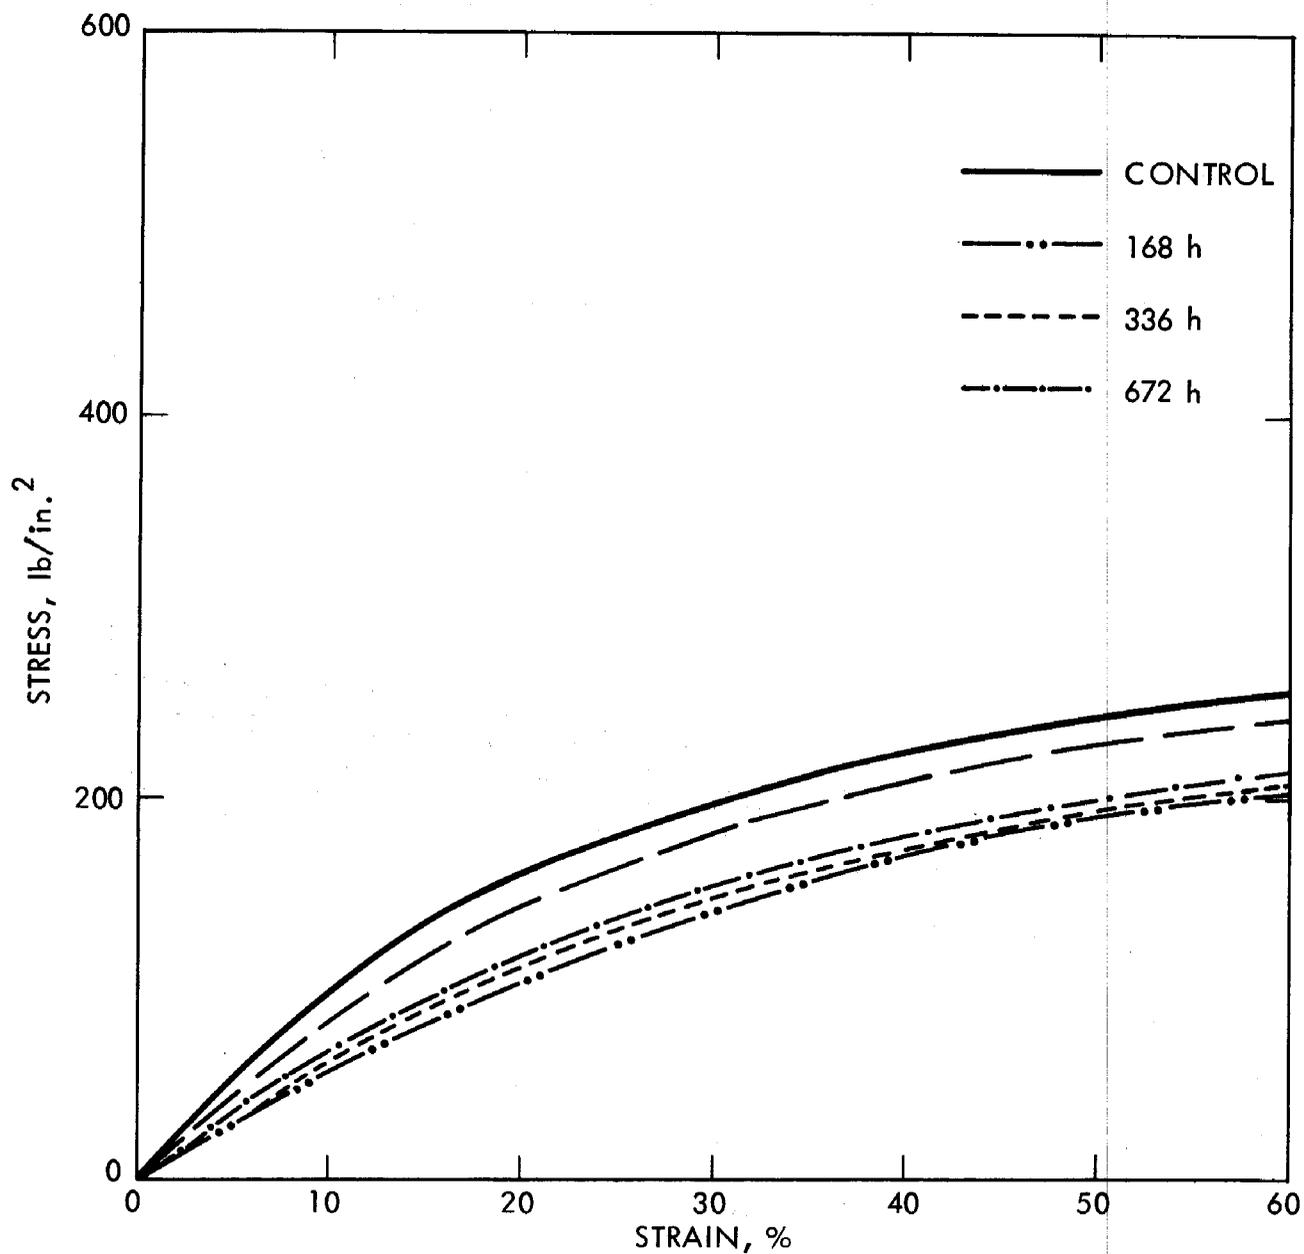


Figure 24. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EVA at 135°C

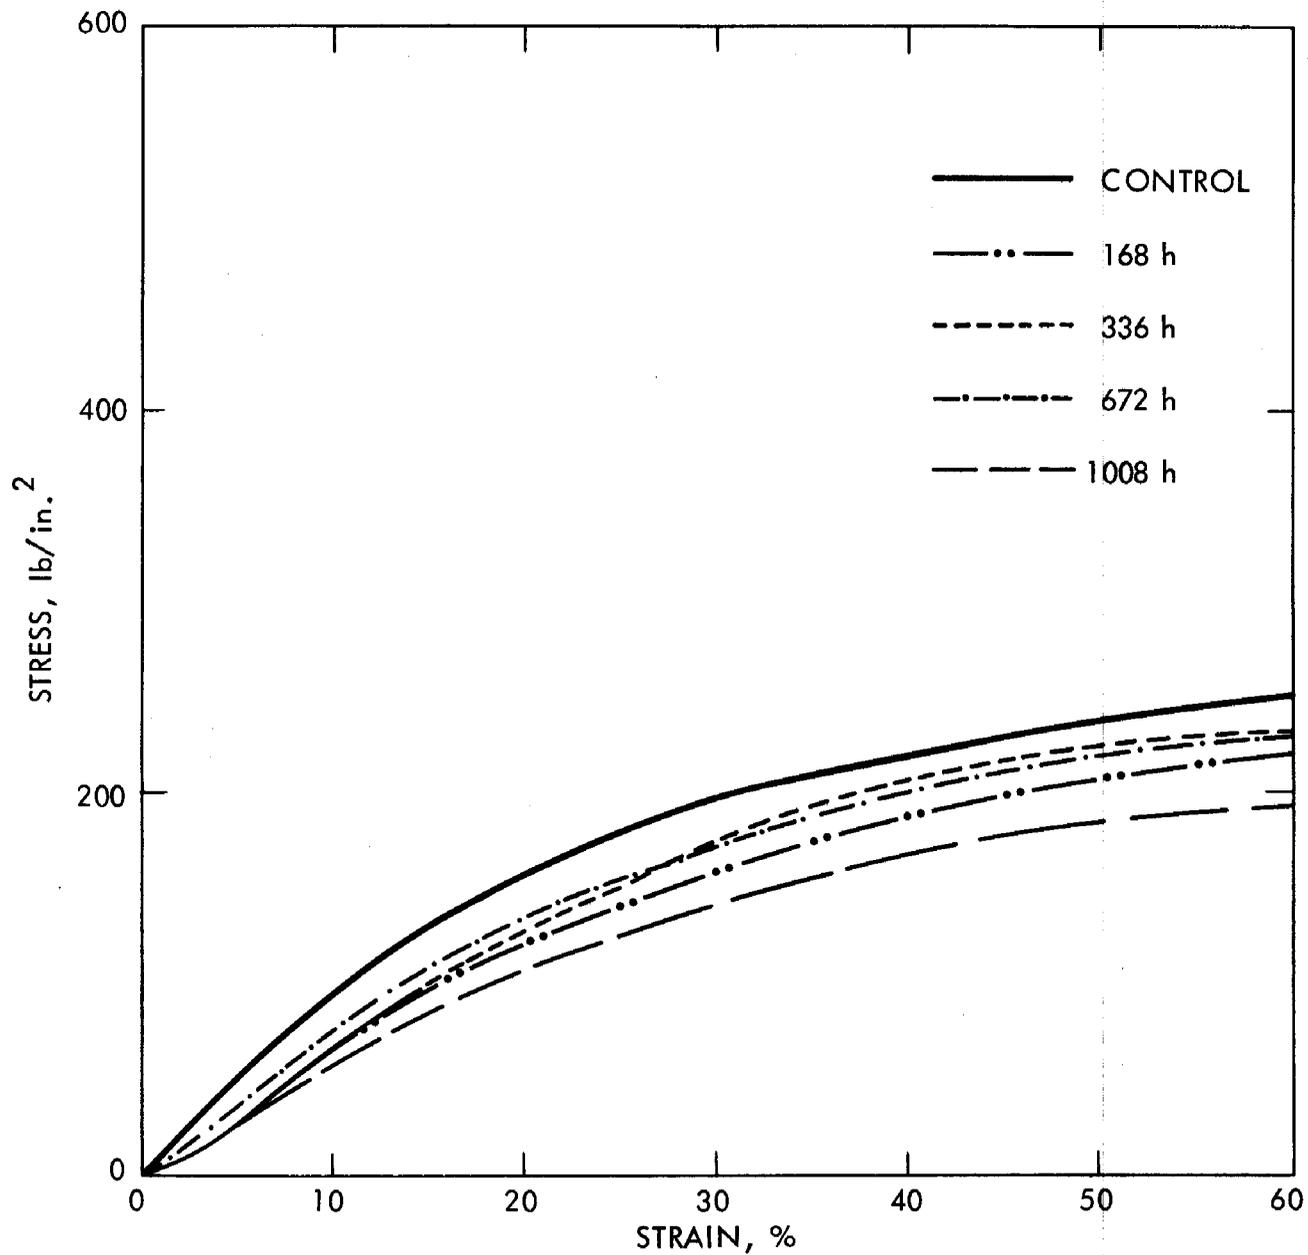


Figure 25. Change in Stress/Strain Response as a Function of Thermal Aging of EVA at 135°C

Table 4. Modulus at 5% Strain as a Function of Open Photothermal Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C

| TEMPERATURE<br>°C | TIME OF<br>AGING, h | MODULUS, lb/in. <sup>2</sup><br>5% STRAIN |
|-------------------|---------------------|---|
| ROOM TEMP. (30)   | 0.0                 | 1015                                      |
| 70                | 400                 | 586                                       |
|                   | 500                 | 650                                       |
| 85                | 200                 | 582                                       |
|                   | 800                 | 628                                       |
| 105               | 200                 | 836                                       |
|                   | 800                 | 566                                       |
| 135               | 84                  | 734                                       |
|                   | 168                 | *   |

\*SAMPLE DEGRADED, UNABLE TO OBTAIN MODULUS DATA

Table 5. Modulus at 5% Strain as a Function of Covered Photothermal Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C

| TEMPERATURE,<br>°C | TIME OF<br>AGING, h       | MODULUS, lb/in. <sup>2</sup><br>5% STRAIN |
|--------------------|---------------------------|---|
| ROOM TEMP. (30)    | 0                         | 1015                                      |
| 70                 | 200<br>500                | 671<br>630                                |
| 85                 | 200<br>800                | 846<br>504                                |
| 105                | 200<br>800                | 550<br>664                                |
| 135                | 168<br>336<br>672<br>1008 | 600<br>580<br>625<br>869                  |

Table 6. Modulus at 5% Strain as a Function of Thermal Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C

| TEMPERATURE,<br>°C | TIME OF<br>AGING, h | MODULUS, lb/in. <sup>2</sup><br>5% STRAIN |
|--------------------|---------------------|---|
| ROOM TEMP. (30)    | 0                   | 1015                                      |
| 70                 | 200                 | 855                                       |
|                    | 400                 | 554                                       |
|                    | 500                 | 640                                       |
| 85                 | 200                 | 577                                       |
|                    | 800                 | 700                                       |
| 105                | 200                 | 786                                       |
|                    | 800                 | 610                                       |
| 135                | 168                 | 560                                       |
|                    | 336                 | 582                                       |
|                    | 672                 | 742                                       |
|                    | 1008                | 870                                       |

C. WEIGHT LOSS

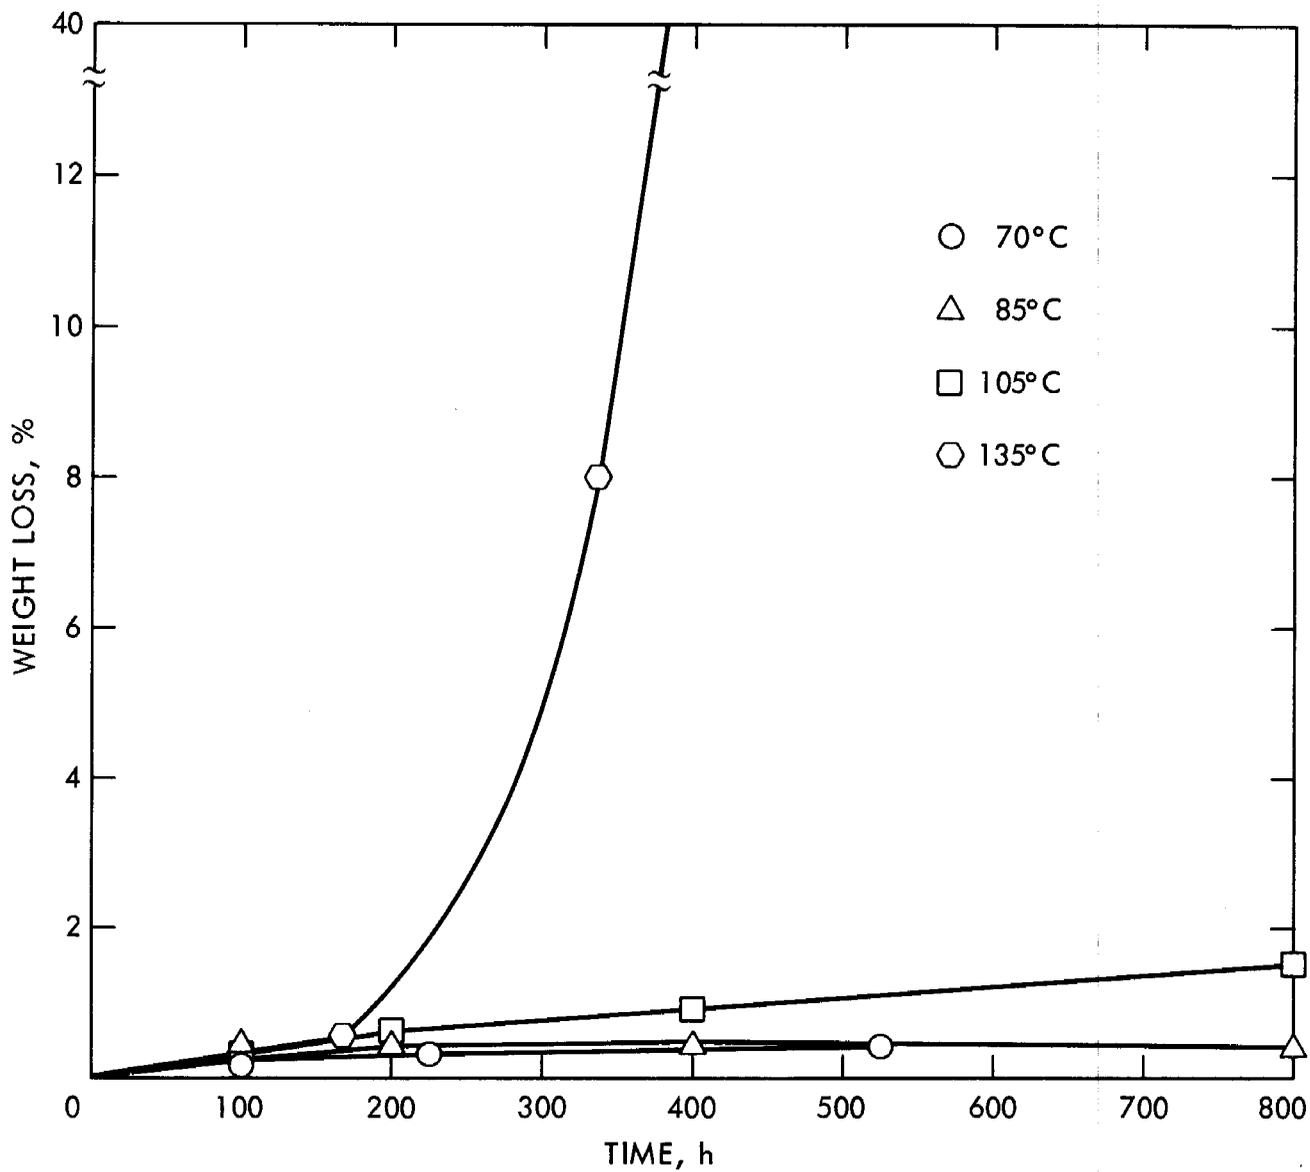


Figure 26. Weight Loss as a Function of Open Photothermal Aging of EVA at 70°C, 85°C, 105°C, and 135°C

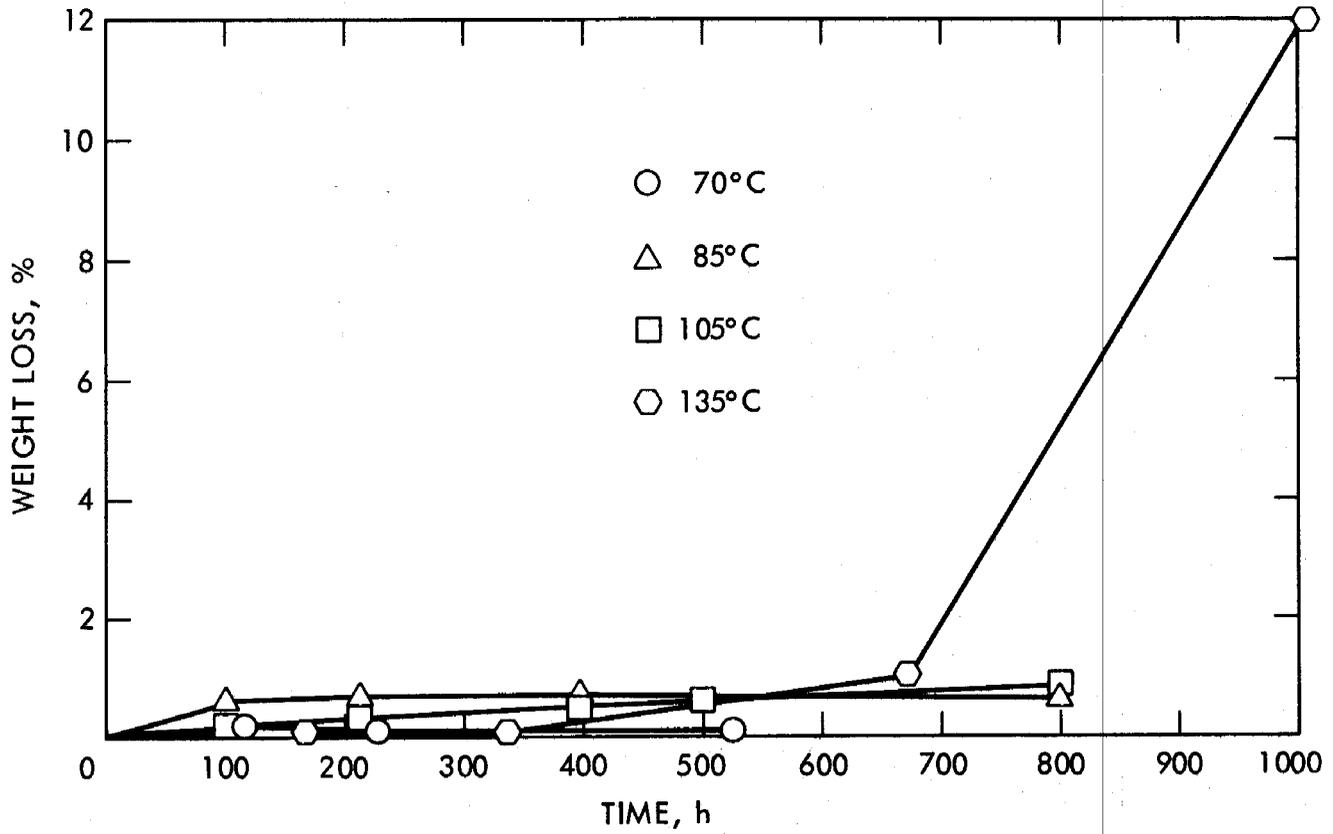


Figure 27. Weight Loss as a Function of Covered Photothermal Aging of EVA at 70°C, 85°C, 105°C, and 135°C

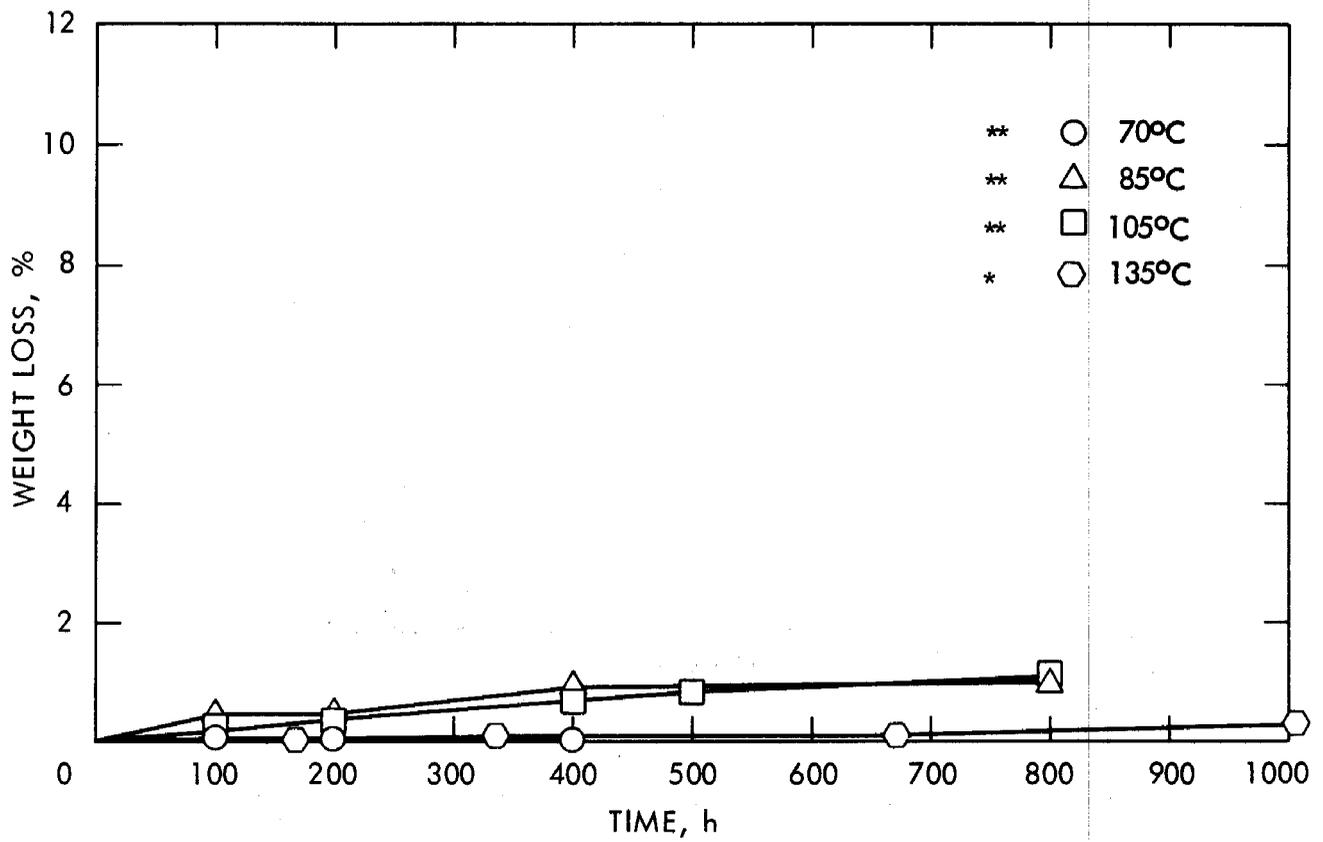


Figure 28. Weight Loss as a Function of Thermal Aging of EVA at 70°C, 85°C, 105°C, and 135°C

D. OTHER PROPERTIES

Table 7. Sol/Gel and Molecular Weight Data as a Function of Open Photothermal Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, %   | GEL, %   | MOL WT (SOL) |
|-------|------------------|---|----------|----------|--------------|
| 30    | 0                | $5.62 \times 10^{-6}$                     | 30       | 70       | 206,000      |
| 85    | 800              | $4.32 \times 10^{-6}$                     | 33       | 67       | 118,000      |
| 105   | 200              | $3.11 \times 10^{-6}$                     | 33       | 67       | 91,000       |
|       | 800              | $5.86 \times 10^{-6}$                     | 33       | 67       |              |
| 135   | 84               | $7.0 \times 10^{-6}$                      | 55<br>22 | 45<br>78 |              |
|       | 168              | $5.6 \times 10^{-6}$                      |          |          |              |
|       | 336              | $11.3 \times 10^{-6}$                     |          |          |              |
|       | 1008             | $20.4 \times 10^{-6}$                     |          |          |              |

Table 8. Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, % | GEL, % | MOL WT (SOL) |
|-------|------------------|---|--------|--------|--------------|
| 30    | 0                | $5.62 \times 10^{-6}$                     | 30     | 70     | 206,000      |
| 85    | 800              | $7.8 \times 10^{-6}$                      | 29     | 71     | 75,000       |
| 105   | 800              | $10.10 \times 10^{-6}$                    | 34     | 66     | 44,000       |
| 135   | 168              | $7.1 \times 10^{-6}$                      | 39     | 61     |              |
|       | 336              | $33.8 \times 10^{-6}$                     | 29     | 71     |              |
|       | 672              | $72.8 \times 10^{-6}$                     | 26     | 74     |              |
|       | 1008             | $39.8 \times 10^{-6}$                     | 18     | 82     |              |

Table 9. Sol/Gel and Molecular Weight Data as a Function of Thermal Aging of EVA at 30°C, 70°C, 85°C, 105°C, and 135°C

| T °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, % | GEL, % | MOL WT (SOL) |
|------|------------------|---|--------|--------|--------------|
| 30   | 0                | $5.62 \times 10^{-6}$                     | 30     | 70     | 206,000      |
| 85   | 800              | $2.29 \times 10^{-6}$                     | 35     | 65     | 168,000      |
| 105  | 800              | $1.33 \times 10^{-6}$                     | 37     | 63     | 174,000      |
| 135  | 168              | $6.76 \times 10^{-6}$                     | 26     | 74     |              |
|      | 336              | $5.34 \times 10^{-6}$                     | 30     | 70     |              |
|      | 672              | $5.59 \times 10^{-6}$                     | 30     | 70     |              |
|      | 1008             | $6.09 \times 10^{-6}$                     | 33     | 67     |              |

### SECTION III

#### PVB (MONSANTO SAFLEX)

The following figures and tables offer data on optical transmittance (Figures 29 through 33); mechanical properties (Figures 34 through 39, Tables 10 through 12); weight loss (Figures 40 through 42) of PVB (Monsanto Saflex).

A. OPTICAL TRANSMITTANCE

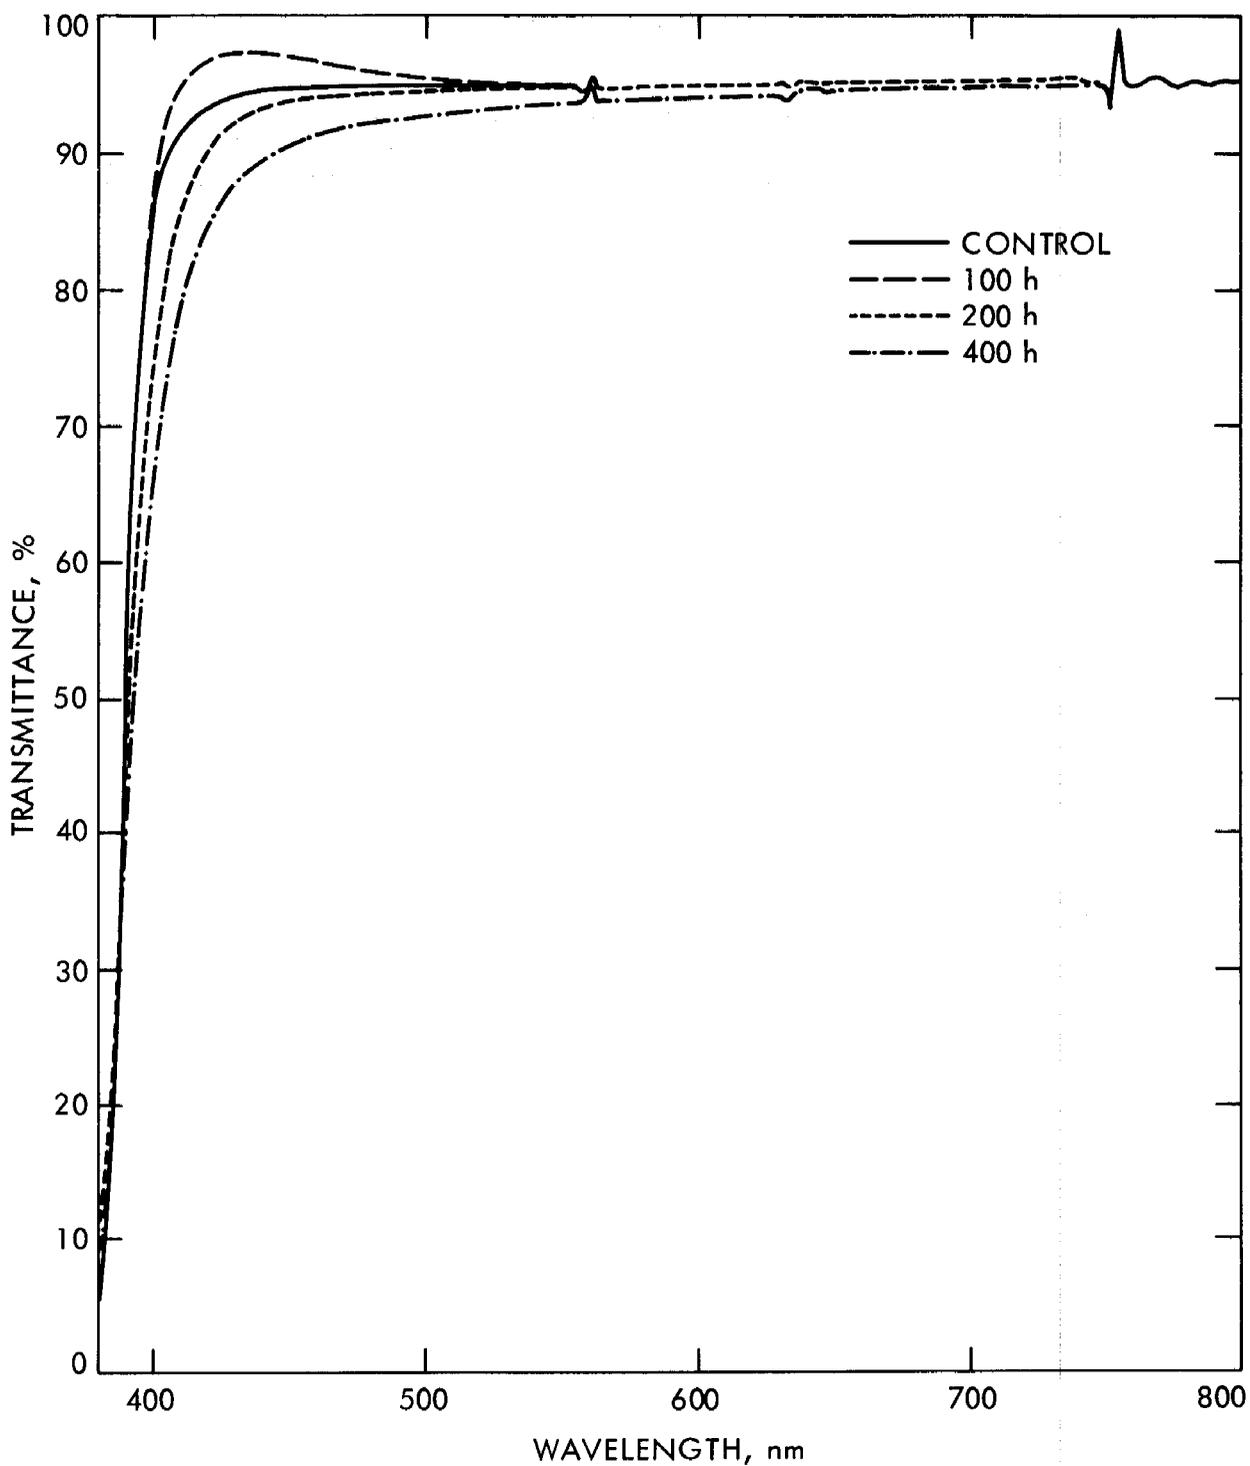


Figure 29. Change in Optical Transmittance as a Function of Open Photothermal Aging of PVB at 70°C

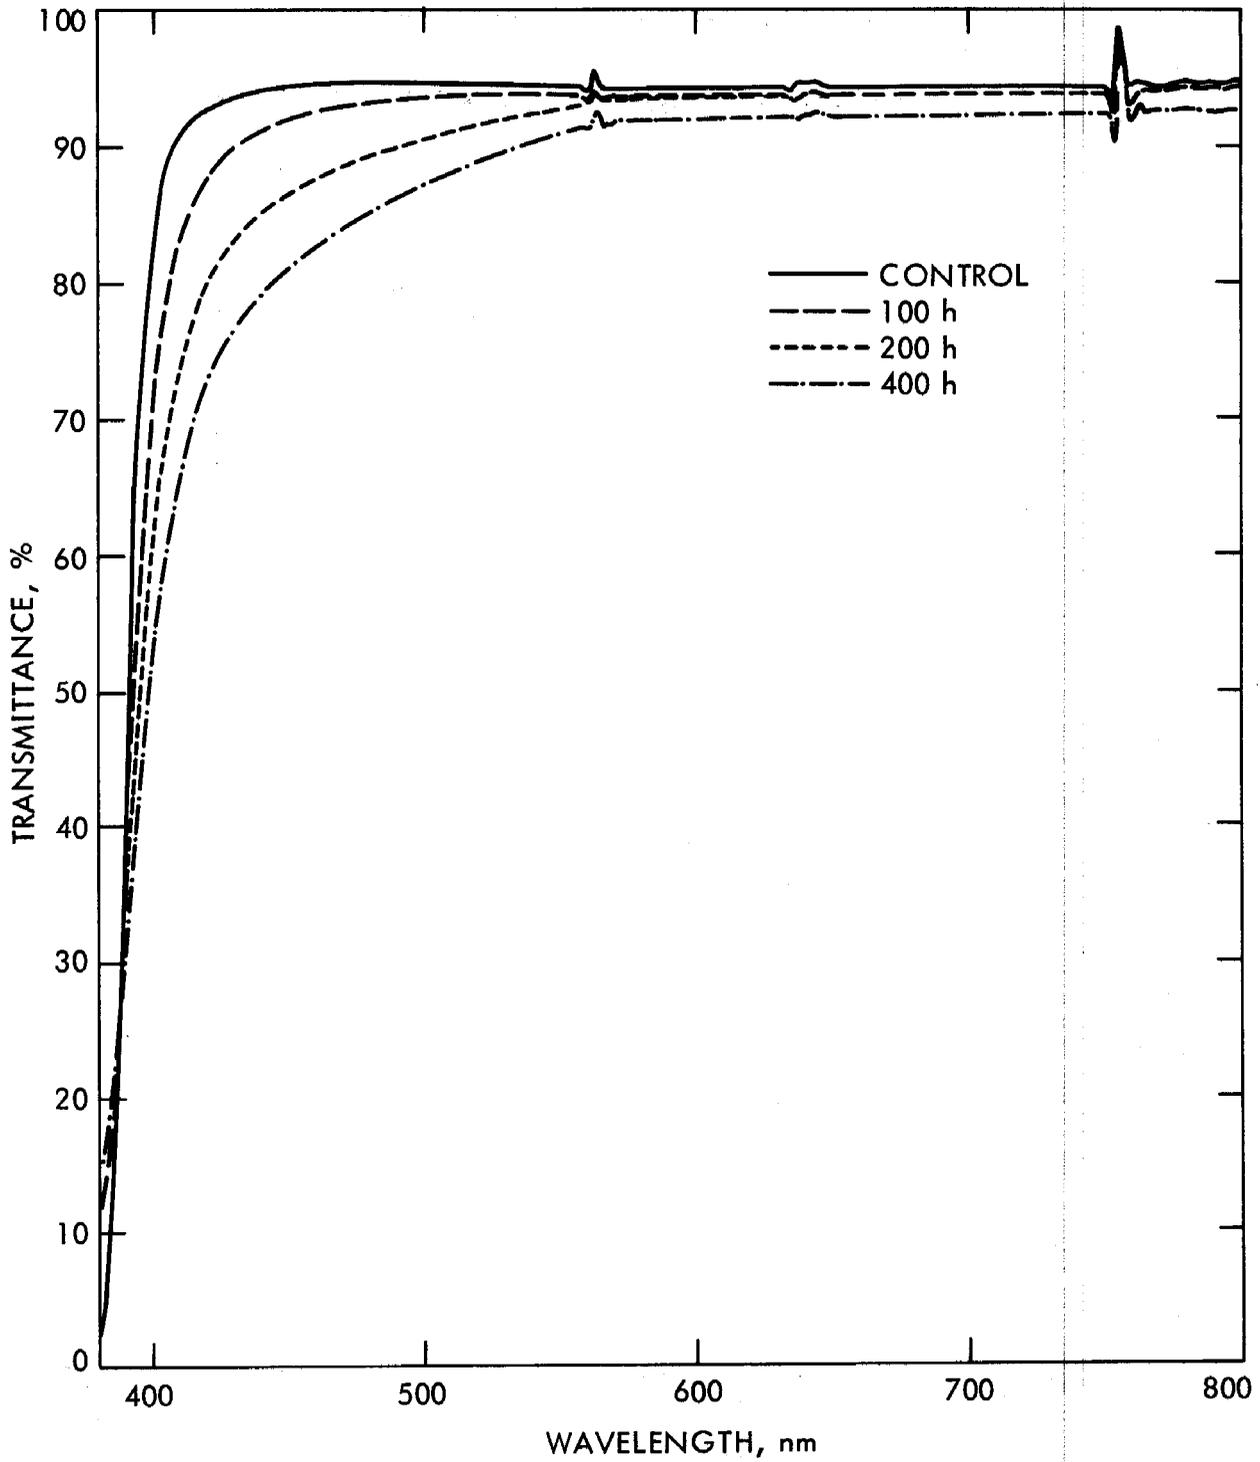


Figure 30. Change in Optical Transmittance as a Function of Covered Photothermal Aging of PVB at 70°C

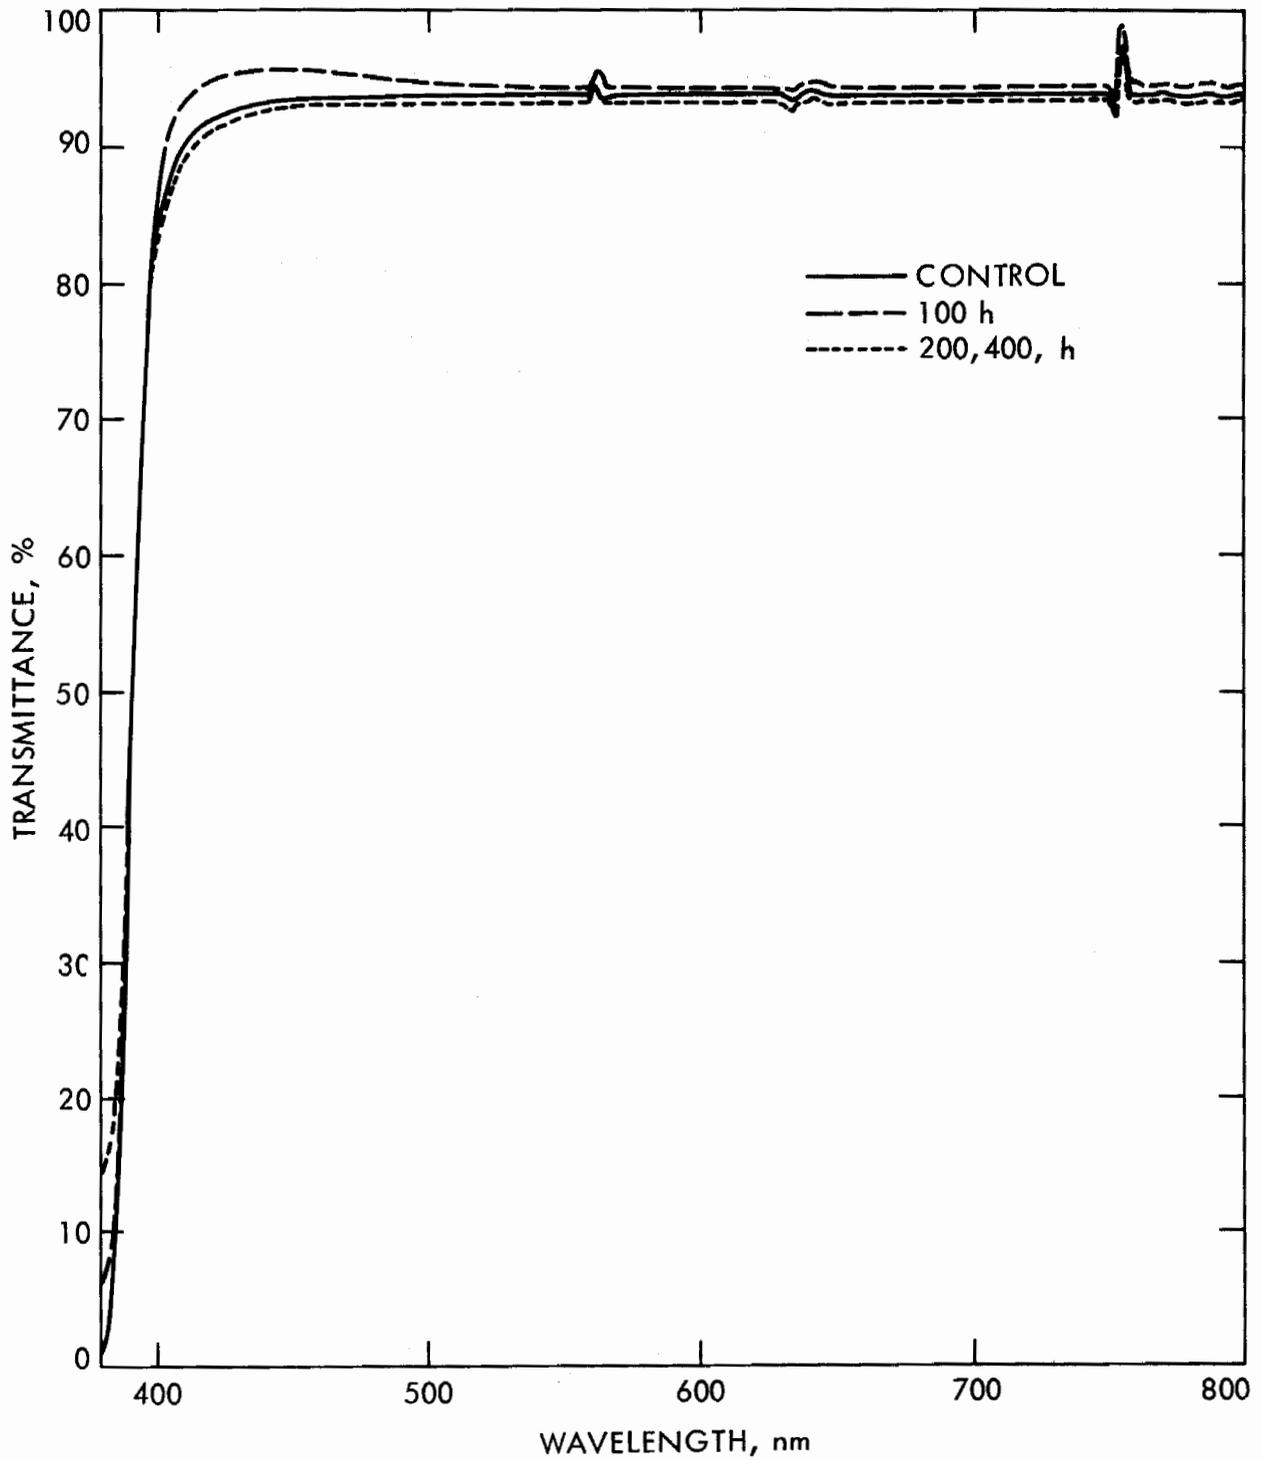


Figure 31. Change in Optical Transmittance as a Function of Thermal Aging of PVB at 70°C

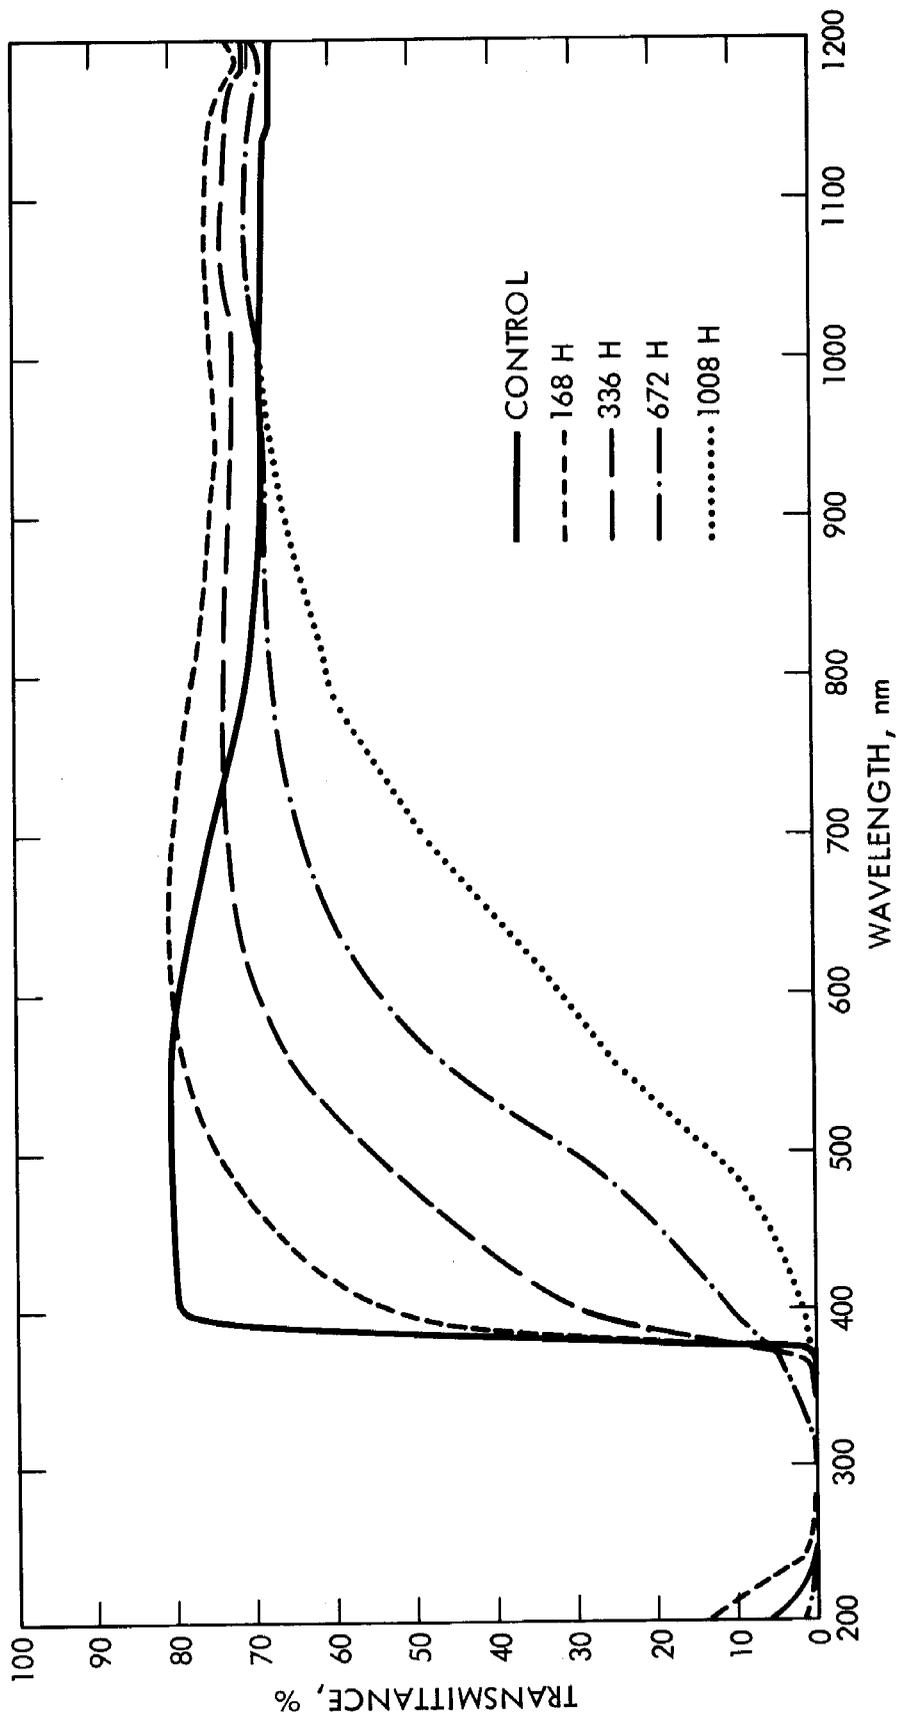


Figure 32. Change in Optical Transmittance as a Function of Covered Photothermal Aging of PVB at 135°C

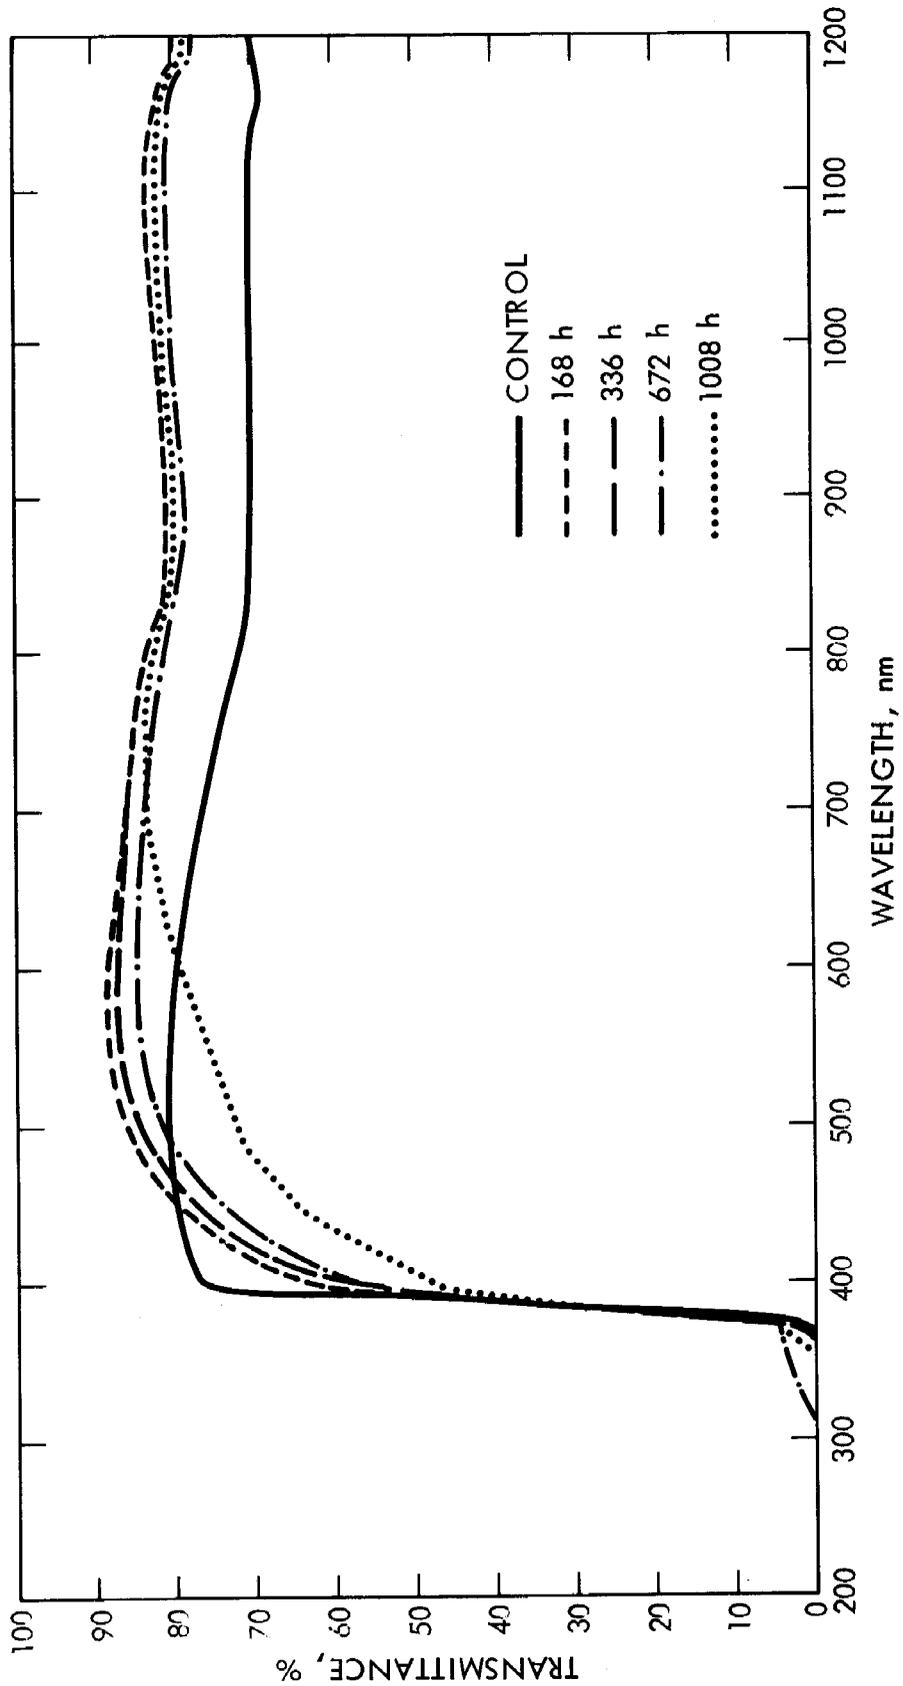


Figure 33. Change in Optical Transmittance as a Function of Thermal Aging of PVB at 135°C

B. MECHANICAL PROPERTIES

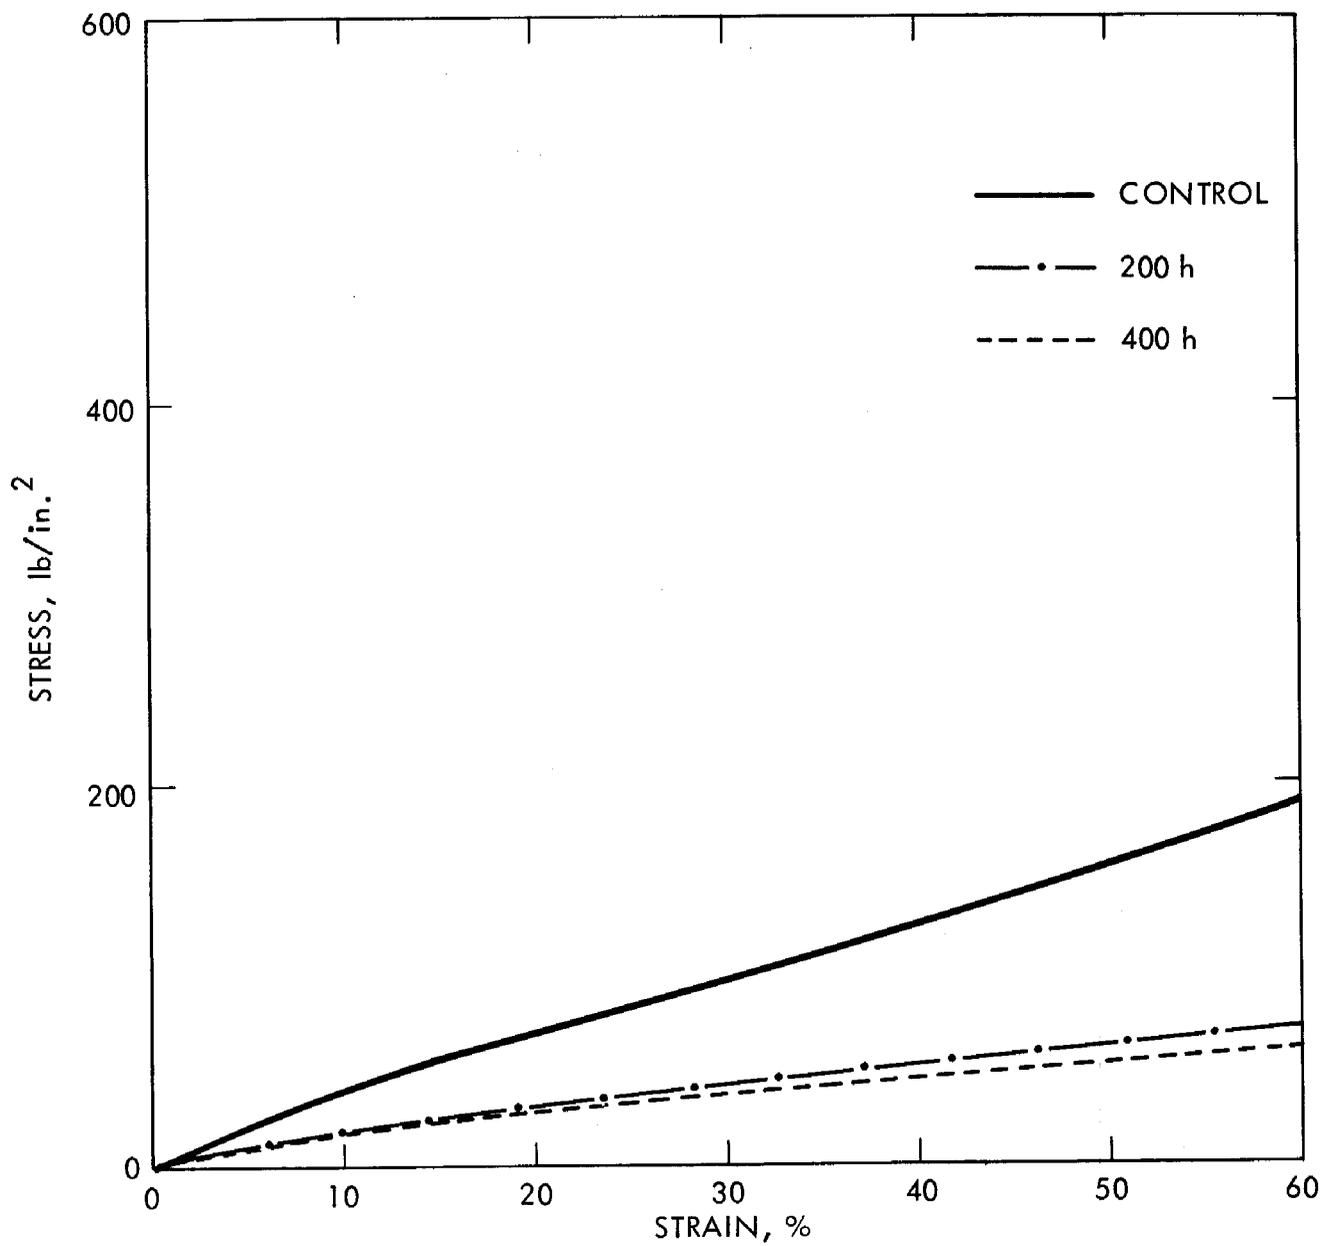


Figure 34. Change in Stress/Strain Response as a Function of Open Photothermal Aging of PVB at 70°C

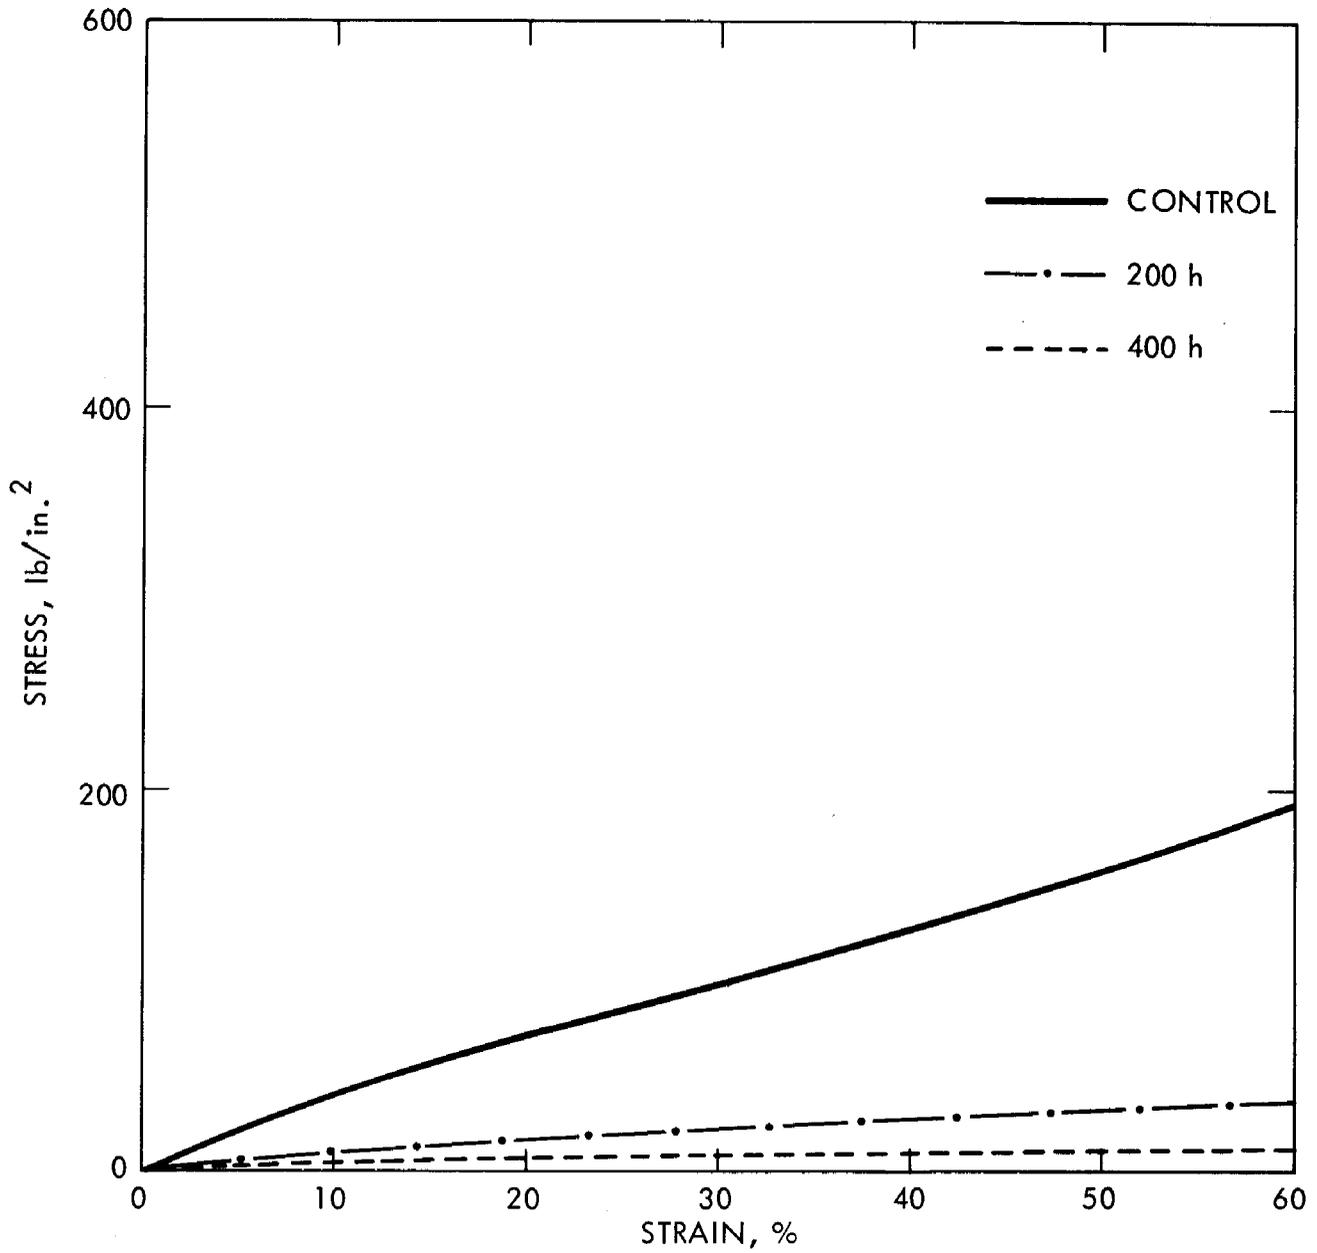


Figure 35. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of PVB at 70°C

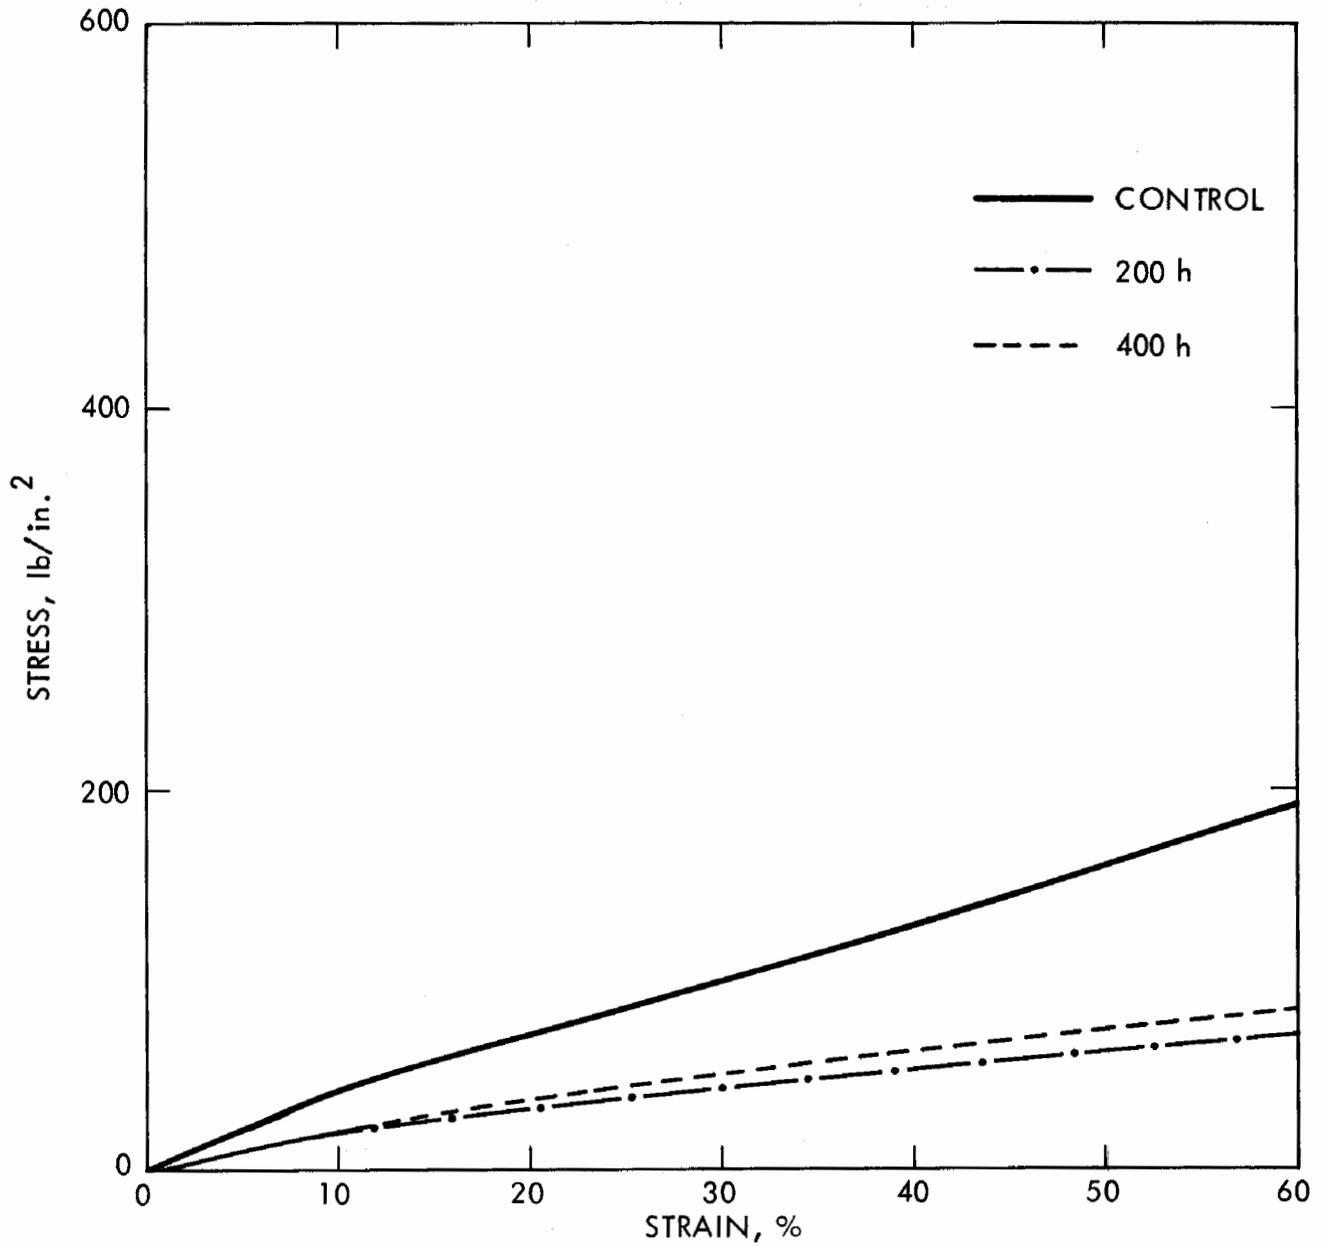


Figure 36. Change in Stress/Strain Response as a Function of Thermal Aging of PVB at 70°C

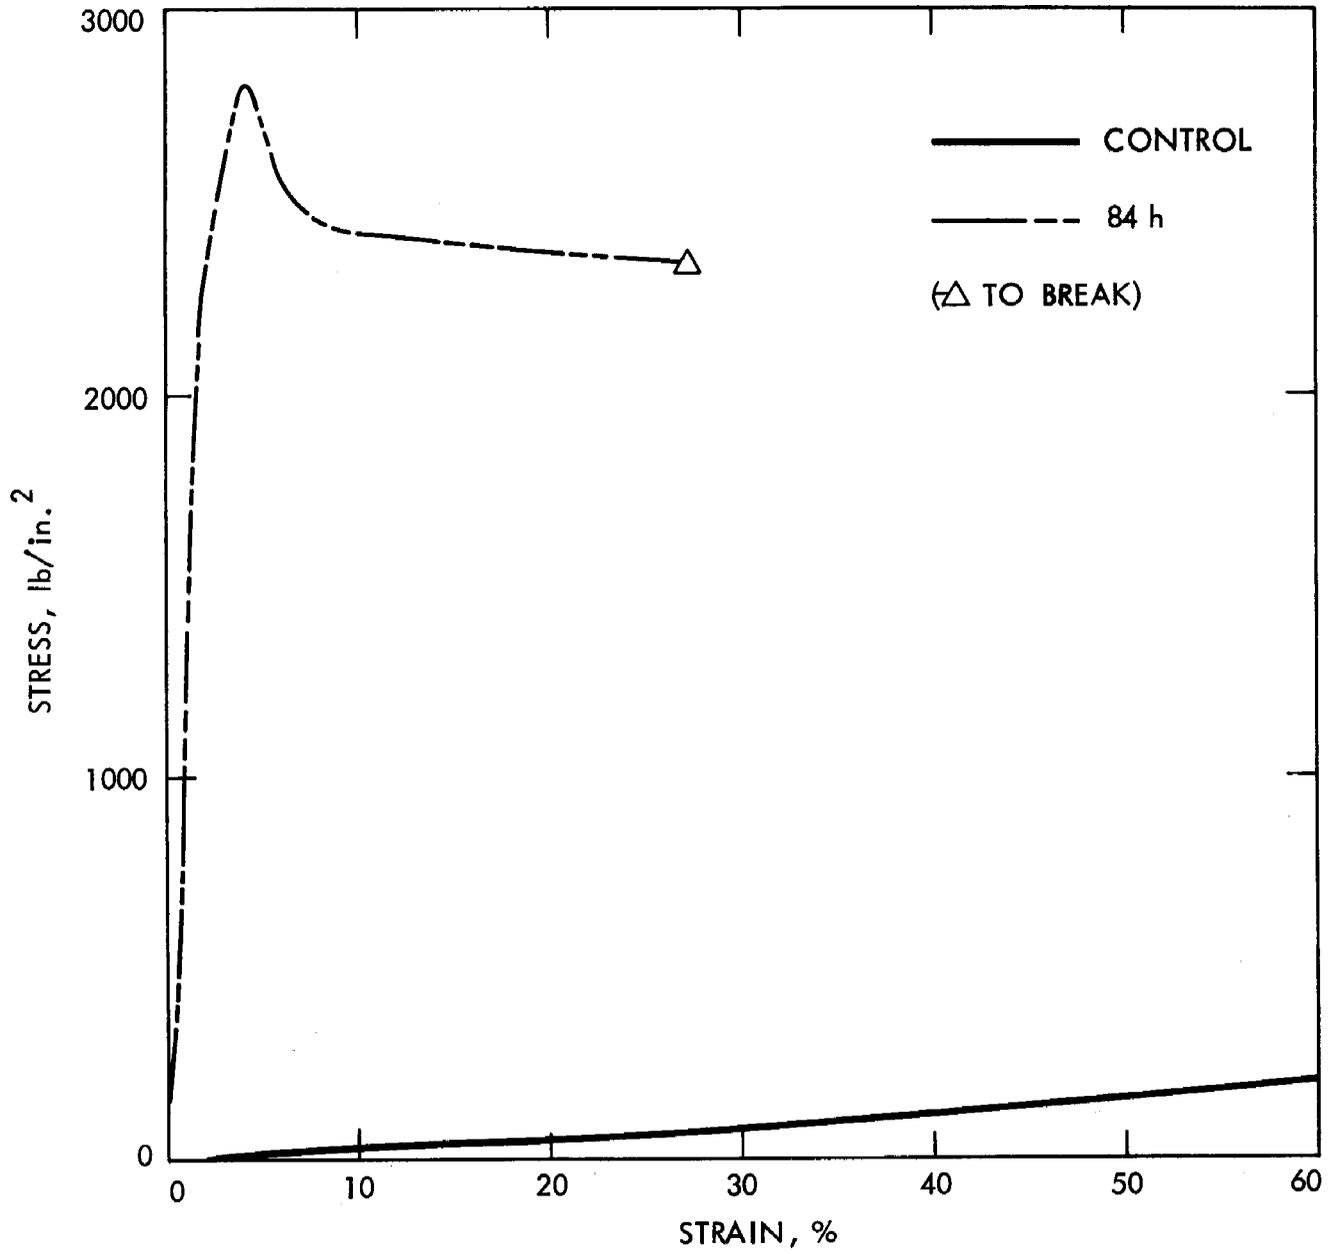


Figure 37. Change in Stress/Strain Response as a Function of Open Photothermal Aging of PVB at 135°C

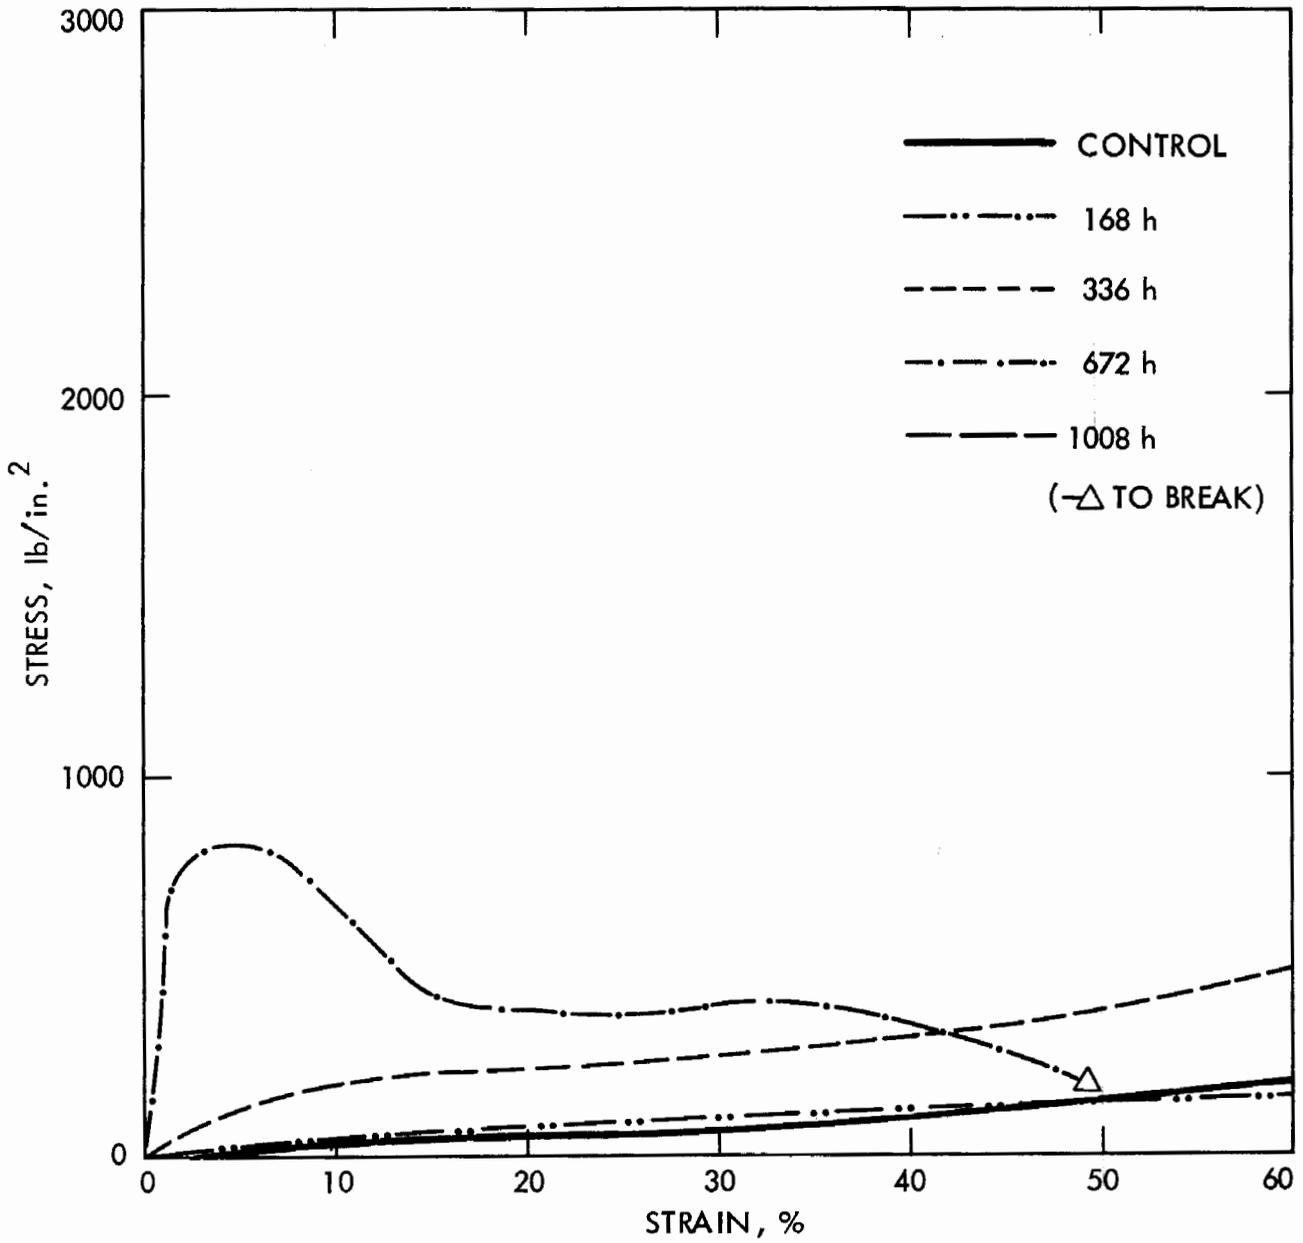


Figure 38. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of PVB at 135°C

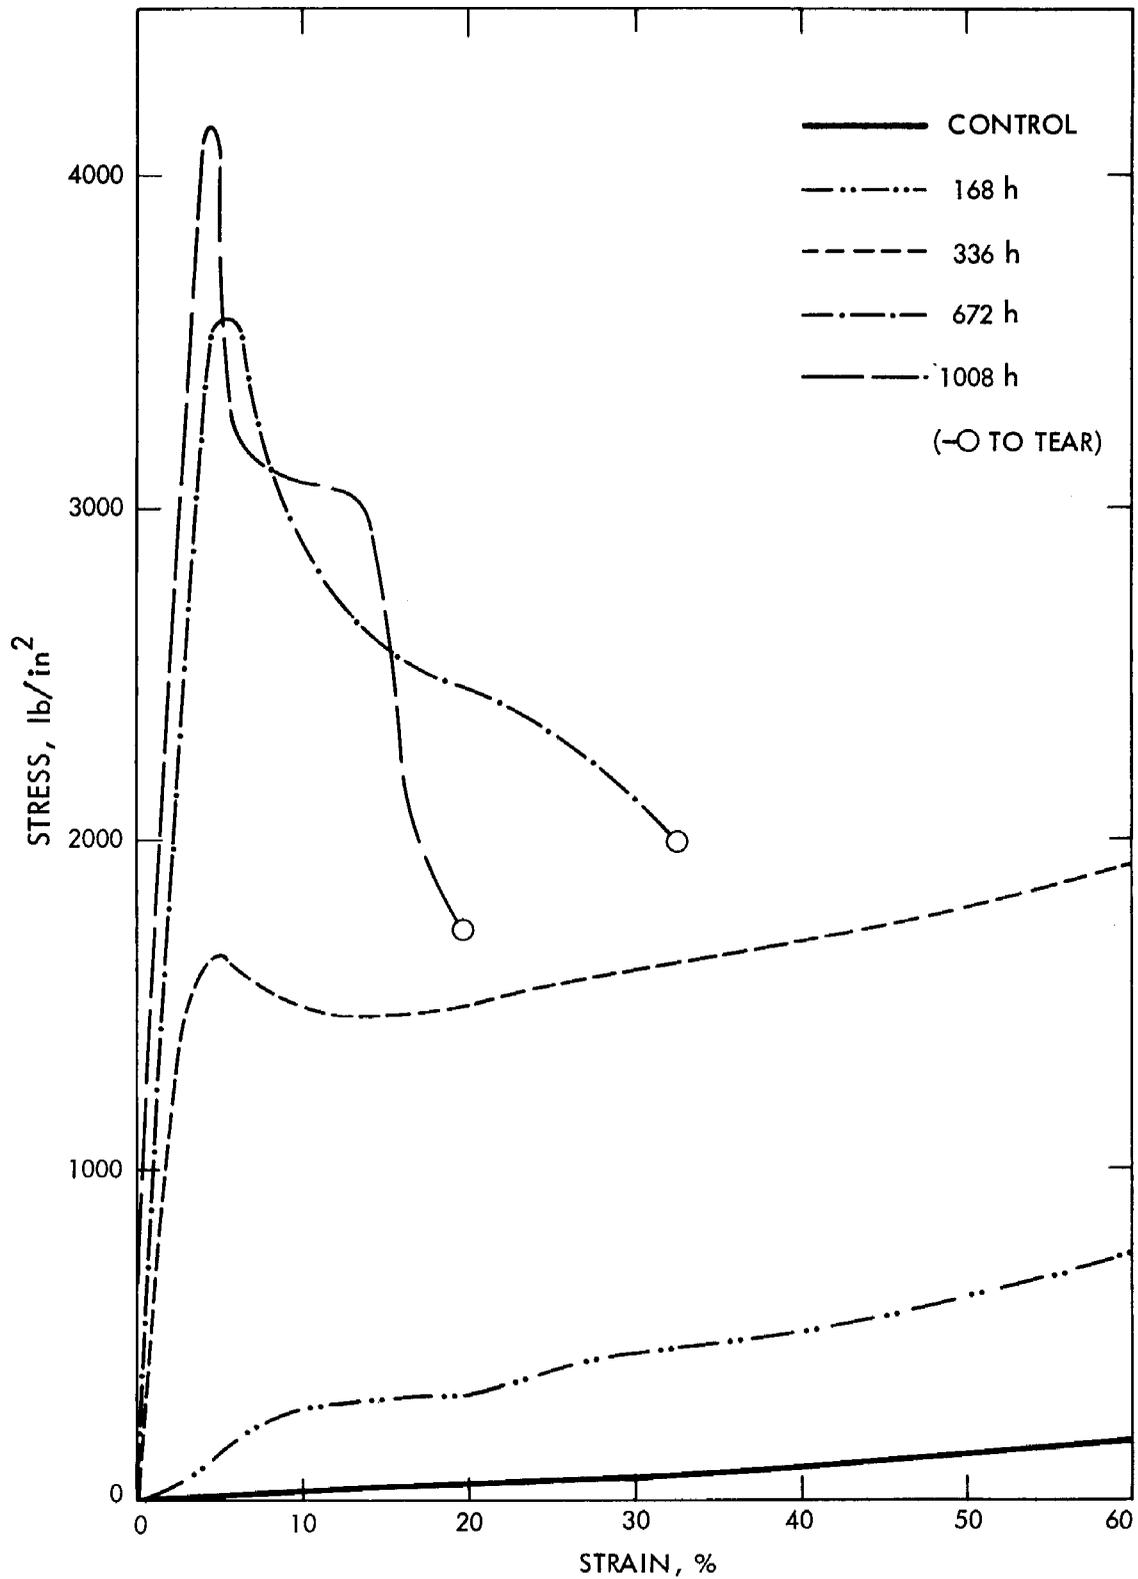


Figure 39. Change in Stress/Strain Response as a Function of Thermal Aging of PVB at 135°C

Table 10. Modulus at 5% Strain as a Function of Open Photothermal Aging of PVB at 30°C, 70°C, and 135°C

| TEMPERATURE,<br>°C | TIME OF<br>AGING, h | MODULUS, lb/in. <sup>2</sup><br>5% STRAIN |
|--------------------|---------------------|---|
| ROOM TEMP. (30)    | 0                   | 348                                       |
| 70                 | 400                 | 244                                       |
| 135                | 84                  | 52,800                                    |

Table 11. Modulus at 5% Strain as a Function of Covered Photothermal Aging of PVB at 30°C, 70°C, and 135°C

| TEMPERATURE,<br>°C | TIME OF<br>AGING, h | MODULUS, lb/in. <sup>2</sup><br>5% STRAIN |
|--------------------|---------------------|---|
| ROOM TEMP. (30)    | 0                   | 348                                       |
| 70                 | 200                 | 100                                       |
|                    | 400                 | 47  |
| 135                | 168                 | 638                                       |
|                    | 336                 | 2610                                      |
|                    | 672                 | 39,200*                                   |
|                    | 1008                | 90,000*                                   |

\* 1% STRAIN

Table 12. Modulus at 5% Strain as a Function of Thermal Aging of PVB at 30°C, 70°C, and 135°C

| TEMPERATURE,<br>°C | TIME OF<br>AGING, h | MODULUS, lb/in. <sup>2</sup><br>5% STRAIN |
|--------------------|---------------------|---|
| ROOM TEMP. (30)    | 0                   | 348                                       |
| 70                 | 200                 | 219                                       |
|                    | 400                 | 238                                       |
| 135                | 168                 | 3110                                      |
|                    | 336                 | 32,277                                    |
|                    | 672                 | 70,500                                    |
|                    | 1008                | 71,600                                    |

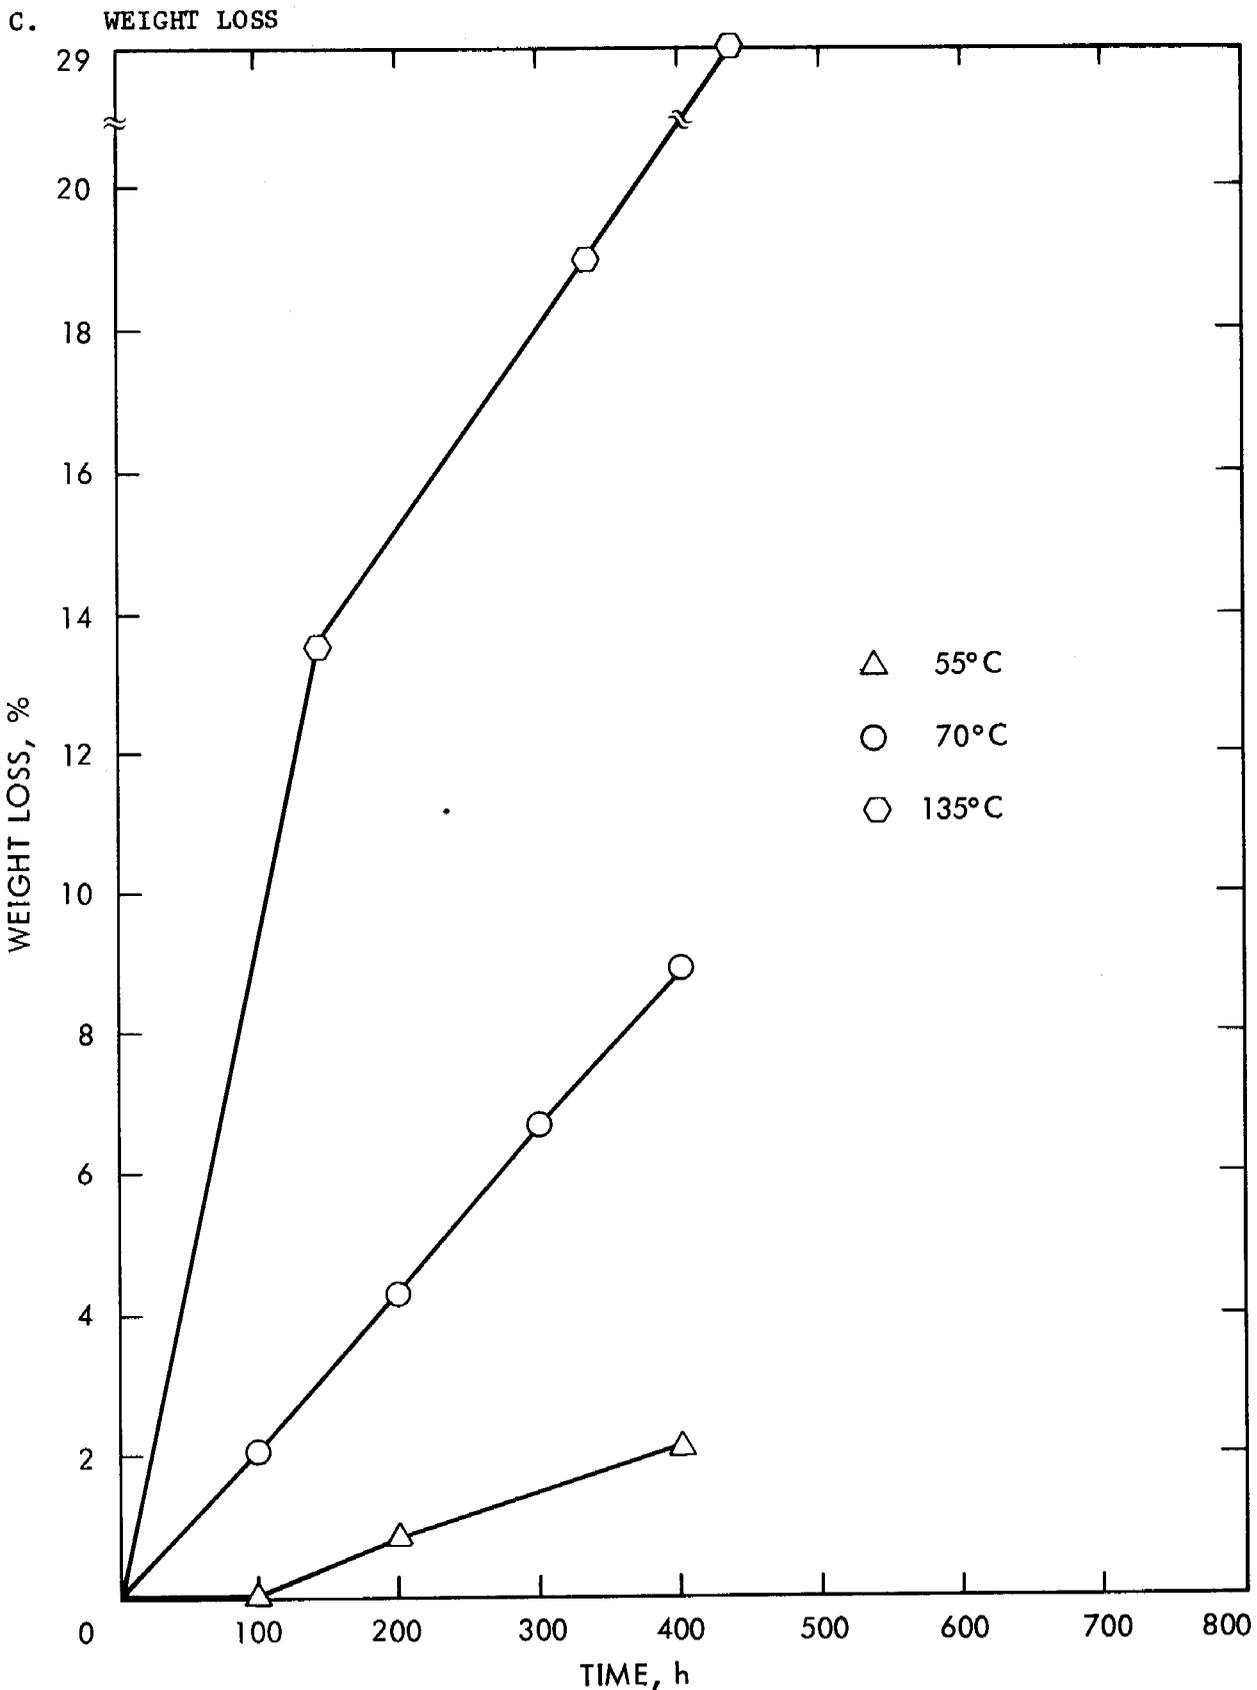


Figure 40. Weight Loss as a Function of Open Photothermal Aging of PVB at 55°C, 70°C, and 135°C

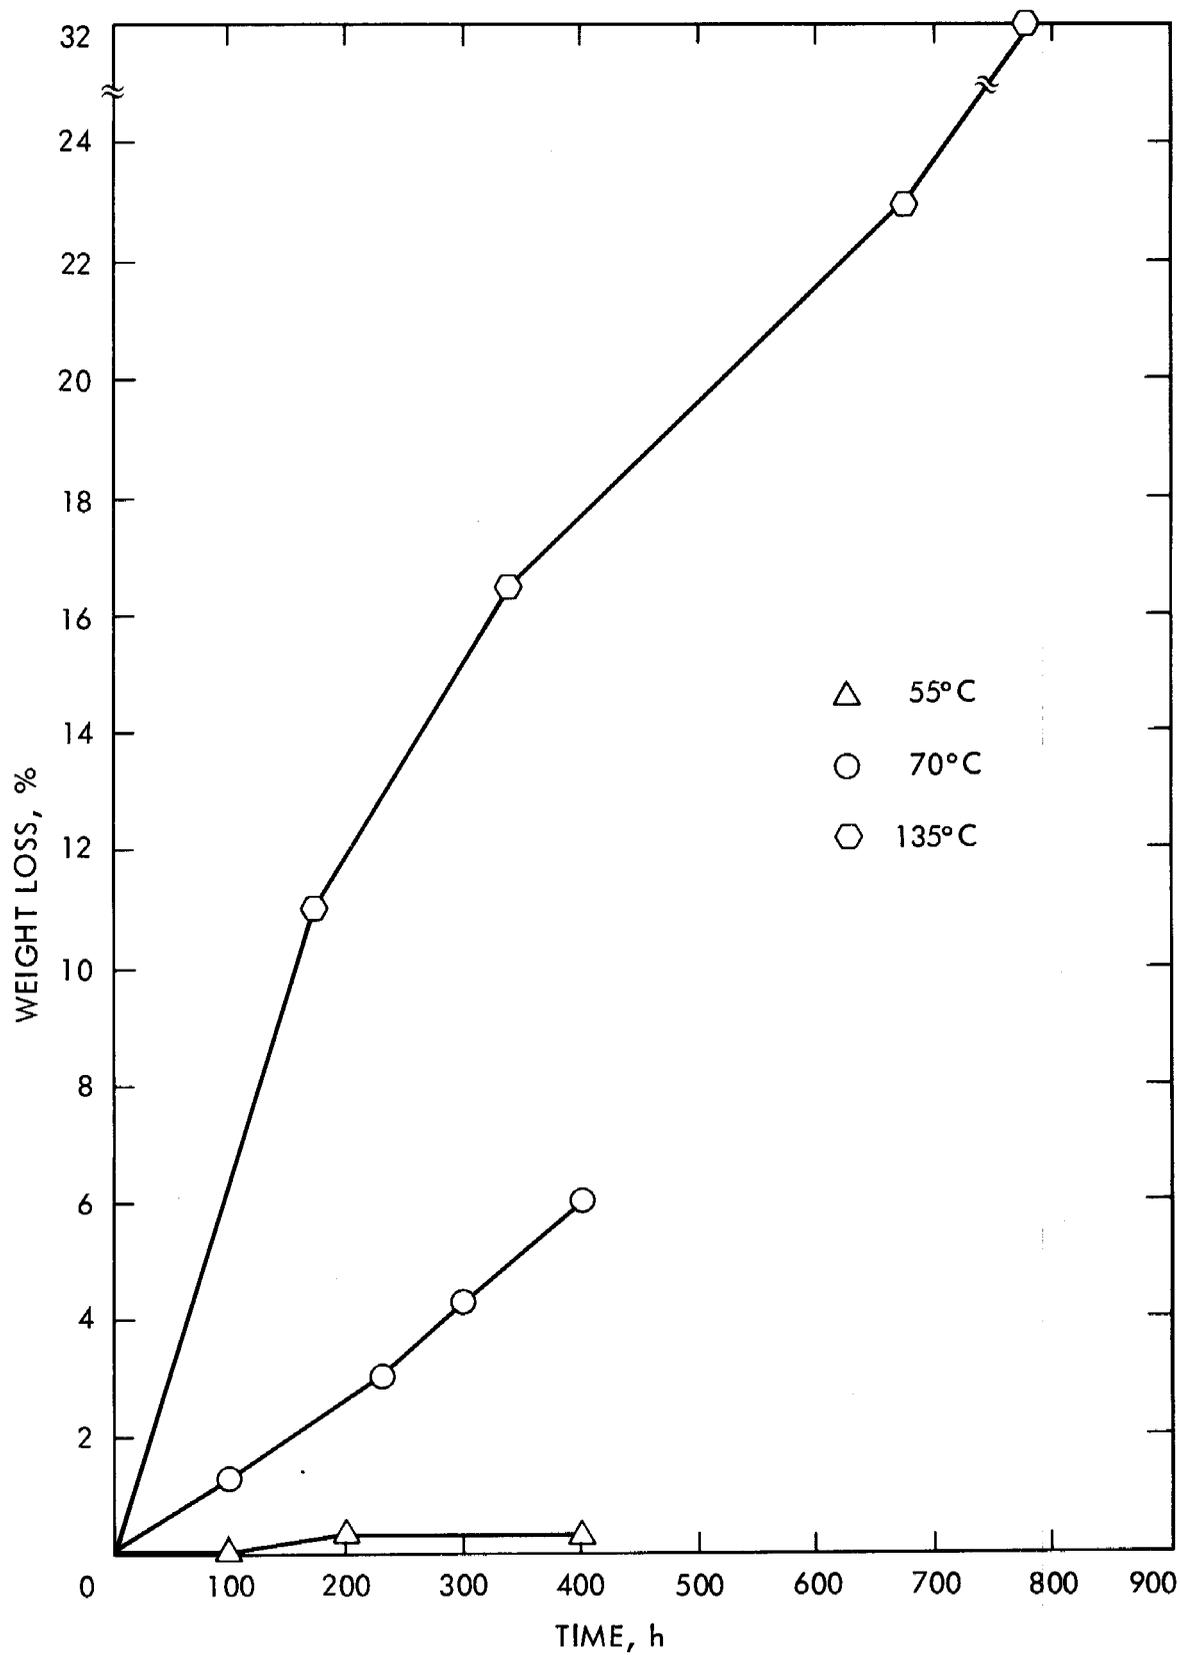


Figure 41. Weight Loss as a Function of Covered Photothermal Aging of PVB at 55°C, 70°C, and 135°C

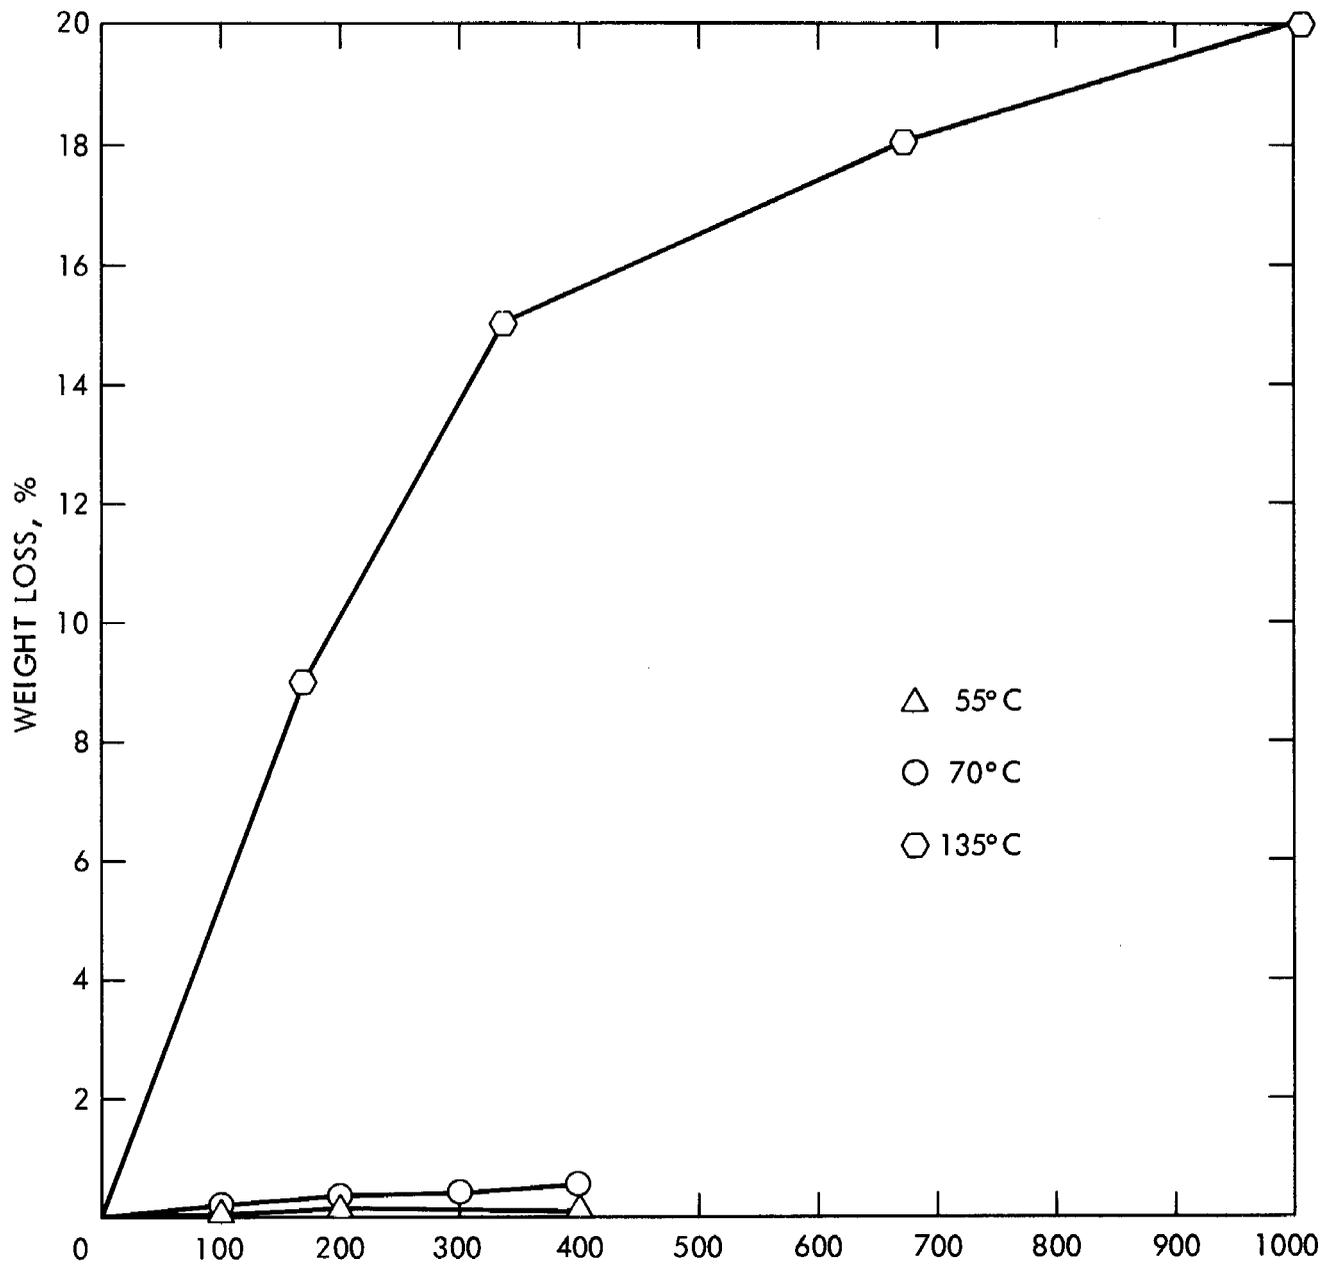


Figure 42. Weight Loss as a Function of Thermal Aging of PVB at 55°C, 70°C, and 135°C

## SECTION IV

### RTV SILICONE ELASTOMER (GE RTV-615)

The following figures and tables offer data on optical transmittance (Figures 43 through 51); mechanical properties (Figures 52 through 60, Tables 13 through 15); weight loss (Figures 61 through 63); other properties (Tables 16 through 18) of RTV silicone elastomer (GE RTV-615).

A. OPTICAL TRANSMITTANCE

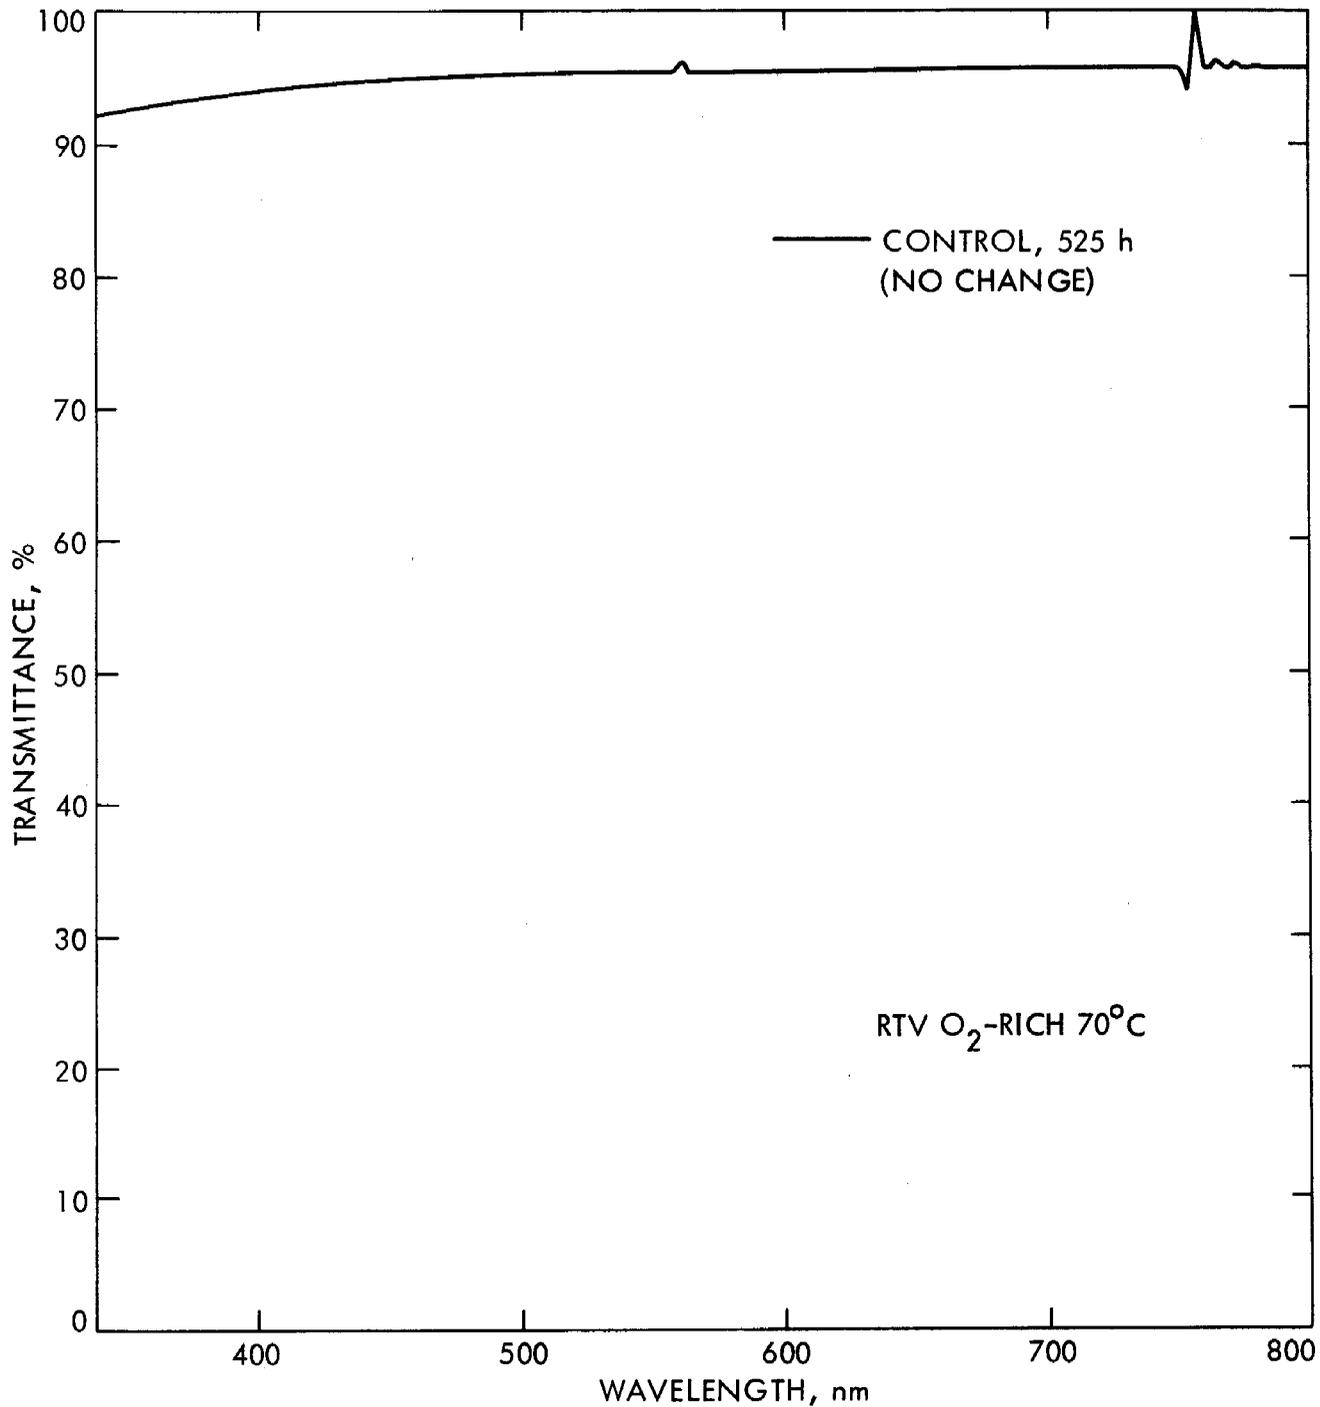


Figure 43. Change in Optical Transmittance as a Function of Open Photothermal Aging of RTV at 70°C

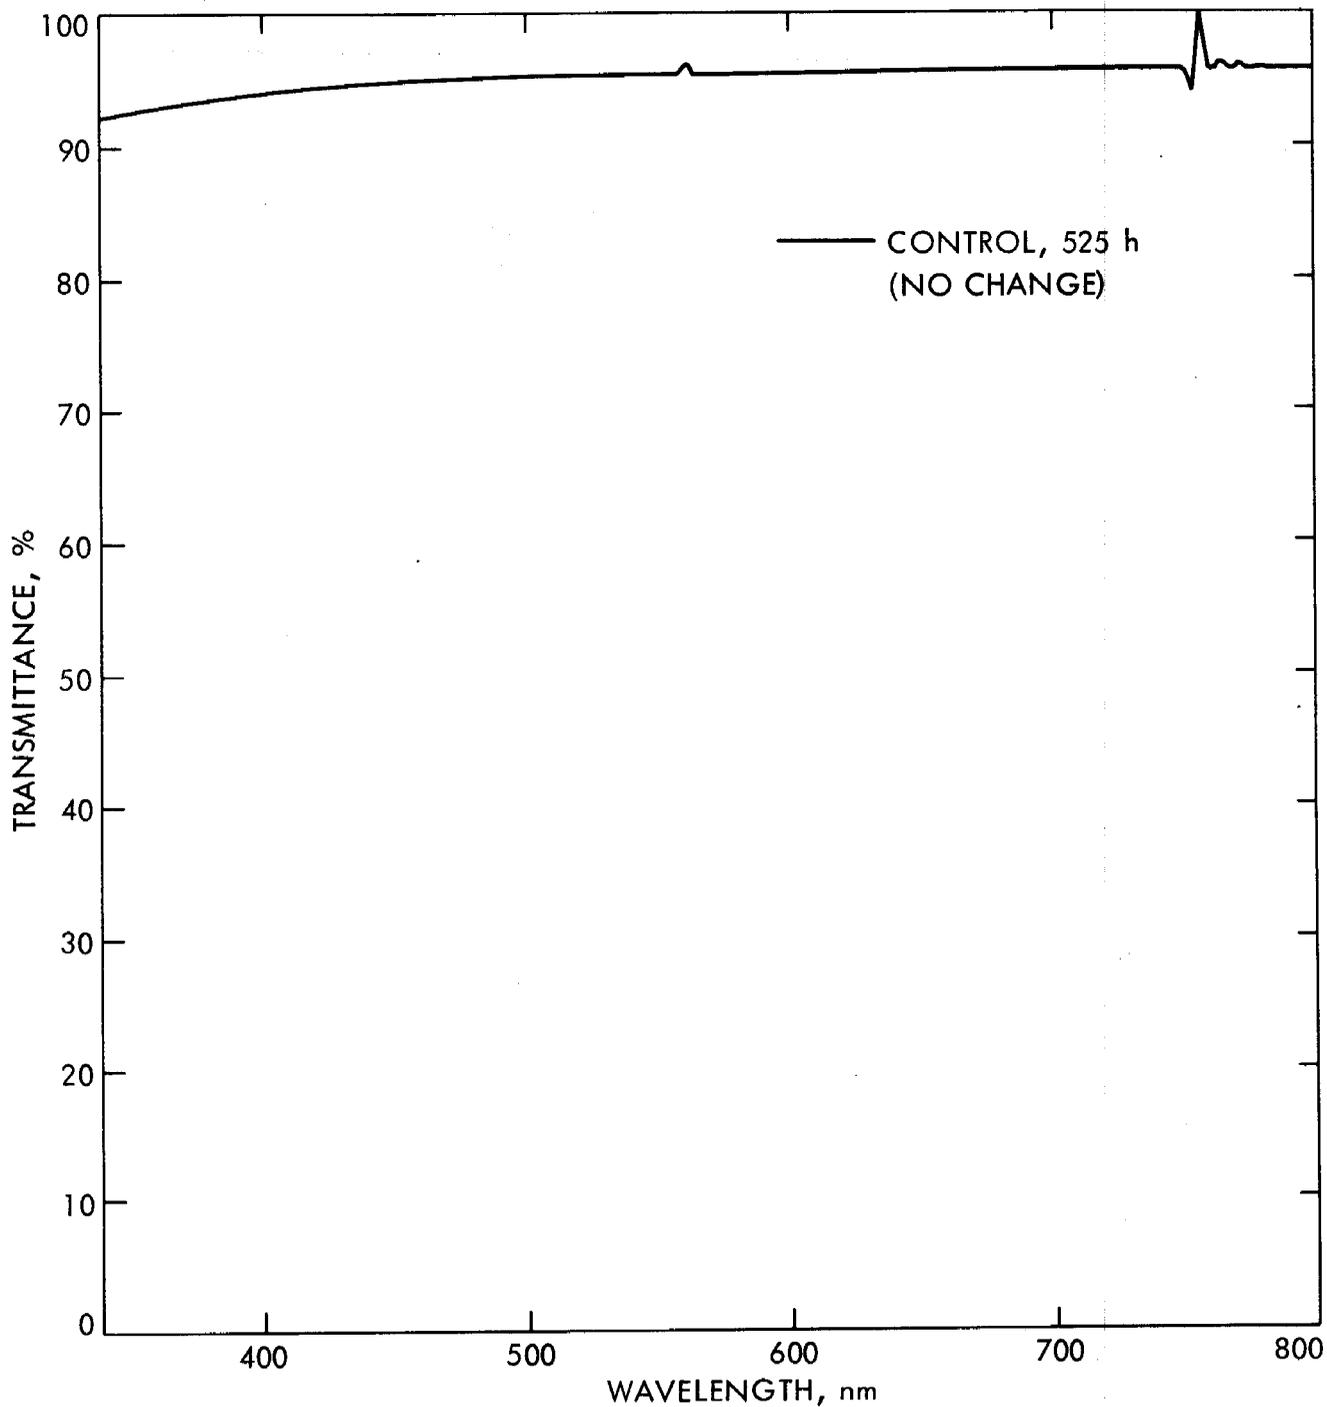


Figure 44. Change in Optical Transmittance as a Function of Covered Photothermal Aging of RTV at 70°C

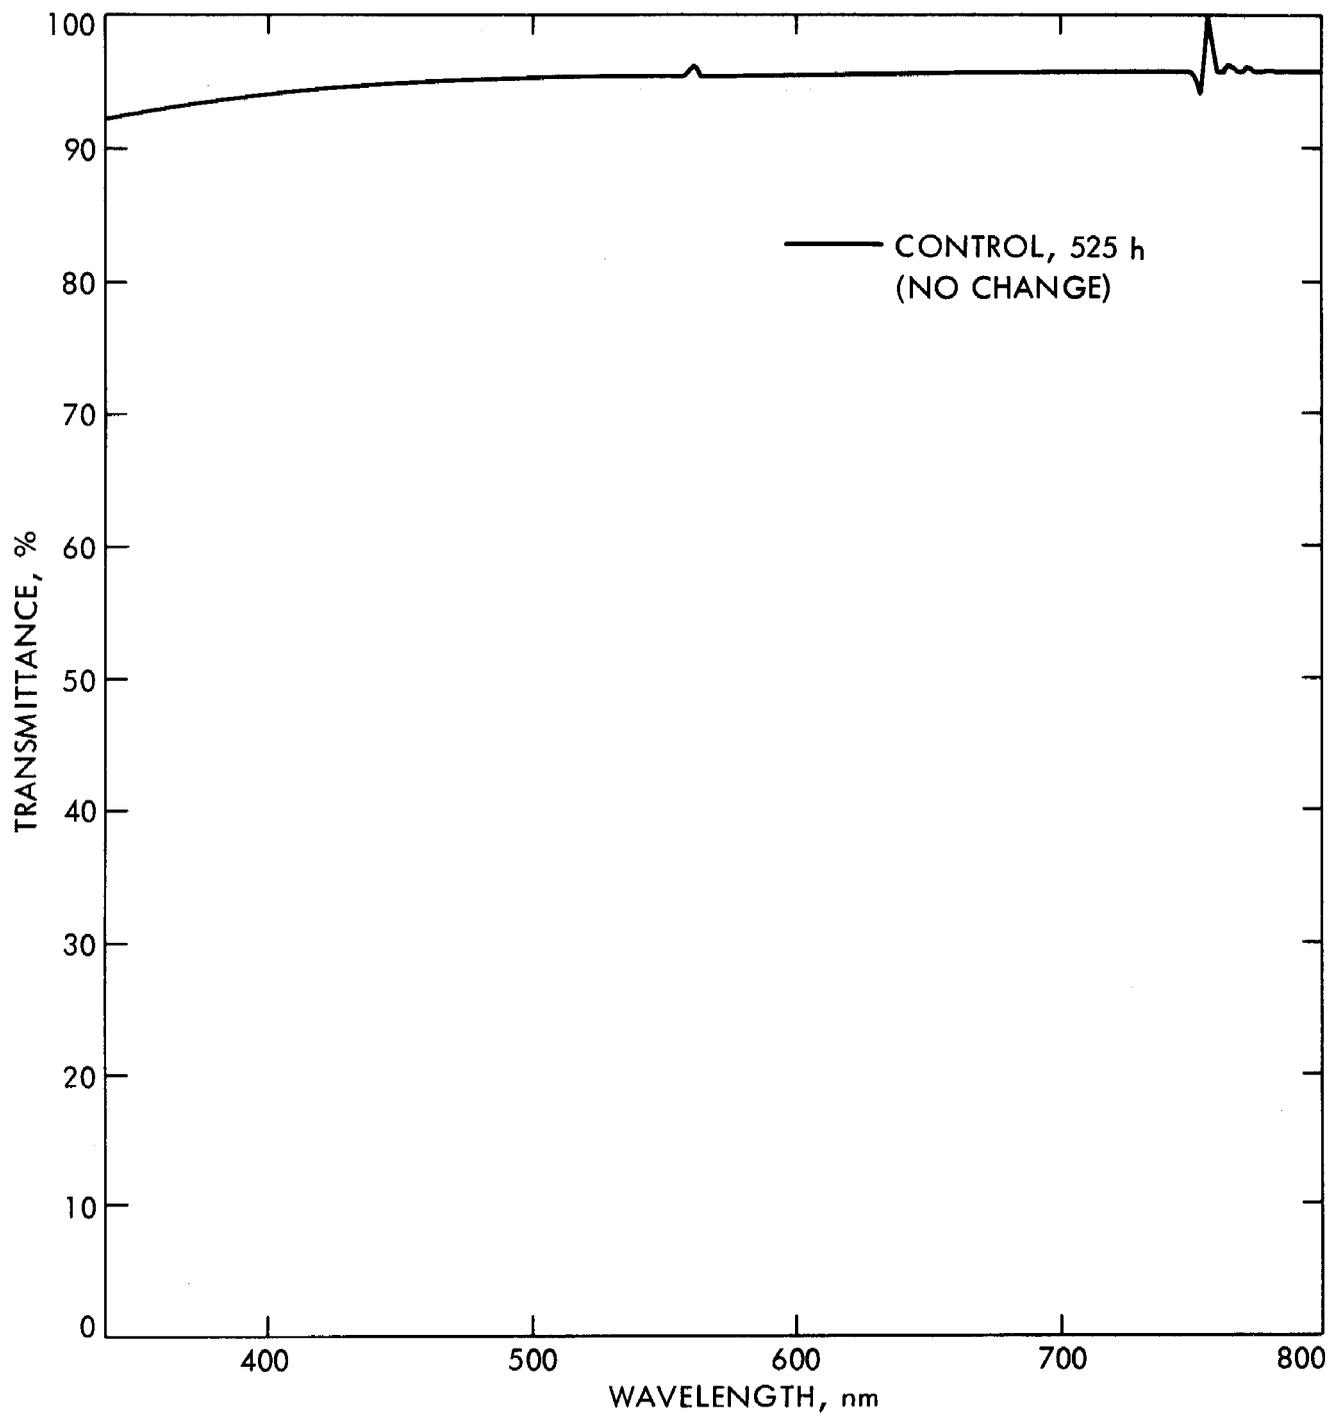


Figure 45. Change in Optical Transmittance as a Function of Thermal Aging of RTV at 70°C

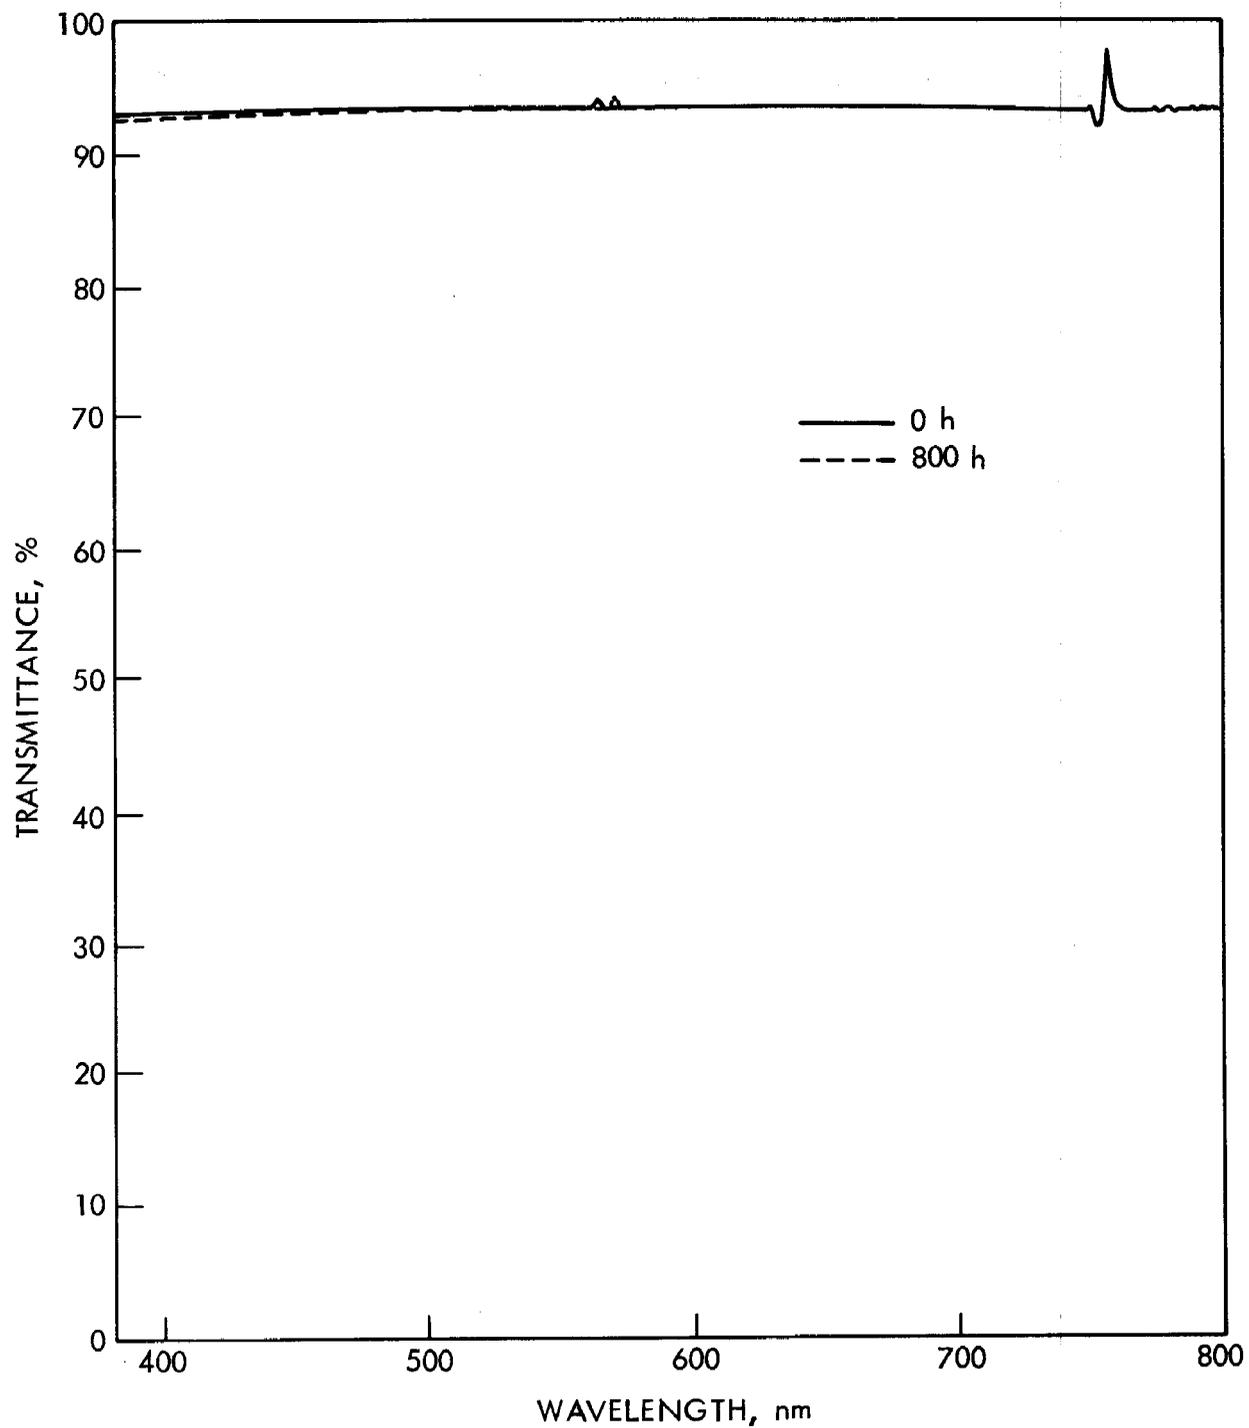


Figure 46. Change in Optical Transmittance as a Function of Open Photothermal Aging of RTV at 85°C

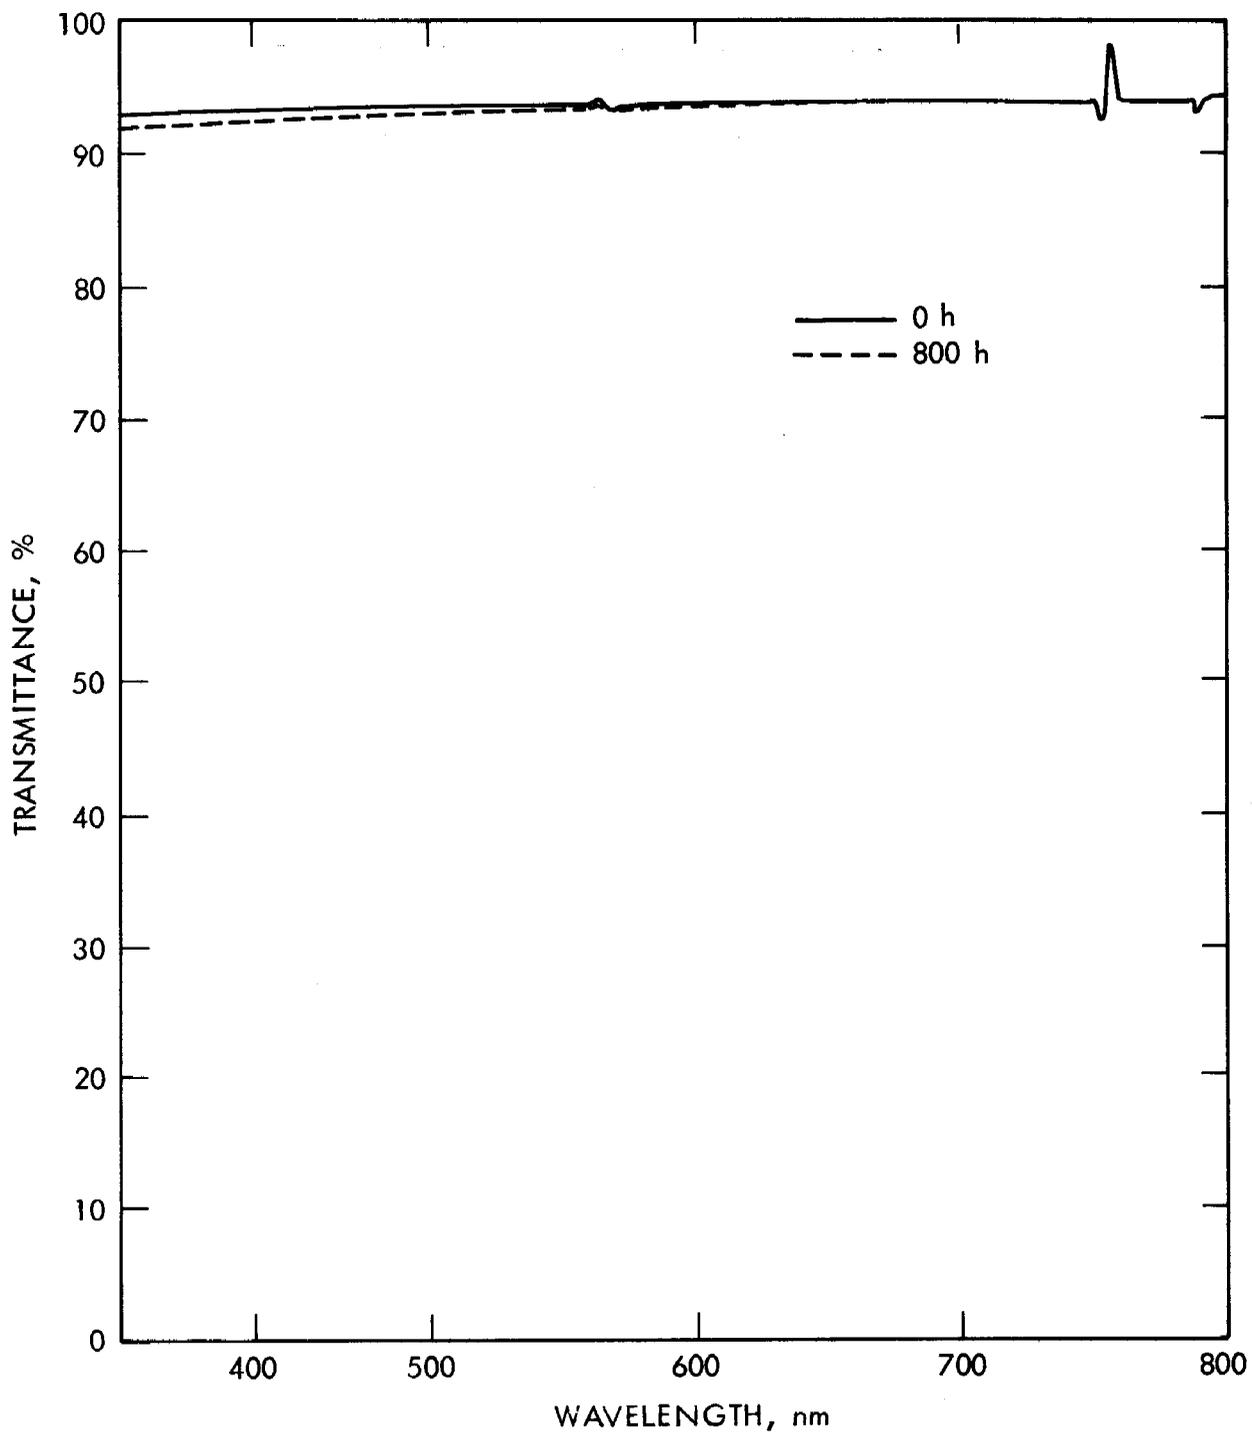


Figure 47. Change in Optical Transmittance as a Function of Covered Photothermal Aging of RTV at 85°C

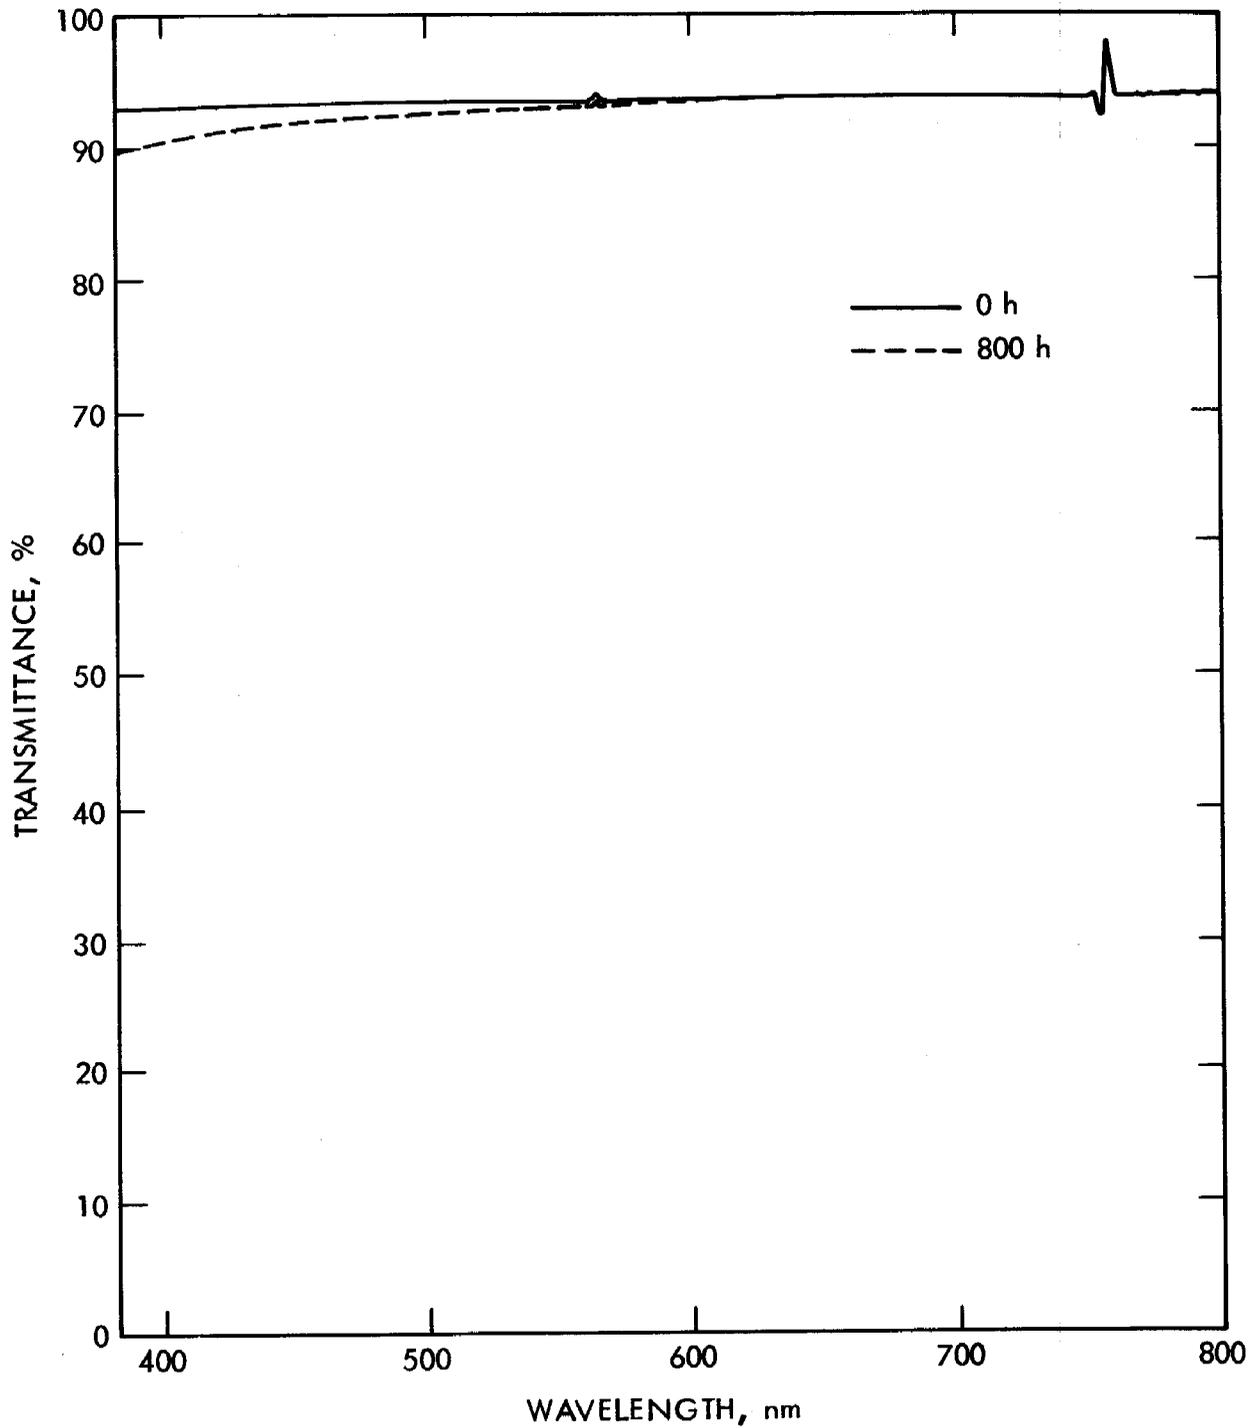


Figure 48. Change in Optical Transmittance as a Function of Thermal Aging of RTV at 85°C

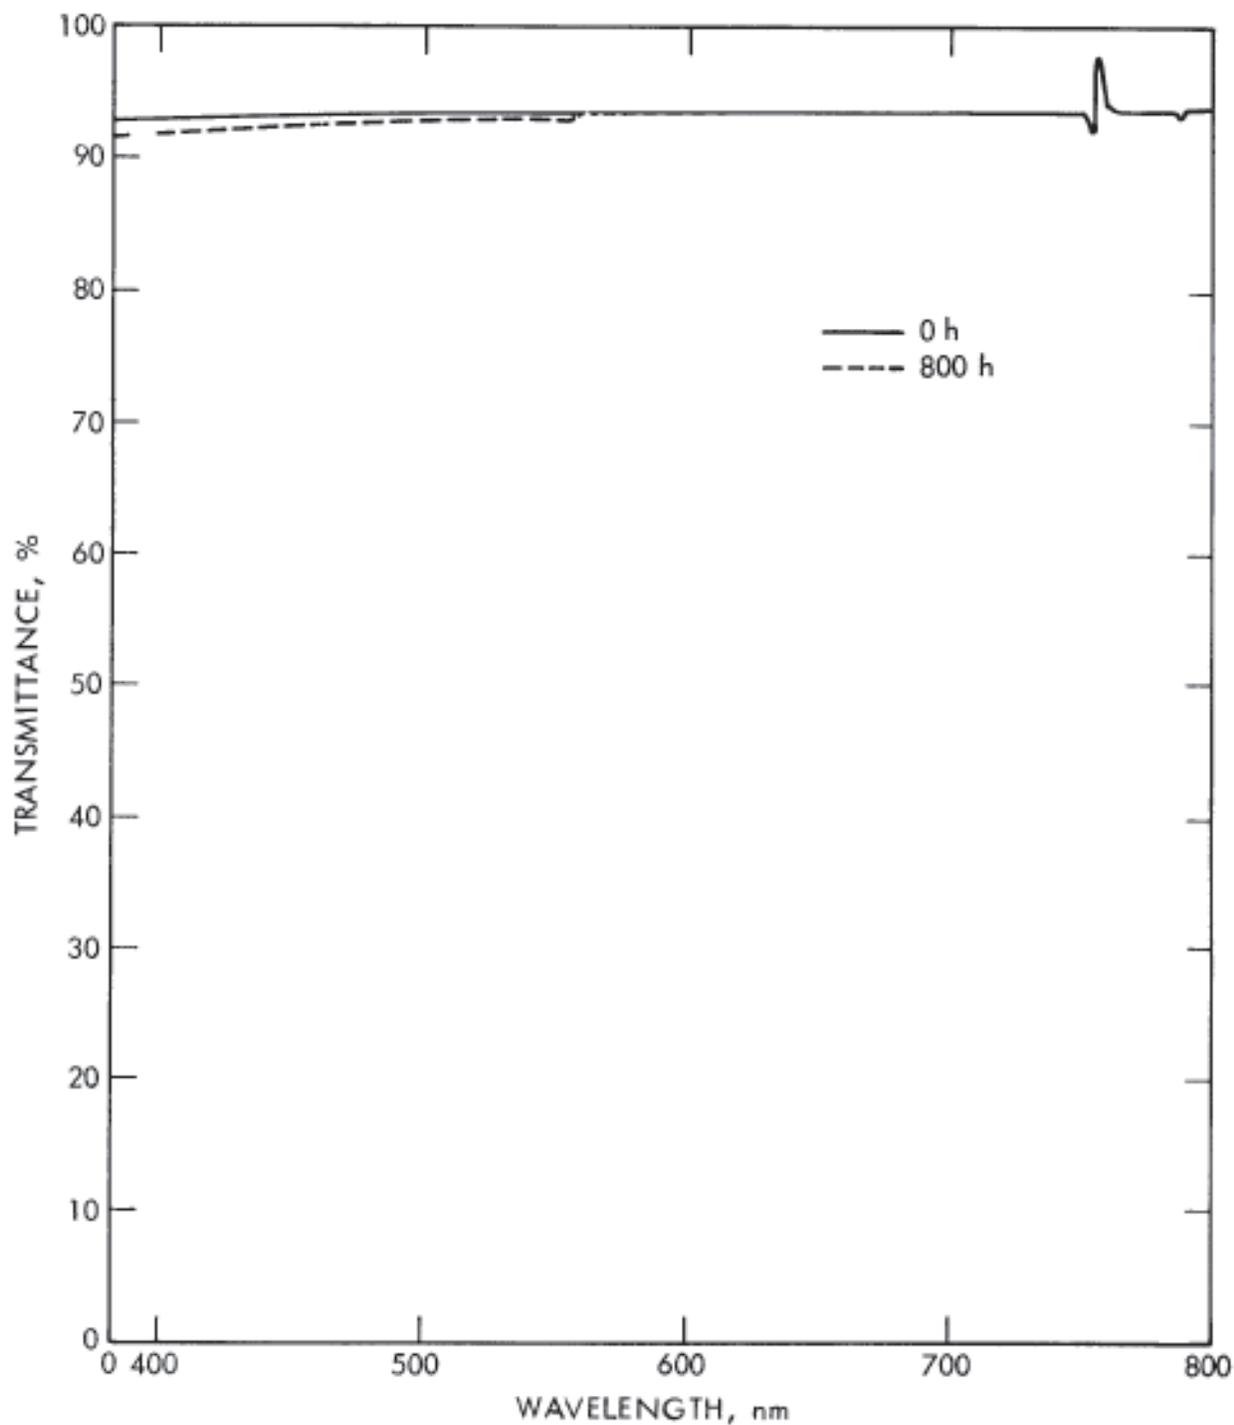


Figure 49. Change in Optical Transmittance as a Function of Open Photothermal Aging of RTV at 105°C

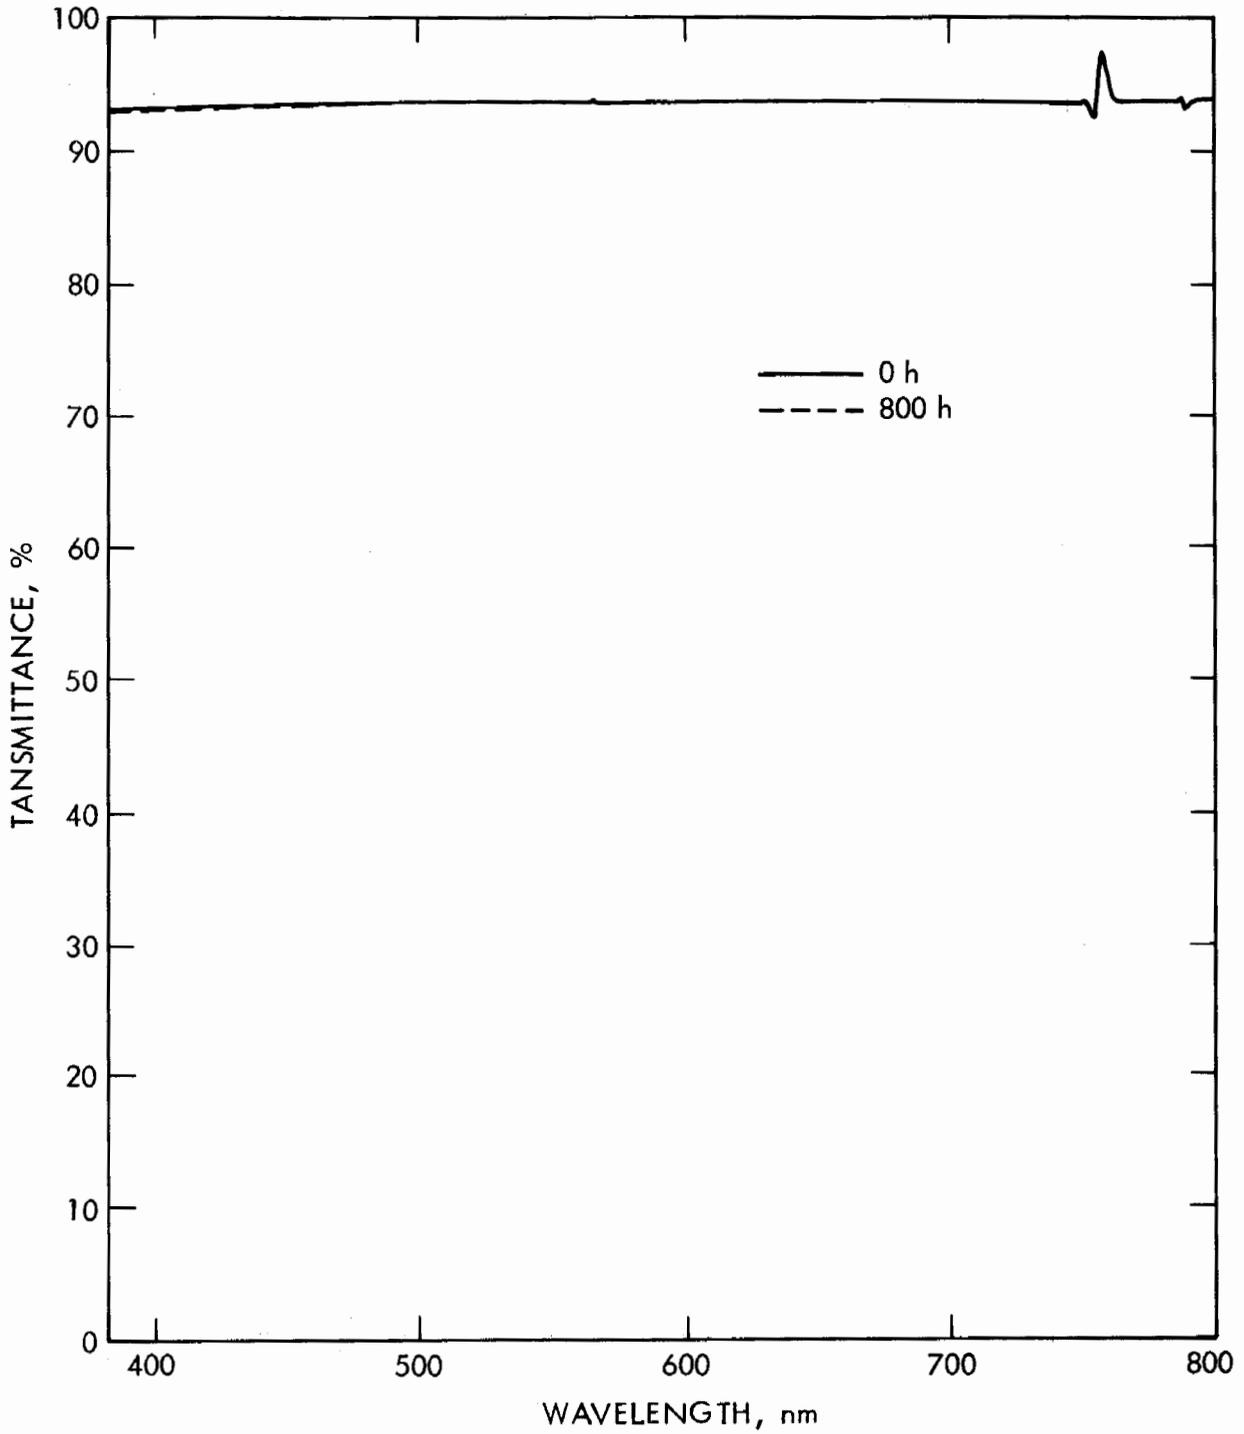


Figure 50. Change in Optical Transmittance as a Function of Covered Photothermal Aging of RTV at 105°C

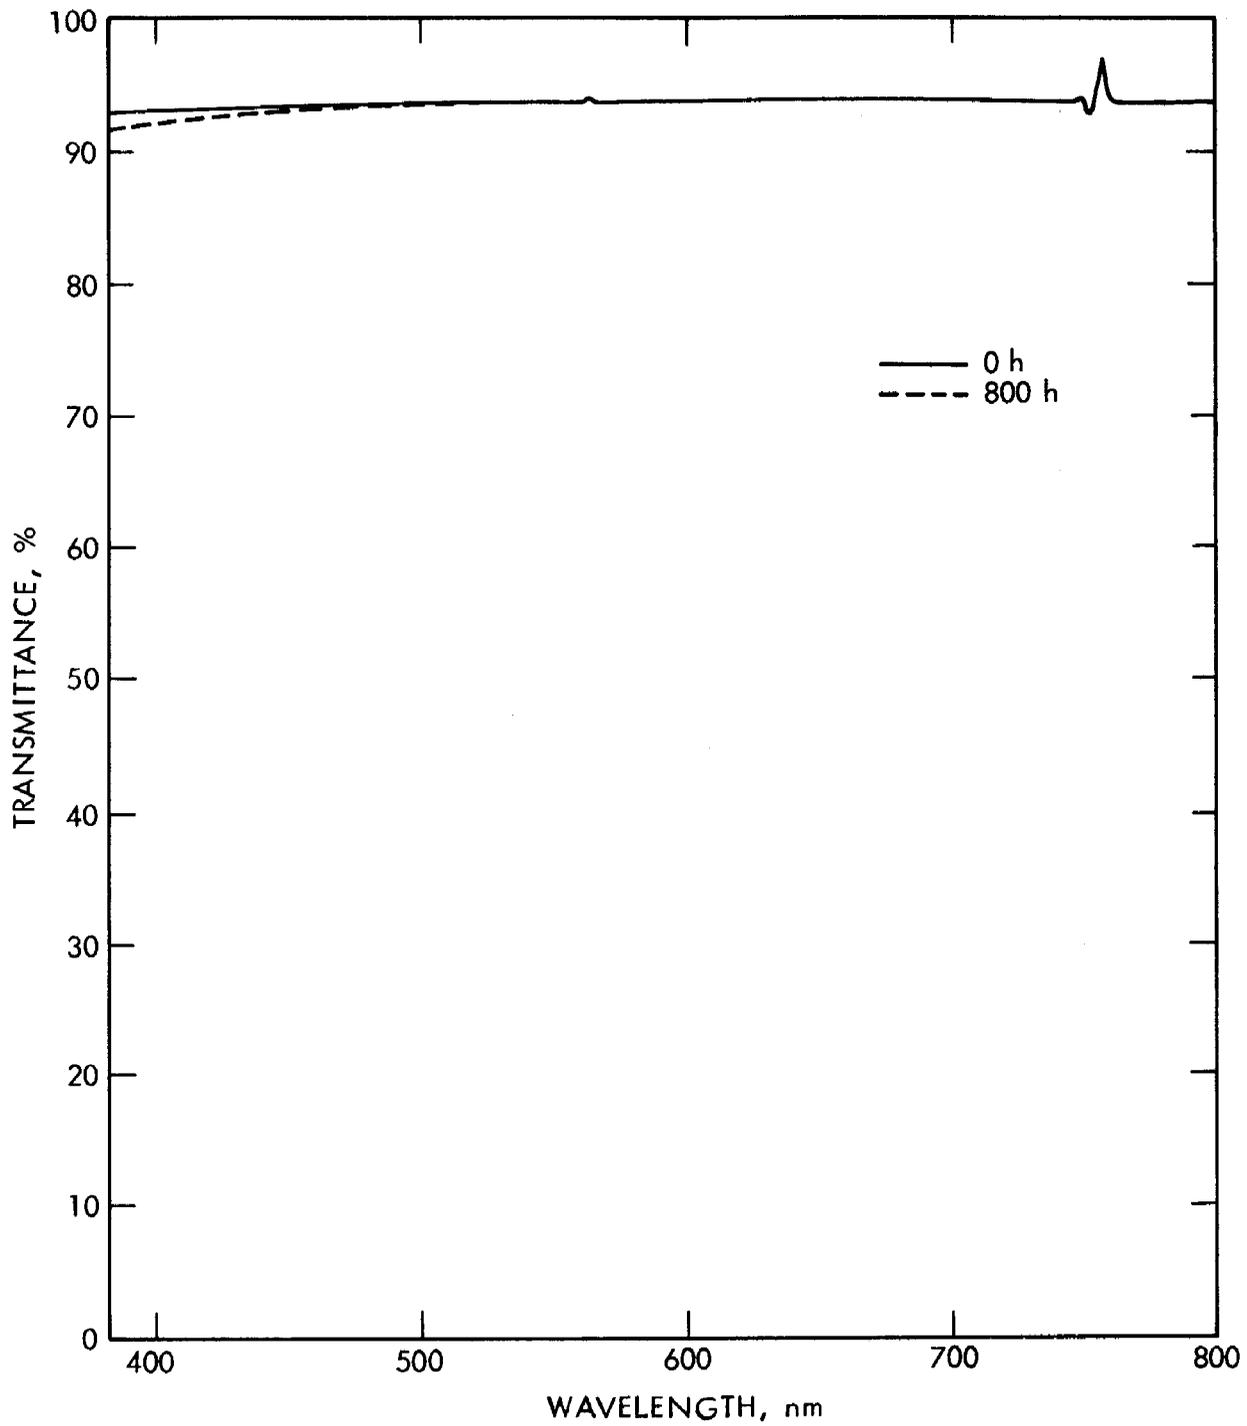


Figure 51. Change in Optical Transmittance as a Function of Thermal Aging of RTV at 105°C

B. MECHANICAL PROPERTIES

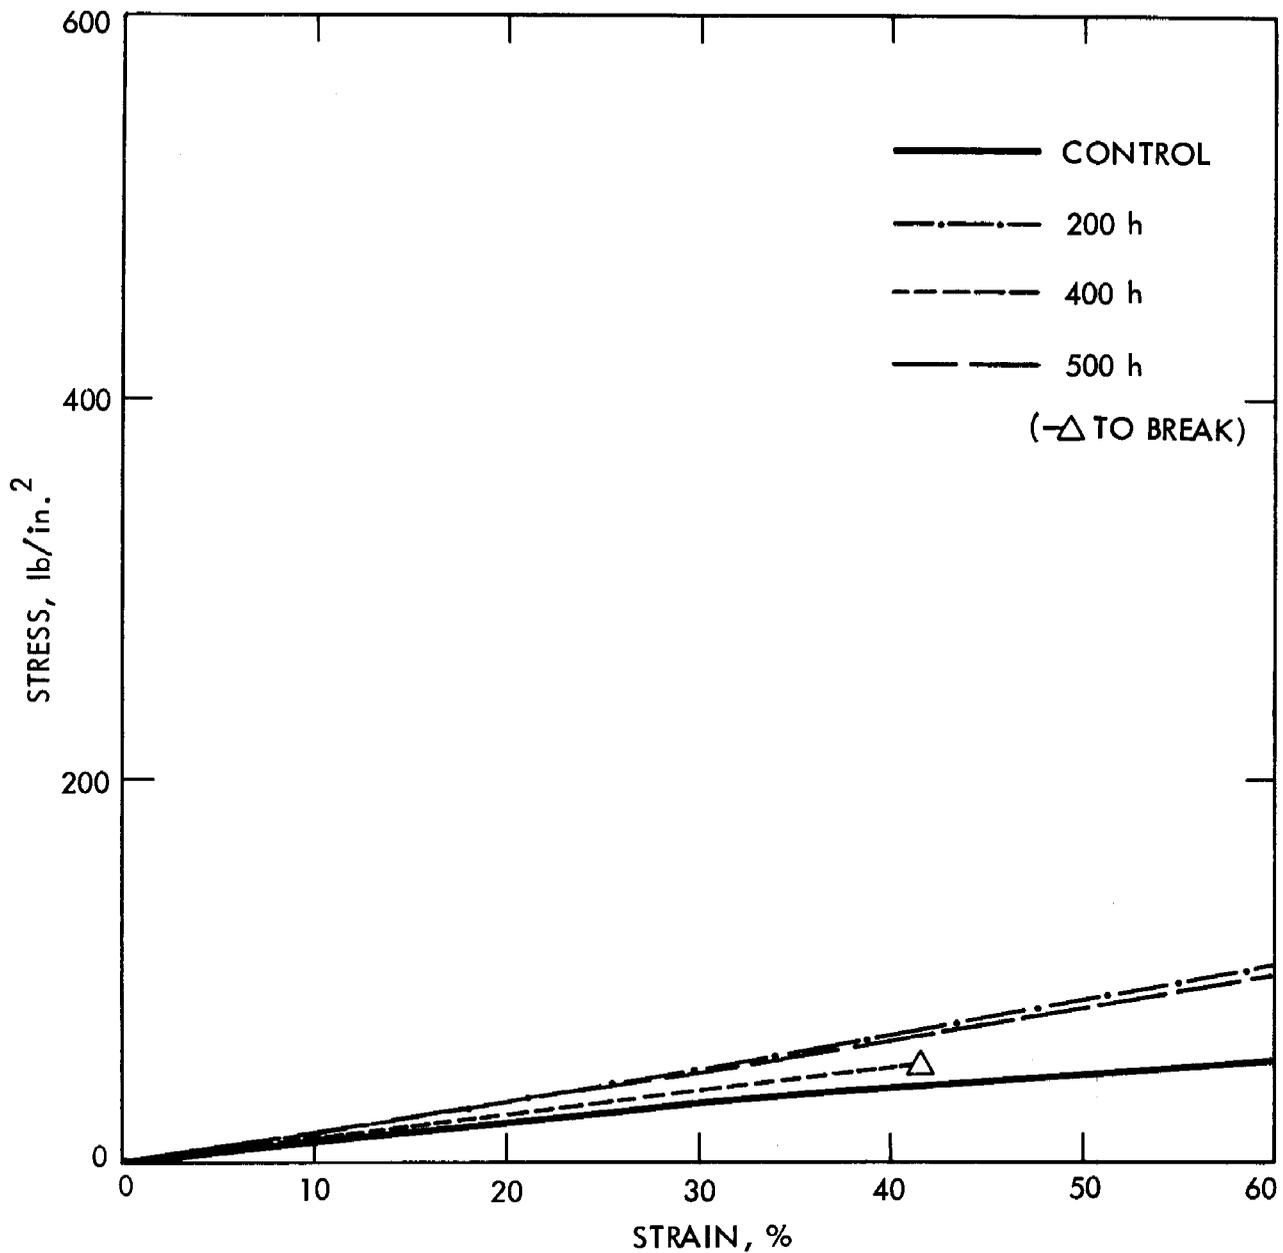


Figure 52. Change in Stress/Strain Response as a Function of Open Photothermal Aging of RTV at 70°C

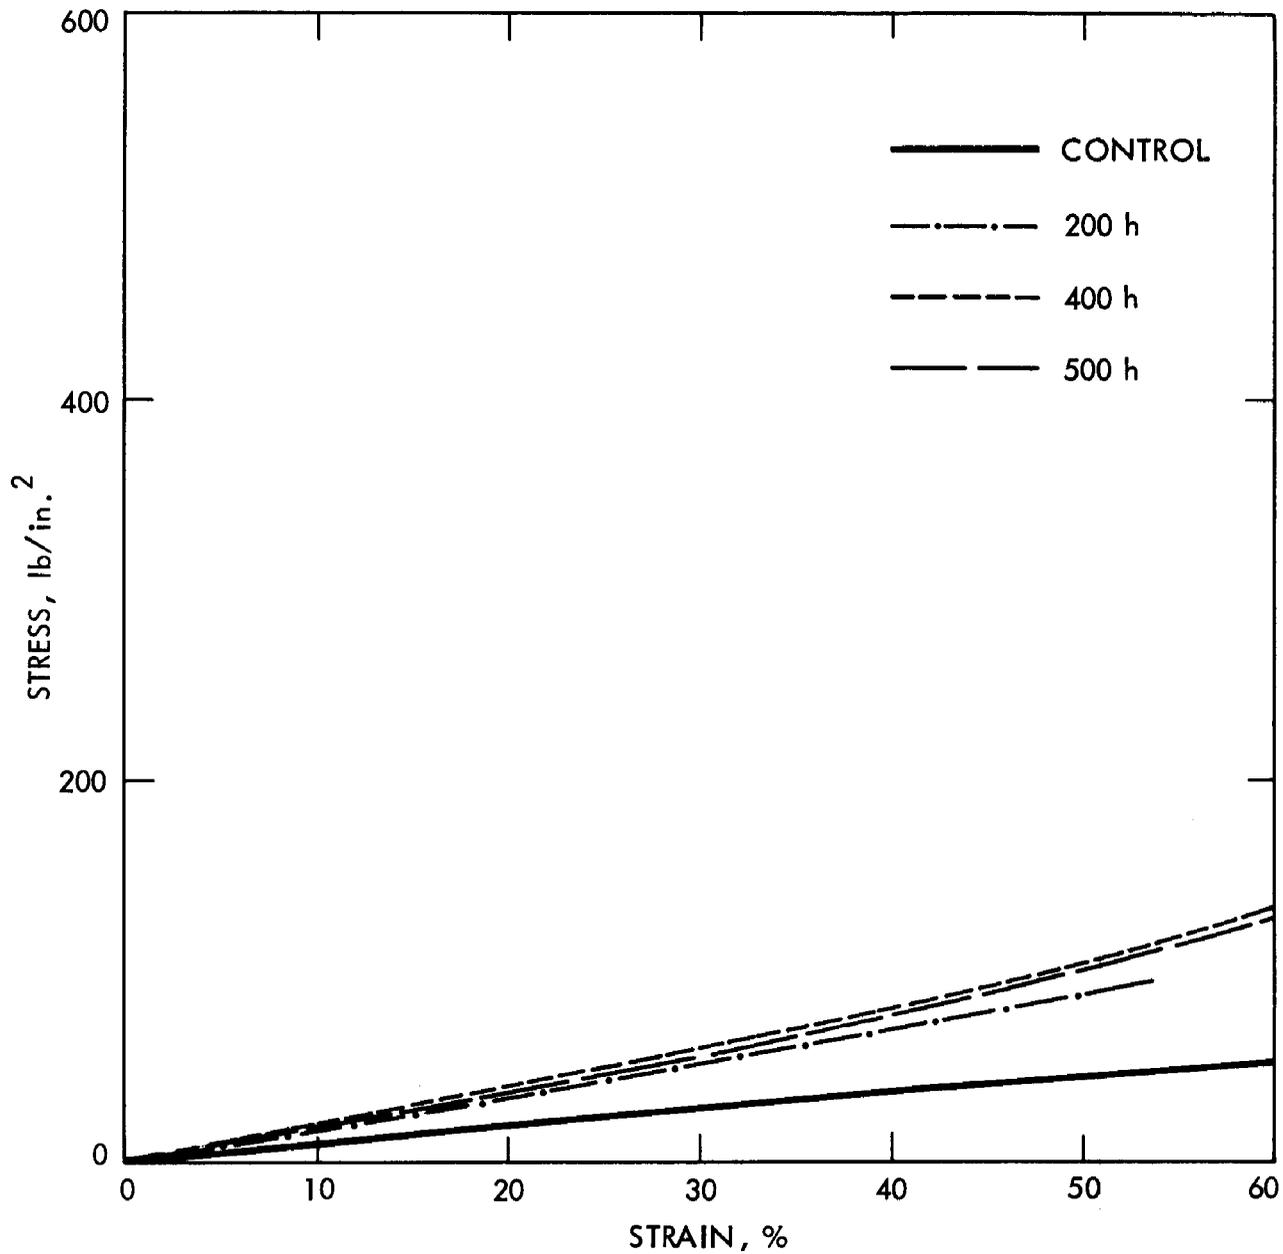


Figure 53. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of RTV at 70°C

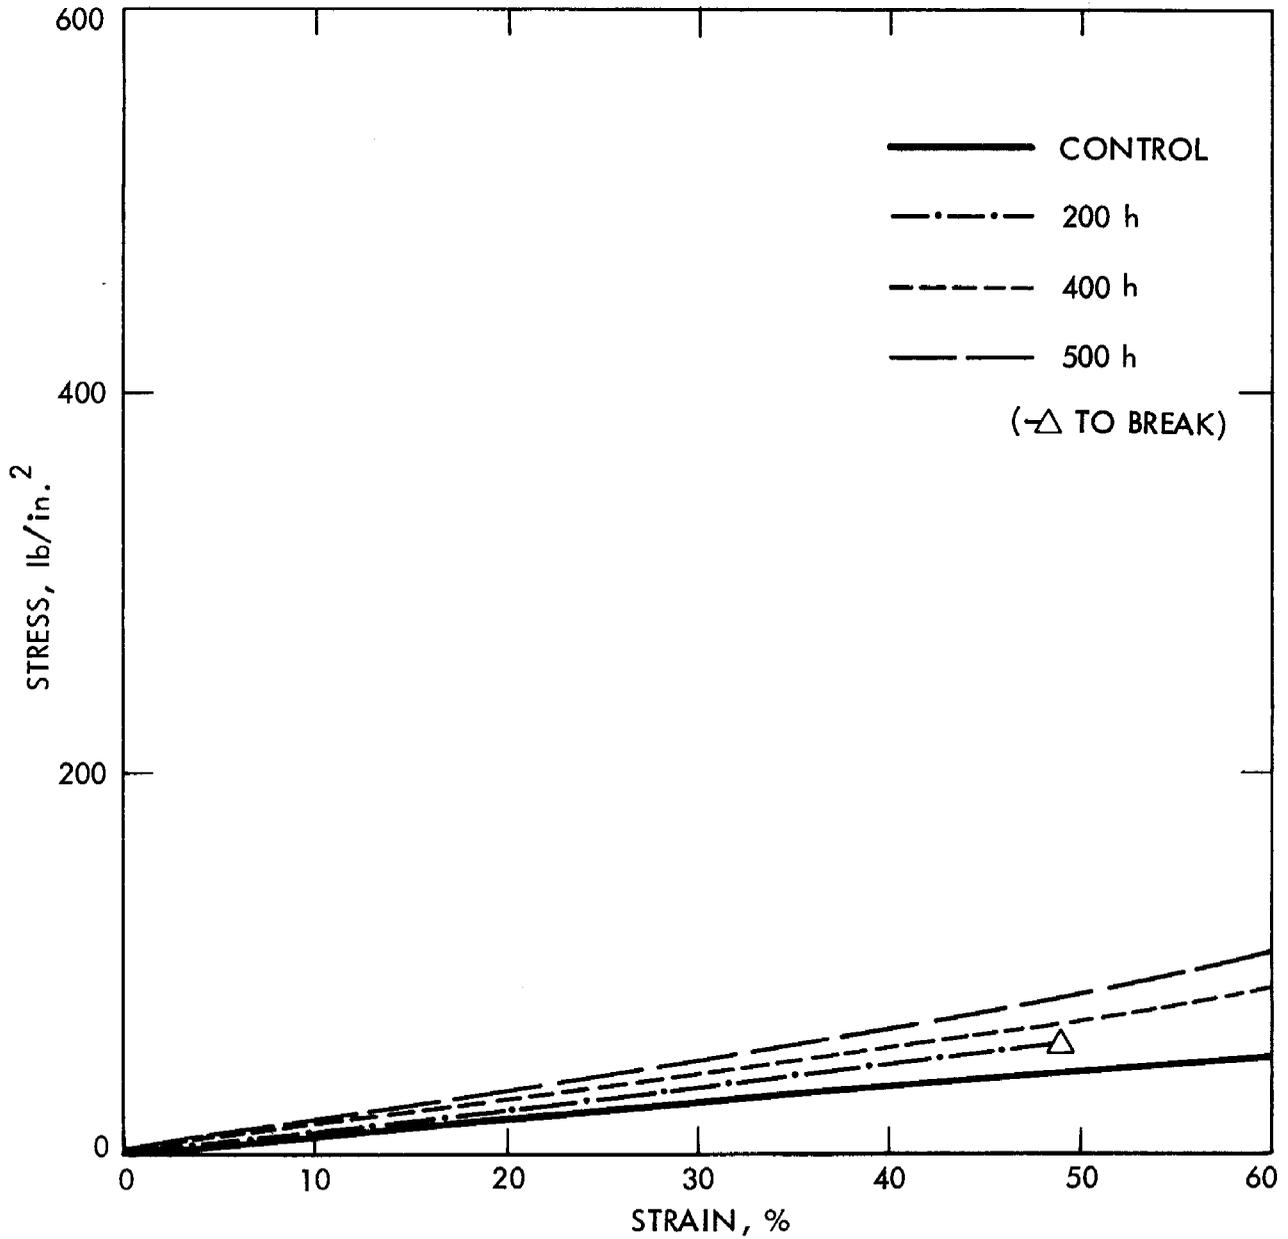


Figure 54. Change in Stress/Strain Response as a Function of Thermal Aging of RTV at 70°C

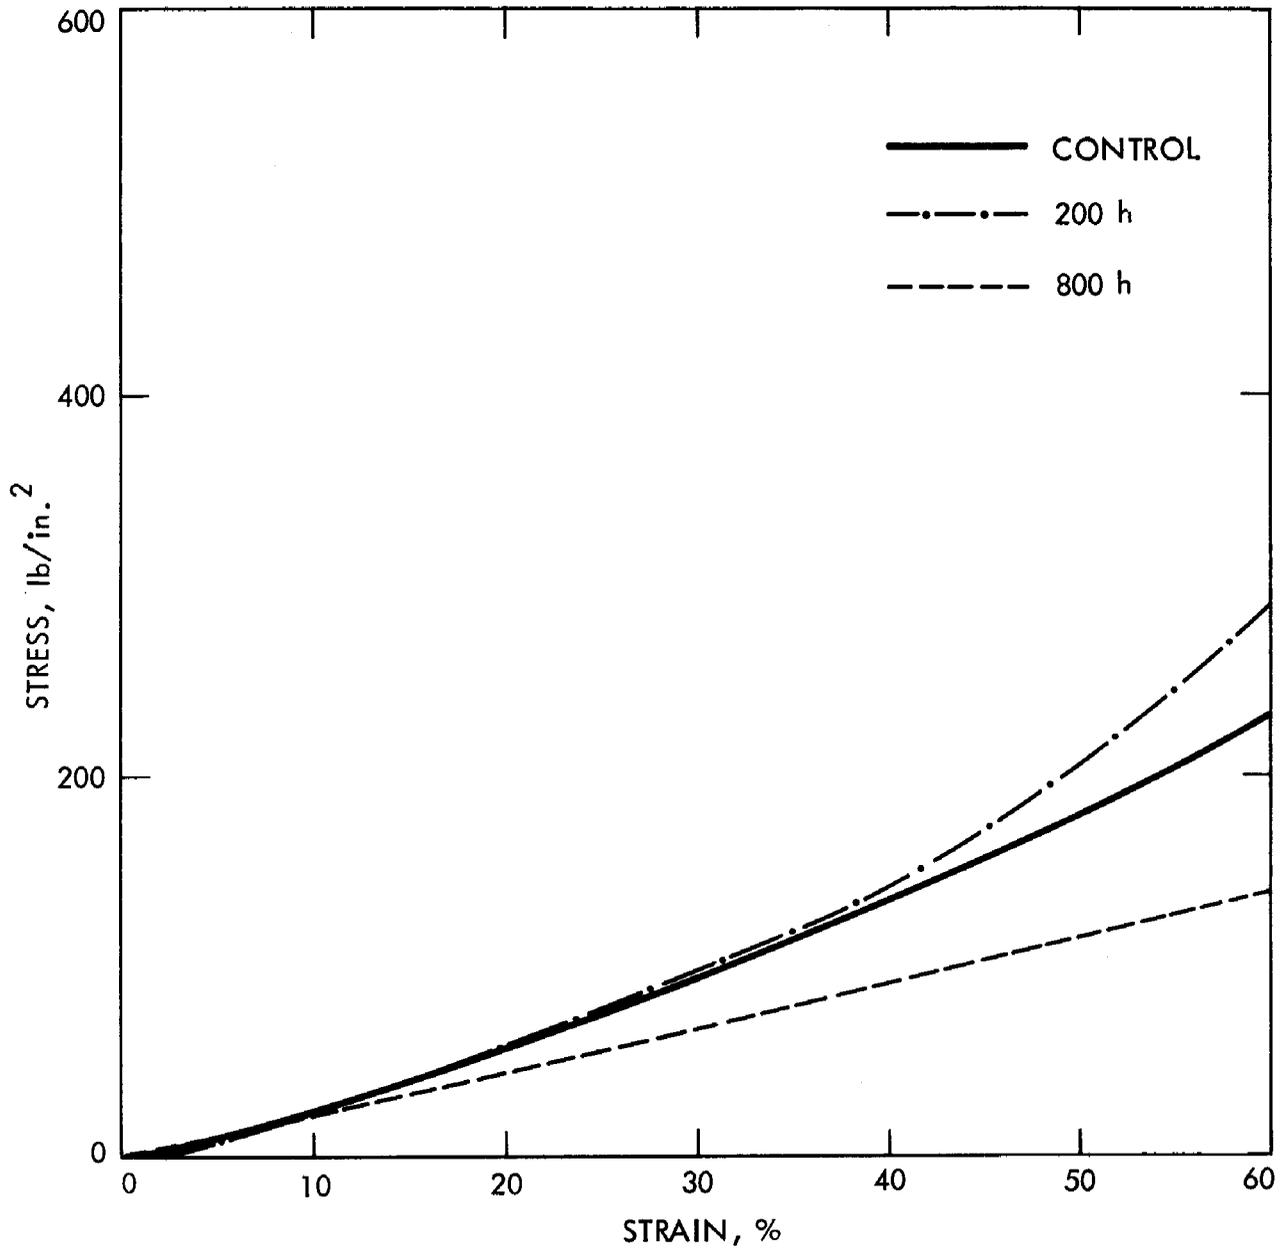


Figure 55. Change in Stress/Strain Response as a Function of Open Photothermal Aging of RTV at 85°C

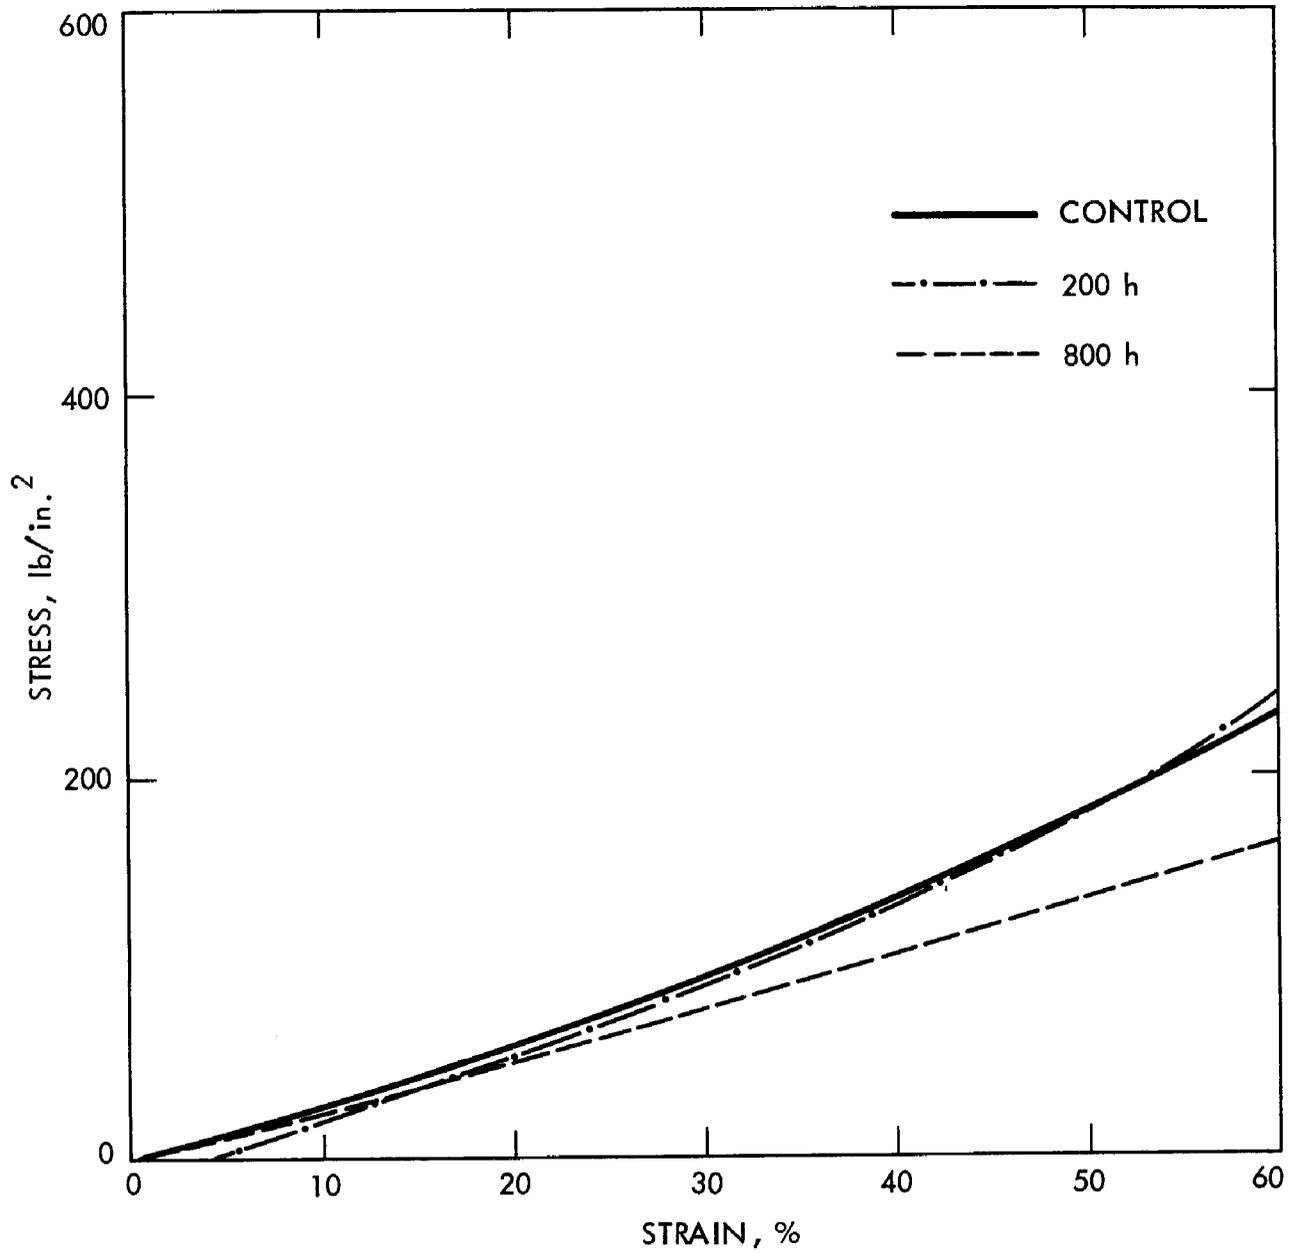


Figure 56. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of RTV at 85°C

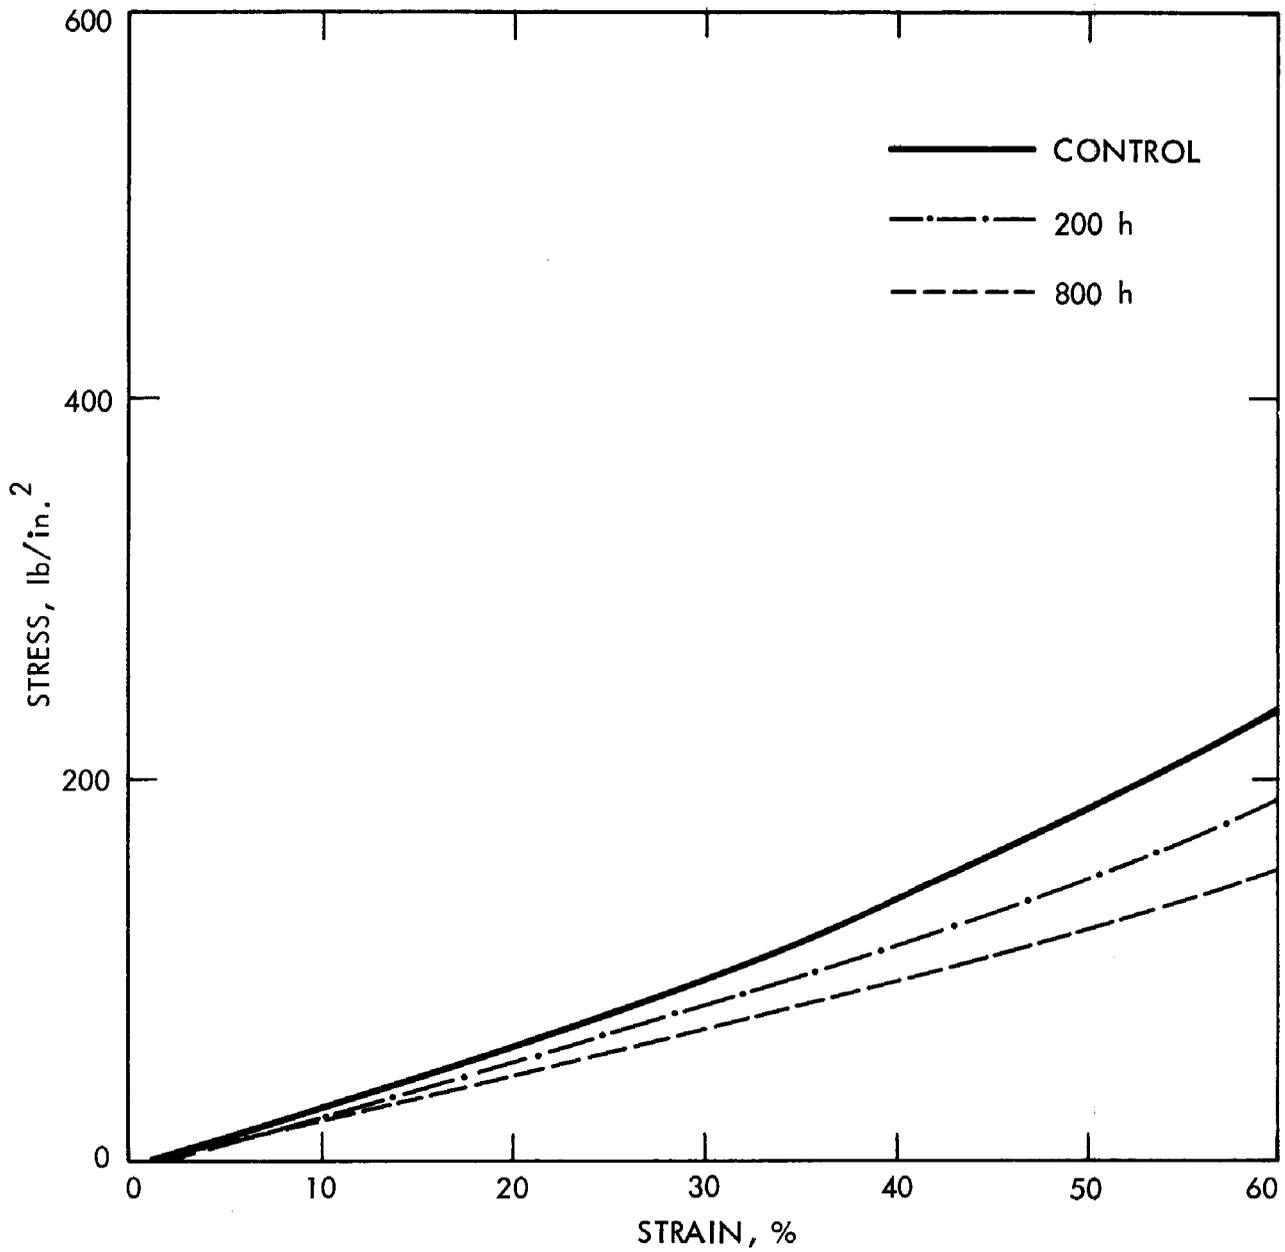


Figure 57. Change in Stress/Strain Response as a Function of Thermal Aging of RTV at 85°C

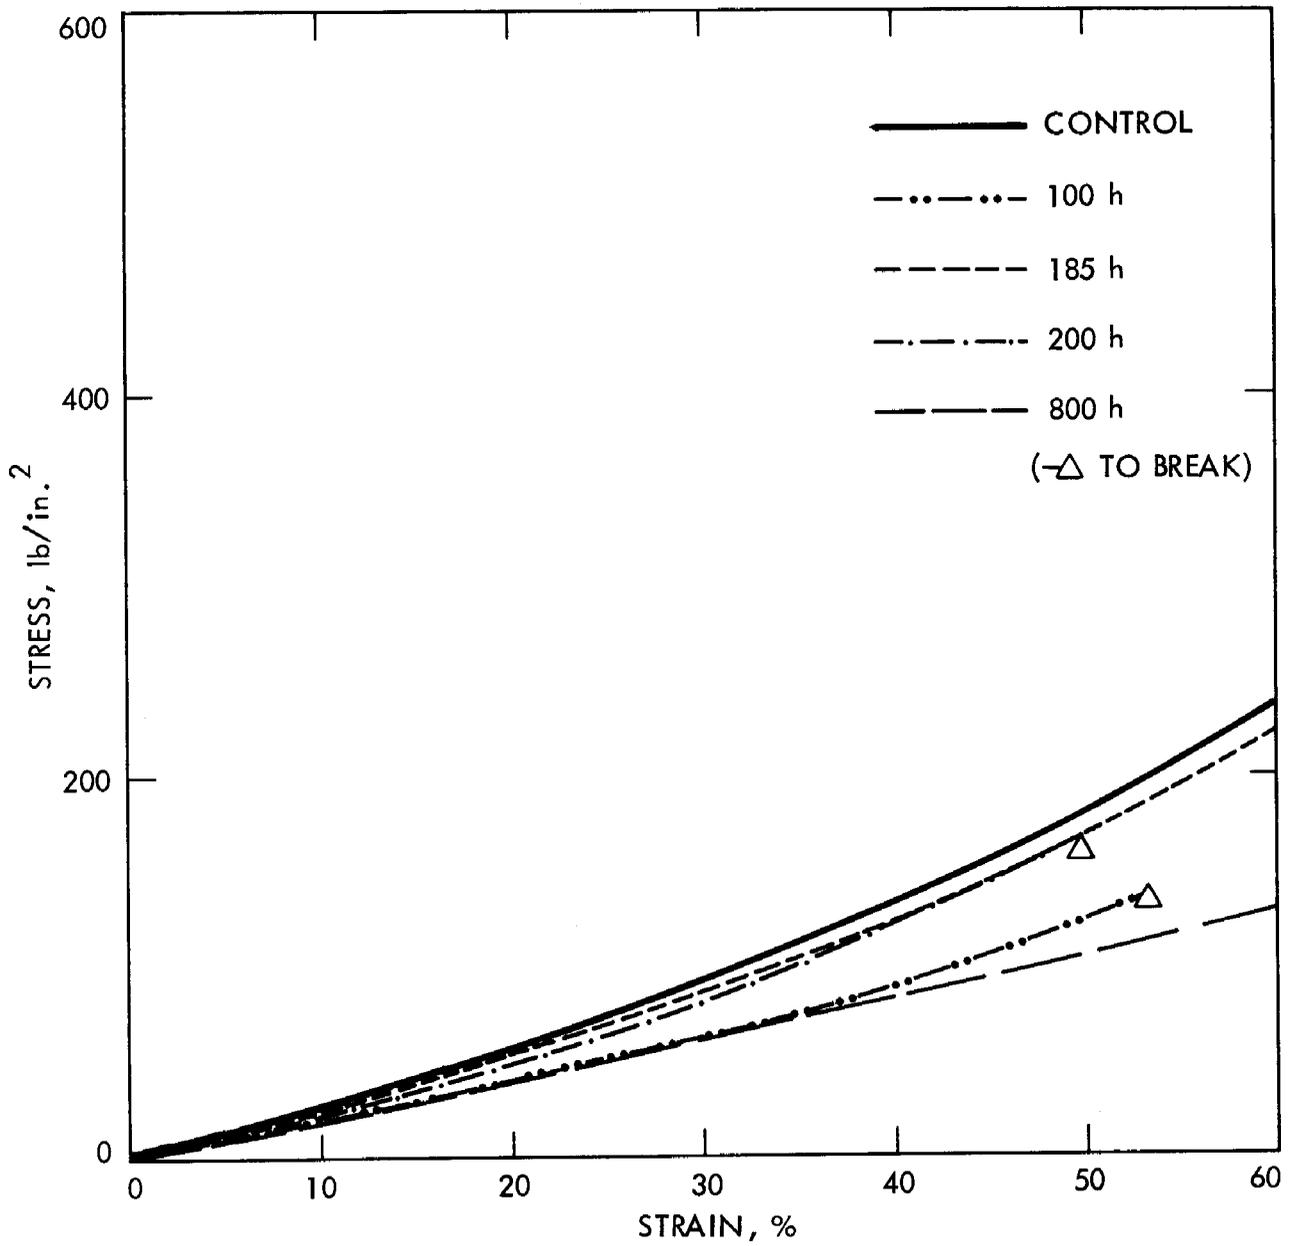


Figure 58. Change in Stress/Strain Response as a Function of Open Photothermal Aging of RTV at 105°C

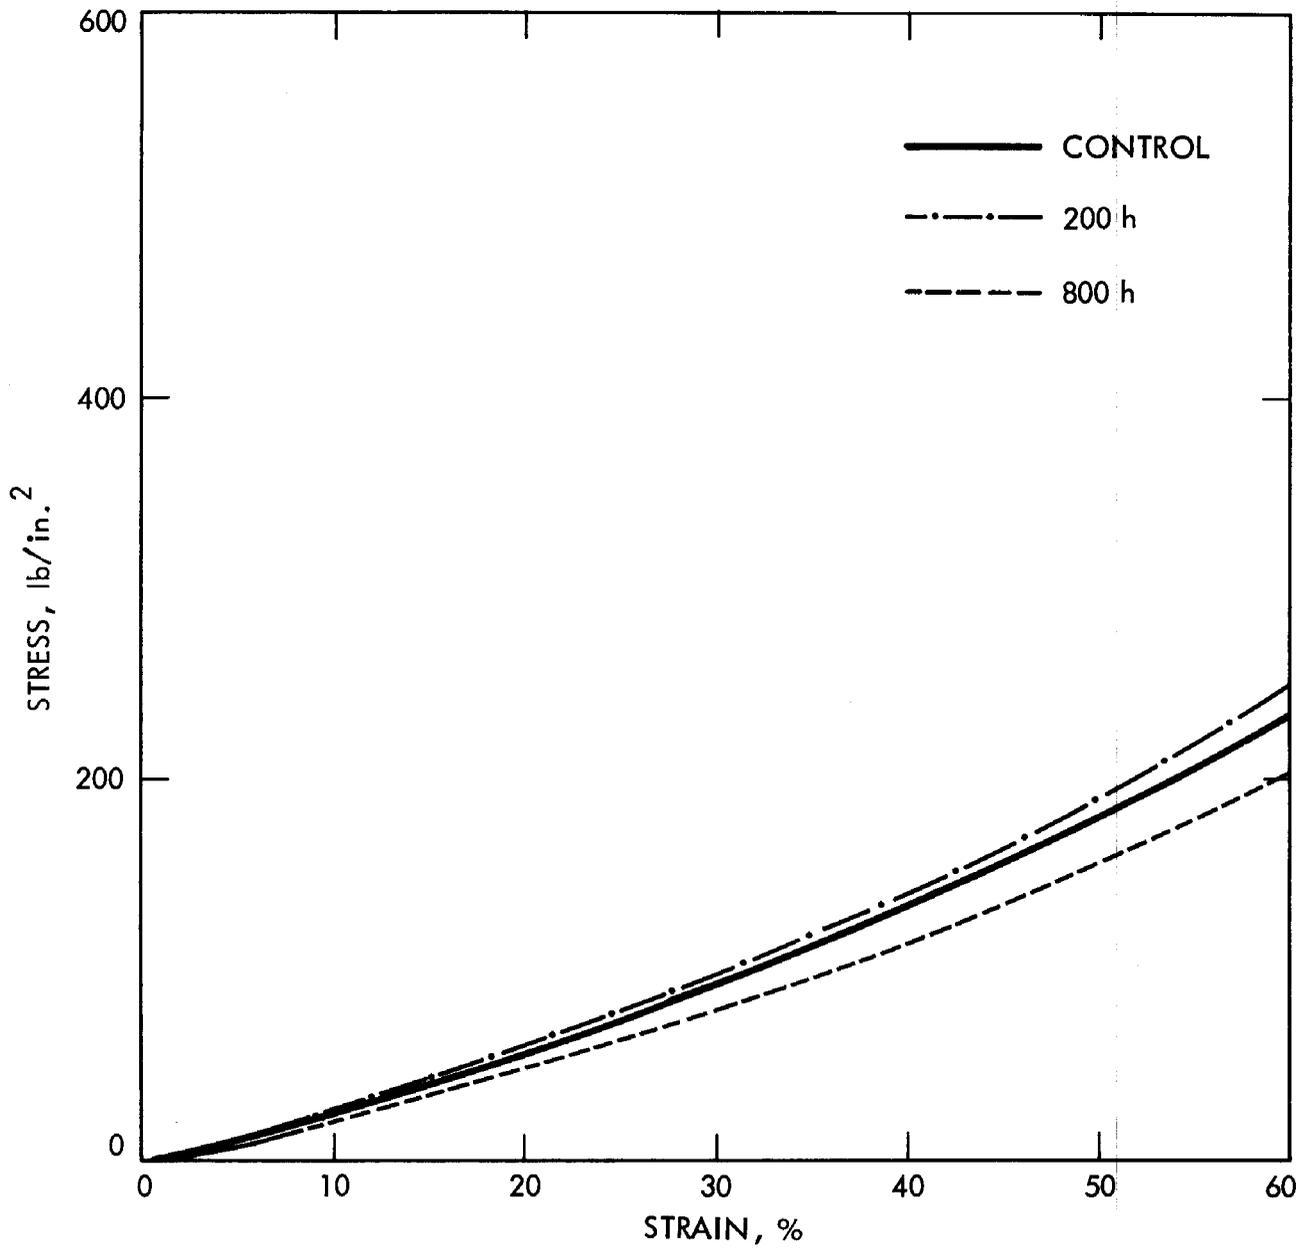


Figure 59. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of RTV at 105°C

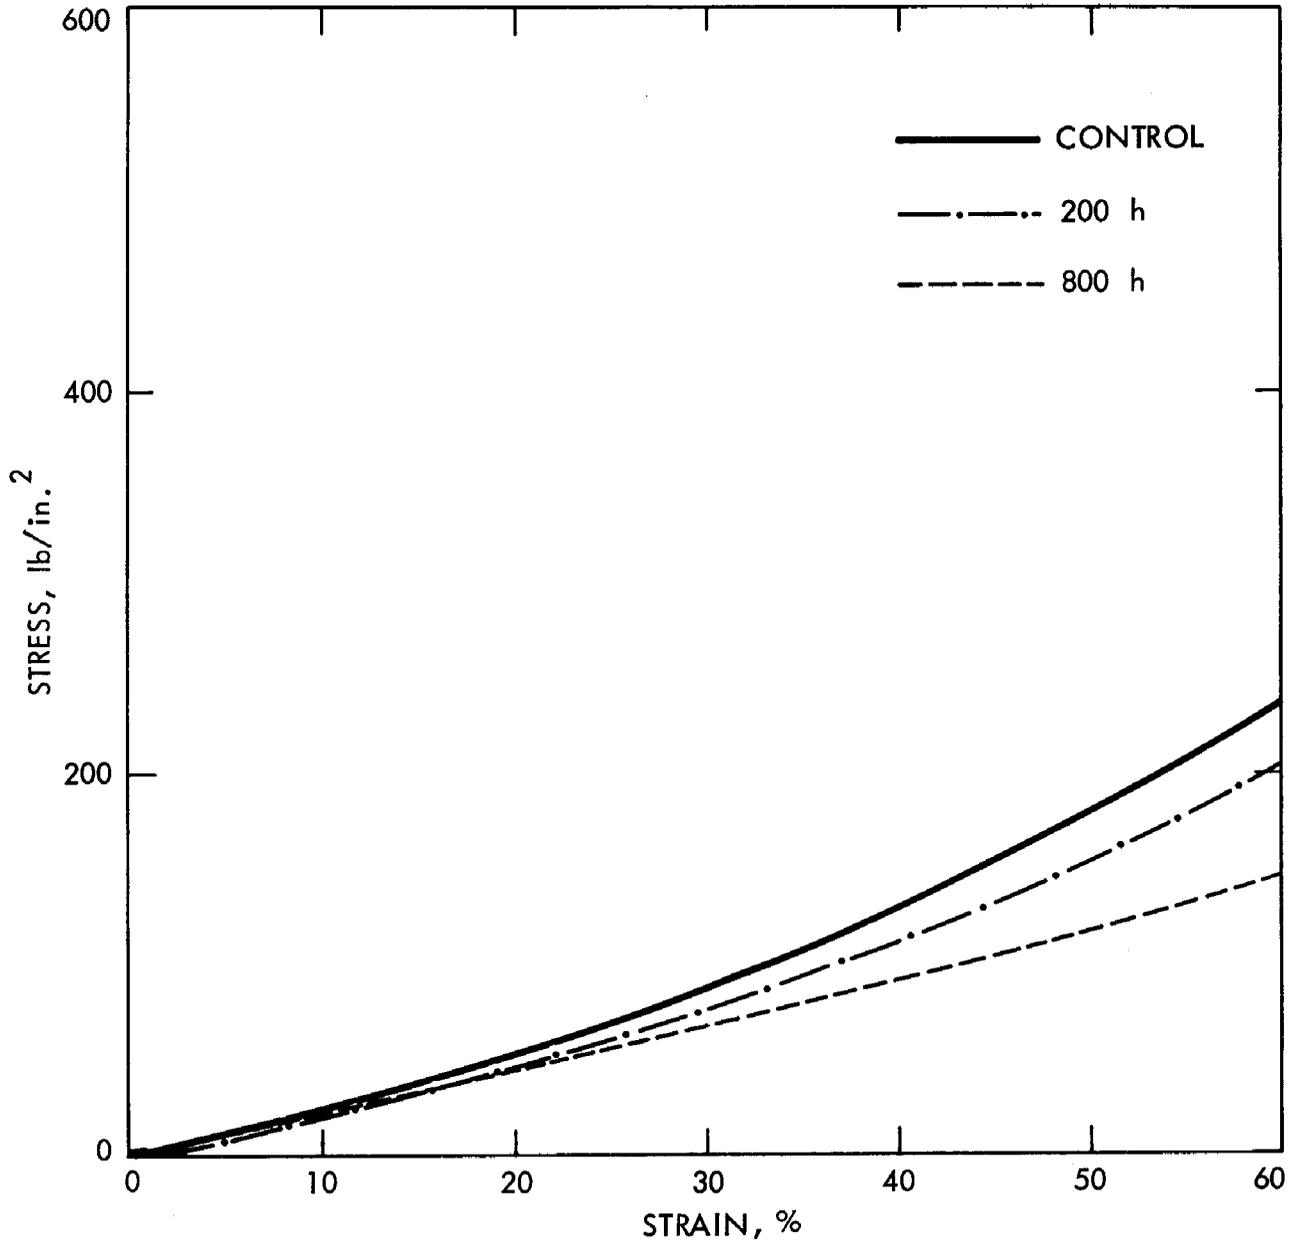


Figure 60. Change in Stress/Strain Response as a Function of Thermal Aging of RTV at 105°C

Table 13. Modulus at 5% Strain as a Function of Open Photothermal Aging of RTV at 30°C, 70°C, 85°C, and 105°C

| TEMPERATURE,<br>°C | TIME OF<br>AGING, h | MODULUS, In lb/in. <sup>2</sup><br>5% STRAIN |          |
|--------------------|---------------------|--|----------|
|                    |                     | SAMPLE 1                                     | SAMPLE 2 |
| ROOM TEMP. (30)    | 0                   | 110  | 322      |
|                    |                     |  |          |
| 70                 | 200                 | 186  |          |
|                    | 400                 | 141  |          |
|                    | 500                 | 167  |          |
| 85                 | 200                 |  | 335      |
|                    | 800                 |  | 314      |
| 105                | 100                 |  | 238      |
|                    | 200                 |  | 300      |
|                    | 800                 |  | 285      |

Table 14. Modulus at 5% Strain as a Function of Covered Photothermal Aging of RTV at 30°C, 70°C, 85°C, and 105°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |          |
|-----------------|------------------|--|----------|
|                 |                  | SAMPLE 1                               | SAMPLE 2 |
| ROOM TEMP. (30) | 0                | 110                                    | 322      |
|                 |                  |  |          |
| 70              | 200              | 234                                    |          |
|                 | 400              | 217                                    |          |
|                 | 500              | 234                                    |          |
| 85              | 200              |  | 308      |
|                 | 800              |  | 301      |
| 105             | 200              |  | 341      |
|                 | 800              |  | 312      |

Table 15. Modulus at 5% Strain as a Function of Thermal Aging of RTV at 30°C, 70°C, 85°C, and 105°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |          |
|-----------------|------------------|--|----------|
|                 |                  | SAMPLE 1                               | SAMPLE 2 |
| ROOM TEMP. (30) | 0                | 110                                    | 322      |
|                 |                  |  |          |
| 70              | 200              | 158                                    |          |
|                 | 400              | 158                                    |          |
|                 | 500              | 179                                    |          |
| 85              | 200              |  | 275      |
|                 | 800              |  | 270      |
| 105             | 200              |  | 266      |
|                 | 800              |  | 263      |

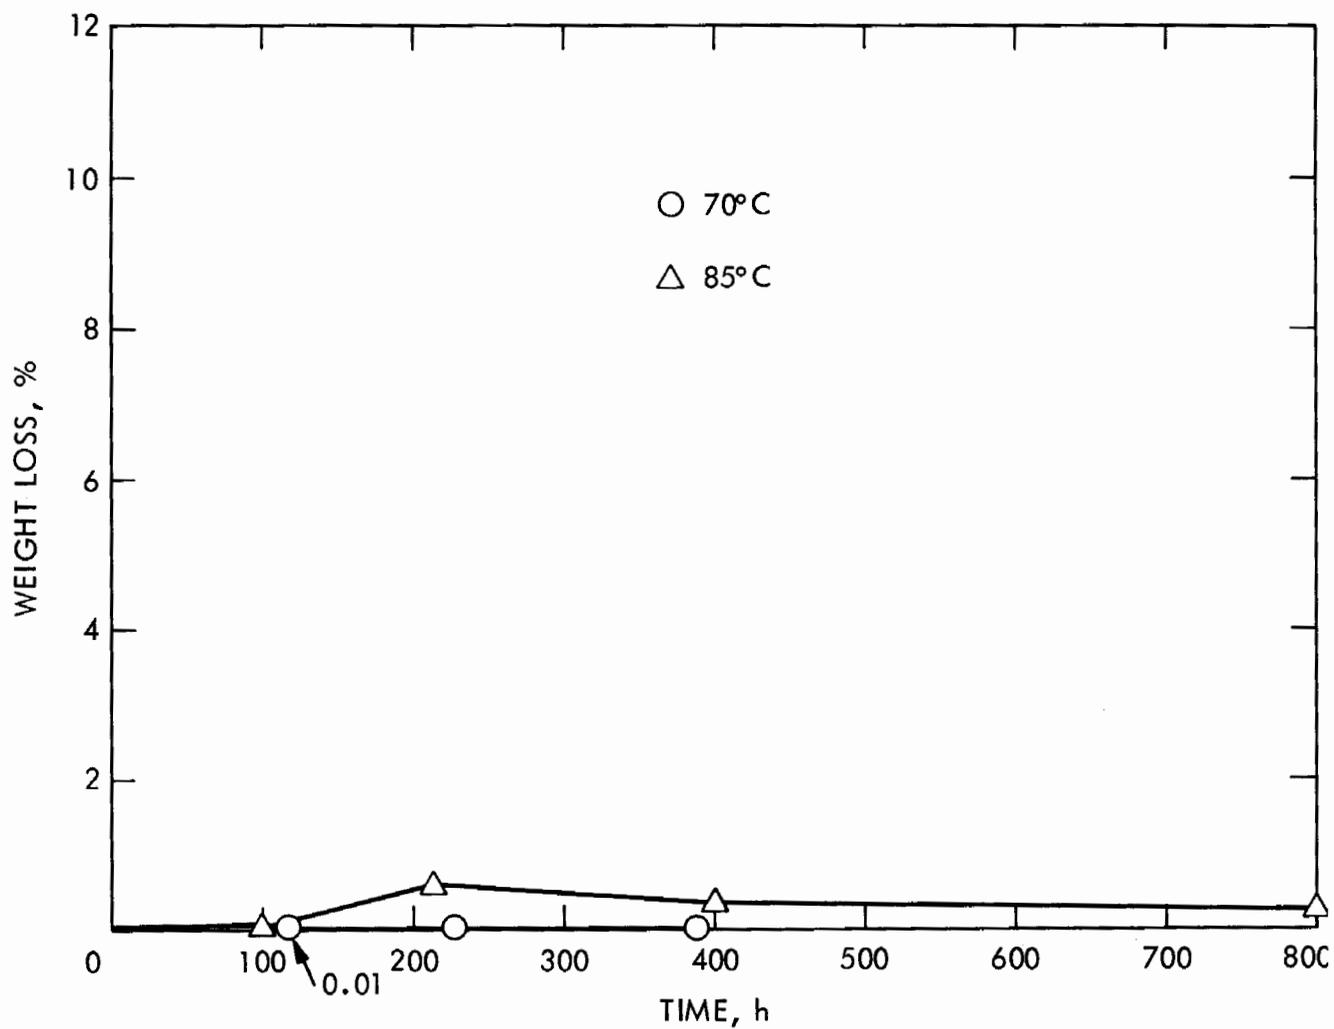


Figure 61. Weight Loss as a Function of Open Photothermal Aging of RTV at 70°C and 85°C

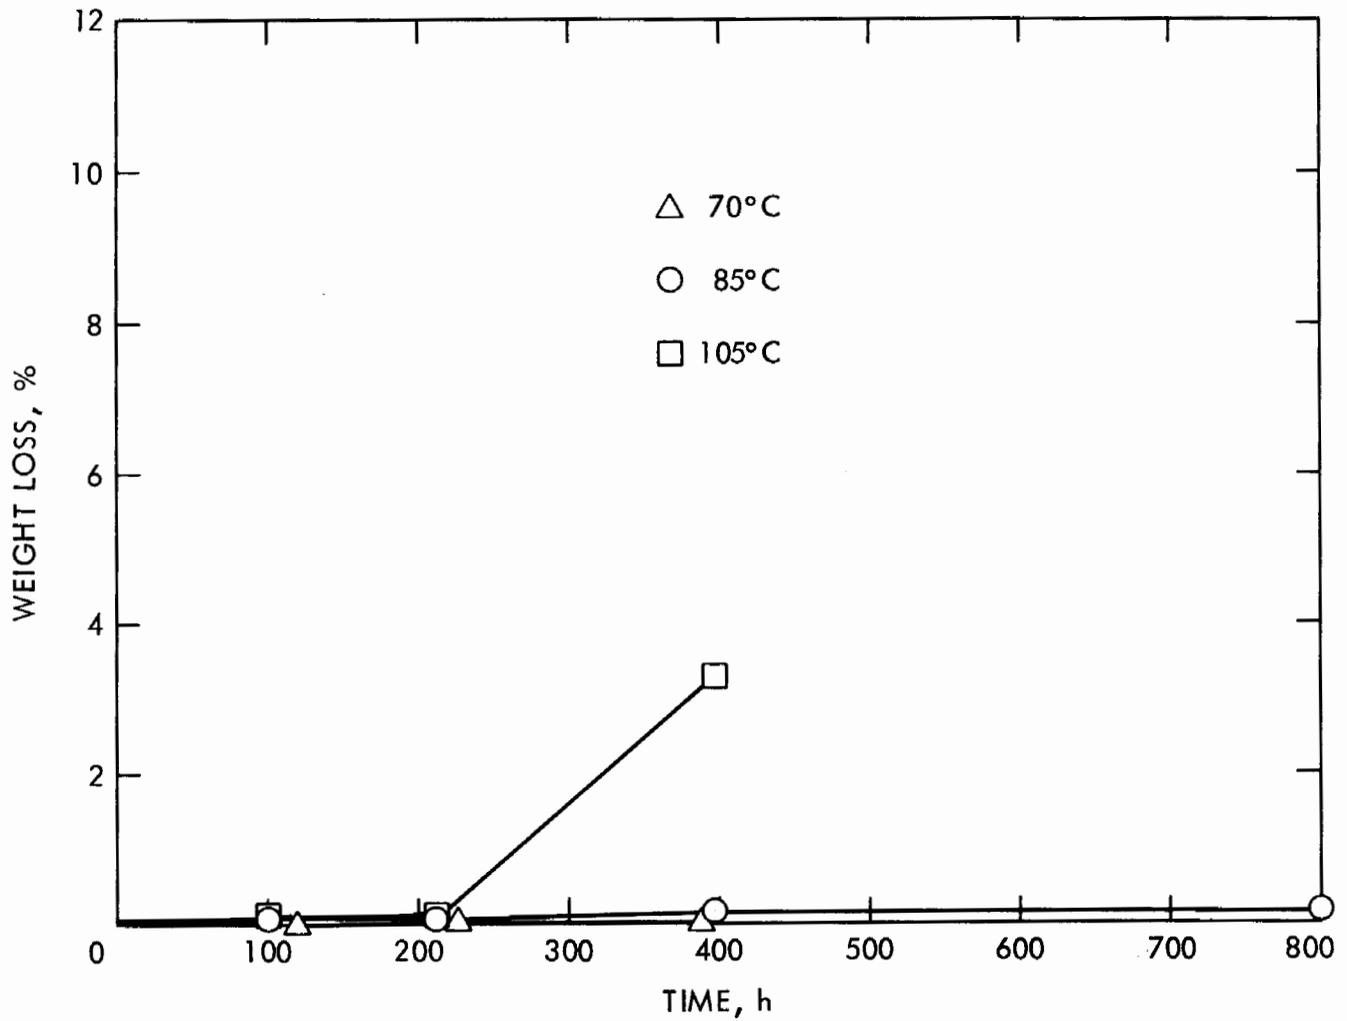


Figure 62. Weight Loss as a Function of Covered Photothermal Aging of RTV at 70°C, 85°C, and 105°C

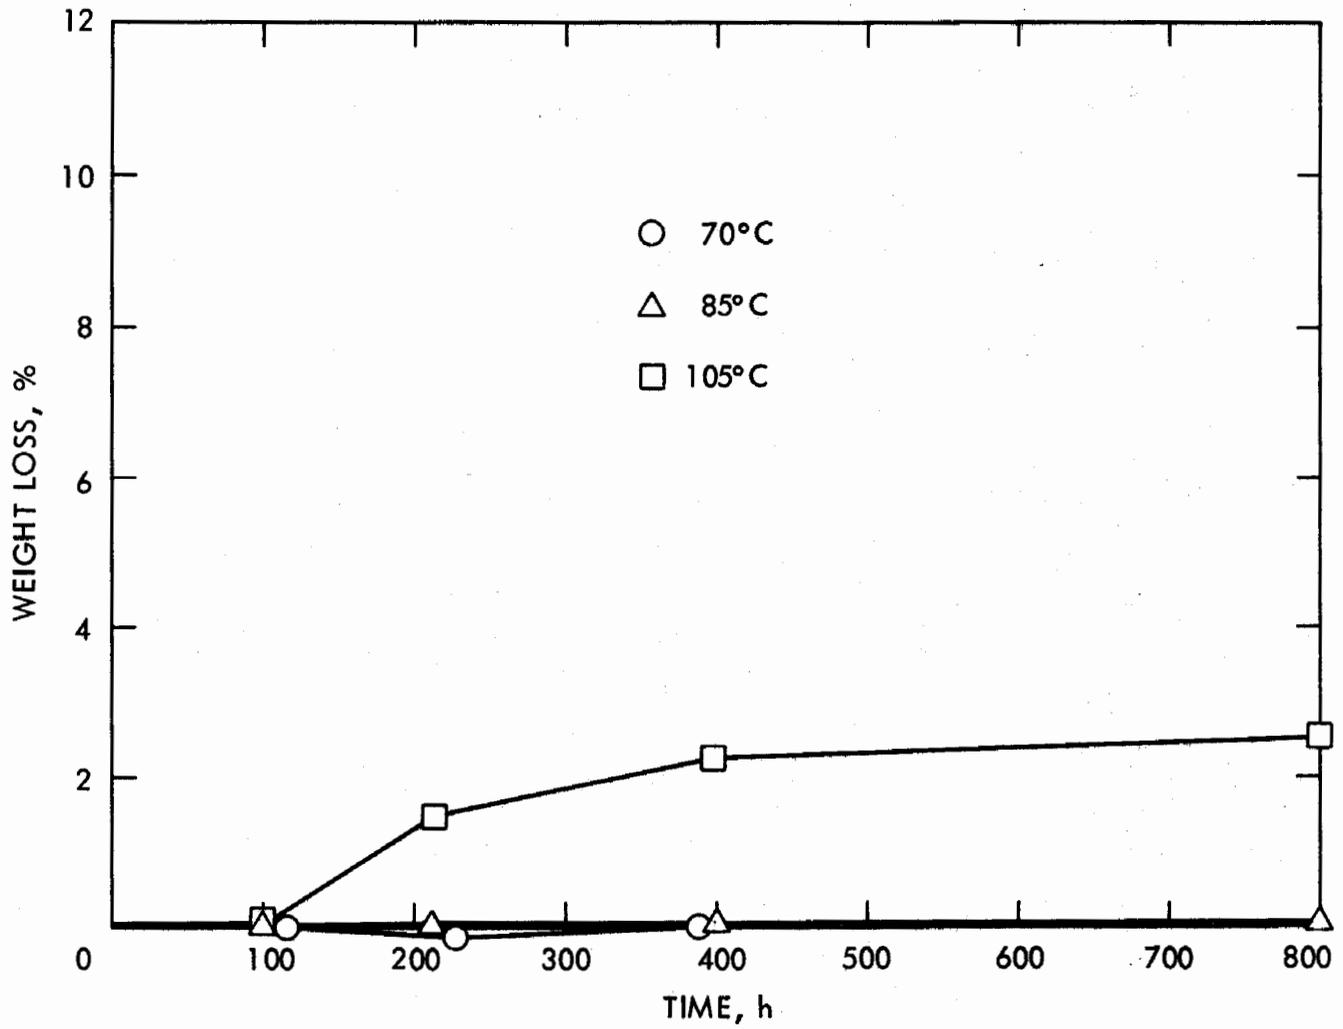


Figure 63. Weight Loss as a Function of Thermal Aging of RTV at 70°C, 85°C, and 105°C

D. OTHER PROPERTIES

Table 16. Sol/Gel and Molecular Weight Data as a Function of Open Photothermal Aging of RTV at 30°C, 70°C, 85°C, and 105°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> |                         | SOL, % |   | GEL, % |    | MOL WT (SOL) |      |
|-------|------------------|---|-------------------------|--------|---|--------|----|--------------|------|
|       |                  | SAMPLE 1                                  | SAMPLE 2                | 1      | 2 | 1      | 2  | 1            | 2    |
| 30    | 0                | 2.04 x 10 <sup>-4</sup>                   | 7.97 x 10 <sup>-4</sup> |        | 4 |        | 96 |              | 2000 |
|       |                  |   |                         |        |   |        |    |              |      |
| 70    | 500              | 2.70 x 10 <sup>-4</sup>                   |                         | 4      |   | 96     |    | 2000         |      |
| 85    | 800              |   | 7.62 x 10 <sup>-4</sup> |        | 4 |        | 96 |              | 2000 |
| 105   | 800              |   | 7.42 x 10 <sup>-4</sup> |        | 4 |        | 96 |              | 2000 |

Table 17. Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of RTV at 30°C, 70°C, 85°C, and 105°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> |                         | SOL, % |   | GEL, % |    | MOL WT (SOL) |      |
|-------|------------------|---|-------------------------|--------|---|--------|----|--------------|------|
|       |                  | SAMPLE 1                                  | SAMPLE 2                | 1      | 2 | 1      | 2  | 1            | 2    |
| 30    | 0                | 2.04 x 10 <sup>-4</sup>                   | 7.97 x 10 <sup>-4</sup> |        | 4 |        | 96 |              | 2000 |
|       |                  |   |                         |        |   |        |    |              |      |
| 70    | 500              | 4.69 x 10 <sup>-4</sup>                   |                         | 3      |   | 97     |    | 2000         |      |
| 85    | 800              |   | 7.69 x 10 <sup>-4</sup> |        | 4 |        | 96 |              | 2000 |
| 105   | 800              |   | 8.79 x 10 <sup>-4</sup> |        | 4 |        | 96 |              | 2000 |

Table 18. Sol/Gel and Molecular Weight Data as a Function of Thermal Aging of RTV at 30°C, 70°C, 85°C, and 105°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> |                         | SOL, % |     | GEL, % |      | MOL WT (SOL) |      |
|-------|------------------|---|-------------------------|--------|-----|--------|------|--------------|------|
|       |                  | SAMPLE 1                                  | SAMPLE 2                | 1      | 2   | 1      | 2    | 1            | 2    |
| 30    | 0                | 2.04 × 10 <sup>-4</sup>                   | 7.97 × 10 <sup>-4</sup> |        | 4   |        | 96   |              | 2000 |
|       |                  |   |                         |        |     |        |      |              |      |
| 70    | 500              | 2.75 × 10 <sup>-4</sup>                   |                         | 3.5    |     | 96.5   |      | 2000         |      |
| 85    | 800              |   | 5.83 × 10 <sup>-4</sup> |        | 4   |        | 96   |              | 2000 |
| 105   | 800              |   | 6.08 × 10 <sup>-4</sup> |        | 3.5 |        | 96.5 |              | 2000 |

## SECTION V

### EMA (SPRINGBORN A-13404)

The following figures and tables offer data on mechanical properties (Figures 64 and 65, Tables 19 and 20); weight loss (Figures 66 through 68); other properties (Tables 21 through 23) of EMA (Springborn A-13404).

A. MECHANICAL PROPERTIES

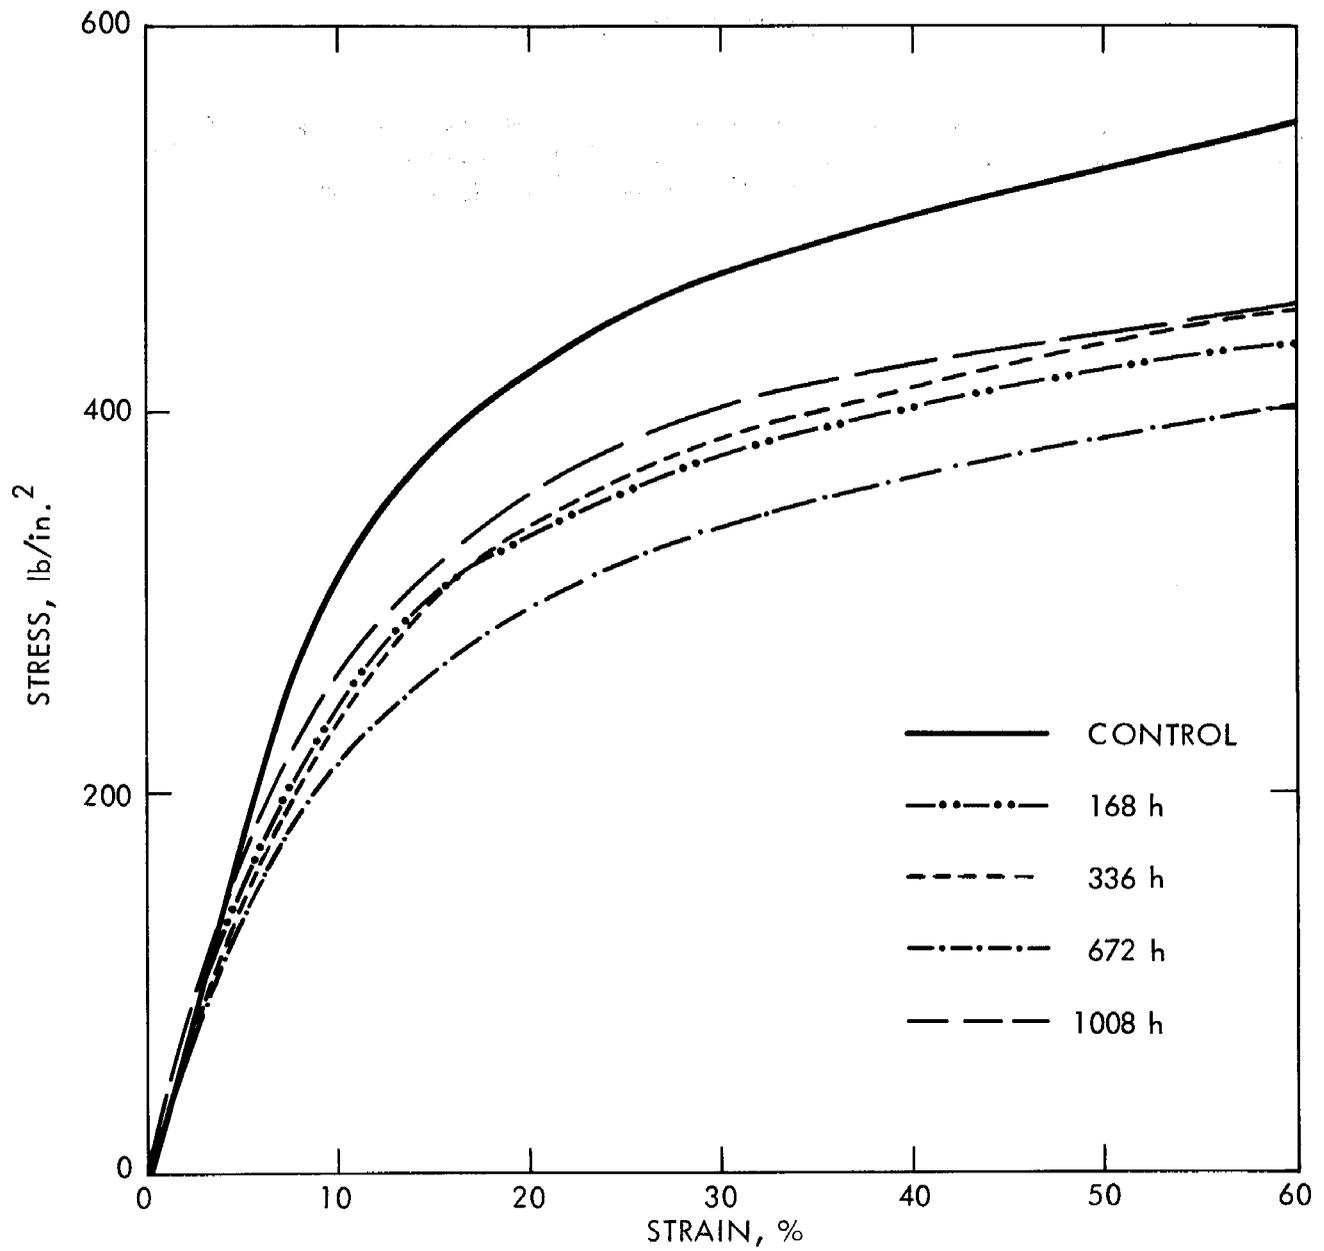


Figure 64. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of EMA at 135°C

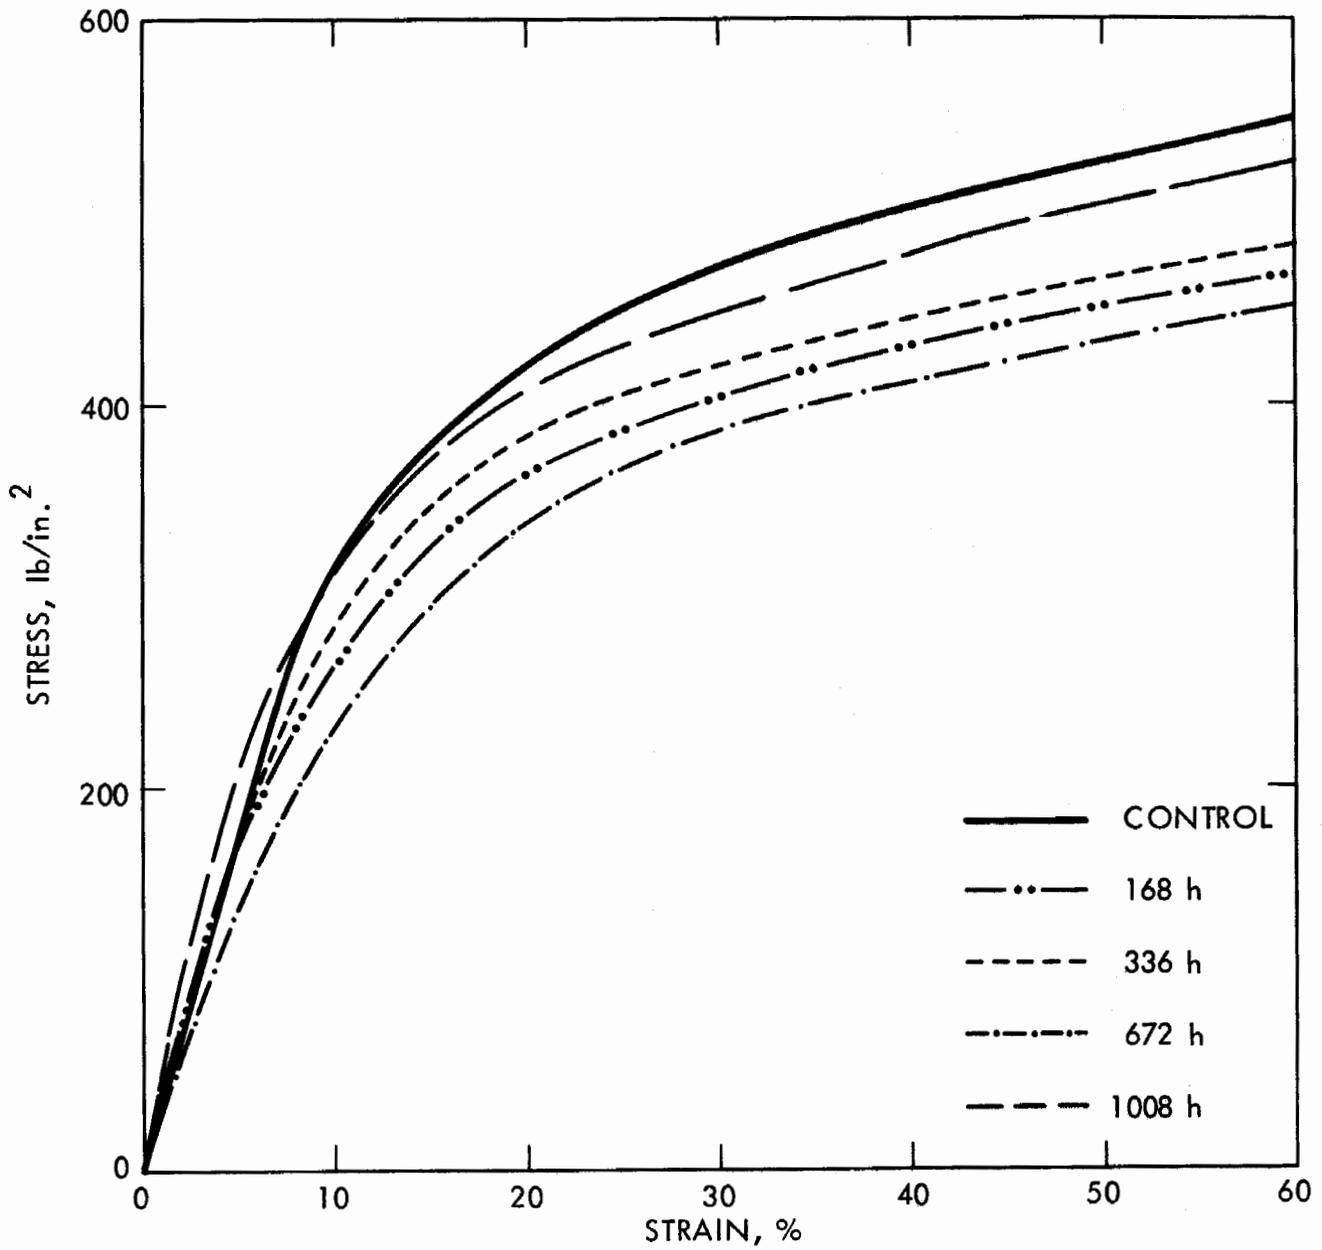


Figure 65. Change in Stress/Strain Response as a Function of Thermal Aging of EMA at 135°C

Table 19. Modulus at 5% Strain as a Function of Covered Photothermal Aging of EMA at 30°C and 135°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, LB/in. <sup>2</sup> 5% STRAIN |
|-----------------|------------------|--|
| ROOM TEMP. (30) | 0                | 3548                                   |
| 135             | 168              | 3016                                   |
|                 | 336              | 2871                                   |
|                 | 672              | 2552                                   |

Table 20. Modulus at 5% Strain as a Function of Thermal Aging of EMA at 30°C and 135°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |
|-----------------|------------------|--|
| ROOM TEMP. (30) | 0                | 3548                                   |
| 135 *           | 168              | 3398                                   |
|                 | 336              | 3530                                   |
|                 | 672              | 2736                                   |
|                 | 1008             | 4231                                   |

\* IN A COVERED CONFIGURATION (SANDWICH)

B. WEIGHT LOSS

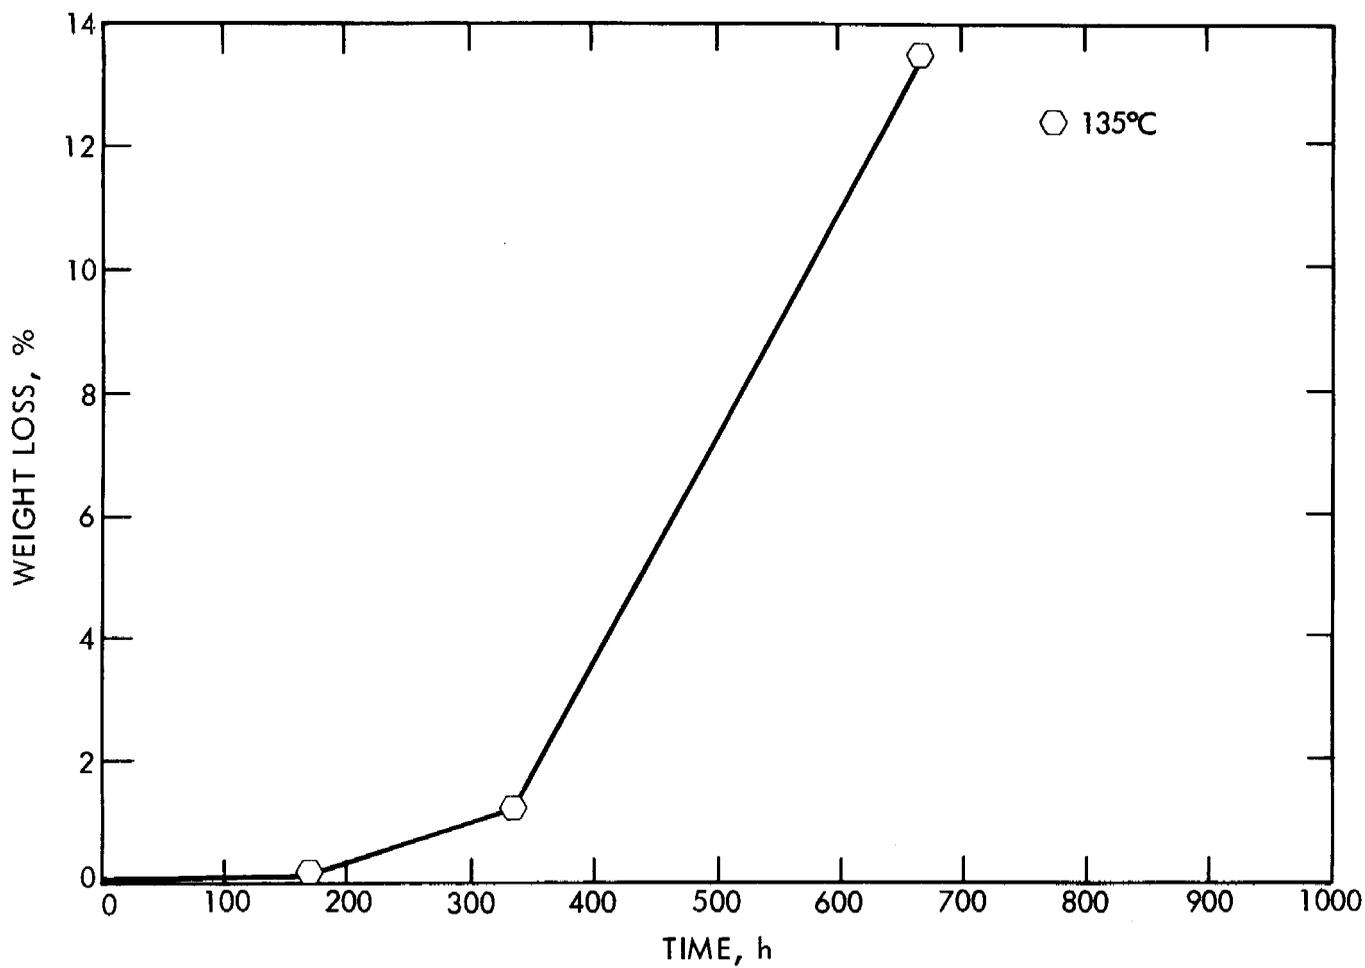


Figure 66. Weight Loss as a Function of Open Photothermal Aging of EMA at 135°C

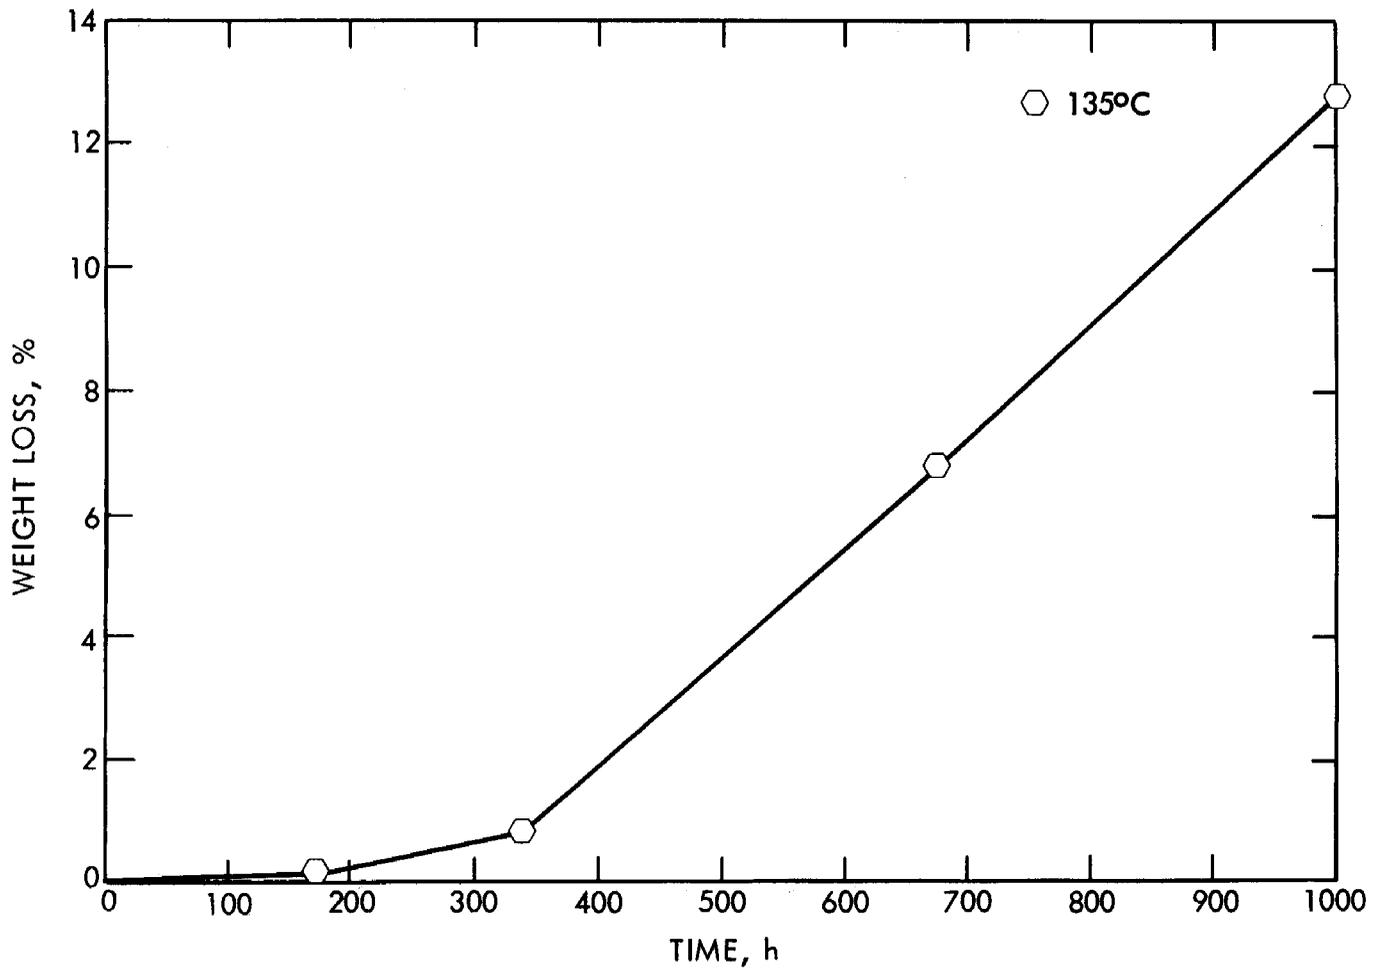


Figure 67. Weight Loss as a Function of Covered Photothermal Aging of EMA at 135°C

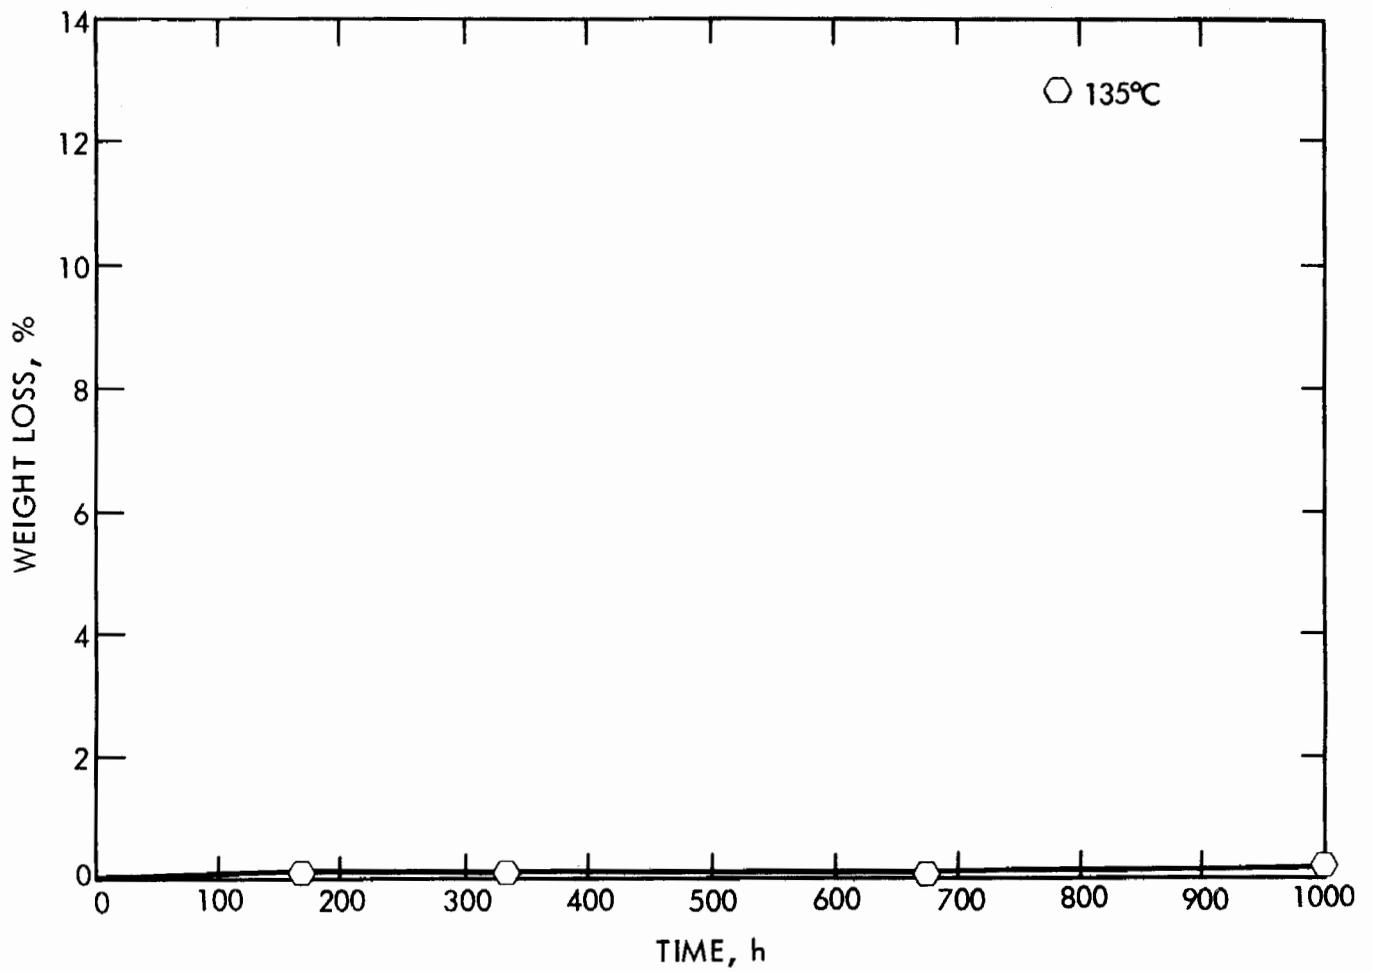


Figure 68. Weight Loss as a Function of Thermal Aging of EMA at 135°C in a Covered (Sandwich) Configuration

C. OTHER PROPERTIES

Table 21. Sol/Gel and Molecular Weight Data as a Function of Open Photothermal Aging of EMA at 30°C and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, % | GEL, % |
|-------|------------------|---|--------|--------|
| 30    | 0                | $2.0 \times 10^{-4}$                      | 15     | 85     |
| 135   | 84               | $3.5 \times 10^{-4}$                      | 10     | 90     |
|       | 168              | $3.42 \times 10^{-4}$                     | 11     | 89     |
|       | 336              | $3.55 \times 10^{-4}$                     | 12     | 88     |
|       | 672              | $2.77 \times 10^{-4}$                     | 18     | 82     |

Table 22. Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of EMA at 30°C and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, % | GEL, % |
|-------|------------------|---|--------|--------|
| 30    | 0                | $2.0 \times 10^{-4}$                      | 15     | 85     |
| 135   | 168              | $1.0 \times 10^{-4}$                      | 22     | 78     |
|       | 336              | $0.8 \times 10^{-4}$                      | 26     | 74     |
|       | 672              | $1.0 \times 10^{-4}$                      | 32     | 68     |
|       | 1008             | $2.3 \times 10^{-4}$                      | 20     | 80     |

Table 23. Sol/Gel and Molecular Weight Data as a Function of Thermal Aging of EMA at 30°C and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, % | GEL, % |
|-------|------------------|---|--------|--------|
| 30    | 0                | $2.0 \times 10^{-4}$                      | 15     | 85     |
| 135 * | 168              | $3.61 \times 10^{-4}$                     | 10     | 90     |
|       | 336              | $3.53 \times 10^{-4}$                     | 10     | 90     |
|       | 672              | $3.74 \times 10^{-4}$                     | 10     | 90     |
|       | 1008             | $3.63 \times 10^{-4}$                     | 11     | 89     |

\* IN A CLOSED (SANDWICH) CONFIGURATION

## SECTION VI

### PnBA (SPRINGBORN A-13870)

The following figures and tables offer data on mechanical properties (Figures 69 through 71, Tables 24 through 26); weight loss (Figures 72 and 73); other properties (Tables 27 through 29) of PnBA (Springborn A-13870).

A. MECHANICAL PROPERTIES

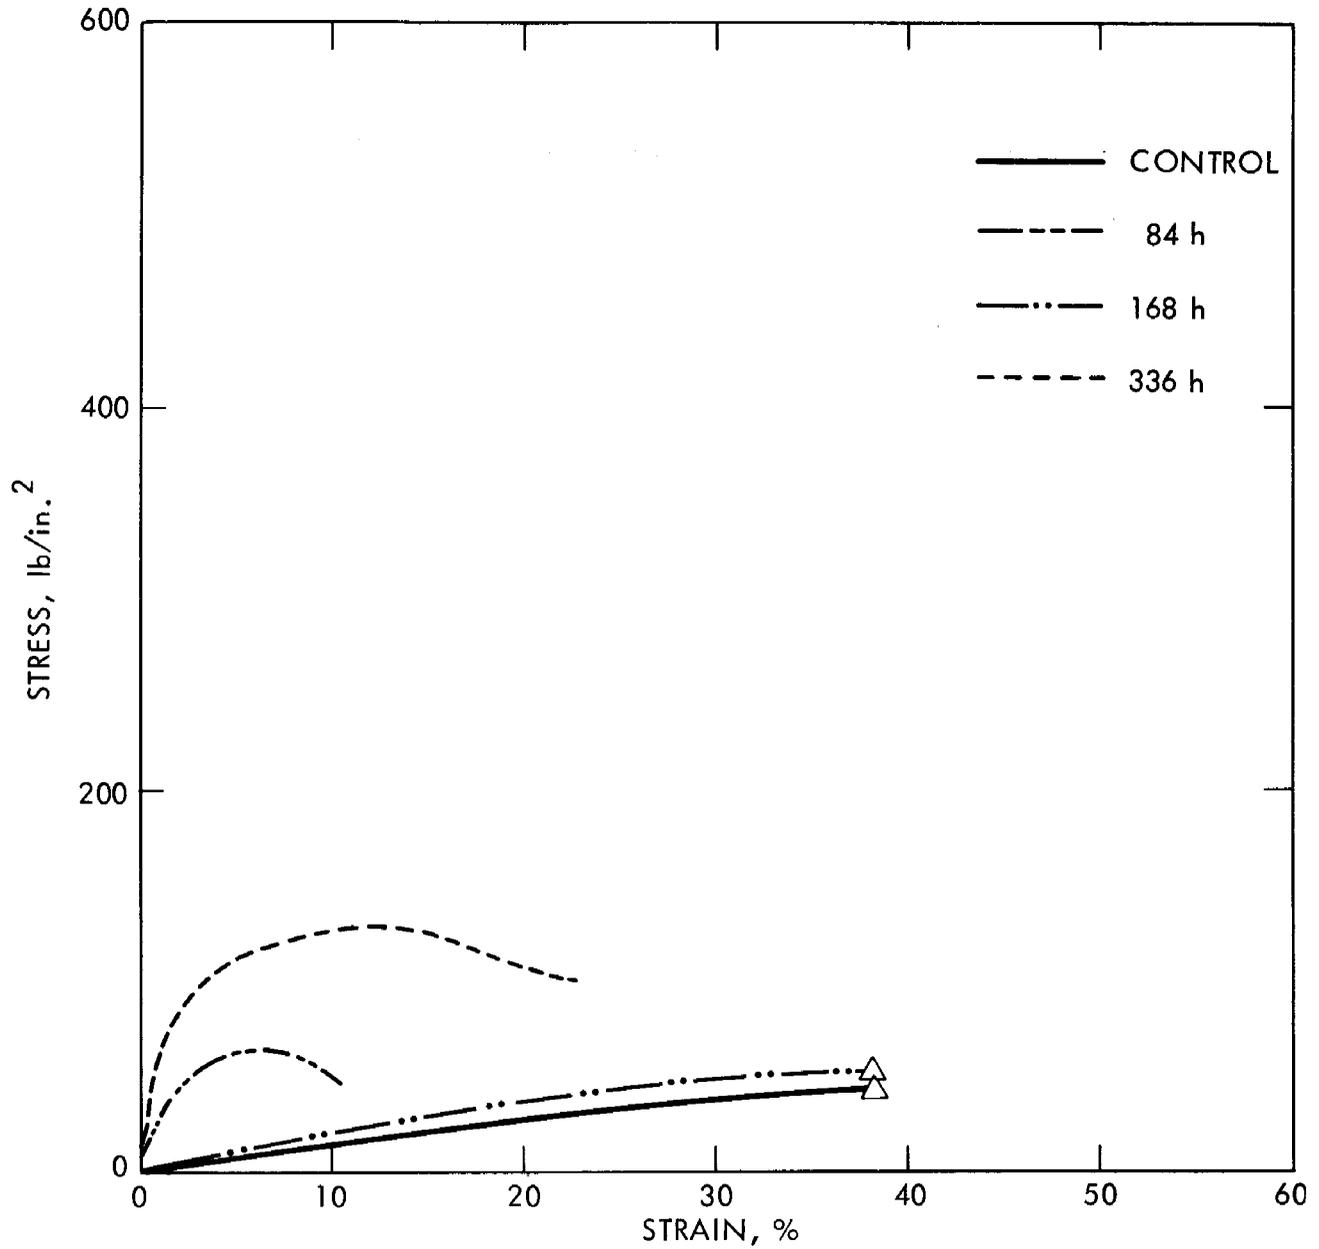


Figure 69. Change in Stress/Strain Response as a Function of Open Photothermal Aging of PnBA at 135°C

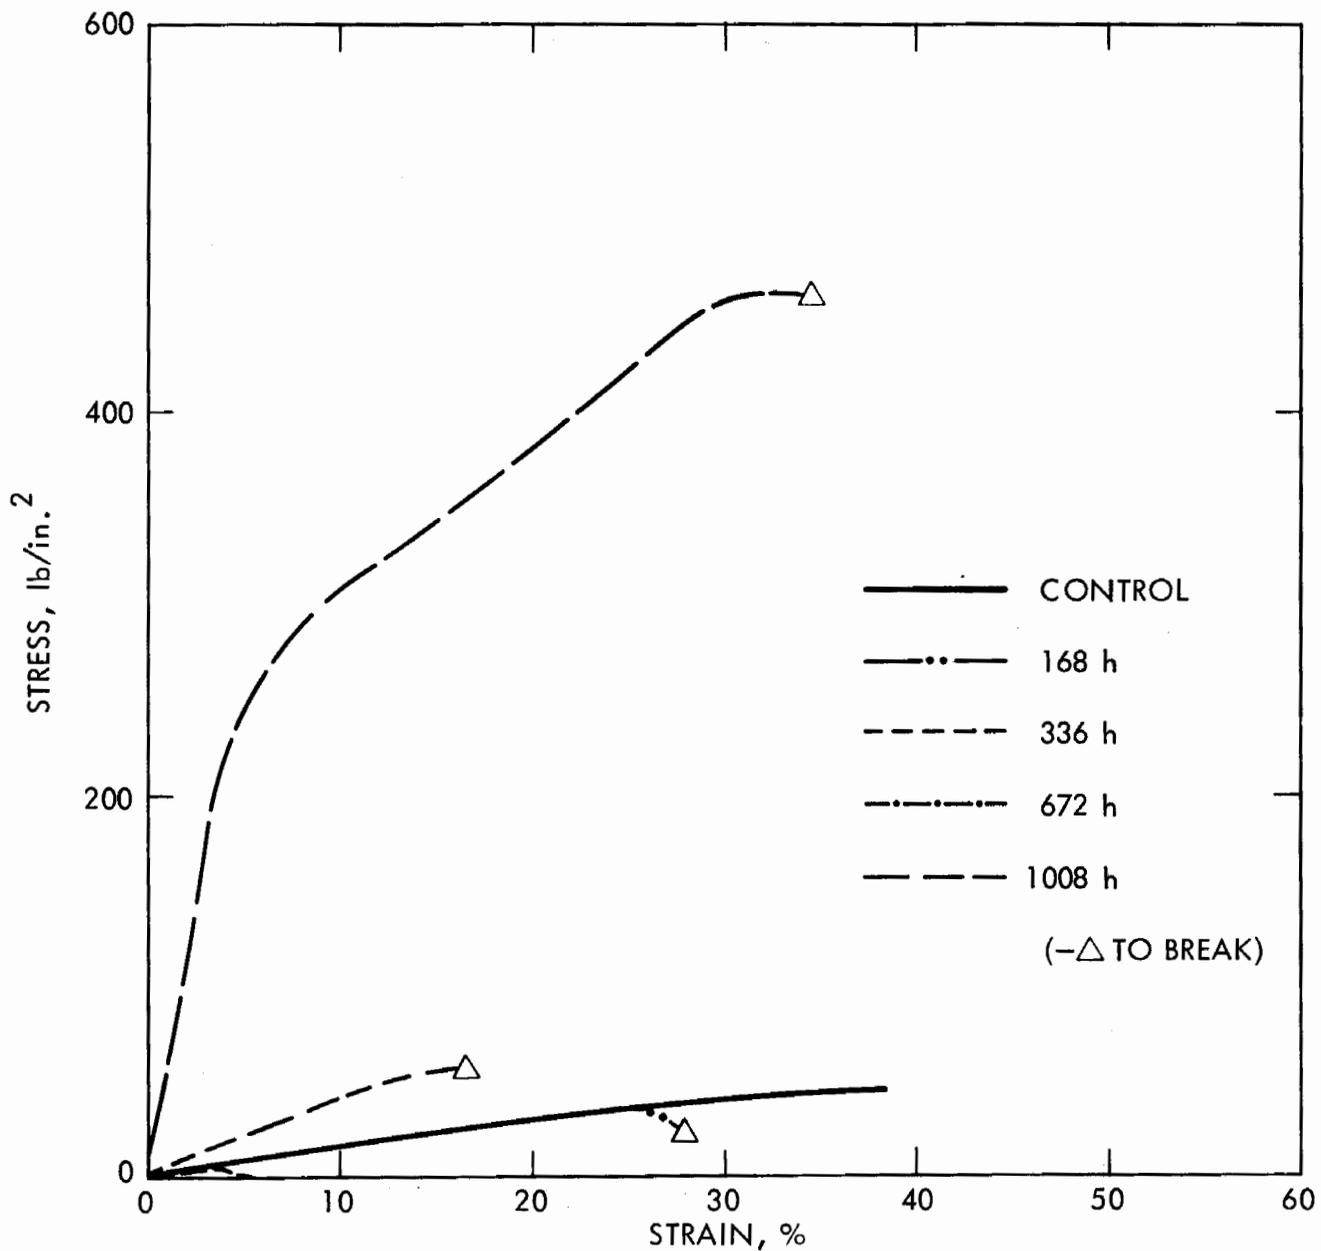


Figure 70. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of PnBA at 135°C

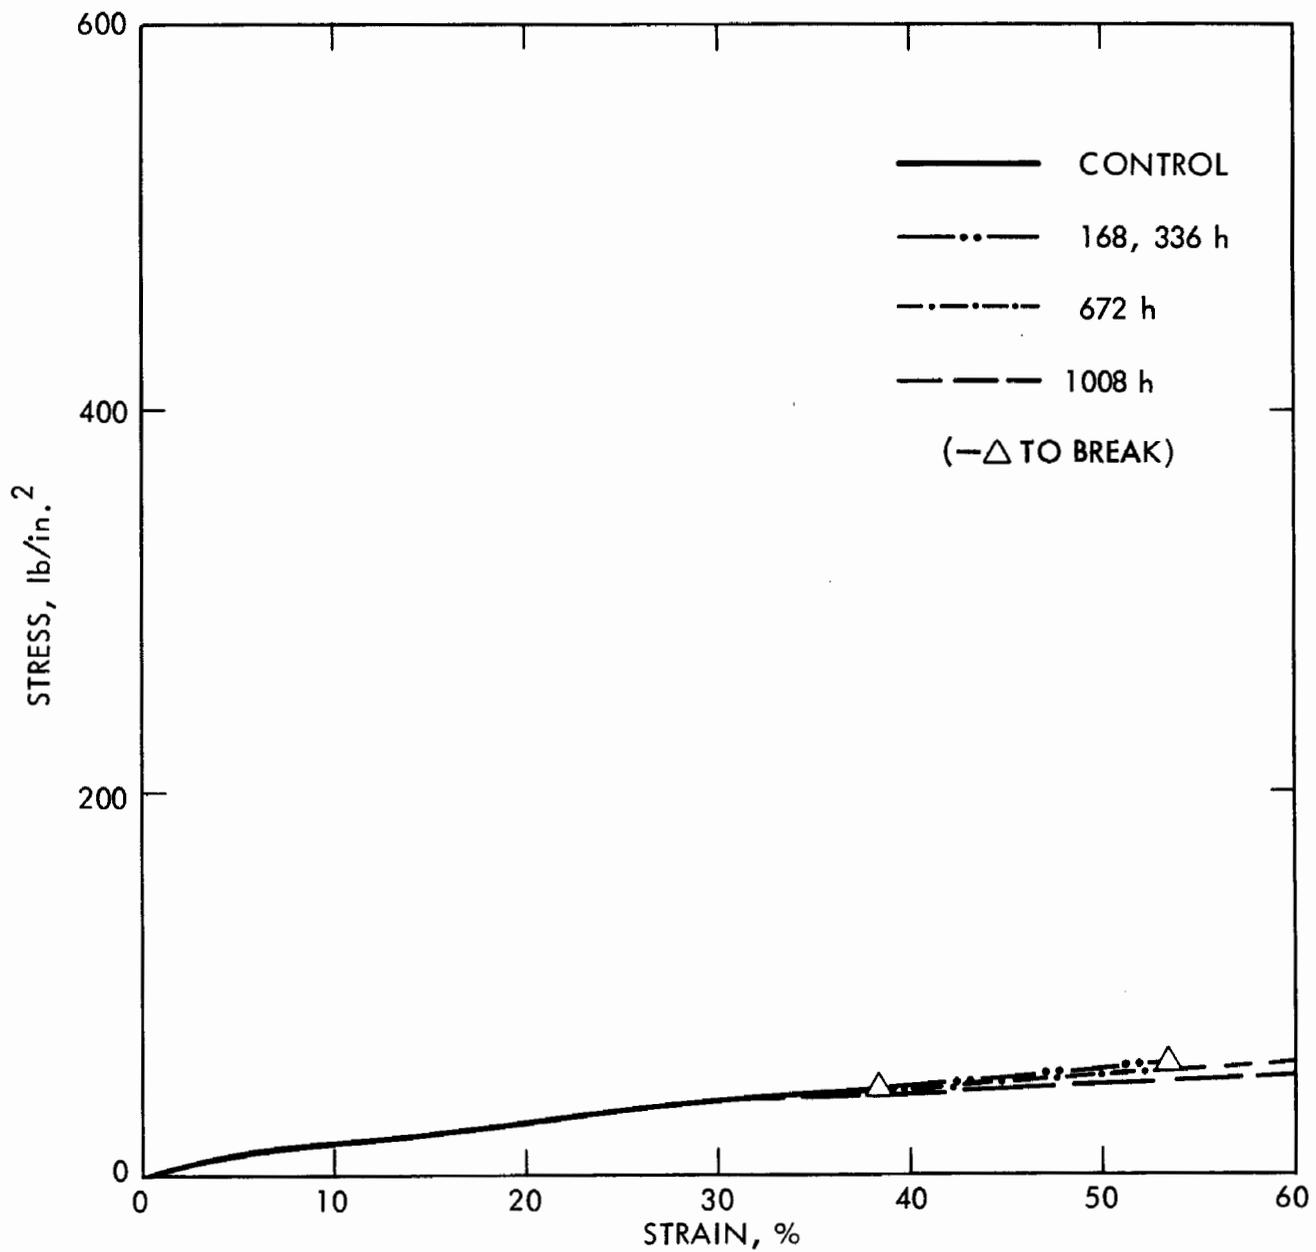


Figure 71. Change in Stress/Strain Response as a Function of Thermal Aging of PnBA at 135°C

Table 24. Modulus at 5% Strain as a Function of Open  
Photothermal Aging of PnBA at 30°C and 135°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |
|-----------------|------------------|--|
| ROOM TEMP. (30) | 0                | 175                                    |
| 135             | 84<br>168<br>336 | 281<br>1250<br>2175                    |

Table 25. Modulus at 5% Strain as a Function of Covered Photothermal Aging of PnBA at 30°C and 135°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |
|-----------------|------------------|--|
| ROOM TEMP. (30) | 0                | 175                                    |
| 135             | 168              | 155                                    |
|                 | 336              | 4915                                   |
|                 | 672              | 450                                    |
|                 | 1008             | 350                                    |

Table 26. Modulus at 5% Strain as a Function of Thermal Aging of PnBA at 30°C and 135°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |
|-----------------|------------------|--|
| ROOM TEMP. (30) | 0                | 175                                    |
| 135 *           | 168              | 169                                    |
|                 | 336              | 174                                    |
|                 | 672              | 181                                    |
|                 | 1008             | 171                                    |

\* IN A COVERED (SANDWICH) CONFIGURATION

B. WEIGHT LOSS

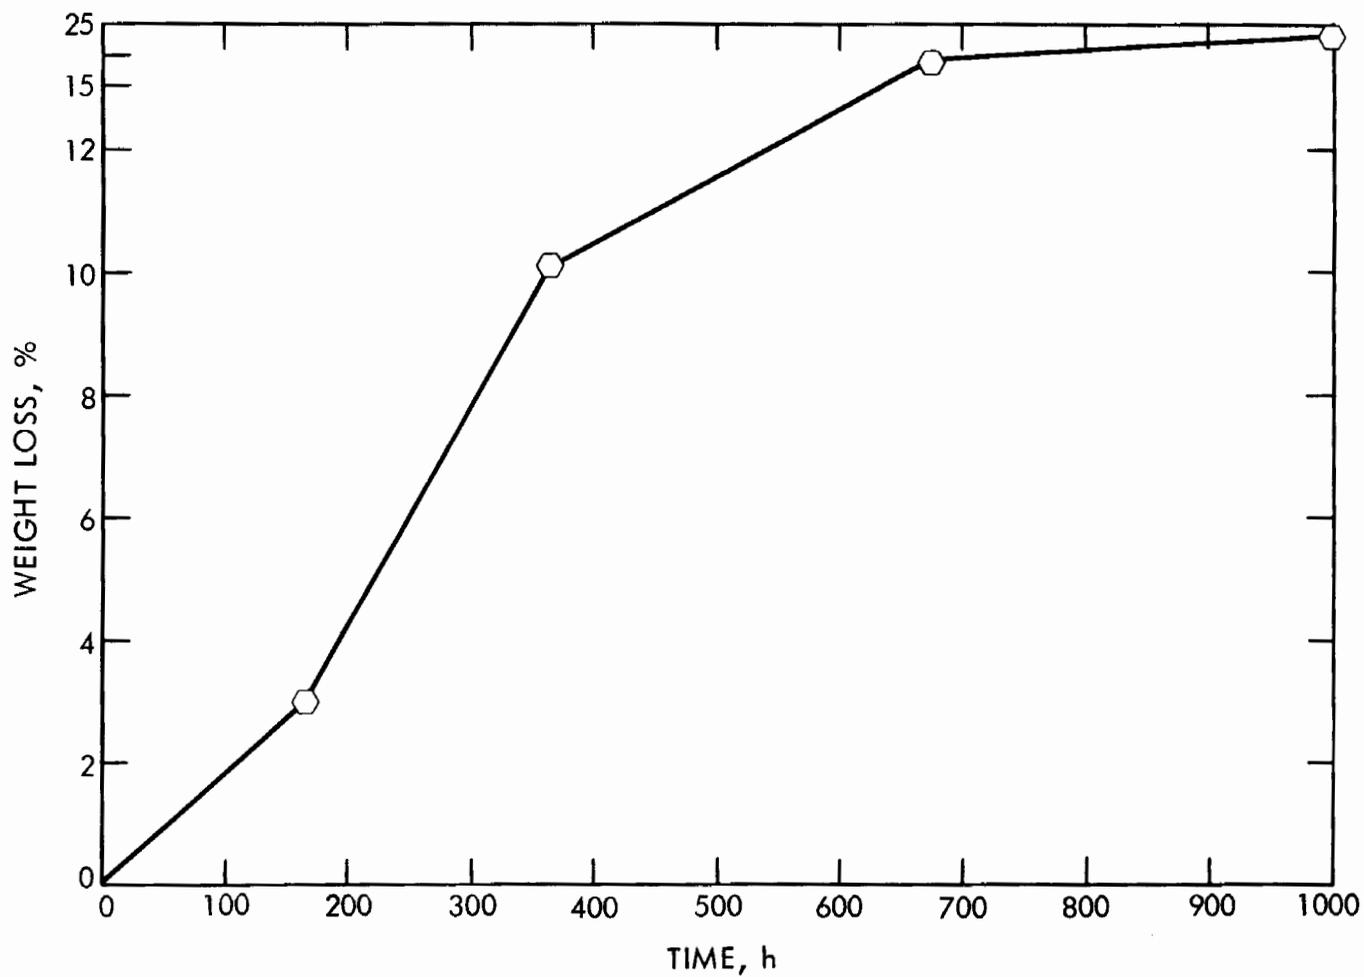


Figure 72. Weight Loss as a Function of Covered Photothermal Aging of PnBA at 135°C

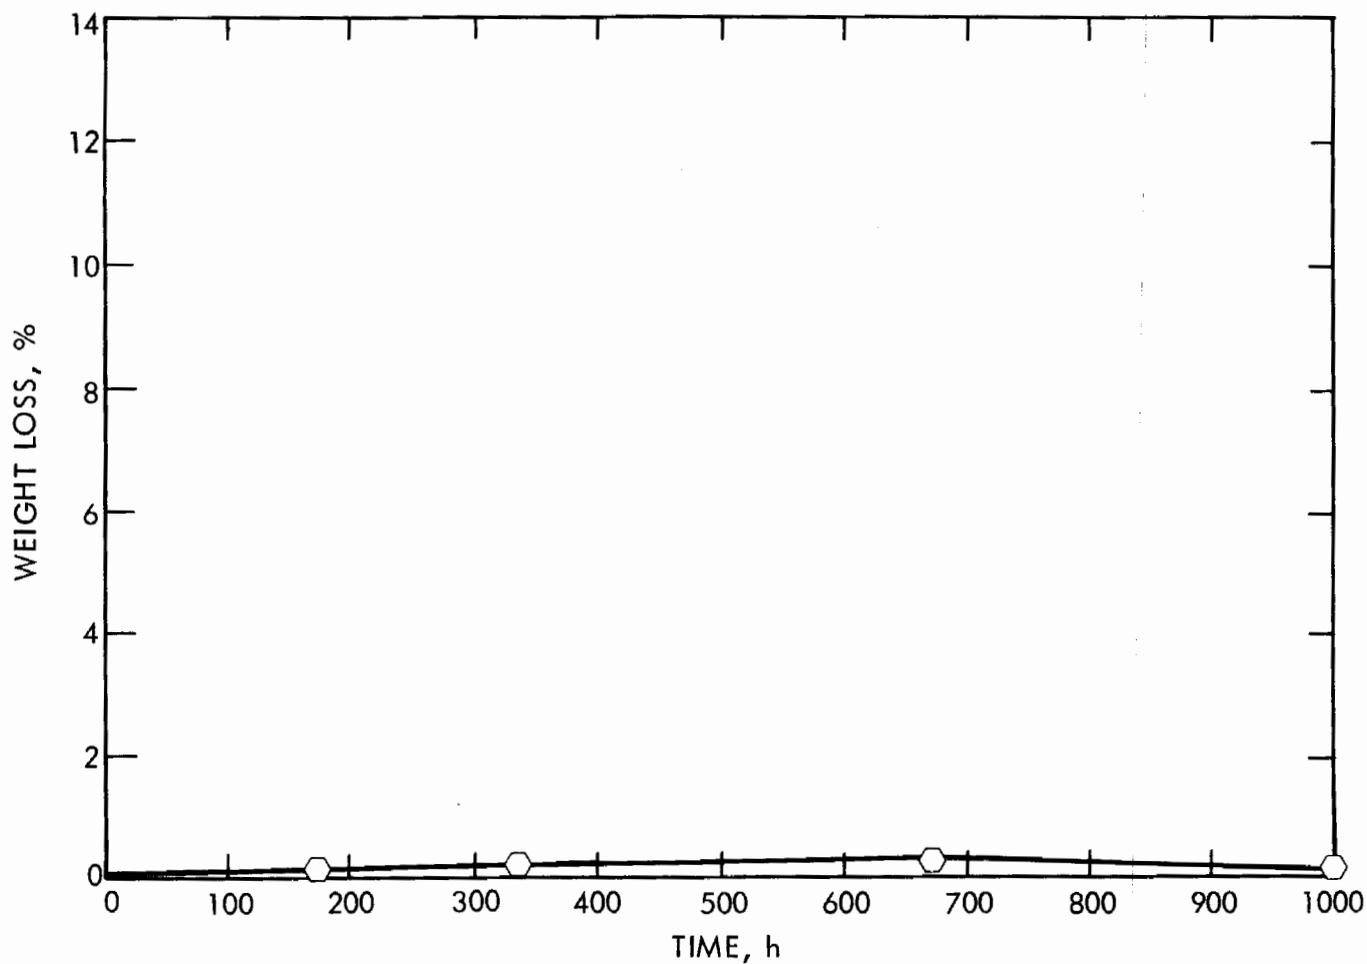


Figure 73. Weight Loss as a Function of Thermal Aging of PnBA at 135°C in a Covered (Sandwich) Configuration

OTHER PROPERTIES

Table 27. Sol/Gel and Molecular Weight Data as a Function of Open Photothermal Aging of PnBA at 30°C and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, % | GEL, % |
|-------|------------------|---|--------|--------|
| 30    | 0                | $4.34 \times 10^{-4}$                     | 15     | 85     |
| 135   | 84               | $6.61 \times 10^{-4}$                     | 6      | 94     |
|       | 168              | $7.69 \times 10^{-4}$                     | 6      | 94     |
|       | 336              | $8.14 \times 10^{-4}$                     | 5      | 95     |
|       | 672              | $9.83 \times 10^{-4}$                     | 3      | 97     |

Table 28. Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of PnBA at 30°C and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, % | GEL, % |
|-------|------------------|---|--------|--------|
|       | 0                | 4.34 x 10 <sup>-4</sup>                   | 15     | 85     |
| 135   | 168              | 4.79 x 10 <sup>-4</sup>                   | 11     | 89     |
|       | 336              | 27.12 x 10 <sup>-4</sup>                  | 1      | 99     |
|       | 672              | 7.08 x 10 <sup>-4</sup>                   | 6      | 94     |
|       | 1008             | 14.13 x 10 <sup>-4</sup>                  | 6      | 94     |

Table 29. Sol/Gel and Molecular Weight Data as a Function of Thermal Aging of PnBA at 30°C and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> | SOL, % | GEL, % |
|-------|------------------|---|--------|--------|
| 30    | 0                | $4.34 \times 10^{-4}$                     | 15     | 85     |
| 135*  | 168              | $4.28 \times 10^{-4}$                     | 16     | 84     |
|       | 336              | $4.29 \times 10^{-4}$                     | 16     | 84     |
|       | 672              | $4.18 \times 10^{-4}$                     | 16     | 84     |
|       | 1008             | $4.37 \times 10^{-4}$                     | 15     | 85     |

\* IN A CLOSED (SANDWICH) CONFIGURATION

## SECTION VII

### POLYURETHANE (H.J. QUINN -- DEVELOPMENT ASSOCIATES Z-2591)

The following figures and tables offer data on optical transmittance (Figures 74 through 76); mechanical properties (Figures 77 through 80, Tables 30 through 32); weight loss (Figures 81 through 83); other properties (Tables 33 through 35) of polyurethane (H.J. Quinn Co. -- Development Associates Z-2591).

A. OPTICAL TRANSMITTANCE

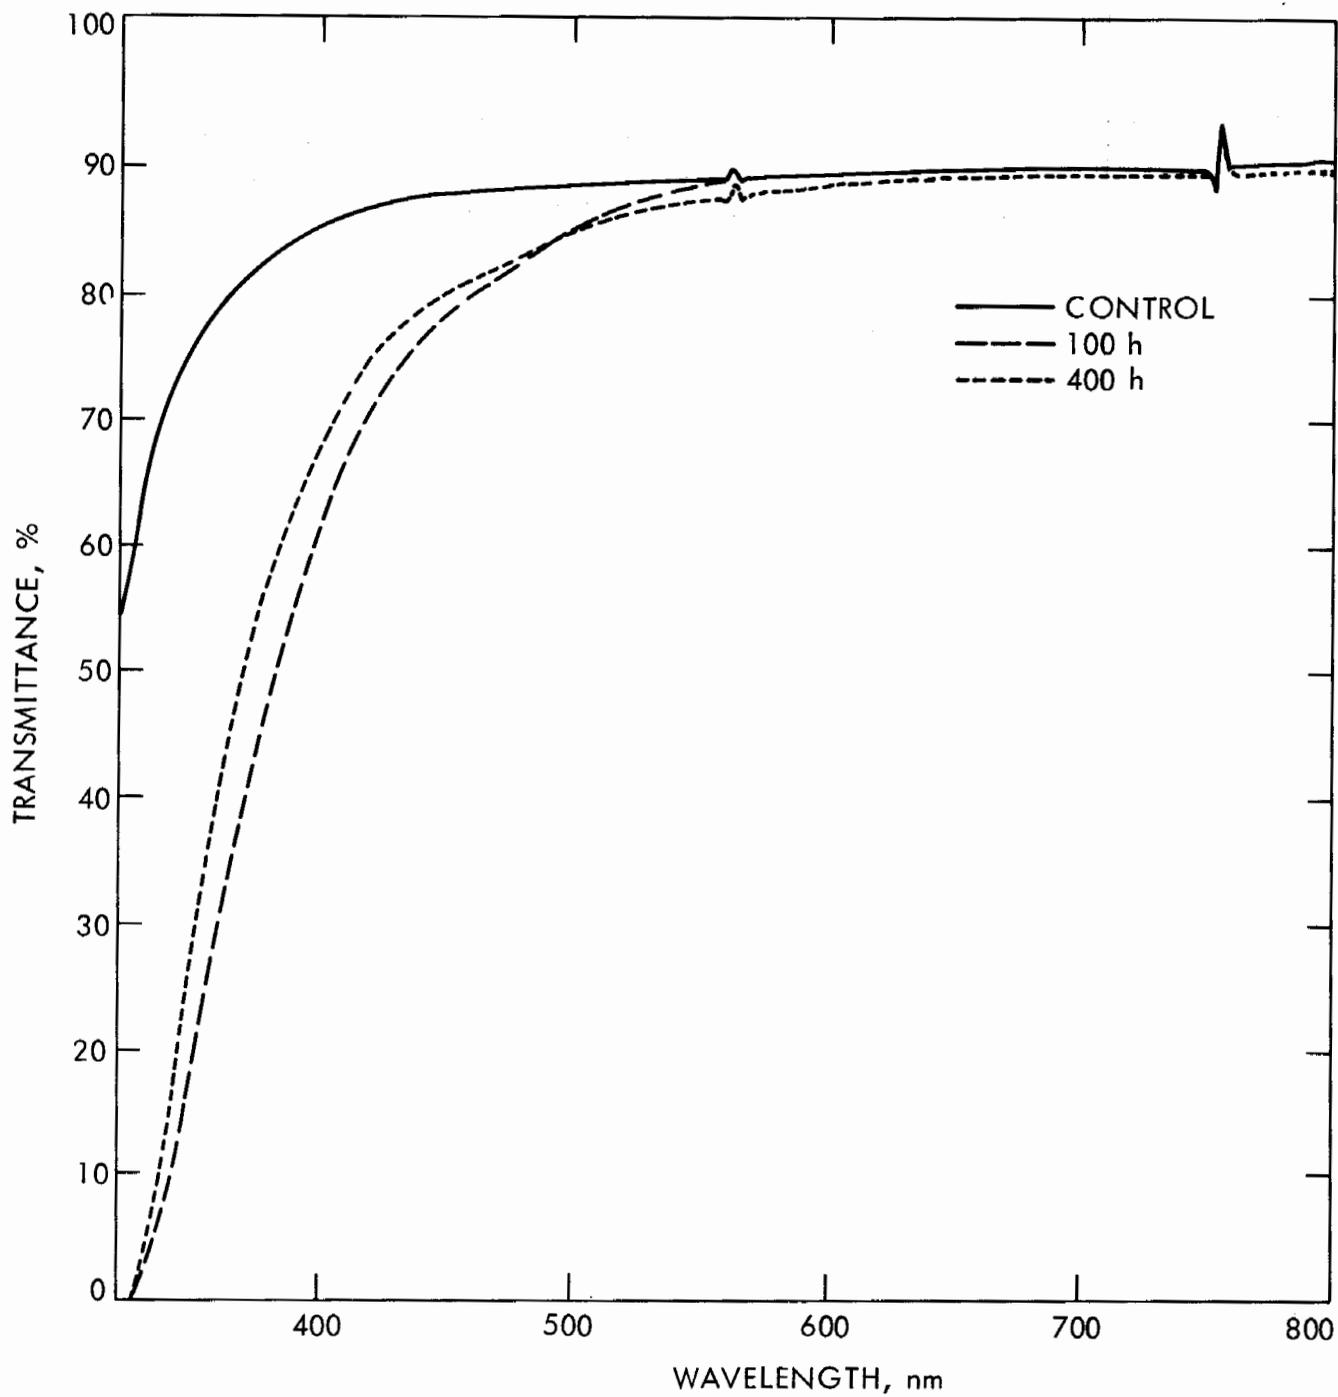


Figure 74. Change in Optical Transmittance as a Function of Open Photothermal Aging of Polyurethane at 70°C

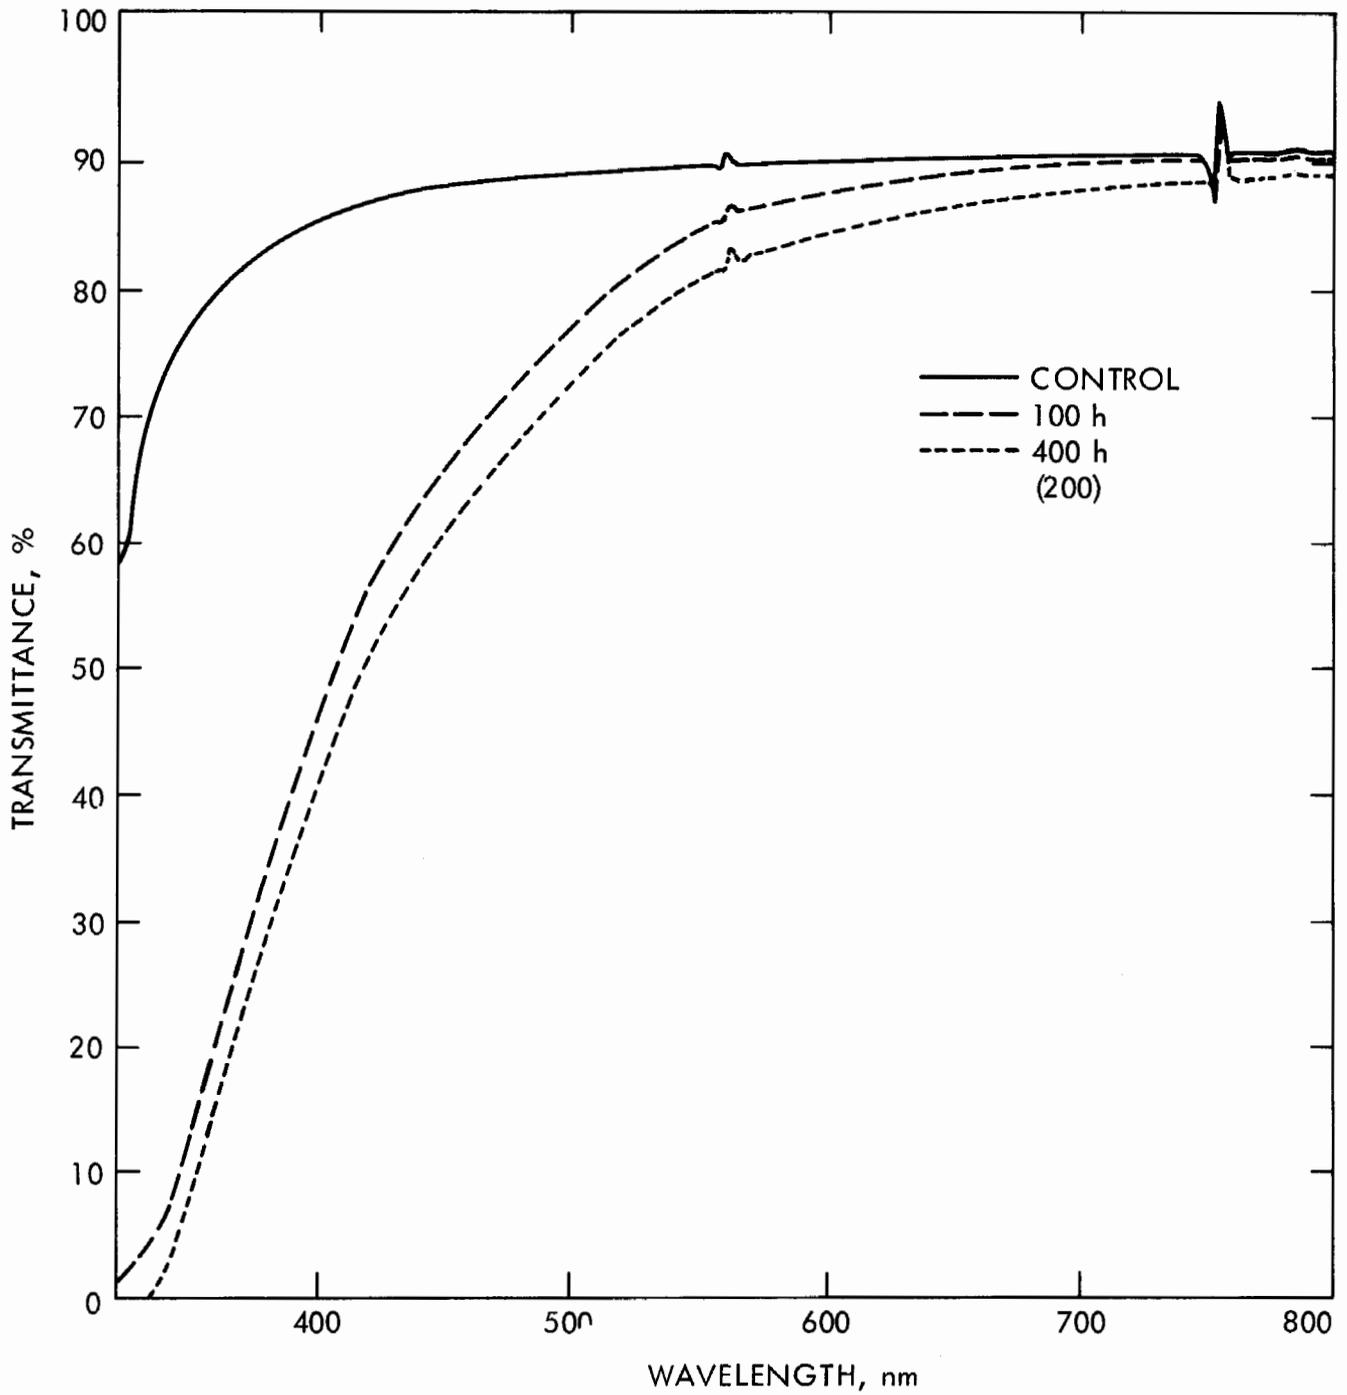


Figure 75. Change in Optical Transmittance as a Function of Covered Photothermal Aging of Polyurethane at 70°C

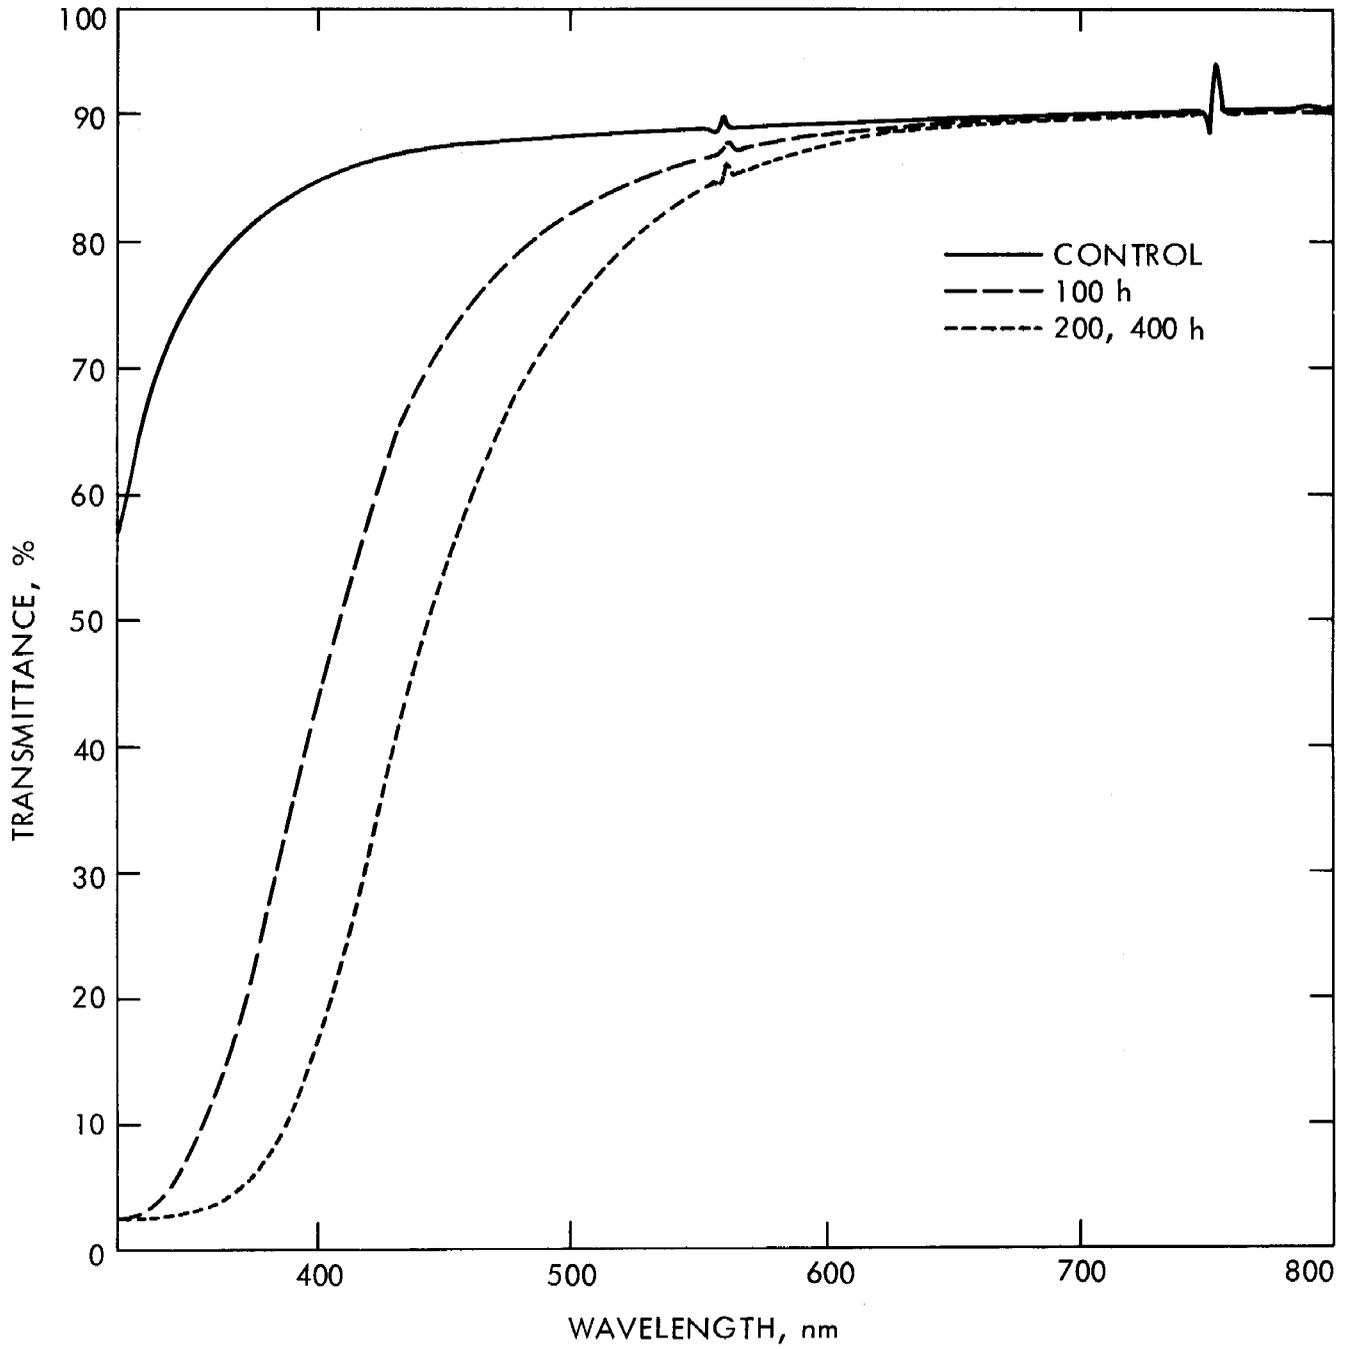


Figure 76. Change in Optical Transmittance as a Function of Thermal Aging of Polyurethane at 70°C

B. MECHANICAL PROPERTIES

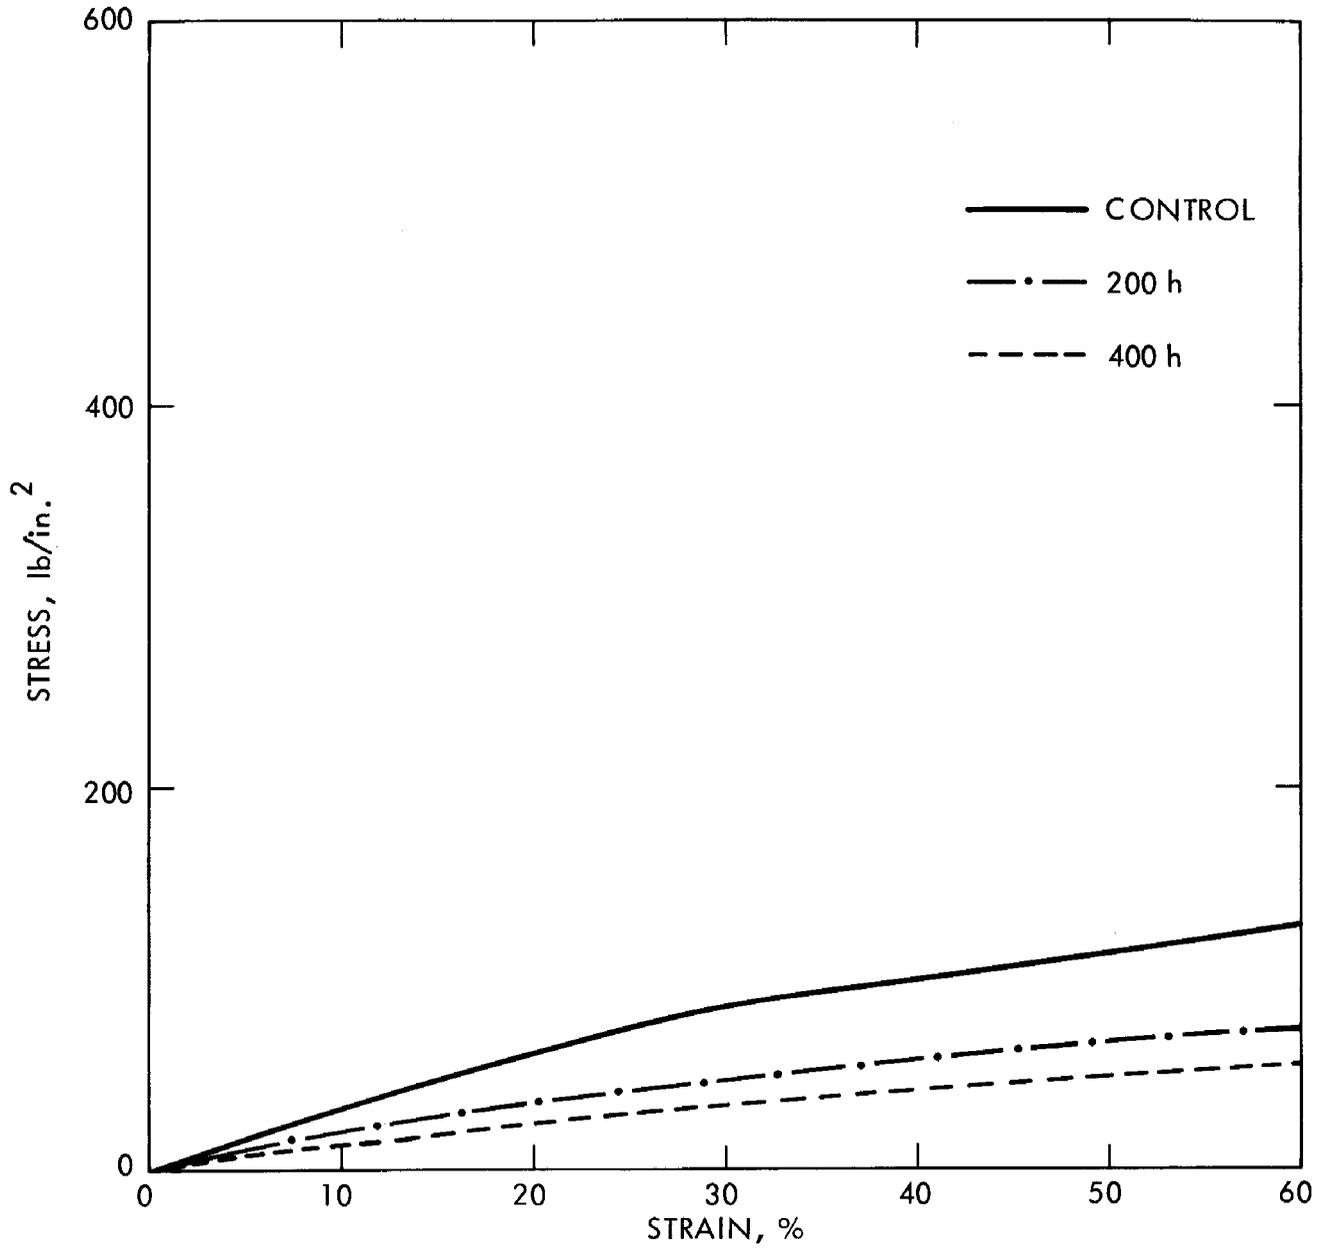


Figure 77. Change in Stress/Strain Response as a Function of Open Photothermal Aging of Polyurethane at 70°C

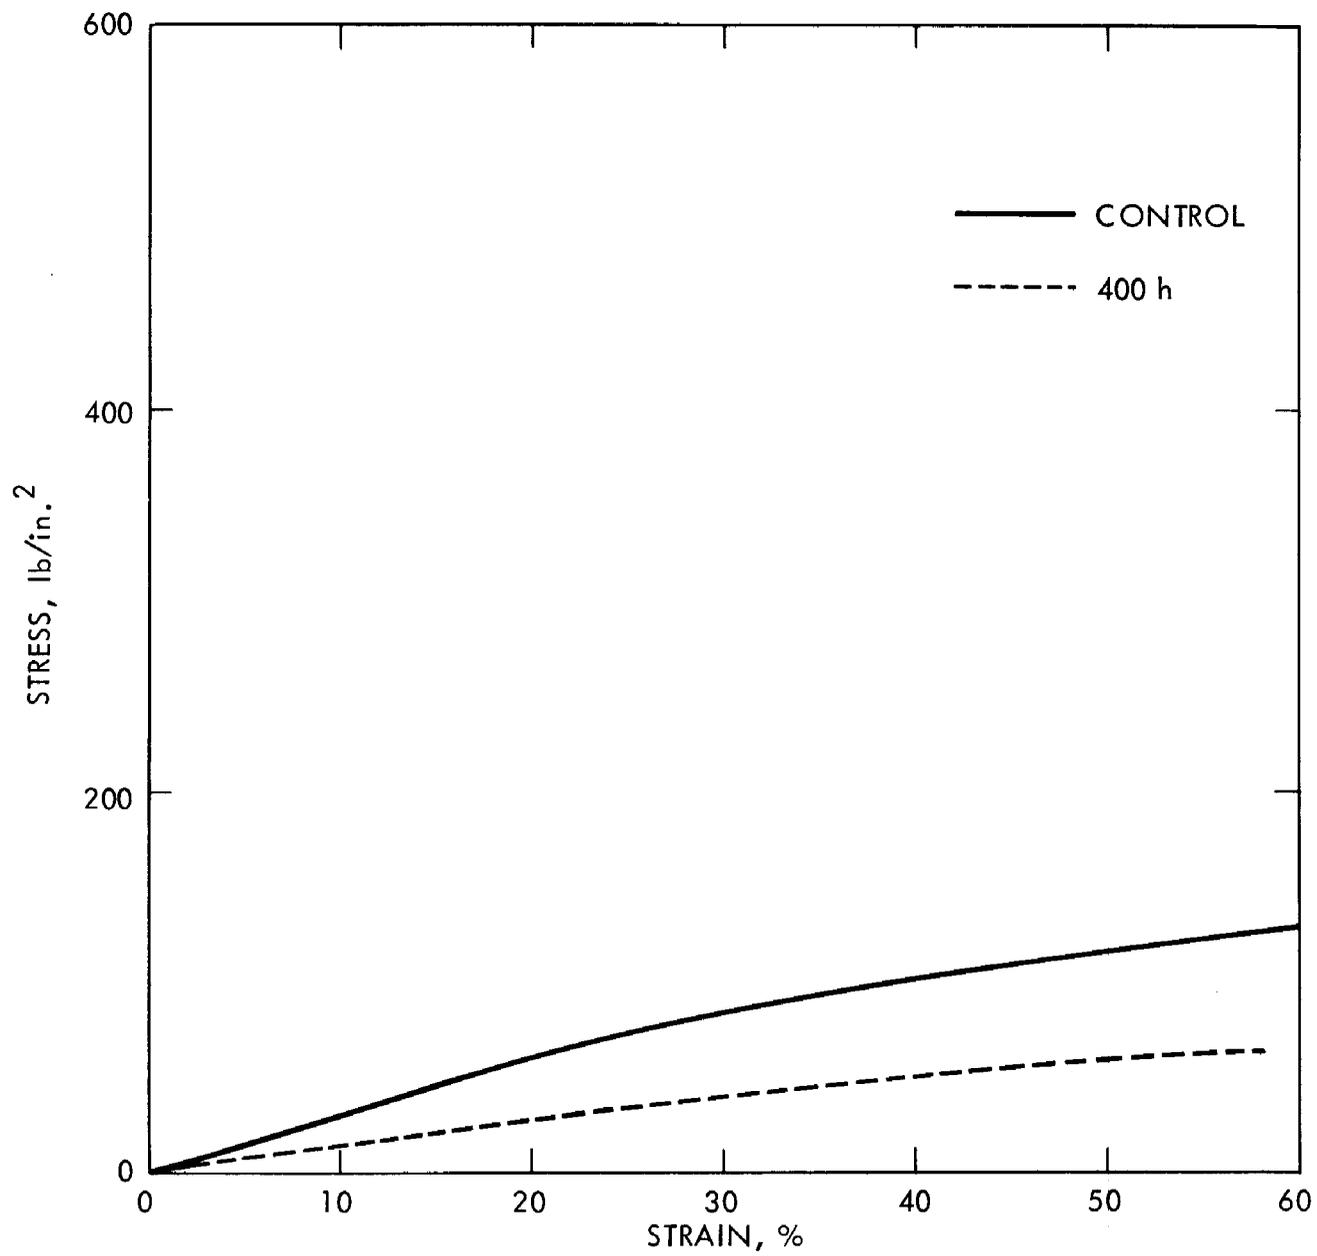


Figure 78. Change in Stress/Strain Response as a Function of Covered Photothermal Aging of Polyurethane at 70°C


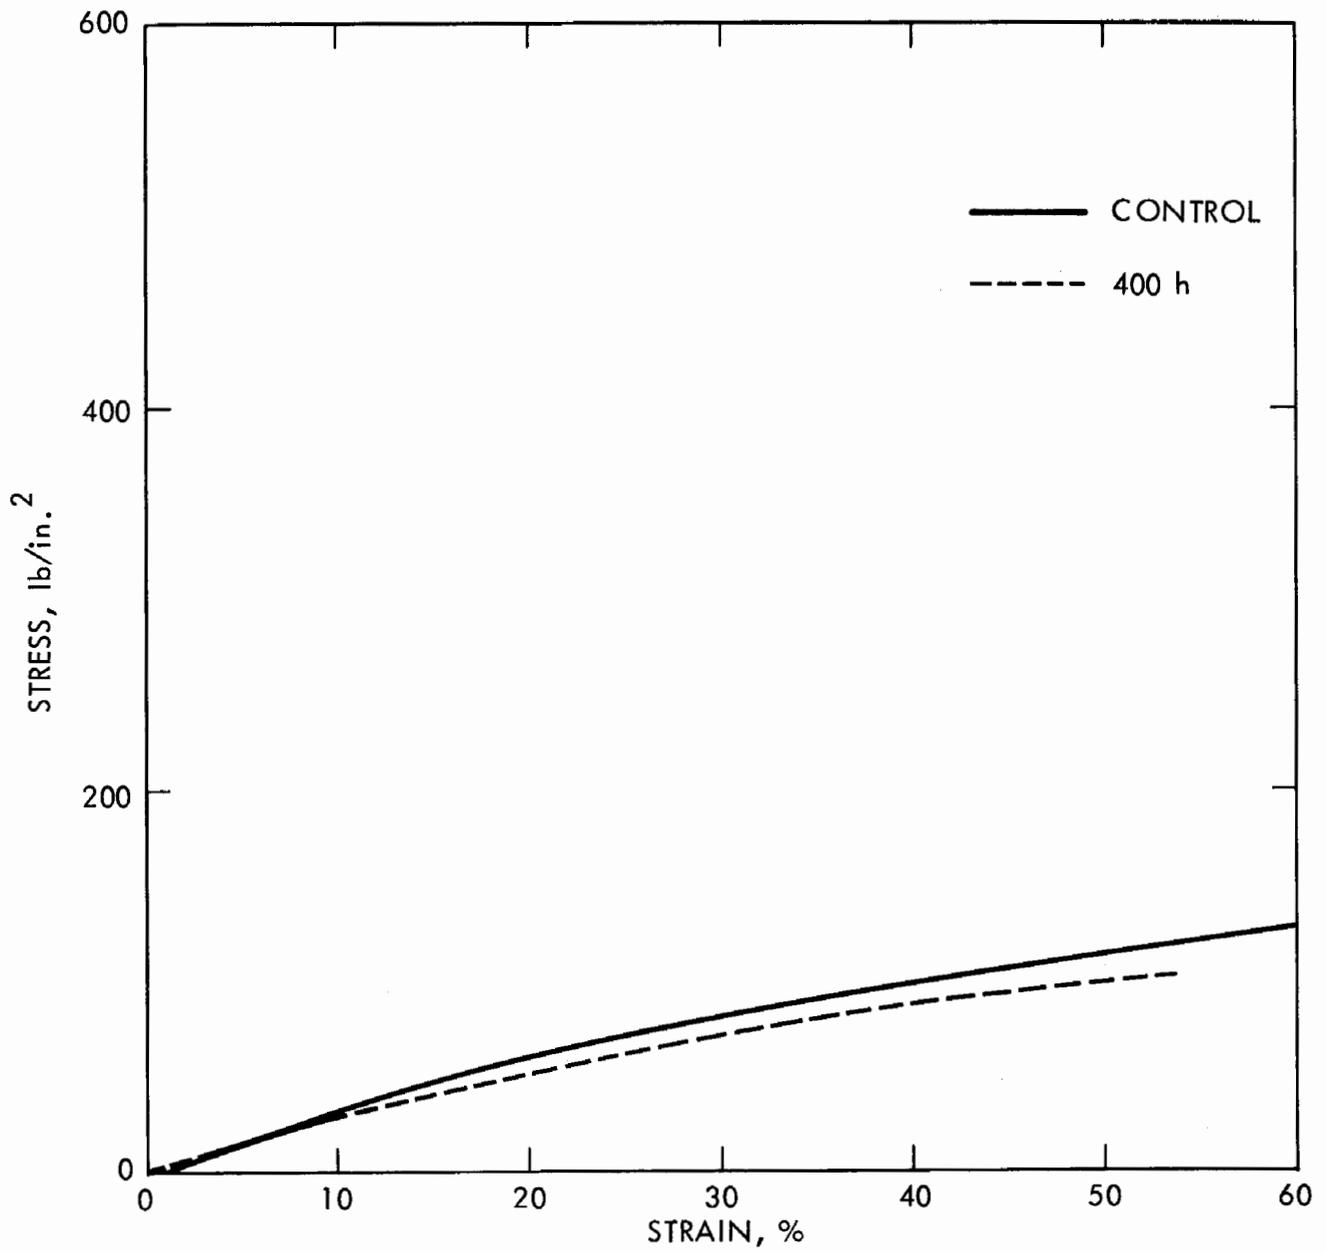


Figure 79. Change in Stress/Strain Response as a Function of Thermal Aging of Polyurethane at 70°C

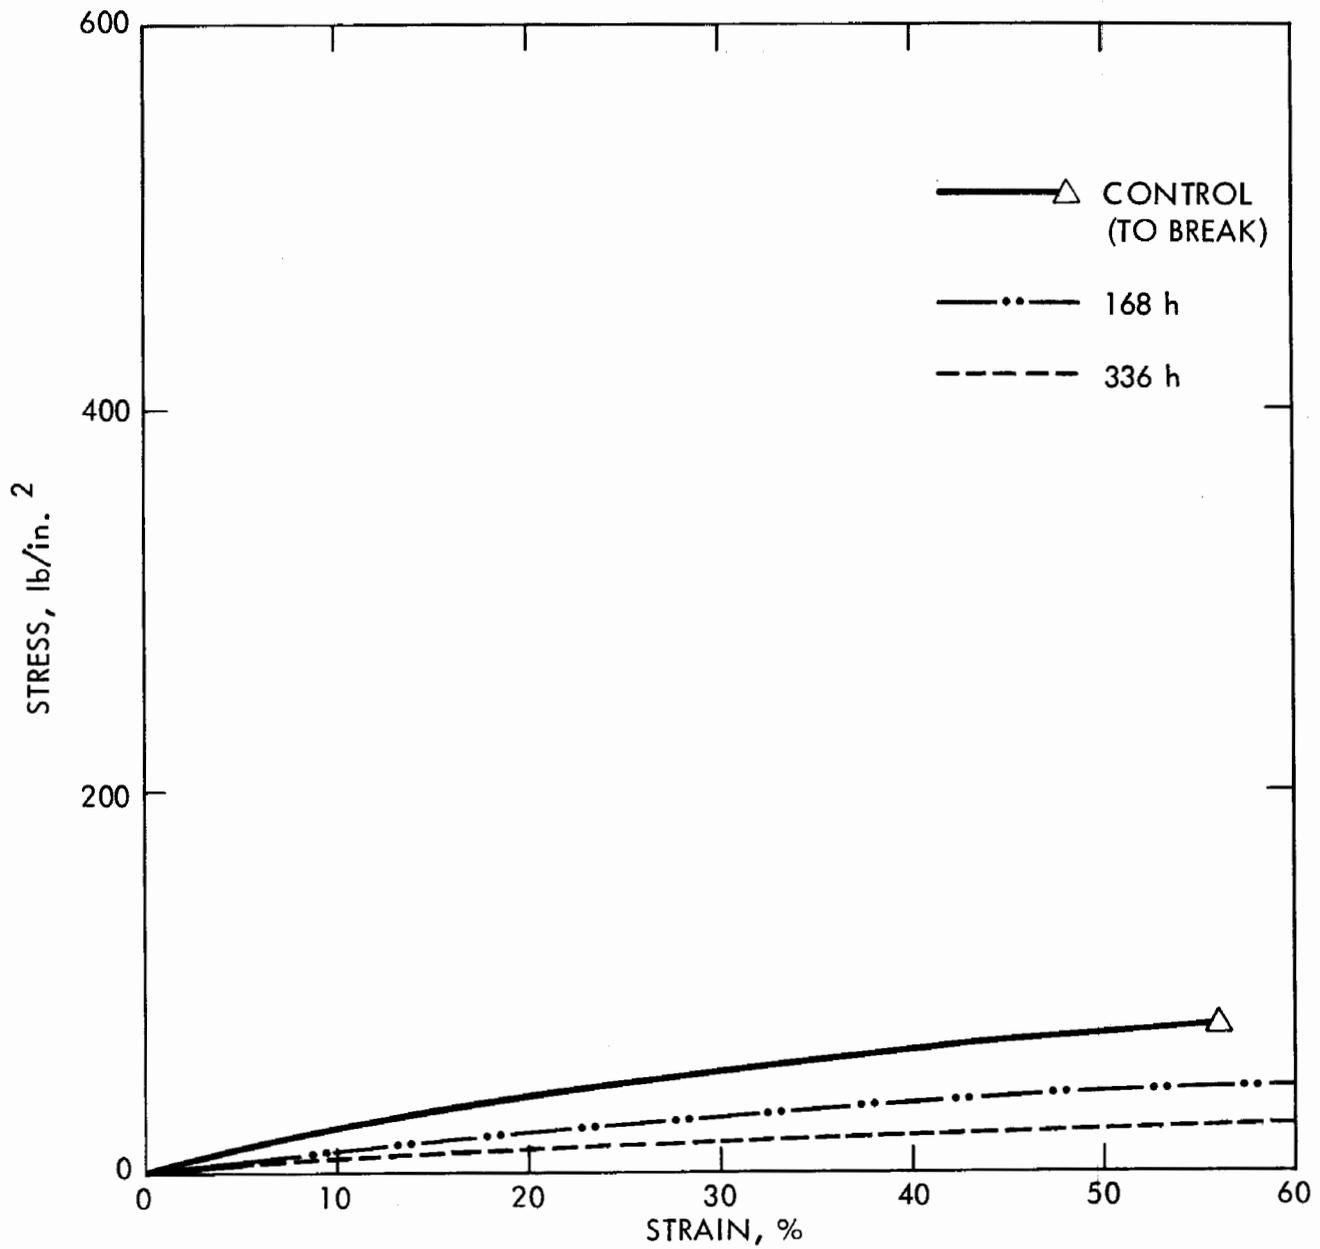

\* IN A CLOSED (SANDWICH) CONFIGURATION

Figure 80. Change in Stress/Strain Response as a Function of Thermal Aging of Polyurethane at 135°C in a Closed (Sandwich) Configuration

Table 30. Modulus at 5% Strain as a Function of Open Photothermal Aging of Polyurethane at 30°C and 70°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |
|-----------------|------------------|--|
| ROOM TEMP. (30) | 0                | 380                                    |
| 70*             | 200              | 205                                    |
|                 | 400              | 118                                    |

\* PU (QUINN)

Table 31. Modulus at 5% Strain as a Function of Covered Photothermal Aging of Polyurethane at 30°C and 70°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |
|-----------------|------------------|--|
| ROOM TEMP. (30) | 0                | 380                                    |
| 70*             | 200              | 153                                    |
|                 | 400              | 154                                    |
| 135**           | 168              | 73                                     |
|                 | 336              | FLOW                                   |

\* PU (QUINN)

\*\* PU (DEVELOPMENT ASSOCIATES Z-2591)

Table 32. Modulus at 5% Strain as a Function of Thermal Aging of Polyurethane at 30°C and 70°C

| TEMPERATURE, °C | TIME OF AGING, h | MODULUS, lb/in. <sup>2</sup> 5% STRAIN |
|-----------------|------------------|--|
| ROOM TEMP. (30) | 0                | 380                                    |
| 70*             | 400              | 300                                    |
| 135**♦          | 168<br>336       | 101<br>54                              |

\* PU (QUINN)

\*\* PU (DEVELOPMENT ASSOCIATES Z-2591)

♦ IN A COVERED (SANDWICH) CONFIGURATION

C. WEIGHT LOSS

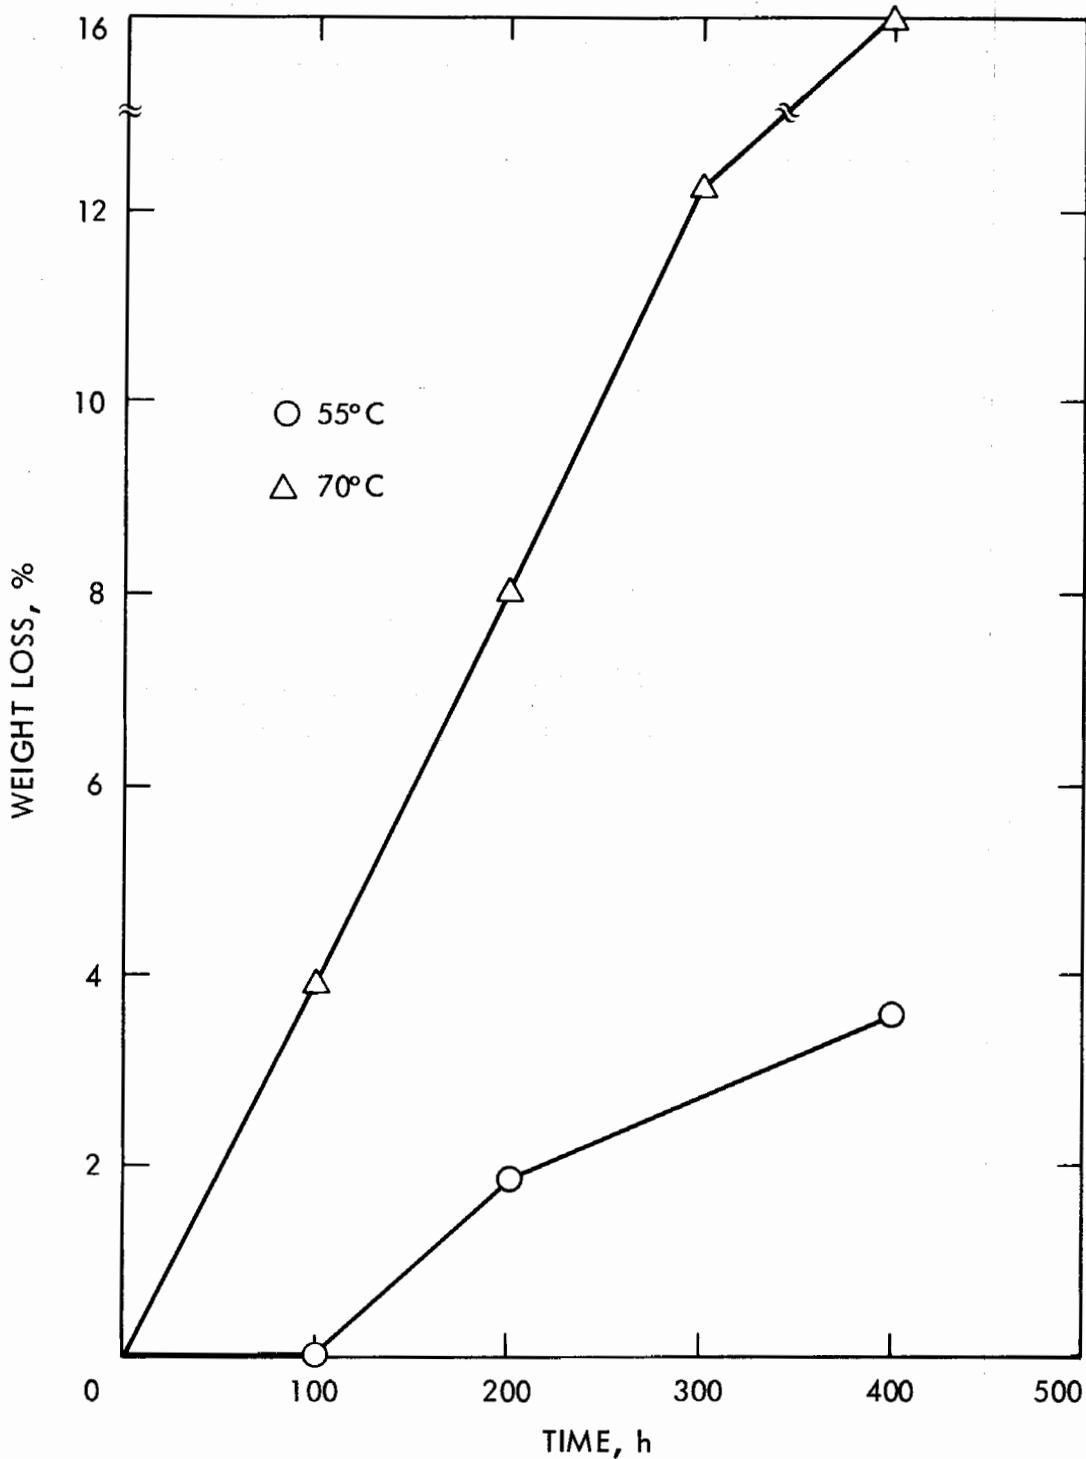


Figure 81. Weight Loss as a Function of Open Photothermal Aging of Polyurethane (Quinn) at 55°C and 70°C

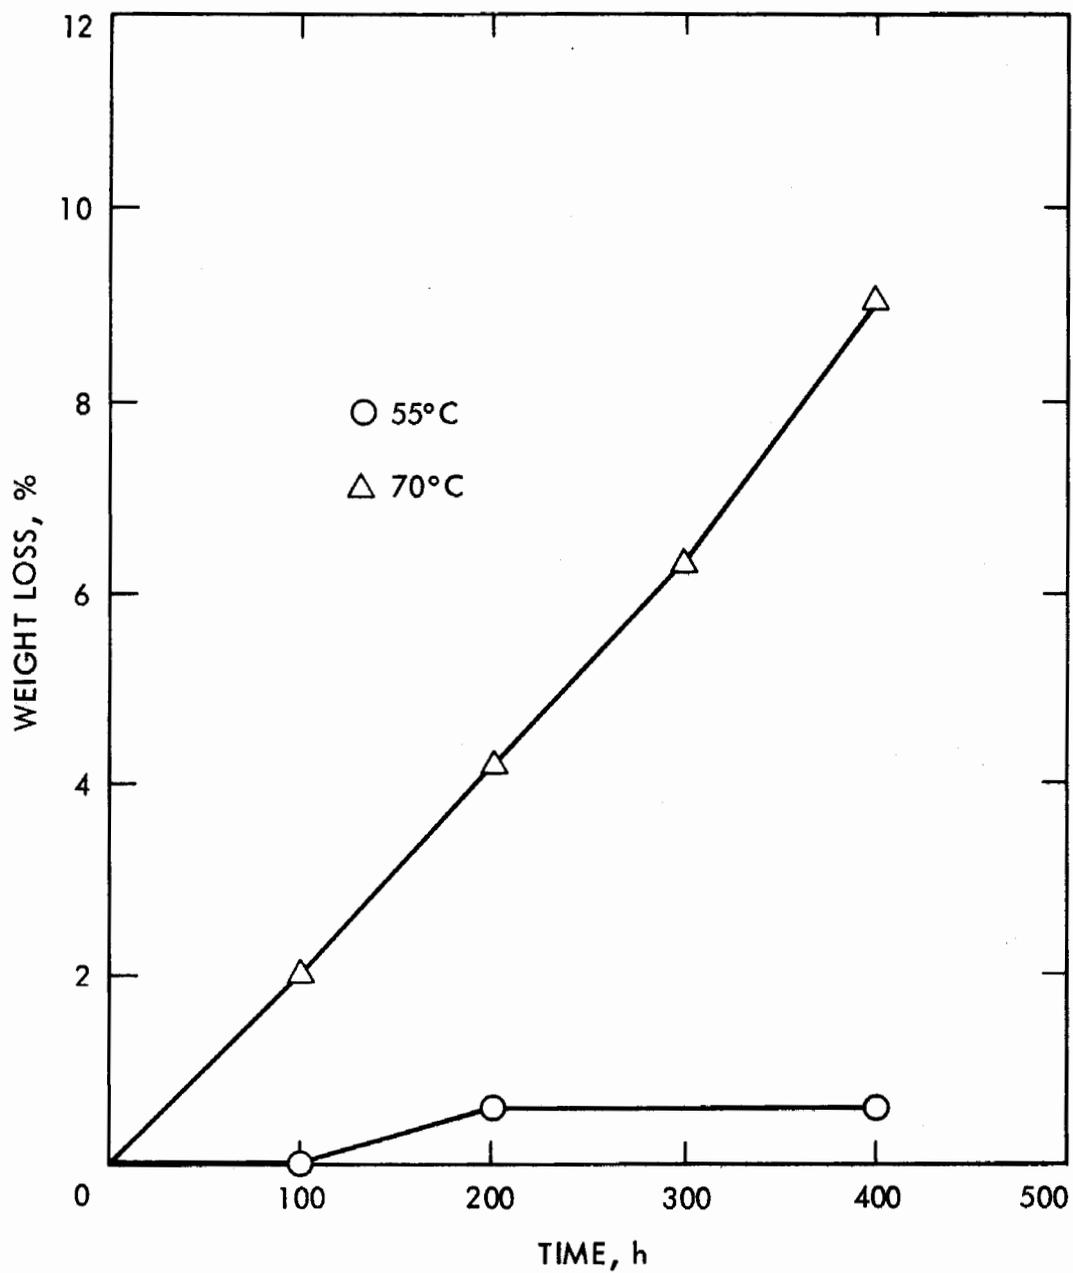


Figure 82. Weight Loss as a Function of Covered Photothermal Aging of Polyurethane (Quinn) at 55°C and 70°C

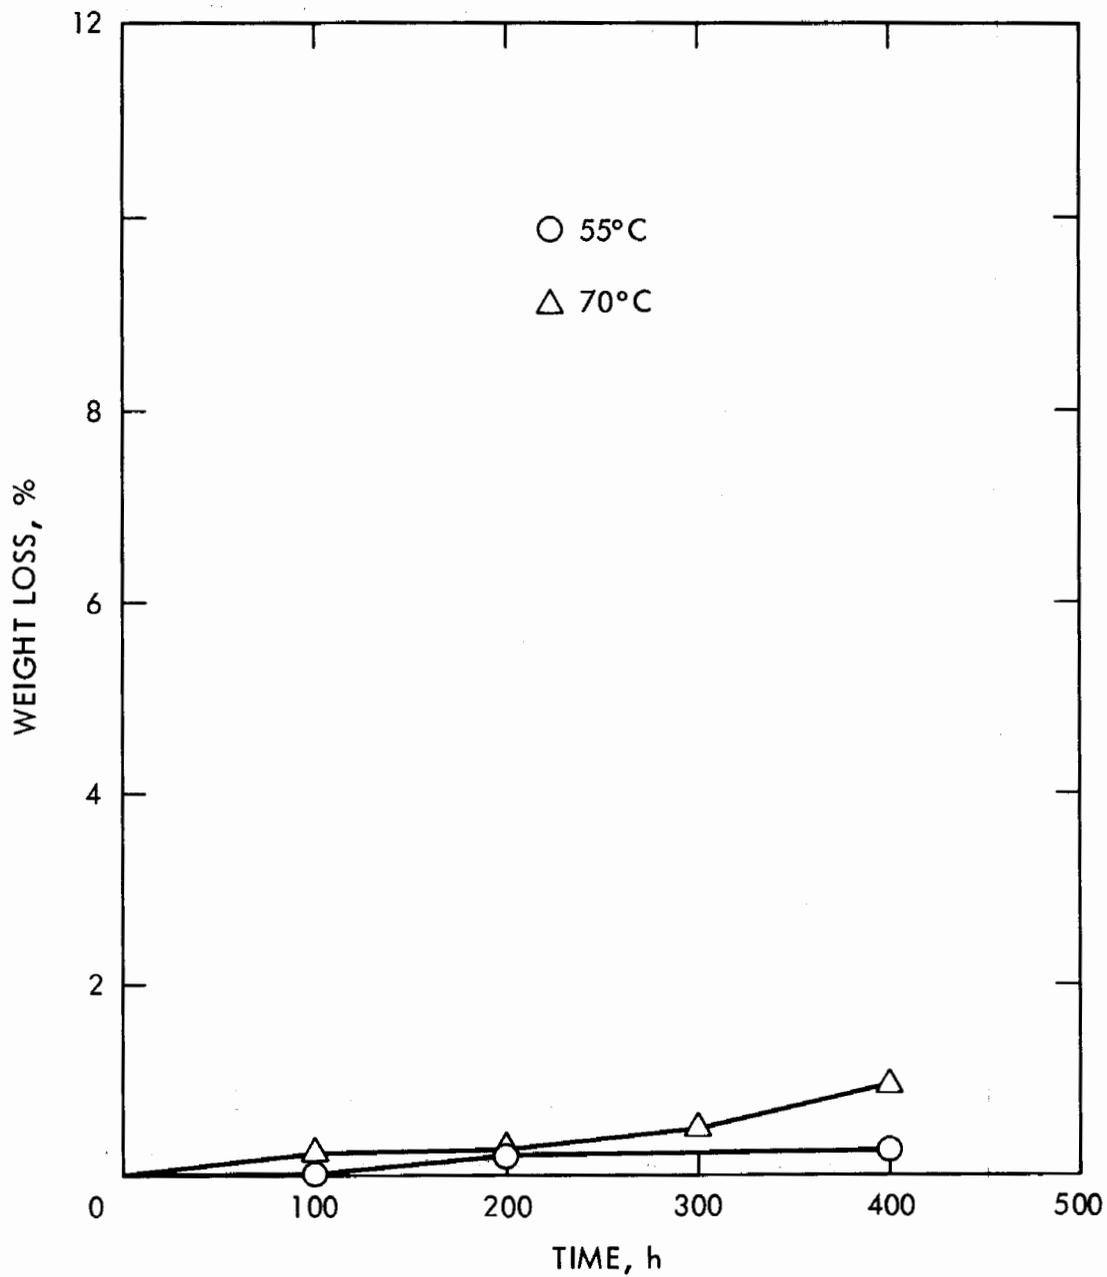


Figure 83. Weight Loss as a Function of Thermal Aging of Polyurethane (Quinn) at 55°C and 70°C

D. OTHER PROPERTIES

Table 33. Sol/Gel and Molecular Weight Data as a Function of Open Photothermal Aging of Polyurethane at 30°C and 70°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> |                         | SOL, % |   | GEL, % |   | MOL WT (SOL) |   |
|-------|------------------|---|-------------------------|--------|---|--------|---|--------------|---|
|       |                  | SAMPL 1                                   | SAMPLE 2                | 1      | 2 | 1      | 2 | 1            | 2 |
| 30    | 0                | 166.0 × 10 <sup>-6</sup>                  | 71.0 × 10 <sup>-6</sup> | 4      |   | 96     |   |              |   |
|       |                  |   |                         |        |   |        |   |              |   |
| 70*   | 400              | 57.0 × 10 <sup>-6</sup>                   |                         | 21     |   | 79     |   | 10,000       |   |

\* PU (QUINN)

Table 34. Sol/Gel and Molecular Weight Data as a Function of Covered Photothermal Aging of Polyurethane at 30°C, 70°C and 135°C

| T, °C | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> |                         | SOL, % |    | GEL, % |    | MOL WT (SOL) |   |
|-------|------------------|---|-------------------------|--------|----|--------|----|--------------|---|
|       |                  | SAMPLE 1                                  | SAMPLE 2                | 1      | 2  | 1      | 2  | 1            | 2 |
| 30    |                  | 166.0 × 10 <sup>-6</sup>                  | 71.0 × 10 <sup>-6</sup> | 4      |    | 96     |    | 5,000        |   |
|       |                  |   |                         |        |    |        |    |              |   |
| 70*   | 400              | 52.0 x                                    |                         | 25     |    | 75     |    | 10,000       |   |
| 135** | 168              |   | x 10 <sup>-6</sup>      |        | 18 |        | 82 |              |   |
|       | 336              |   | 1.1 x 10 <sup>-6</sup>  |        | 12 |        | 88 |              |   |

\* PU (QUINN)

\*\* PU (DEVELOPMENT ASSOCIATES Z-2591)

Table 35. Sol/Gel and Molecular Weight Data as a Function of Thermal Aging of Polyurethane at 30°C, 70°C and 135°C

| T, °C  | TIME OF AGING, h | CROSSLINKING DENSITY, MOL/cm <sup>3</sup> |                         | SOL, % |    | GEL, % |    | MOL WT (SOL) |   |
|--------|------------------|---|-------------------------|--------|----|--------|----|--------------|---|
|        |                  | SAMPLE 1                                  | SAMPLE 2                | 1      | 2  | 1      | 2  | 1            | 2 |
| 30     | 0                | 166.0 × 10 <sup>-6</sup>                  | 71.0 × 10 <sup>-6</sup> | 4      |    | 96     |    | 5,000        |   |
|        |                  |   |                         |        |    |        |    |              |   |
| 70*    | 400              | 105.0 × 10 <sup>-6</sup>                  |                         |        |    |        |    | 10,000       |   |
| 135**♦ | 168              |   | 27.6 × 10 <sup>-6</sup> |        | 8  |        | 92 |              |   |
|        | 336              |   | 4.4 × 10 <sup>-6</sup>  |        | 17 |        | 83 |              |   |

\* PU (QUINN)

\*\* PU (DEVELOPMENT ASSOCIATES Z-2591)

♦ IN A COVERED (SANDWICH) CONFIGURATION

SECTION VIII

KORAD (XCEL CORP.)

Figure 84 offers data on transmittance spectra of Korad (Xcel Corp.).

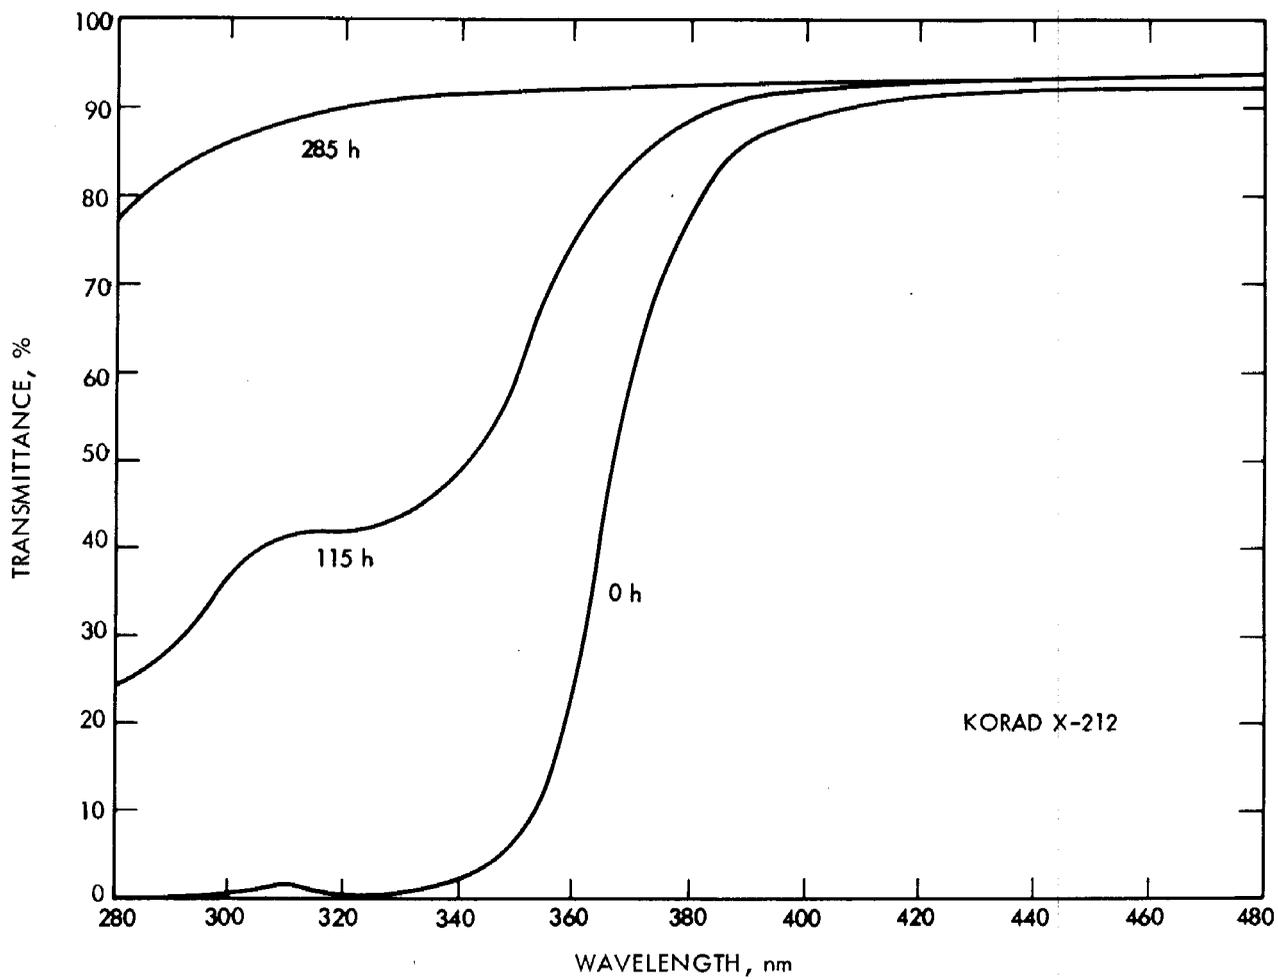


Figure 84. UV/VIS Transmittance Spectra as a Function of Open Photothermal Aging of Korad at 85°C

SECTION IX

TEDLAR (DU PONT UTB-100)

Figures 85 through 87 offer data on absorbance spectra of Tedlar (Du Pont UTB-100).

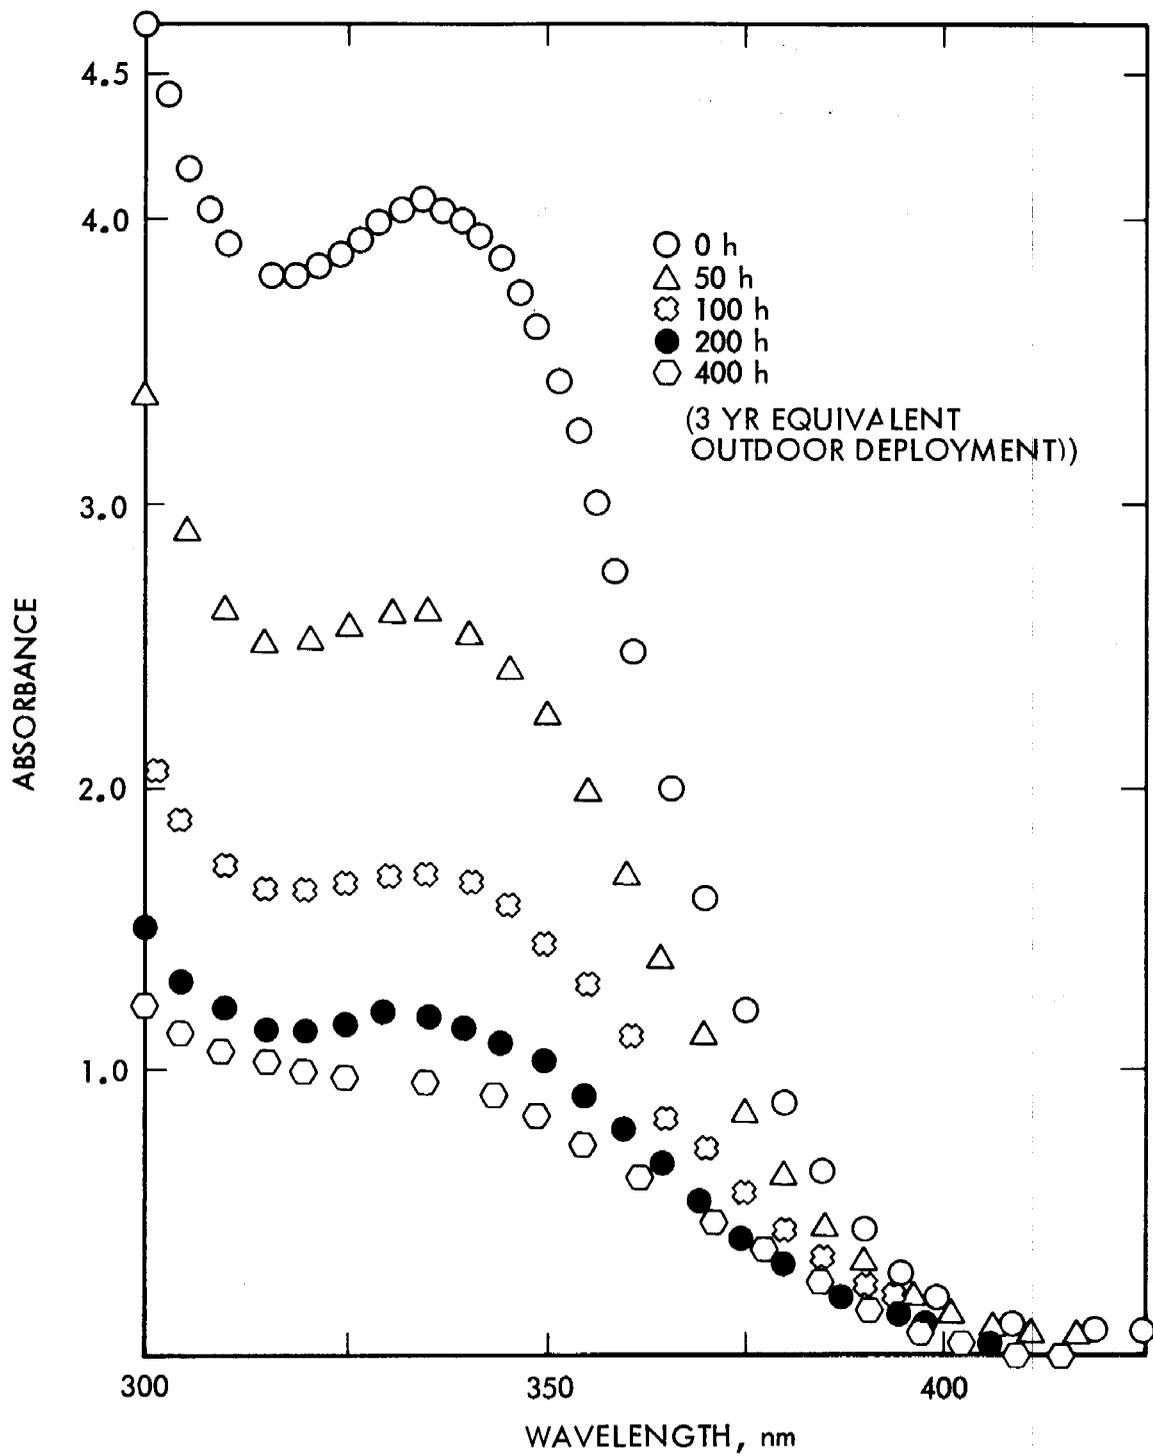


Figure 85. UV/VIS Absorbance Spectra as a Function of Open Photothermal Aging of Tedlar UTB-100 at 85°C

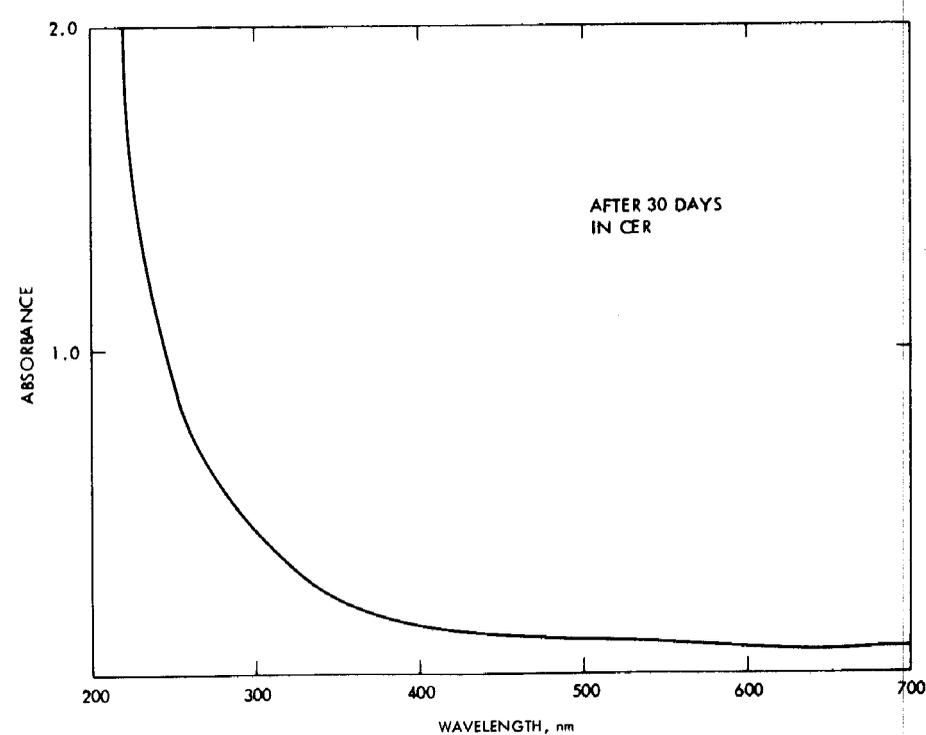
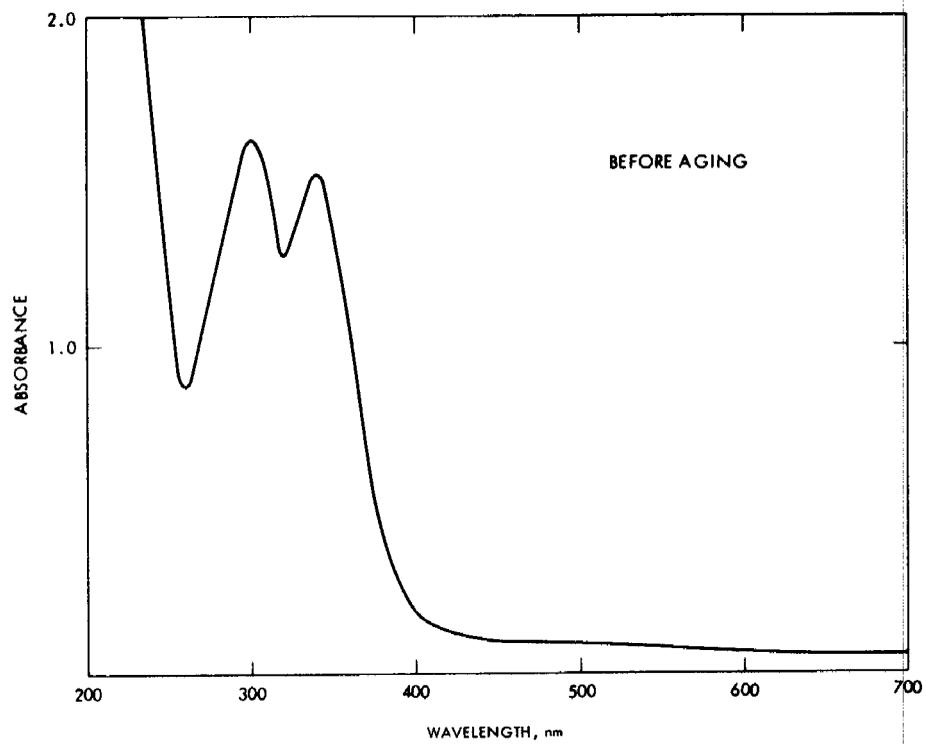


Figure 86. UV/VIS Absorbance Spectra Before and After 30 days of Aging of Tedlar UTB-100 in CER at 55°C

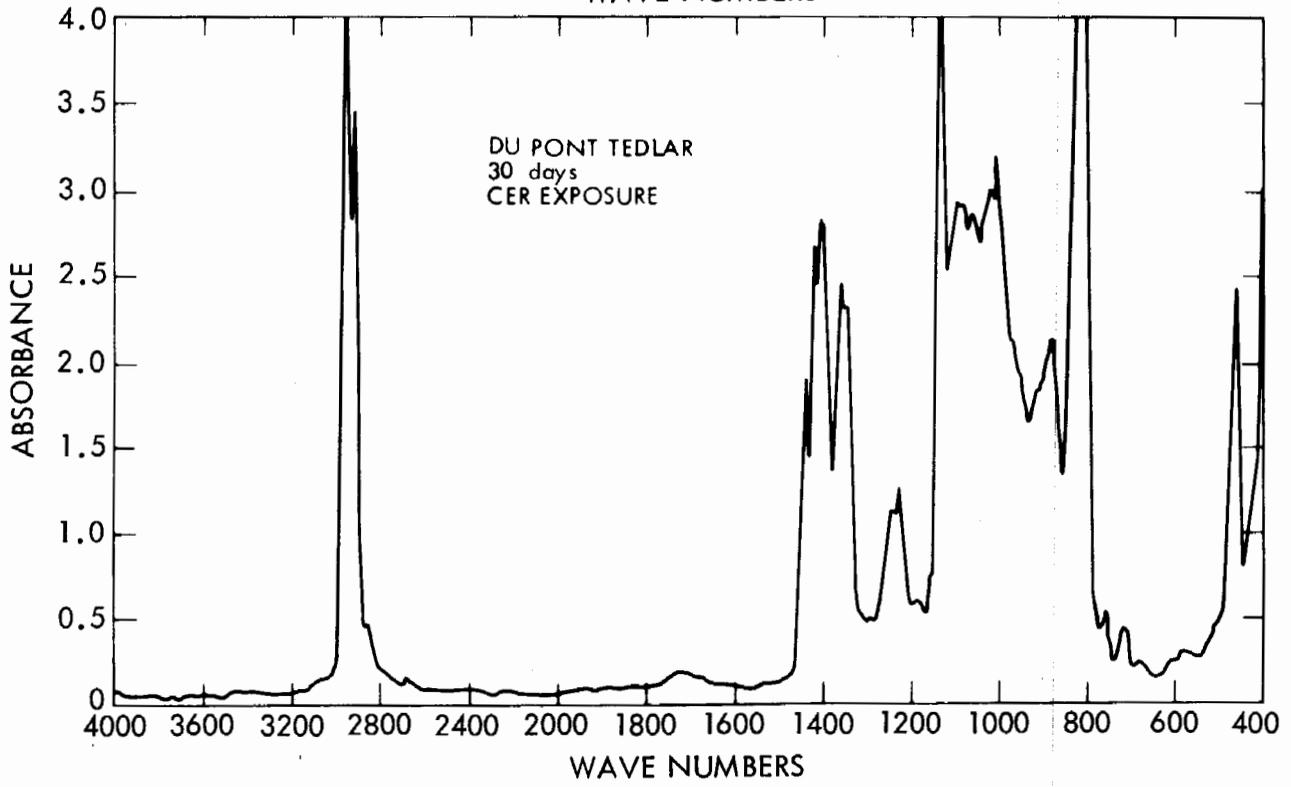
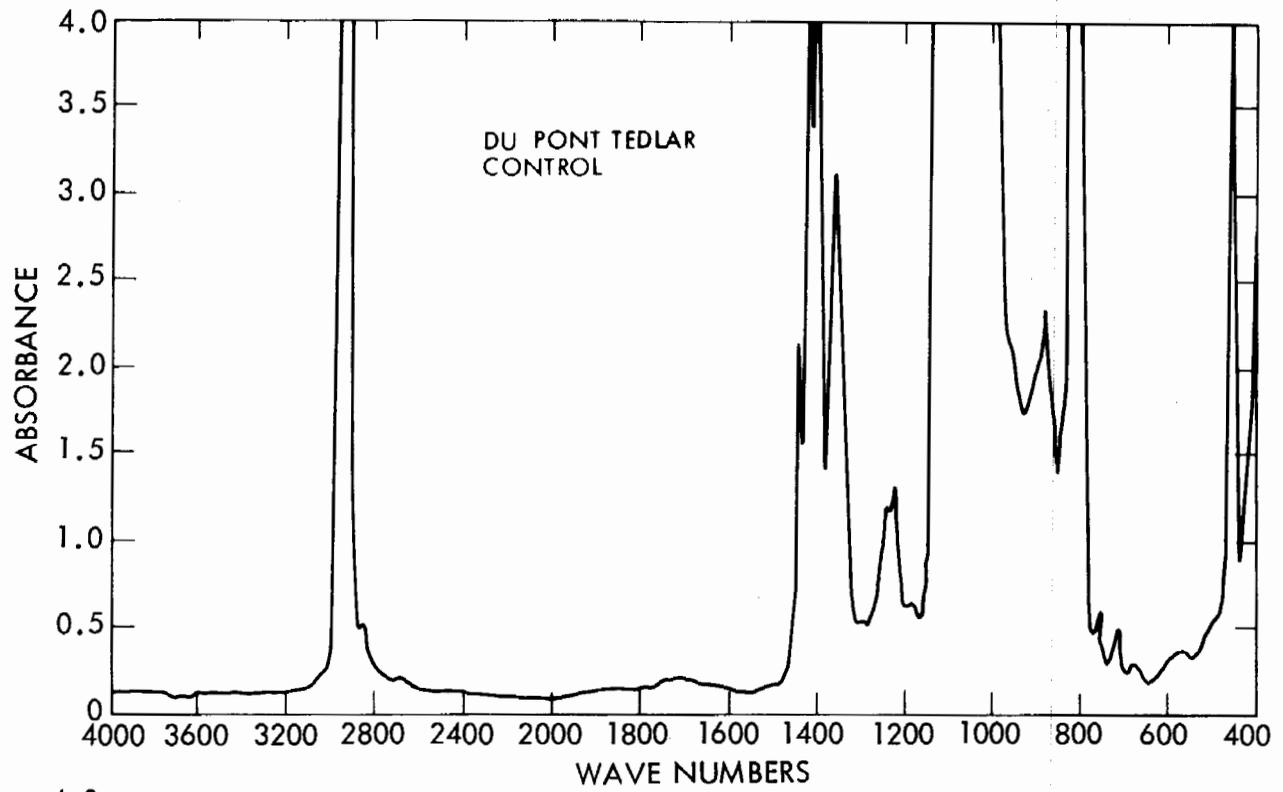


Figure 87. FT-IR Absorbance Spectra Before and After 30 days of Aging of Tedlar UTB-100 in CER at 55°C

SECTION X

ACRYLAR (3M CO. X-22416)

Figures 88 through 93 offer data on optical properties of Acrylar (3M Co. X-22416).

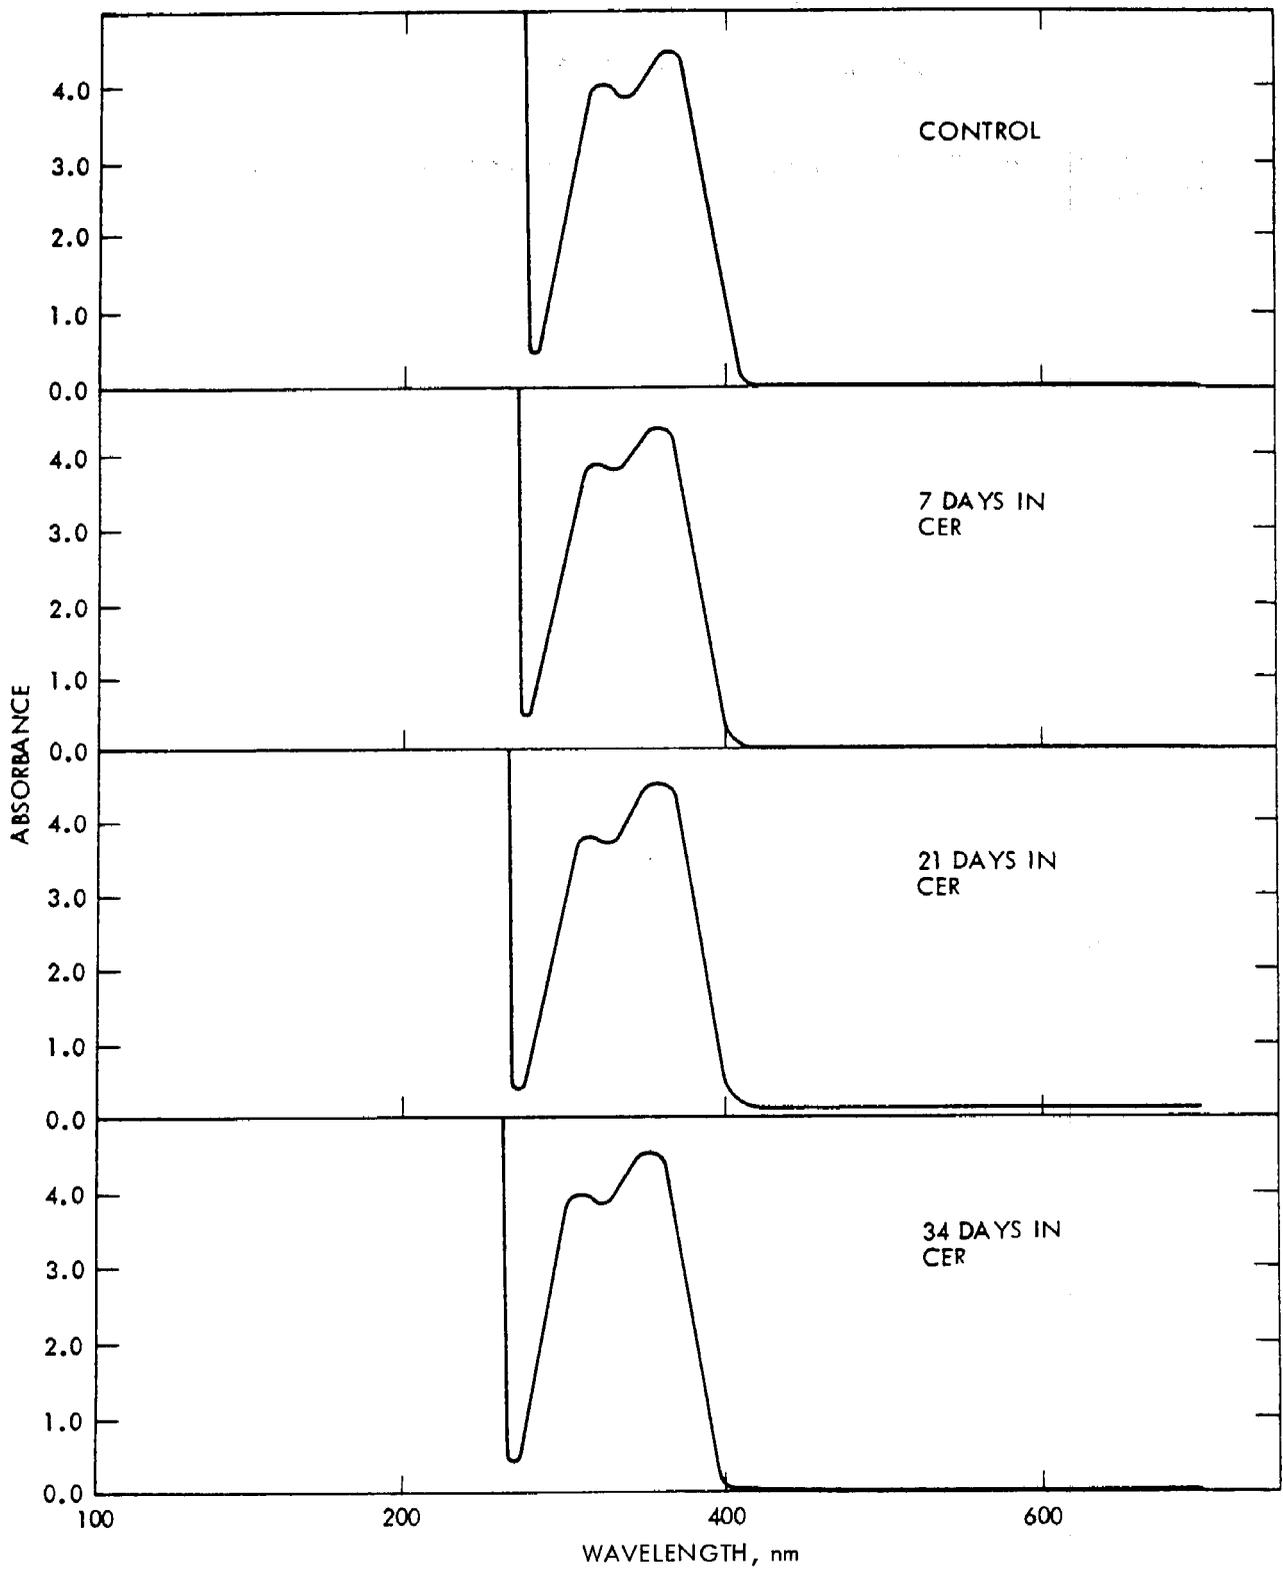


Figure 88. UV/VIS Absorbance Spectra Before and After 34 days of Aging of Acrylar Films (X-22416) in CER

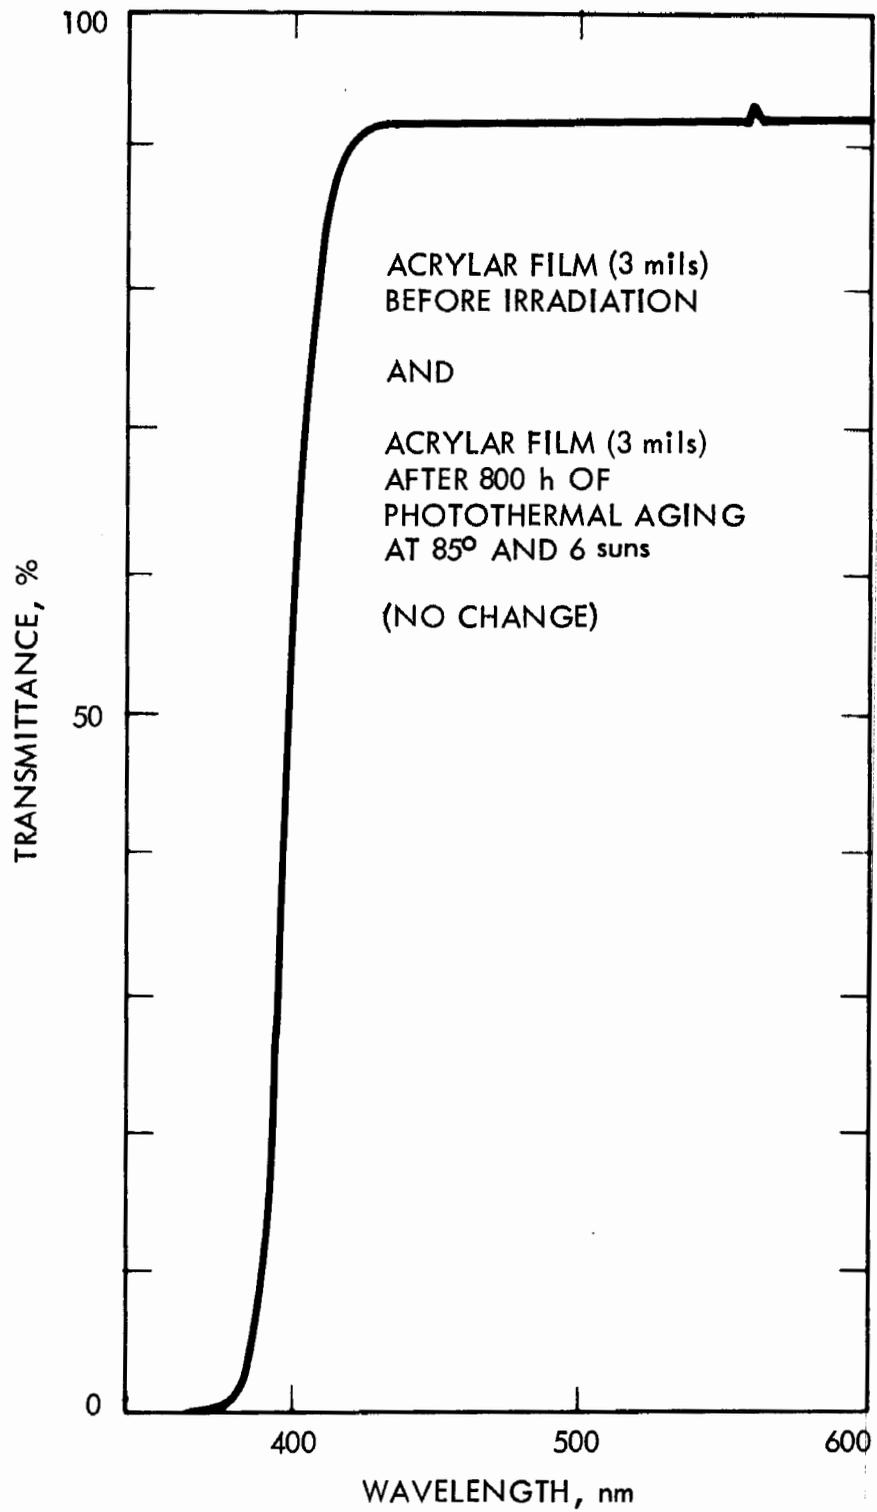


Figure 89. UV/VIS Transmittance Spectra Before and After 800 h of Open Photothermal Aging of Acrylar Film at 85°C

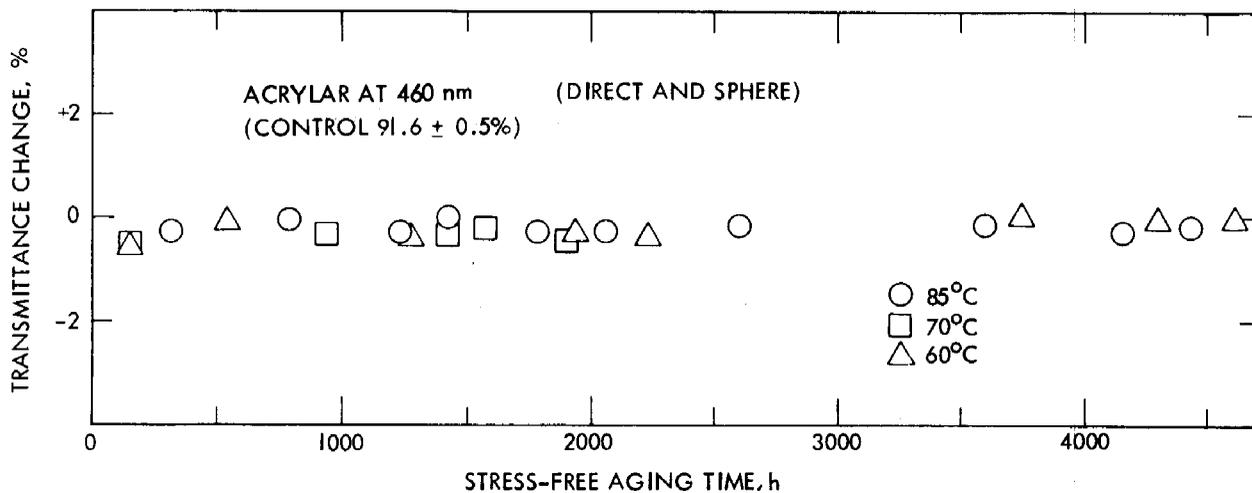


Figure 90. Change in Transmittance of Acrylar Films at 460 nm at 60°C, 70°C and 80°C

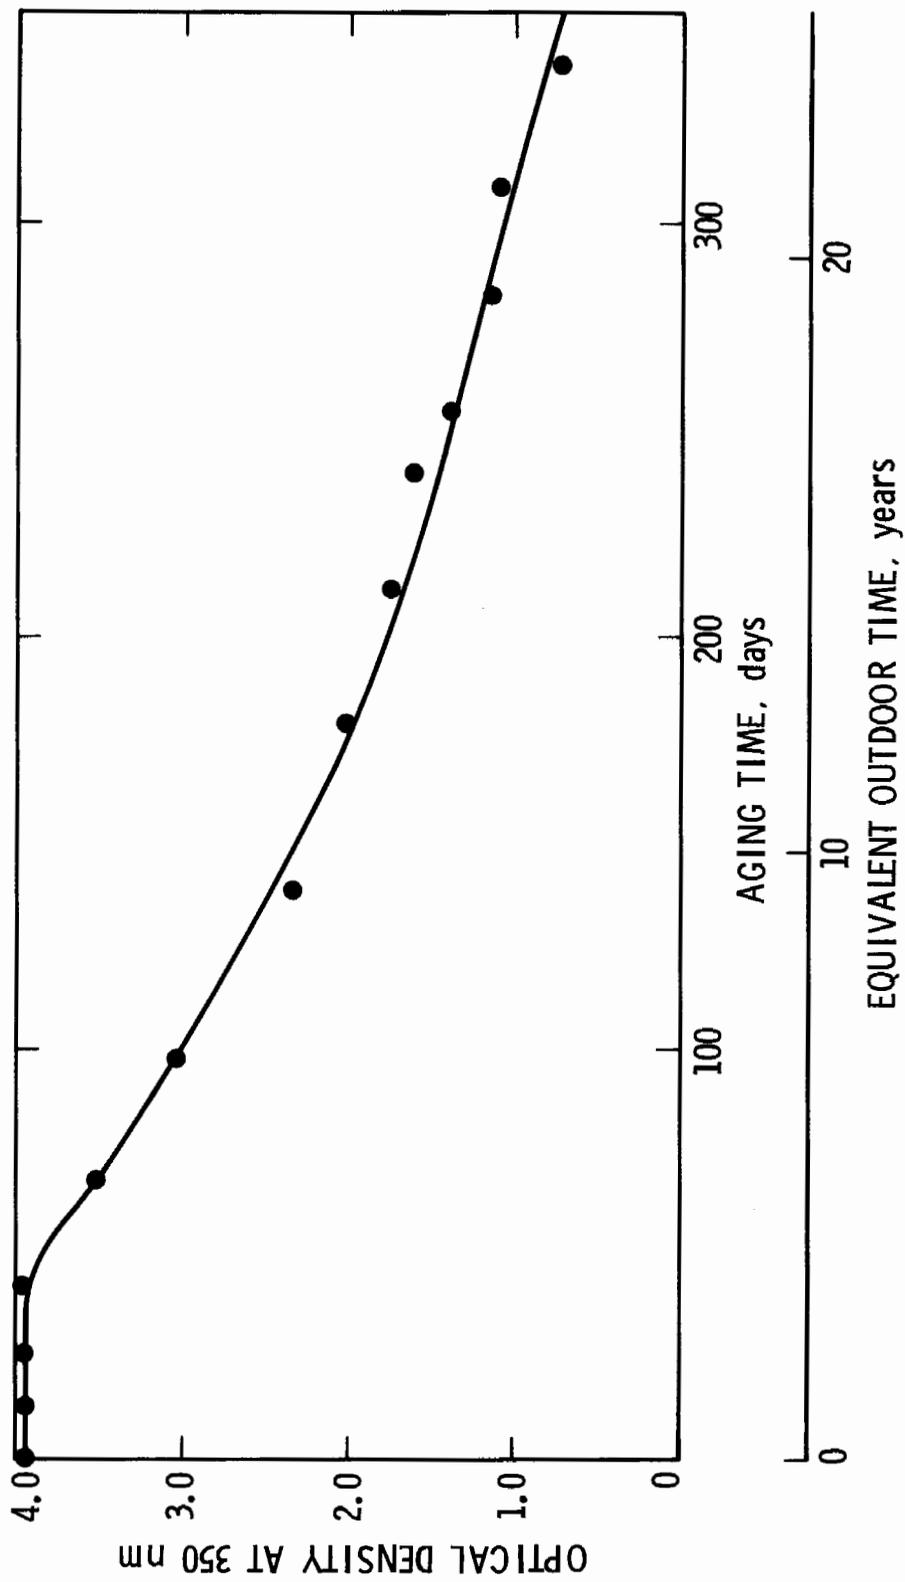


Figure 91. UV-Screening Capability of Acrylar as a Function of Accelerated Aging Inside the CER at 55°C

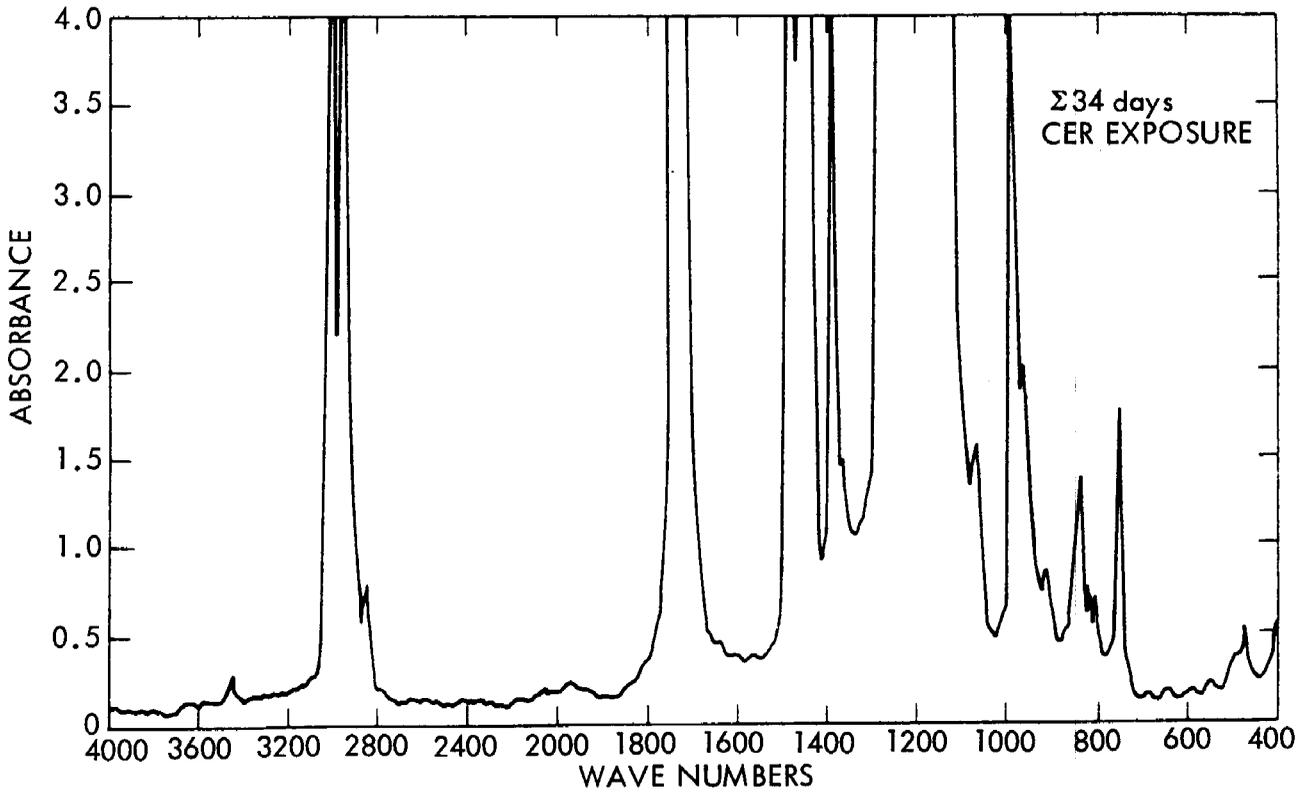
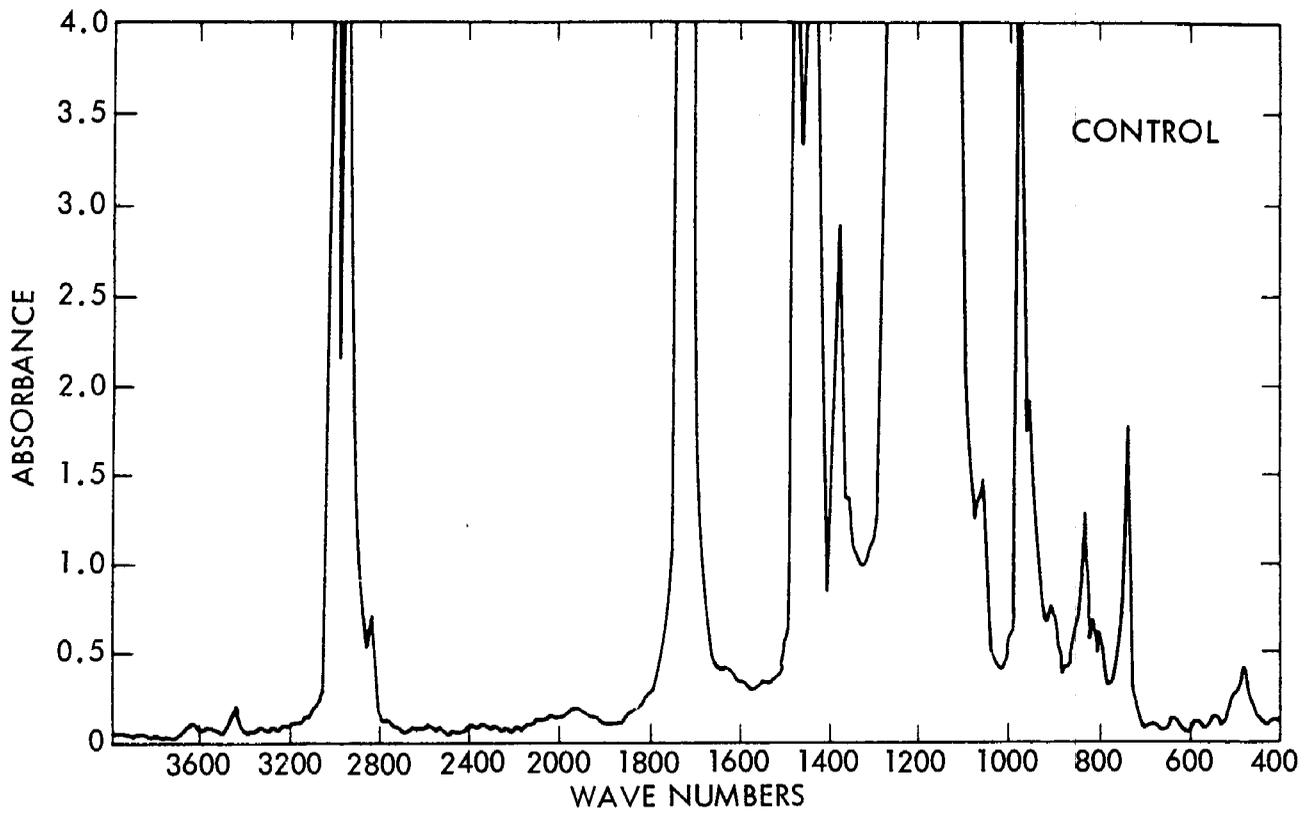


Figure 92. FT-IR Absorbance Spectra Before and After 34 days of Aging of Acrylar Films (X-22416) in CER at 55°C

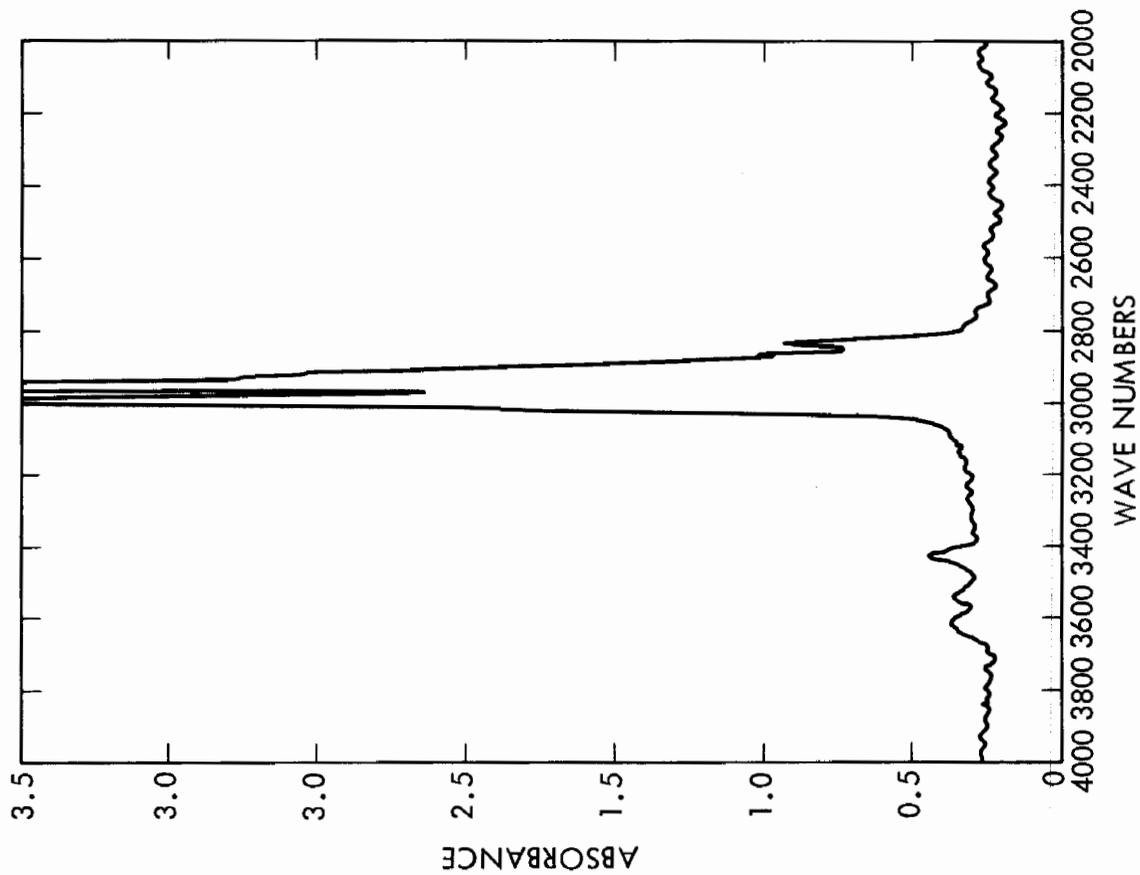
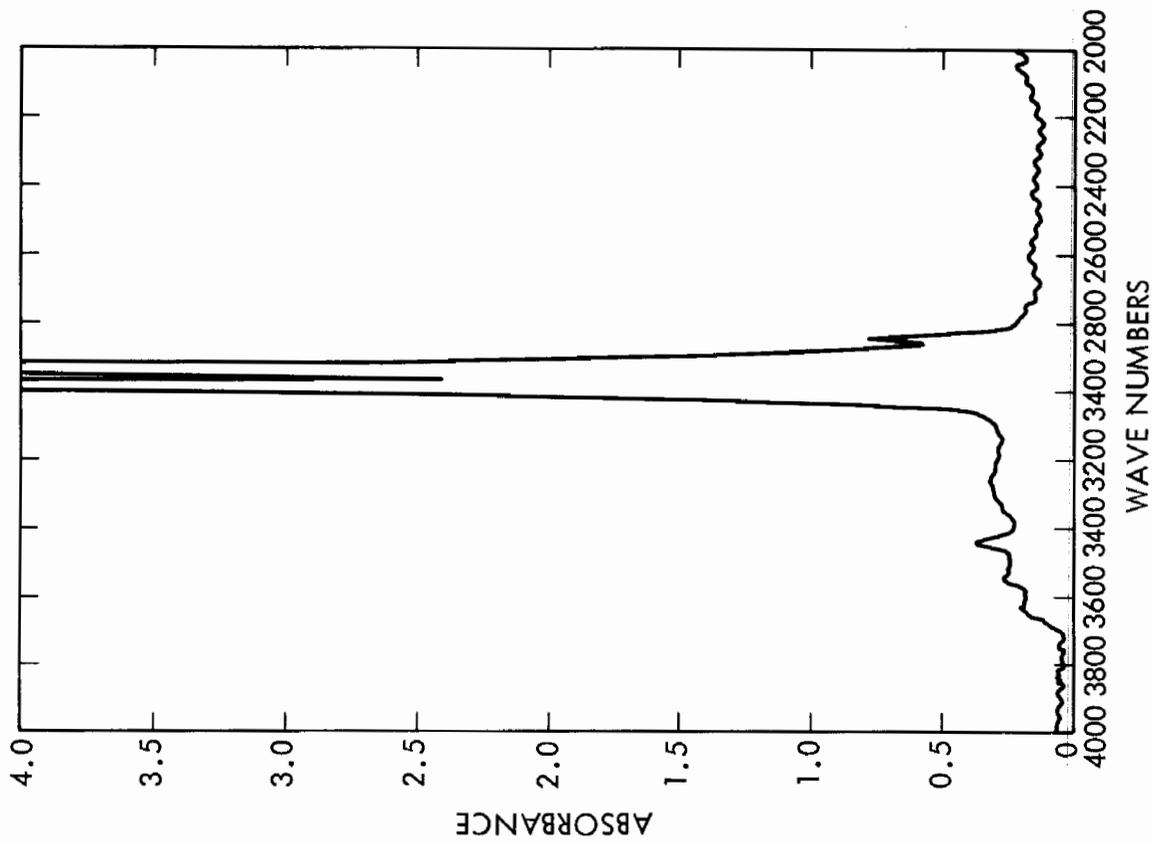


Figure 93. FT-IR Absorbance Spectra Before and After 282 days of Aging of Acrylar Films (X-22416) in CER at 55°C

SECTION XI

KYNAR (PENNWALT CORP.)

Figures 94 and 95 offer data on optical properties and Table 36 offers data on shrinkage of Kynar (Pennwalt Corp.)

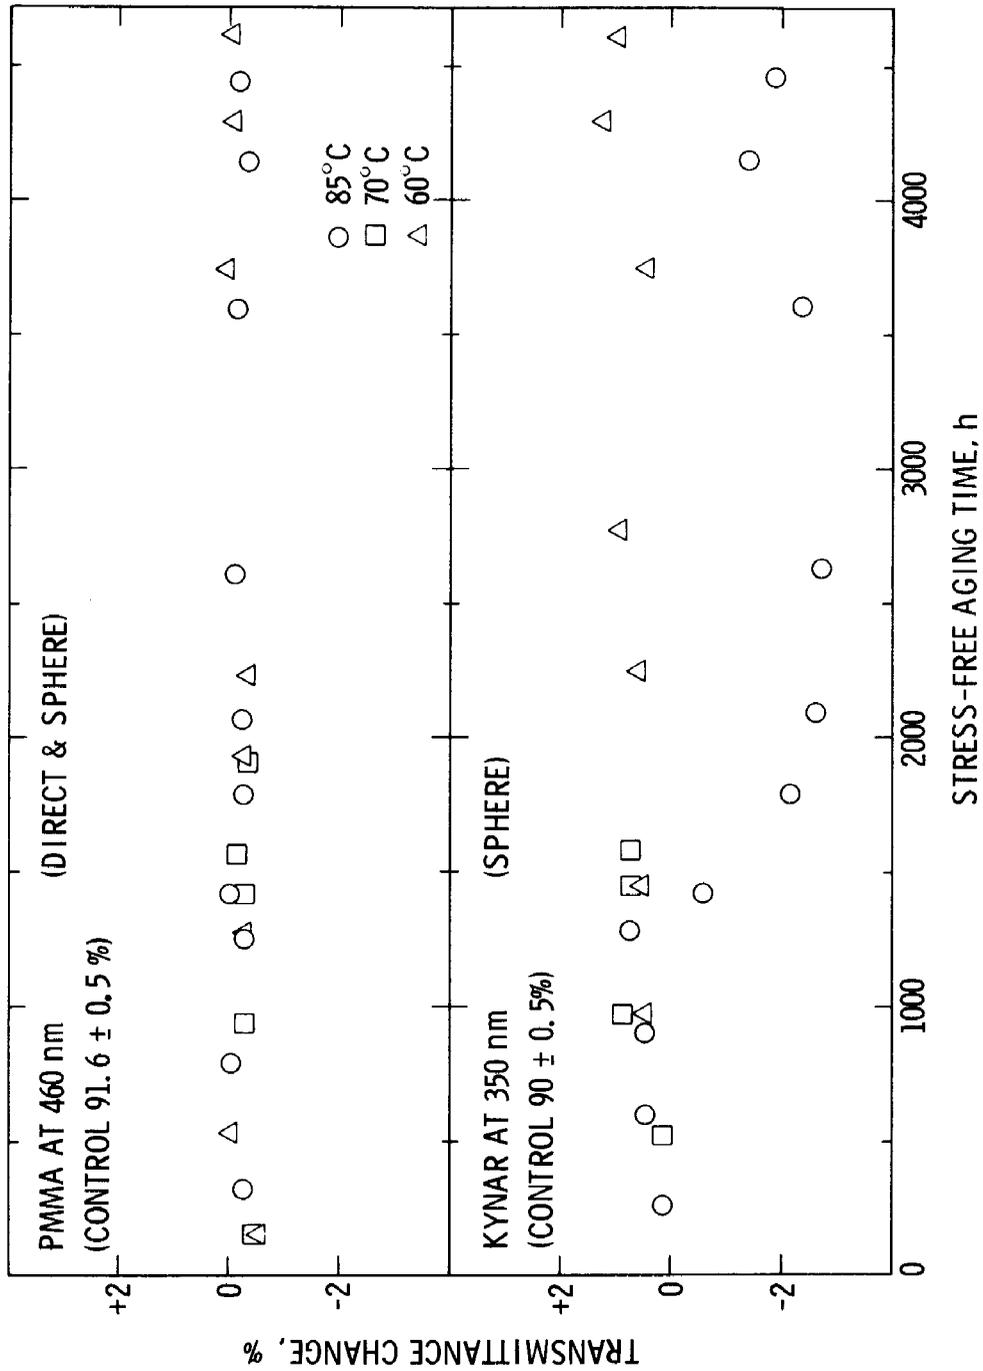


Figure 94. Change in Transmittance at 350 nm as a Function of Thermal Aging of Kynar in a Dark Oven at 60°C, 70°C, and 85°C

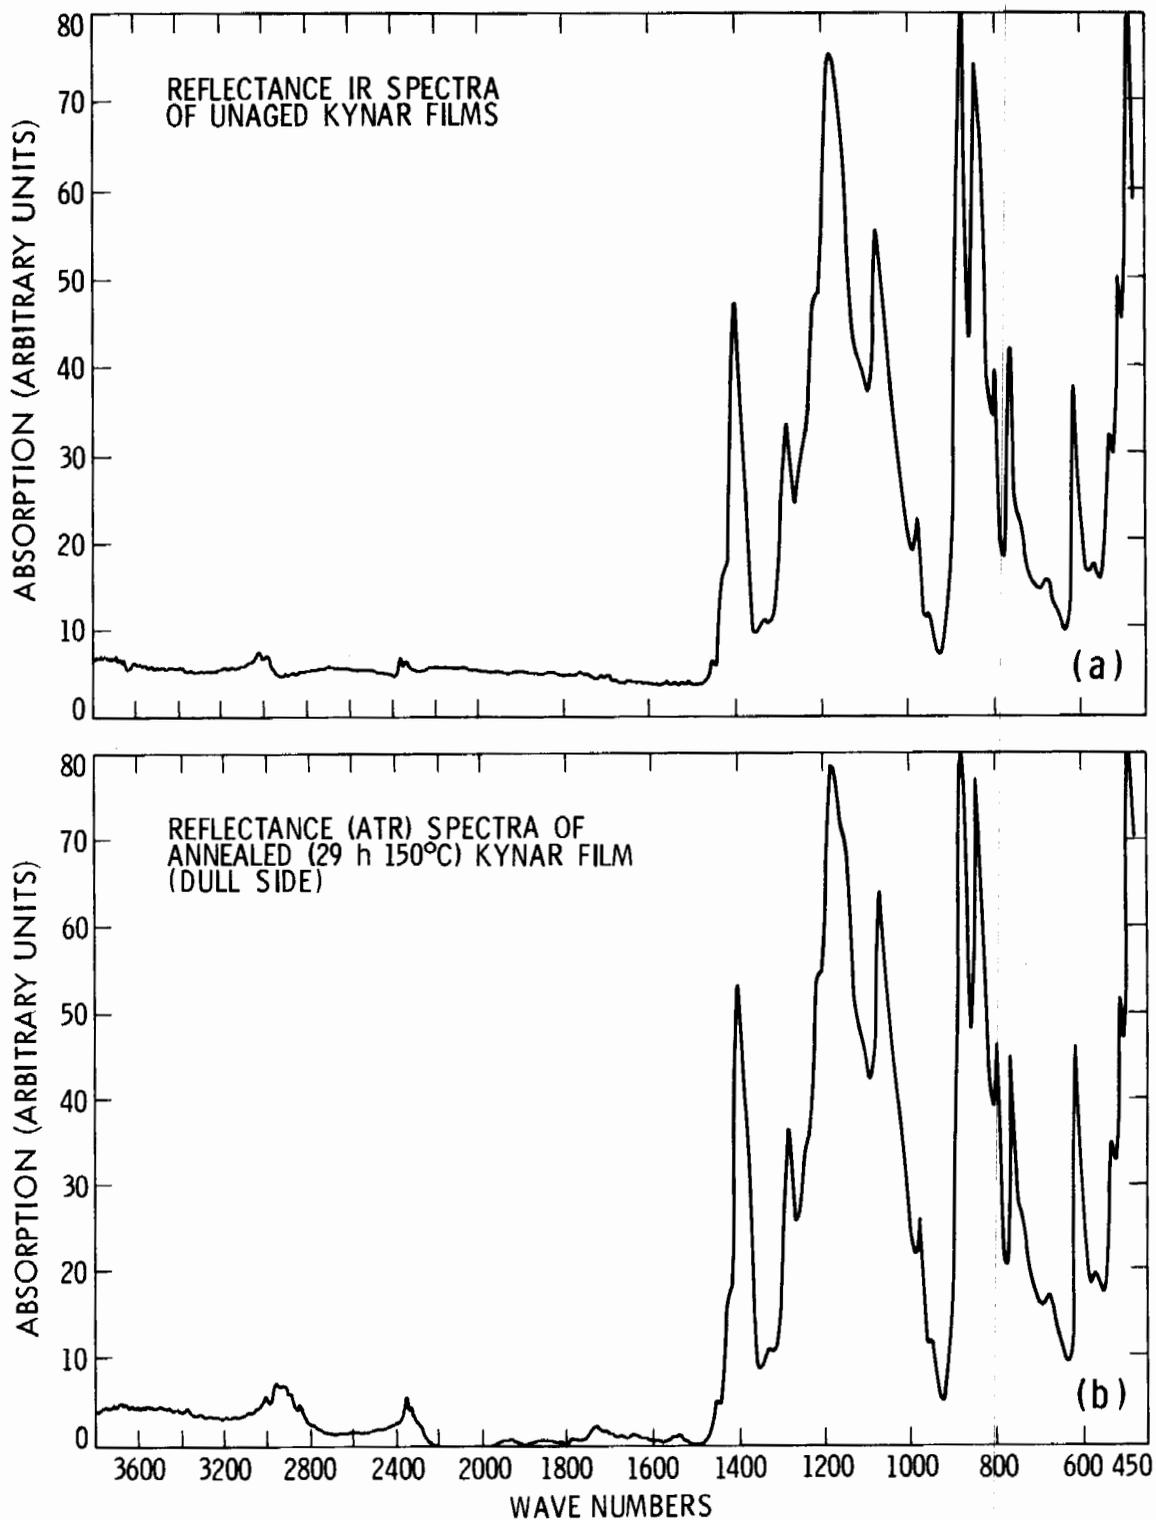


Figure 95. Reflectance IR Spectra Before and After 29 Hours of Thermal Aging of Kynar Film in a Dark Oven at 150°C

Table 36. Shrinkage as a Function of Thermal Aging of Kynar in Dark Oven at 150°C

| TIME OF AGING, h | LINEAR SHRINKAGE, % |
|------------------|---------------------|
| 0.5              | 31                  |
| 1.0              | 30                  |
| 2.0              | 34                  |
| 3.0              | 34                  |
| 5.0              | 34                  |
| 29.0             | 34                  |

## SECTION XII

### REFERENCES

1. Gupta, A., Photodegradation of Polymeric Encapsulants of Solar Cell Modules, JPL Internal Document No. 5101-77, Jet Propulsion Laboratory, Pasadena, California, August 1978.
2. Gupta, A., Effects of Photodegradation on Chemical Structure and Surface Characteristics of Silicon Pottants Used in Solar Cell Modules, JPL Internal Document No. 5101-79, Jet Propulsion Laboratory, Pasadena, California, August 1978.
3. Gupta, A., and Di Stefano, S., "Photocatalytic Degradation of a Cross-Linked Ethylene/Vinyl Acetate (EVA) Elastomer," *Polymer Preprints*, Vol. 21, p. 178, Jet Propulsion Laboratory, Pasadena, California, 1980.
4. Gupta, A., Kliger, D., and Scott, G.W., "Photochemistry of Ultraviolet Stabilizers and Stabilized System," *Organic Coatings and Plastics Chemistry*, Vol. 42, p. 490, 1980.
5. Gupta, A., Liang, R., Tsya, F.D., and Moacanin, J., "Characterization of a Dissociative Excited State in the Solid State: Photochemistry of Poly(Methyl Methacrylate)," *Macromolecules*, Vol. 13, p. 1696, 1980.
6. Liang, R., Yavrouian, A., and Gupta, A., "Development of a Weatherable Acrylic Elastomer for Solar Cell Encapsulation," *Proceedings of the 158th meeting of the Electrochemical Society, Hollywood, Florida, Vols. 81-83*, p. 261, 1981.
7. Liang, R., et al, "Photothermal Degradation of Ethylene/Vinylacetate Copolymer," *Proceedings of te Polymer Alloys Symposium, 182nd national meeting of the American Chemical Society, New York, New York, 1982.*
8. Liang, R., Tsay, F.D., and Gupta, A., "Photodegradation of Poly(n-butyl acrylate)", *Macromolecules*, Vol. 15, p. 974, (1982).
9. Cuddihy, E.F., Development of Reduced Variable Master Curves for Estimating Tensile Stresses of Encapsulated Solar Cells Caused by Module Deflection or Thermal Expansion, JPL Internal Document No. 5101-182, Jet Propulsion Laboratory, Pasadena, California, October 1981.
10. Liang, R., Gupta, A., and Di Stefano, S., Photothermal Characterization of Encapsulant Materials for Photovoltaic Modules, JPL Publication 82-42, DOE/JPL 1012-72, JPL Document No. 5101-210, Jet Propulsion Laboratory, Pasadena, California, June 1982.
11. Laue, E., and Gupta, A., Reactor for Simulation and Acceleration of Solar Ultraviolet Damage, JPL Publication 79-92, DOE/JPL 1012-31, JPL Document No. 5101-135, Jet Propulsion Laboratory, Pasadena, California, September 1979.

12. Liang, R., Coulter, D.R., and Gupta, A., "Novel Diagnostic Techniques for Early Detection of Photooxidation in Polymers," Polymer Preprints, Vol. 23, p. 215, 1982; Proceedings of the Symposium on Polymer Applications in Solar Energy, 183rd national meeting of American Chemical Society, Las Vegas. Nevada, March 1982.